



# The use of USPV to anticipate failure in concrete under compression

Hisham Y. Qasrawi\*, Iqbal A. Marie

*Civil Engineering Department, Faculty of Engineering, Hashemite University, Zarqa 13115, Jordan*

Received 5 February 2003; accepted 24 June 2003

## Abstract

The use of the ultrasonic pulse velocity tester is introduced as a tool to monitor basic initial cracking of concrete structures and hence to introduce a threshold limit for possible failure of the structures. Experiments using ultrasonic pulse velocity tester have been carried out, under laboratory conditions, on various concrete specimens loaded in compression up to failure. Special plots, showing the relation between the velocity through concrete and the stress during loading, have been introduced. Also, stress–strain measurements have been carried out in order to obtain the corresponding strains. Results showed that severe cracking occurred at a stress level of about 85% of the rupture load. The average velocity at this critical limit was about 94% of the initial velocity and the corresponding strain was in the range of 0.0015 to 0.0021. The sum of the crack widths has been estimated using special relations and measurements. This value that corresponds to the 94% relative velocity was between 5.2 and 6.8 mm.

© 2003 Elsevier Ltd. All rights reserved.

*Keywords:* Concrete; Pulse velocity; Nondestructive testing

## 1. Introduction

The ultrasonic pulse velocity has been used on concrete for more than 60 years. Powers in 1938 and Obert in 1939 were the first to develop and extensively use the resonance frequency method [1]. Since then, ultrasonic techniques have been used for the measurements of the various properties of concrete [2–31]. Also, many international committees, specifications and standards adopted the ultrasonic pulse velocity methods for evaluation of concrete. Examples are the ASTM C597, BS 1881: Part 203 and ACI 224R, ACI 228.1R, ACI228.2R and ACI228.2R [19–24].

The principle of the test is that the velocity of sound in a solid material,  $V$ , is a function of the square root of the ratio of its modulus of elasticity,  $E$ , to its density,  $d$ , as given by the following equation:

$$V = f\left(\frac{gE}{d}\right) \quad (1)$$

where  $g$  is the gravity acceleration. As noted in the previous equation, the velocity is dependent on the modulus of elasticity of concrete. Relationships between pulse velocity and modulus of elasticity of concrete are given in

Refs. [4,12,28]. Monitoring modulus of elasticity for concrete through results of pulse velocity is not normally recommended because concrete does not fulfill the physical requirements for the validity of the equation normally used for calculations for homogenous, isotropic and elastic materials (Eq. (2)) [4,28].

$$V^2 = \frac{E_d(1 - \mu)}{\rho(1 + \mu)(1 - \mu)} \quad (2)$$

where  $V$  is the wave velocity,  $\rho$  is the density,  $\mu$  is Poisson's ratio and  $E_d$  is the dynamic modulus of elasticity.

On the other hand, it has been shown that the strength of concrete and its modulus of elasticity are related [6,29].

The method starts with the determination of the time required for a pulse of vibrations at an ultrasonic frequency to travel through concrete. Once the velocity is determined, an idea about quality, uniformity, condition and strength of the concrete tested can be attained. In the test, the time the pulses take to travel through concrete is recorded. Then, the velocity is calculated as:

$$V = \frac{L}{T} \quad (3)$$

where  $V$ = pulse velocity,  $L$ = travel length in meters (Fig. 1) and  $T$ =effective time in seconds, which is the measured time minus the zero time correction.

\* Corresponding author.

*E-mail address:* [hqasrawi2000@yahoo.com](mailto:hqasrawi2000@yahoo.com) (H.Y. Qasrawi).

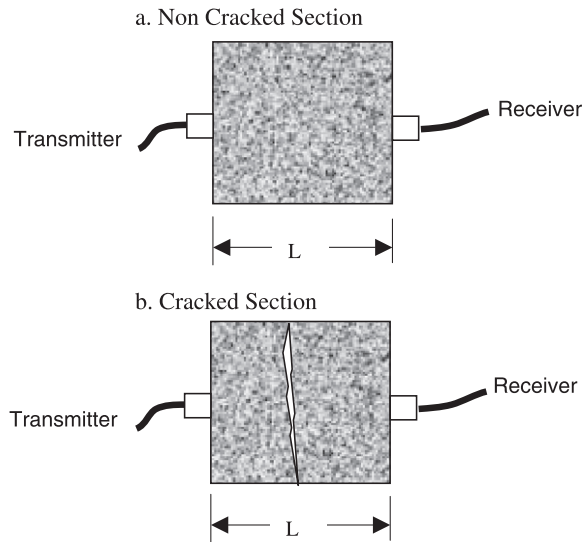


Fig. 1. Test procedure in noncracked and cracked samples.

The zero time correction is equal to the travel time between the transmitting and receiving transducers when they are pressed firmly together. Based on that principle, Whitehurst [3] introduced a relationship between the wave velocity and the quality of concrete as early as 1951.

The variation of the results due to the surface properties, presence of steel reinforcement, presence of voids and cracks, properties of aggregate and mix proportions have been studied and shown in the literature [5,7,9,10,21–24]. Many attempts have been made to correlate the velocity to the strength of concrete either directly or by the use of combined ultrasonic and rebound hammer [8,14,15,18,21–25].

Special techniques for investigating damage in concrete by the use of wave velocity through cracked concrete have been introduced by Toutanji [1], Selleck et al. [16], Nogueira and Willam [17] and Berthaud [26,27].

From the literature review, it can be concluded that the ultrasonic pulse velocity results can be used to:

- (a) check the uniformity of concrete,
- (b) detect cracking and voids inside concrete,
- (c) control the quality of concrete and concrete products by comparing results to a similarly made concrete,
- (d) detect condition and deterioration of concrete,
- (e) detect the depth of a surface crack and
- (f) determine the strength if previous data is available.

## 2. Research idea

The determination of the level of failure may be difficult and unreliable without the use of complicated methods and procedures such as the load test. Sometimes, special procedures and methods have to be designed, tried

and then applied to the element under consideration. Such methods are usually slow and costly. However, no final conclusions can be drawn without the application of such methods, especially when the engineer has to decide on various remedial measures including the demolition of the structure.

The method presented here is a technique that can be applied to structurally cracked elements in order to obtain a simple conclusion about the tested region.

The basic idea is to measure the velocity through concrete in cracked and uncracked regions. It is obvious that the velocity of concrete is reduced when there is an internal crack as shown in Fig. 1 because velocity through concrete is higher than velocity through air or water (the crack is either filled with air or water). Hence, a reduction in the measured velocity can be noticed when the concrete cracks. However, when the cracks are wide, the sound waves are wholly reflected and no signal is received [20].

Furthermore, a relation between the pulse velocity and the crack width was deduced. The basic idea was that the reduction in the velocity through concrete is basically due to the formation of cracks in concrete as shown in Fig. 1. These cracks are assumed to be filled with water because all samples were saturated surface dry at test. The velocity of waves in water has been calculated using the physical relationship:

$$V_w = \sqrt{\frac{B}{\rho}} \quad (4)$$

where  $B$  is the bulk modulus of water, equals  $0.21 \times 10^9$ , and  $\rho$  is the density of water, which equals  $1000 \text{ kg/m}^3$  [32]. Using Eq. (4), the value has been found to be  $1449.1 \text{ m/s}$  and was assumed to be  $1450 \text{ m/s}$  in calculations. This value was consistent with that appeared in the literature [33,34].

The relationship, in its final form, was as follows:

$$w = \frac{\frac{1}{V} - \frac{1}{V_0}}{\frac{1}{V_w} - \frac{1}{V_0}} S \quad (5)$$

where  $w$  is the crack width,  $V$  is the velocity in concrete at any stress level,  $V_0$  is the velocity in concrete at zero stress level,  $V_w$  is the wave velocity in water, taken  $1450 \text{ m/s}$ , and  $S$  is the side length of the cube.

## 3. Research program

The research consisted of the following steps:

1. Under laboratory conditions, 150-mm concrete cubes were prepared. Various water-to-cement (w/c) ratios were

Download English Version:

<https://daneshyari.com/en/article/1458247>

Download Persian Version:

<https://daneshyari.com/article/1458247>

[Daneshyari.com](https://daneshyari.com)