

3rd CIRP Conference on Surface Integrity (CIRP CSI)

Effect of process parameters on the surface roughness of overhanging structures in laser powder bed fusion additive manufacturing

Jason C. Fox^{a*}, Shawn P. Moylan^a, Brandon M. Lane^a

^aNational Institute of Standards and Technology, 100 Bureau Drive, Gaithersburg, MD 20886, USA

* Corresponding author. Tel.: +1-301-975-2171 ; fax: +1-301-975-8058. E-mail address: jason.fox@nist.gov

Abstract

The development of additive manufacturing has allowed for increased flexibility and complexity of designs over formative and subtractive manufacturing. However, a limiting factor of additive manufacturing is the as-built surface quality as well as the difficulty in maintaining an acceptable surface roughness in overhanging structures. In order to optimize surface roughness in these structures, samples covering a range of overhang angles and process parameters were built in a laser powder bed fusion system. Analysis of the surface roughness was then performed to determine a relationship between process parameters, angle of the overhanging surface, and surface roughness. It was found that the analysis of surface roughness metrics, such as R_{pc} , R_{sm} , and R_c , can indicate a shift between surfaces dominated by partially melted powder particles and surfaces dominated by material from the re-solidified melt track.

Published by Elsevier B.V. This is an open access article under the CC BY-NC-ND license (<http://creativecommons.org/licenses/by-nc-nd/4.0/>).

Peer-review under responsibility of the scientific committee of the 3rd CIRP Conference on Surface Integrity (CIRP CSI)

Keywords: Selective Laser Melting (SLM); Roughness; Overhangs

1. Introduction

Additive manufacturing (AM) is a layer by layer process that fabricates parts directly from a 3-D digital model. This is accomplished by slicing the model into layers to create 2-D cross sections that the equipment can use as build instructions. Laser Powder Bed Fusion (L-PBF), for example, will fabricate a part by spreading a thin layer of powder (20 μm to 100 μm) across a build platform and using a high power laser to selectively melt regions of that layer. Once the layer is melted, the build platform lowers, new powder is spread across the build platform, and the process repeats until the build is complete.

A key advantage to AM over formative (e.g., casting) or subtractive (e.g., milling) methods is the ability to produce highly complex shapes. However, a limiting factor in AM is the as-built quality of surfaces. Methods exist to process surfaces after a part has been built [1,2] and during the build process through laser re-melting [3] and pulse shaping [4], but as the complexity of parts increases, the ability to successfully post-process the surface decreases [5]. As such, the as-built surface quality of a part has been cited as a key need for AM [6].

The surface roughness of AM parts has been the focus of several studies. Mumtaz and Hopkinson performed a full factorial analysis of the top and side surface roughness of multilayer thin-wall Inconel 625 parts, finding that parameter changes that tend to decrease roughness on one surface increase it on the other and optimization of the surface roughness requires a thorough understanding of how changes in process parameters affect different aspects of the part [7]. Strano *et al.* investigated the effect of surface angle on roughness for upward-facing surfaces in 316L steel [8]. Diatlov analysed parts with a wide range of surface slopes and found potential for analysis of the spectrum of the surface profile parameter R_a to determine surface characteristics [9]. Jamshidinia and Kovacevic found that an increase in heat accumulated during the build of thin-walled structures increases the surface roughness through an increase in adherence of partially melted powder particles to the part surface [10].

Triantaphyllou *et al.* investigated the upward- and downward-facing surface roughness for varying angles, compared results from multiple measurement instruments, and found that the S_{sk} parameter can be used for differentiating between upward- and downward-facing surfaces [11]. Aside

from this, however, little research has been performed to characterize downward-facing surface roughness, which is often the highest roughness [12]. Additionally, there is a lack of understanding of how and when structures that characterize the surface occur and how they affect the measured surface roughness parameters.

There is a wide range of mechanisms that contributes to the roughness of an AM surface, including both the process input parameters as well as the complex physical processes that occur during melting and solidification of the metal powder [13]. Understanding of surface characteristics is required in determining their effects on fatigue properties and in designing parts with improved performance [6]. Additionally, surface roughness has the potential to be used as a process signature. A strong quantitative understanding of relationships between measured surface parameters and the surface characteristic causing variation in measurements can determine if defects stem from AM system condition and performance or necessary maintenance (such as beam focus adjustments).

The purpose of this research is to understand the relationship between surface roughness parameters and the contributing surface features as a function of beam power, travel velocity, and overhang angle.

2. Experimental procedure

Experiments were performed on the EOS M270¹ system at the National Institute of Standards and Technology (NIST) using the commercially available EOS StainlessSteel GP1 (corresponds to US classification 17-4 [14]). It should be noted that the material used for the build was powder reclaimed from prior builds using an 80 μm sieve. It is assumed that the condition of the powder can have a large effect on the surface quality of parts being built and analysis of the powder is currently underway. All parts were fabricated during the same build. Thus, while the specific details of the powder have not yet been determined, the powder conditions are consistent across all of the samples.

The parts were designed as parallelepipeds with varying angles of overhang (α) to determine the effect of overhang angle on the surface roughness of the downward-facing surface. Fig. 1 shows an example model of the parallelepiped with a 60° angle overhang ($\alpha = 60^\circ$). Analysis was performed on overhang angles of 30°, 45°, 60°, and 75° as measured from the build plane. Prior experience has shown that the 30° overhang would build poorly (or crash the build) if it were built without supporting structures. To avoid this problem, hatched supports were added beneath the overhang. A 1 mm wide strip down the centre of the overhanging surface was left unsupported to allow measurement of the as-built surface.

To assess the effect of process parameters on surface characteristics, contour parameters with varying beam power and travel velocity were chosen in order to cover a wide range of the process space. Selection of process parameters can be seen in Table 1.

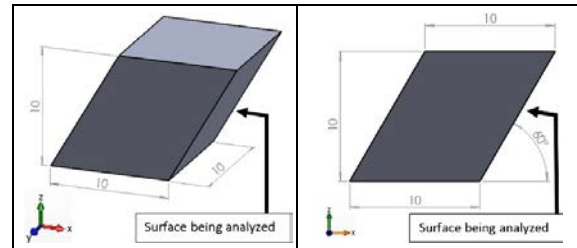


Fig. 1. Model parallelepiped for surface characterization, where $\alpha=60^\circ$. Dimensions are in millimeters. Build direction is positive z.

Table 1. Process parameters for experiments.

Line Energy - P/v (J/m)	Power (W)	Velocity (mm/s)	Contour Number
13.3	40	3000	1
35.7	25	700	2
46.7	140	3000	3
57.1	40	700	4
65	195	3000	5
71.4	25	350	6
114.3	40	350	7
116.4	195	1675	8
278.6	195	700	9

For each contour parameter set, parallelepipeds for each angle were built creating a total of 36 samples. To minimize the effect of incident angle of the laser beam and positional dependency on the build platform [15], all samples were positioned equidistant from the center of the build platform with the down-facing surface forming a straight line to the center of the beam source.

3. Analysis methods

Surface characterization was performed using a white light interferometer, described in detail in [16], and 10x objective lens. Using white light interferometry to analyze a very rough surface is a challenge due to difficulty in achieving null fringe condition (perfect leveling of the sample surface being measured). Because of this, a diamond-turned aluminum disk was first used to level the sample platform prior to any measurements. Thus, leveling the surface was performed as best as possible assuming that the surface being measured and the surface laying on the platform are parallel. This leveling procedure was performed before each measurement session to maintain a consistent leveling for each sample and prevent deviations due to errors caused by the leveling of the samples.

To create a large enough measurement of the sample surface to properly perform digital Gaussian filtering based on the ISO 4287 standard [17], nine images with 20 percent overlap were taken vertically down the downward-facing surface (in the build direction) and stitched together to create an

¹ Certain commercial entities, equipment, or materials may be identified in this document in order to describe an experimental procedure or concept adequately. Such identification is not intended to imply recommendation or

endorsement by the National Institute of Standards and Technology, nor is it intended to imply that the entities, materials, or equipment are necessarily the best available for the purpose.

Download English Version:

<https://daneshyari.com/en/article/1698493>

Download Persian Version:

<https://daneshyari.com/article/1698493>

[Daneshyari.com](https://daneshyari.com)