



Short communication

Silver nanoparticles embedded in modified polyallylamine resin as efficient catalysts for alkyne–azide 1,3-dipolar cycloaddition in water



Xian-Liang Zhao ^{a,*}, Ke-Fang Yang ^{b,**}, Yan Zhang ^a, Li-Wen Xu ^b, Xiao-Qing Guo ^a

^a School of Biological and Chemical Engineering/School of Light Industry, Zhejiang University of Science and Technology, Hangzhou 310023, China

^b Key Laboratory of Organosilicon Chemistry and Material Technology of Ministry of Education, Hangzhou Normal University, Hangzhou 310012, China

ARTICLE INFO

Article history:

Received 11 July 2015

Received in revised form 16 September 2015

Accepted 10 November 2015

Available online 11 November 2015

Keywords:

Silver nanocomposite

Polyallylamine

Modified

Alkyne–azide cycloaddition

Recycle

Water

ABSTRACT

A silver nanoparticle composite based on modified polyallylamine has been synthesized by a simple chemical route and its catalytic activity has been tested for alkyne–azide cycloaddition reaction. This silver nanocomposite shows an excellent catalytic activity at 80 °C for the synthesis of 1,4-disubstituted 1,2,3-triazole by alkyne–azide cycloaddition. The solid silver nanocomposite catalyst was characterized by transmission electron microscopy, Fourier-transform infrared spectroscopy, X-ray diffractometry and thermogravimetric analysis. The developed catalyst is stable in air, easy to prepare and can be recovered easily and reused ten times without a significant decrease in activity.

© 2015 Published by Elsevier B.V.

1. Introduction

The Huisgen 1,3-dipolar cycloaddition reaction between azides and terminal alkynes is a widely studied “click” reaction to synthesize 1,2,3-triazoles [1]. This reaction has been applied extensively in pharmaceuticals, drug discovery, agrochemicals, dyes, corrosion inhibitors, photostabilizers, photographic materials and biochemistry [2–7]. The copper-catalyzed alkyne–azide cycloaddition is regarded as the most efficient click chemistry [8–10]. The heterogeneous nature of catalysts offers advantages of thermal stability and reusability [11–14]. The catalytic activity of copper nanoparticles (Cu NPs) in the azide–alkyne click reaction has received much interest [15–21]. Silver nanoparticles (Ag NPs) have been employed catalysts in organic synthesis. However, Ag NPs have received less attention in terms of their application in the azide–alkyne click reaction [22]. Although Jana et al. reported on a silver–graphene nanocomposite for a “one-pot” azide–alkyne click reaction, the application of other Ag NPs immobilized on polymers still needs to be explored [23].

Polymers are excellent host materials for the preparation of metal nanoparticles. Various synthetic polymers, such as poly(methyl methacrylate), polystyrene, poly(vinyl alcohol) and poly(vinyl pyrrolidone),

have been used in the synthesis of metal nanoparticles [24–28]. However, minimal work has been carried out where polyallylamine has been used as a capping agent to stabilize metal nanoparticles [29–31]. Among them, Kuo just reported the syntheses and characterization of silver nanoparticles stabilized by poly(allylamine) (PAA) and by polyethyleneiminated poly-(allylamine). The application of Ag NPs still needs to be explored.

Herein, we describe the advantages of Ag NPs in modified polyallylamine as a simple, inexpensive and general and efficient heterogeneous catalyst for use in the Huisgen 1,3-dipolar reaction of alkyne–azide cycloaddition in water.

2. Experimental


2.1. Instruments

Infrared spectra were recorded on a Perkin Elmer Fourier-transform infrared (FTIR) spectrometer using KBr. FEI Technai G2 transmission electron microscope was used for transmission electron microscopic (TEM) image of sample. Thermogravimetric analysis (TGA) was carried out on a Mettler-Toledo 851E instrument. X-ray diffraction patterns were recorded on a Rigaku, D-5000 diffractometer, using Ni-filtered Cu-K radiation ($\lambda = 1.5405 \text{ \AA}$). ¹H NMR spectra were recorded on a 400 (Varian, Palo Alto, USA) spectrometer in CDCl₃ solution with tetramethylsilane as an internal standard. Chemical shift values are given in parts per million.

* Correspondence to: X.-L. Zhao, School of Biological and Chemical Engineering, Zhejiang University of Science and Technology, Hangzhou 310023, China.

** Corresponding author.

E-mail addresses: xlzhao@iccas.ac.cn (X.-L. Zhao), kfyang@hznu.edu.cn (K.-F. Yang).

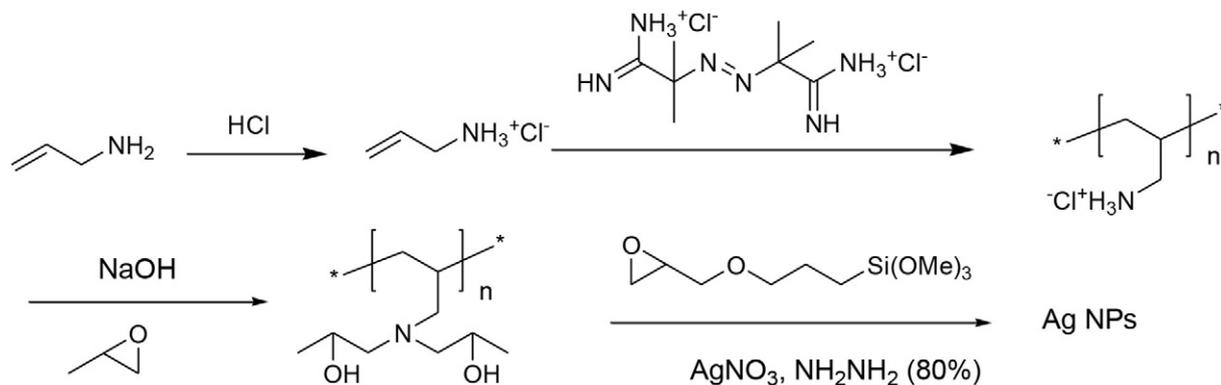

Scheme 1. Synthesis for silver nanocomposite.

2.2. Preparation of silver nanocomposite

The modified polyallylamine (10.0 g) was dissolved in water (30.0 mL) to obtain a clear solution at room temperature. Silver nitrate (3.26 g) was dissolved in water (10.0 mL) and added into the solution at room temperature. Ammonia water was added into the solution to obtain a clear solution at room temperature. (3-Glycidoxypropyl)methyldiethoxysilane (4.0 g) was added into the mixture at room temperature. The mixture was heated to a viscous solid at 120 °C, then cooled to room temperature. Hydrazine hydrate (80 wt.%) (20 mL) was added and stirred at room temperature for 24 h. The resultant brown solid was washed with water and dried at 60 °C for 12 h under vacuum to afford Ag NPs (16.2 g).

2.3. Application of silver nanocomposite as an efficient catalyst in organic reactions

A mixture of benzylazide (133.0 mg, 1.0 mmol), phenylacetylene (102.0 mg, 1.0 mmol), silver nanocomposite (10.0 mg) and water (1.0 mL) was stirred at 80 °C in a test tube. The reaction was extracted using dichloromethane (10.0 mL). The combined organic extract was washed with water (5.0 mL) and dried using anhydrous magnesium sulfate. The solvent was removed in vacuum and the crude product was purified by flash chromatography on silica gel (eluent: ethyl acetate/petroleum ether, 1:10) to afford a colorless solid **3a** (0.223 g, 95%).

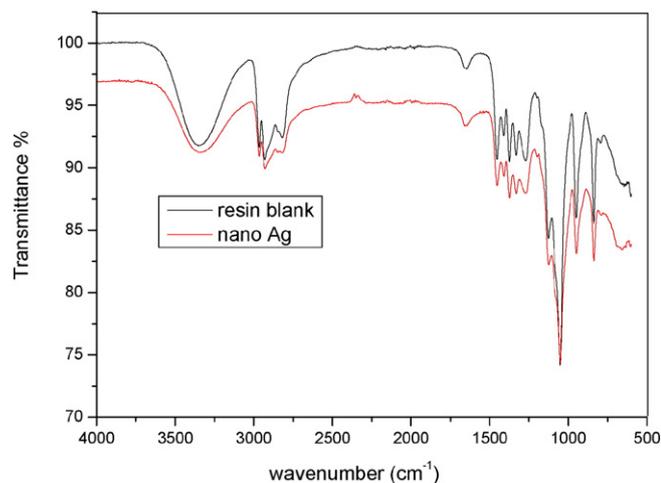


Fig. 1. FTIR spectra of Ag NPs and blank resin.

3. Results and discussion

3.1. Preparation of Ag NPs

The synthesis strategy for the silver–polyamine nanocomposite is shown in the Scheme 1. Polyallylamine was synthesized according our previous work [32]. The modified polyallylamine has a strong tendency to form gel in aqueous solution. This gel that contains hydroxy and amino groups protects and stabilizes the Ag NPs in its strong gel mesh and acts as an excellent surface capping agent in the process.

3.2. Catalyst characterization

3.2.1. FTIR spectra of Ag NPs and blank resin

The FTIR spectra of the blank and silver resin are shown in Fig. 1. The O–H absorption band shifted slightly compared with that of blank polymer composite in the FTIR analysis. This indicates that an interaction occurs between these groups and nanosilver.

3.2.2. X-ray diffractometry of Ag NPs and blank resin

Fig. 2a shows the X-ray diffraction pattern of the blank resin. The resin reflection at 2θ of 18.82° corresponds to the amorphous part of the resin. The resin reflection at 2θ of 28.42°, 40.53°, 50.3° and 73.84° corresponds to the crystalline part of the resin [33–34].

Fig. 2b shows the X-ray diffraction pattern of the silver resin. The reflections at 2θ of 38.3°, 43.6°, 64.6° and 77.80° correspond to (111), (200), (220) and (311) planes of silver, respectively [24–28]. The reflection of resin at 2θ of 19.22° corresponds to the amorphous part of the

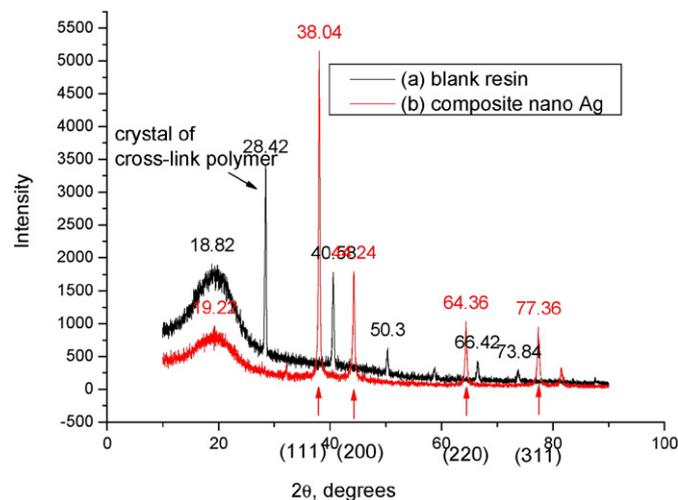


Fig. 2. X-ray diffraction pattern of Ag NPs and blank resin.

دانلود مقاله



<http://daneshyari.com/article/49267>



- ✓ امکان دانلود نسخه تمام متن مقالات انگلیسی
- ✓ امکان دانلود نسخه ترجمه شده مقالات
- ✓ پذیرش سفارش ترجمه تخصصی
- ✓ امکان جستجو در آرشیو جامعی از صدها موضوع و هزاران مقاله
- ✓ امکان پرداخت اینترنتی با کلیه کارت های عضو شتاب
- ✓ دانلود فوری مقاله پس از پرداخت آنلاین
- ✓ پشتیبانی کامل خرید با بهره مندی از سیستم هوشمند رهگیری سفارشات