



Short communication

Preparation of a highly dispersed Ni₂P/Al₂O₃ catalyst using Ni–Al–CO₃^{2–} layered double hydroxide as a nickel precursor

Hua Song^{a,*}, Quanming Ren^a, Feng Li^a, Hualin Song^b, RuiMa^a^a Provincial Key Laboratory of Oil & Gas Chemical Technology, College of Chemistry & Chemical Engineering, Northeast Petroleum University, Daqing 163318, Heilongjiang, China^b Key Laboratory of Cancer Prevention and Treatment of Heilongjiang Province, Mudanjiang Medical University, Mudanjiang 157011, China

ARTICLE INFO

Article history:

Received 8 August 2015

Received in revised form 7 October 2015

Accepted 9 October 2015

Available online 22 October 2015

Keywords:

Nickel phosphide (Ni₂P)

Hydrodesulfurization (HDS)

Layered double hydroxide (LDH)

Microwave–hydrothermal treatment

ABSTRACT

We now report a novel method for the synthesis of a Ni₂P/Al₂O₃-LW catalyst using Ni–Al–CO₃^{2–} layered double hydroxide (Ni–Al–CO₃^{2–}-LDH) as a nickel precursor and ammonium dihydrogen phosphate as a phosphorous precursor under microwave–hydrothermal (MWH) treatment for 20 min at 363 K. The catalysts were characterized by XRD, TPR, BET, CO uptake and XPS. MWH treatment can promote the formation of smaller and highly dispersed Ni₂P particles and a higher surface area of the catalyst. The Ni₂P/Al₂O₃-LW shows hydrodesulfurization activity of 99.3%, which was much higher than that found for the Ni₂P/Al₂O₃ catalyst obtained via an impregnation method.

© 2015 Published by Elsevier B.V.

1. Introduction

Recently, hydrodesulfurization (HDS) of fuel oils has received a lot of attention due to more stringent environmental regulations enacted throughout the world. Therefore, the development of highly active HDS catalysts has been an urgent subject worldwide [1–3]. In order to effectively achieve HDS, many efforts have been devoted to prepare excellent active catalysts including phosphide, carbide and nitride catalysts [4,5]. In recent years, catalysts for HDS derived from layered double hydroxide (LDH) precursors have attracted a lot of attention because their HDS activity was much higher than those found for other conventional catalysts [6,7].

LDH is a class of material with the general formula [M₁²⁺_xM₂³⁺(OH)₂]^{x+}(A^{n–})_{x/n}·mH₂O, where M²⁺ and M³⁺ are divalent and trivalent metal cations within the hydrotalcite-like compounds, respectively, and A^{n–} denotes an organic or inorganic anion [8]. The M²⁺ and M³⁺ cations are uniformly dispersed within the layers. Thus, these layered materials have been widely used as catalysts, catalyst precursors or catalyst supports [9]. Li et al. [10] have reported a NiAl₃MoW-5 catalyst with a layered structure that showed about two times higher HDS activity than commercially available catalysts. Faro Jr. et al. [11] found that an unsupported NiMoAl catalyst prepared from NiAl-terephthalate LDH showed higher HDS activity than that found for the conventional NiMo/Al₂O₃ catalyst. An unsupported CoMgMoAl hydrotreated catalyst prepared from CoMgAl-terephthalate LDH possessed higher HDS

selectivity than that found for a commercially available CoMo/Al₂O₃ catalyst [12].

Microwave irradiation has been applied for the rapid synthesis of inorganic solids and organic reactions [13]. It was found that hydrotalcites obtained by a microwave–hydrothermal (MWH) method present smaller crystallite sizes with improved dispersion and higher specific surface area than conventional samples [14]. Siffert et al. [15] have prepared a Co–Al mixed oxide catalyst using microwave irradiation, which possessed smaller particle sizes and a larger surface area and showed improved activity than that found for the corresponding catalyst prepared using a co-precipitation method. However, to the best of our knowledge, the Ni₂P catalyst derived from an LDH precursor has not been previously reported for use in HDS.

In this work, the Ni₂P/Al₂O₃-LW catalyst precursor was prepared via a novel method using Ni–Al–CO₃^{2–}-LDH as the nickel precursor and NH₄H₂PO₄ as a phosphorous precursor under MWH treatment conditions. The Ni₂P/Al₂O₃-LW catalyst, which exhibits a smaller crystallite size and better dispersion of active Ni₂P particles was obtained after H₂ reduction.

2. Experimental

2.1. Synthesis of Ni–Al–CO₃^{2–}-LDH

The pristine Ni–Al–CO₃^{2–} layered double hydroxide (Ni–Al–CO₃^{2–}-LDH) was prepared by coprecipitation. An aqueous solution of NaOH (0.67 mol/L) and Na₂CO₃ (0.02 mol/L) was added dropwise into a mixed salt solution of Ni(NO₃)₂·6H₂O and Al(NO₃)₃·9H₂O (a Ni²⁺/Al³⁺ molar ratio of 3/1) up to the pH of 10 under stirring. The resulted

* Corresponding author.

E-mail address: songhua2004@sina.com (H. Song).

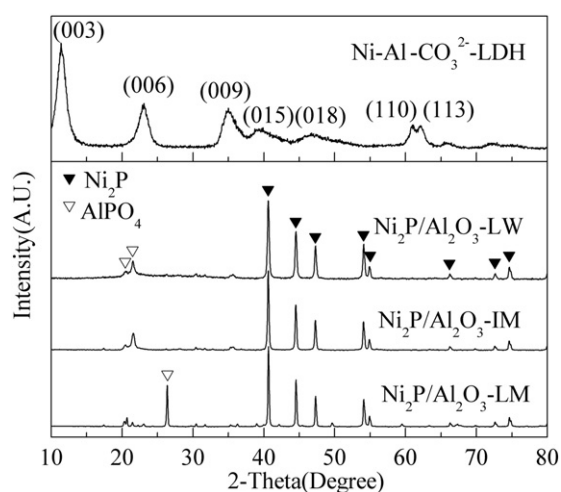


Fig. 1. XRD patterns of the Ni–Al–CO₃²⁻-LDH and Ni₂P/Al₂O₃-X catalysts.

mixture was aged at 333 K for 6 h. The precipitates were filtered and washed with deionized water to obtain the Ni–Al–CO₃²⁻-LDH. The Ni–Al–CO₃²⁻-LDH was calcined to obtain Ni–Al–CO₃²⁻ layered double oxide (denoted as Ni–Al–CO₃²⁻-LDO).

2.2. Preparation of catalyst precursor

The Ni–Al–CO₃²⁻-LDH was added into an ammonium dihydrogen phosphate (NH₄H₂PO₄) solution and treated using MWH for 20 min at 363 K under reflux. The suspension was dried at 393 K for 10 h to obtain the catalyst precursor of Ni₂P/Al₂O₃-LW.

For comparison, the catalyst precursors were prepared by a standard incipient wetness impregnation of the Ni–Al–CO₃²⁻-LDH with a NH₄H₂PO₄ solution for 24 h and impregnation of Al₂O₃ with a mixture of NH₄H₂PO₄ and Ni(NO₃)₂·6H₂O solution, respectively. The resulting solids were dried at 393 K for 10 h to obtain the catalyst precursors Ni₂P/Al₂O₃-LM and Ni₂P/Al₂O₃-IM, respectively.

2.3. Synthesis of Ni₂P/Al₂O₃-X catalyst

The obtained precursors of Ni₂P/Al₂O₃-LW, Ni₂P/Al₂O₃-LM and Ni₂P/Al₂O₃-IM were calcined at 773 K for 3 h, and then reduced in a fixed-bed reactor by heating to 973 K at a rate of 2 K min⁻¹ in a flow of H₂, held for 2 h, then naturally cooled to room temperature in a continuous H₂ flow. The obtained catalyst was passivated in O₂/N₂ mixture (0.5 vol.% of O₂) with flow rate of 20 mL/min for 2 h to obtain the corresponding Ni₂P/Al₂O₃-X (X = LW, LM, IM) catalysts with Ni loading of 64.4 wt.% and an initial Ni/P molar ratio of 1/2, and then which was subjected to characterization.

2.4. Characterization of catalyst

X-ray diffraction (XRD) analysis was carried out on a D/max-2200PC-X-ray diffractometer. Temperature-programmed reduction

(TPR) experiments were carried out with a Builder PCA-1200 apparatus. The specific surfaces (BET) of the catalysts were obtained by using micromeritics adsorption equipment of TRISTAR II 3020. CO chemisorption uptake measurements were performed in a micromeritics ASAP 2010 apparatus. The XPS spectra were acquired using ESCALAB MKII spectrometer. XPS measurements were performed using monochromatic Mg K α radiation (E = 1253.6 eV). The recorded photoelectron binding energies were referenced against the C 1s contamination line at 284.8 eV. Transmission electron microscope (TEM) examinations were performed using the JEM-1010 instrument supplied by JEOL.

2.5. Catalytic activities

The HDS of dibenzothiophene (DBT) was performed in a flowing high-pressure fixed bed stainless steel catalytic reactor (6 mm in diameter, and 400 mm in length) using a feed consisting of a decalin solution of DBT (1 wt.%). Catalytic activities were measured at 613 K, 3.0 MPa, weight hourly space velocities (WHSV) of 2.0 h⁻¹ and hydrogen/oil ratio of 500 (V/V). The catalysts were pressed in disks, crushed, and sieved with 20–40 mesh before use. Prior to reaction, 0.65 g of the catalysts were pretreated in situ with flowing H₂ (40 mL/min) at 773 K for 2 h. Sampling of liquid products was started 2 h after the steady reaction conditions had been achieved. The liquid samples were collected every hour and analyzed by FID gas chromatography with a GC-14C-60 column.

3. Results and discussion

3.1. XRD

As can be seen in Fig. 1, the reflection of the planes (003), (006), (009), (012), (015) and (018) of crystalline LDH were attributed to Ni–Al–CO₃²⁻-LDH. Meanwhile, the typical doublet of the d(110)–d(113) planes of LDH can be clearly observed in the zone around 2 θ = 60–62°. The XRD pattern for Ni–Al–CO₃²⁻-LDH was similar to those reported in the literature [9] for LDH phases, showing that Ni–Al–CO₃²⁻-LDH was successfully prepared.

For all Ni₂P/Al₂O₃-X, the strong diffraction peaks at 2 θ = 40.6°, 44.5°, 47.1° and 54.1° (PDF: 03-0953) can be ascribed to the Ni₂P phase, which indicates that the Ni₂P phase was the dominant phase. However, the AlPO₄ peaks were observed for all the catalysts, which were caused by the strong interactions found between aluminum and phosphorus [16]. Moreover, when compared to Ni₂P/Al₂O₃-IM and Ni₂P/Al₂O₃-LM, the width of the Ni₂P phase of Ni₂P/Al₂O₃-LW was increased. In general, an increase in peak width of the Ni₂P phase exhibits a decrease in the crystallite size (D_c) of the Ni₂P phase. The D_c calculated from Scherrer's equation is listed in Table 1 [17,18]. It can be seen from TEM analysis (Fig. S1 and S2) that the Ni₂P particle sizes ranged from approximately 13 to 75 nm for Ni₂P/Al₂O₃-LM catalyst and from 13 to 59 nm for Ni₂P/Al₂O₃-IM. The Ni₂P/Al₂O₃-LW possessed the smallest Ni₂P particle sizes, which ranged from approximately 7 to 42 nm with average crystallite size of 28.4 nm. This agreed with the result (28.2 nm) obtained by XRD analysis (column 5 of Table 1). The MWH treatment could suppress agglomeration during the nucleation and crystal growth processes,

Table 1
Textural properties of the Ni–Al–CO₃²⁻-LDO, Al₂O₃ and Ni₂P/Al₂O₃-X catalysts.

Sample	S _{BET} (m ² g ⁻¹)	Pore volume (cm ³ g ⁻¹)	Average pore size (nm)	D _c ^a (nm)	CO uptake (μ mol g ⁻¹)	Conversion ^b (%)	Selectivity (%) ^b	
							CHB	BP
Ni ₂ P/Al ₂ O ₃ -LW	29.0	0.183	24.7	28.2	227	99.3	24.7	75.3
Ni ₂ P/Al ₂ O ₃ -IM	9.2	0.042	17.7	34.5	176	88.5	35.2	64.8
Ni ₂ P/Al ₂ O ₃ -LM	5.1	0.001	9.0	40.7	59	55.5	21.5	78.5
Ni–Al–CO ₃ ²⁻ -LDO	87.0	0.220	9.9	–	–	–	–	–
Al ₂ O ₃	255.5	0.314	4.9	–	–	–	–	–

^a Calculated from the D_c = K λ / β cos(θ) (Scherrer equation) based on the Ni₂P (1 1 1).

^b Reaction conditions: T = 653 K, P = 3.0 MPa, WHSV = 2.0 h⁻¹, H₂/oil (V/V) = 500.

دانلود مقاله



<http://daneshyari.com/article/49399>



- ✓ امکان دانلود نسخه تمام متن مقالات انگلیسی
- ✓ امکان دانلود نسخه ترجمه شده مقالات
- ✓ پذیرش سفارش ترجمه تخصصی
- ✓ امکان جستجو در آرشیو جامعی از صدها موضوع و هزاران مقاله
- ✓ امکان پرداخت اینترنتی با کلیه کارت های عضو شتاب
- ✓ دانلود فوری مقاله پس از پرداخت آنلاین
- ✓ پشتیبانی کامل خرید با بهره مندی از سیستم هوشمند رهگیری سفارشات