



# Physical, chemical and antimicrobial implications of the association of propolis with a natural rubber latex membrane



Daniela Cervelle Zancanela<sup>a,\*</sup>, Rondinelli Donizetti Herculano<sup>b</sup>, Cristiano Soleo Funari<sup>c</sup>,  
Caroline Maria Marcos<sup>b</sup>, Ana Marisa Fusco Almeida<sup>b</sup>, Antônio Carlos Guastaldi<sup>a</sup>

<sup>a</sup> São Paulo State University (UNESP), Institute of Chemistry, Araraquara, São Paulo, Brazil

<sup>b</sup> São Paulo State University (UNESP), School of Pharmaceutical Sciences, Araraquara, São Paulo, Brazil

<sup>c</sup> São Paulo State University (UNESP), Faculty of Agricultural Sciences, Botucatu, São Paulo, Brazil

## ARTICLE INFO

### Article history:

Received 18 April 2017

Received in revised form 7 July 2017

Accepted 22 July 2017

Available online 23 July 2017

### Keywords:

Skin wound healing

Antifungal

Cicatrizant

Propolis release

## ABSTRACT

Natural rubber latex (NRL) has shown interesting biomedical properties, such as wound healing improvement, tissue regeneration stimulation and angiogenesis. Propolis, produced by honey bees, acts as an antiseptic agent in beehives. It has been used in ethnopharmacology as an antimicrobial and cicatrizant agent over centuries. The aim of this study was to incorporate propolis into an NRL membrane whilst keeping the antibiotic properties of the former against microorganisms often associated with wound healing delay and the chemical and physical characteristics of the latter. This work has shown that the interactions between the NRL and the propolis constituents were not due to chemical bonding. The propolis-NRL membrane constituents in simulated body fluid were released gradually, reaching 37% release in 144 h. The concentration of released material of 400 µg/mL was able to inhibit 80% of the growth of *C. albicans*. The incorporation of propolis extract into a NRL membrane while keeping the desirable characteristics of both has been demonstrated to be feasible. Therefore, this association might be used as an auxiliary in wound healing processes.

© 2017 Elsevier B.V. All rights reserved.

## 1. Introduction

Natural Rubber Latex (NRL) membranes from *Hevea brasiliensis* are important inductors of the wound healing process and are used in several medical applications, such as in prosthetics and bone grafting [1,2]. In addition, the treatment of diabetic and phlebotrophic ulcers with NRL membranes leads to faster healing due to a vascular growth factor found in NRL, together with the physical blockage to exposure to new infectious agents at the damaged site. Some of the interesting features of NRL membranes are biocompatibility, capacity to stimulate angiogenesis, easy manipulation, low cost and high mechanical resistance [2].

Propolis is a complex mixture of varying resinous, gummy and balsamic materials produced by *Apis mellifera L.* from plant parts, pollen, bee salivary secretions and wax with the purpose of sealing and protecting beehives against infecting microorganisms, among others [3]. In addition to its wide use in ethnopharmacology, its persistent use as a cicatrizant agent over the centuries is one of its most popular uses [4]. A wide range of biological activities of

propolis that may be related to skin healing have been reported in the specialized literature, such as antibacterial, antifungal, skin cell proliferation enhancer, among others [5,6].

The aim of this work was to incorporate propolis into a NRL membrane while keeping its antibiotic properties against microorganisms often associated with wound healing delay and the physical and chemical characteristics of the latter. For that, the following parameters were investigated: (i) the physical and chemical interactions between the NRL membrane and propolis, (ii) the release of propolis constituents from the NRL membrane in simulated body fluid (SBF), (iii) the ability of the released compounds to act as antimicrobial agents and (iv) the effect of the incorporation of propolis into NRL on the membrane mechanical resistance.

## 2. Materials and methods

A propolis extract was produced using a crude dry propolis (ApisFlora, Brazil) sample in EtOH-H<sub>2</sub>O (7:3 v/v) solution [7]. NRL (BDF Rubber Latex Co. Ltd., Brazil) was extracted, centrifuged and kept in an ammonia solution [1,8]. A propolis-NRL membrane was obtained by adding 1 mL of propolis extract to 3 mL of NRL

\* Corresponding author.

E-mail address: [daniela.zancanela@iq.unesp.br](mailto:daniela.zancanela@iq.unesp.br) (D.C. Zancanela).

in Petri dishes and kept at room temperature for 24 h. Pure NRL membranes were also prepared as a control.

Membrane tensile were carried out in a Universal testing machine – EMIC Model DL 2000 with a 50 kgf load cell at 500 mm/min and elongated until failure, following ASTM standard D412. The propolis extract, the pure NRL membrane and the propolis-NRL membrane were characterized by FTIR directly by the attenuated total reflection (ATR) method using a TENSOR 27 (Bruker, Germany) ( $4000\text{--}500\text{ cm}^{-1}$ ) with a resolution of  $4\text{ cm}^{-1}$  and 32 scans [1]. For the compound release study of the propolis-NRL membrane, the membrane was placed into a 10 mL SBF solution. The release behavior was investigated by analyzing aliquots of the solution at predetermined time intervals for 216 h by UV-VIS spectroscopy (216 nm). The amount of substance released was calculated by means of the Lambert Beer law and the line equation was obtained by linear regression of the analytical calibration curve of the extract [8].

The propolis extract produced was evaluated against *C. albicans* (ATCC 90028, from the Laboratory of Clinical Mycology, Depart-

ment of Clinical Analysis, Faculty of Pharmaceutical Sciences of UNESP in Araraquara). The minimum inhibitory concentration (MIC) was determined using the microdilution method described in document M27-A2 from the Clinical Laboratory Standards Institute (CLSI) with serial dilutions of the propolis extract in a RPMI culture medium. The NRL membranes with and without propolis extract were also evaluated for their activities against *C. albicans*. The material released in SBF at  $400\text{ }\mu\text{g/mL}$  was tested in RPMI culture medium for 24 h.

### 3. Results

FTIR-ATR (Fourier Transform Infrared-Attenuated Total Reflection) was used to characterize the interactions among NRL and the propolis constituents. Fig. 1 shows the spectra of the propolis extract and NRL membranes with and without propolis extract.

The spectrum of the pure NRL membrane showed bands characteristic of *cis* 1,4-polyisoprene at  $1375$ ,  $1445$ ,  $2859$  and  $2961\text{ cm}^{-1}$  (Fig. 1) as expected [8]. The propolis extract presented characteristic bands at  $1640$ ,  $1457$ ,  $1252\text{ cm}^{-1}$  typical of aromatic rings and polyols and flavonoids, among other classes of compounds [10] (Fig. 1). The propolis-NRL membrane spectrum showed a sum of the bands observed in the separate analyses of the NRL membrane and propolis (Fig. 1). Moreover, no molecular interactions were observed between propolis and the NRL membrane, suggesting that the interactions between the membrane and the propolis compounds were physical (physical adsorption). This is a desirable behavior, since it allows the release of propolis compounds from the membrane into the wound environment.

Fig. 2 shows the gradual release of propolis constituents by the propolis-NRL membrane over 216 h in a SBF solution.

The large amount of propolis extract compounds released from the propolis-NRL membrane that occurred before stability was reached is called “burst release” (0–5 h) (Fig. 2). In the first hour, the membrane released almost 15.8% of propolis extract compounds and in the first 24 h, about 22%. The release continued up to 37.35% in 144 h, when the concentration became constant (Fig. 2). The release depends mainly on the amount of compounds present in the polymer bulk (encapsulated material) versus the

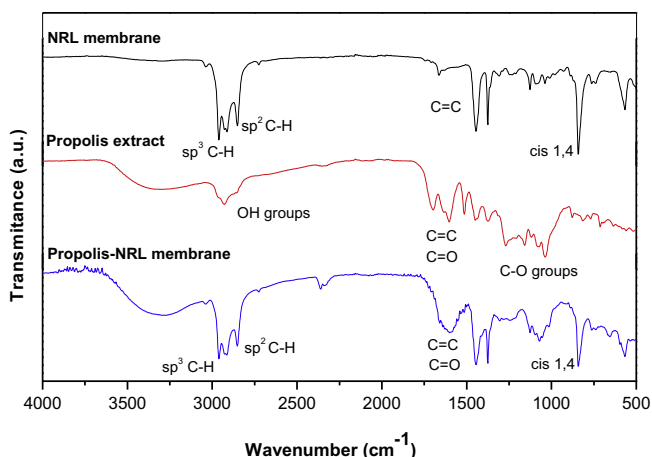


Fig. 1. FTIR-ATR spectra of propolis extract and NRL membranes.

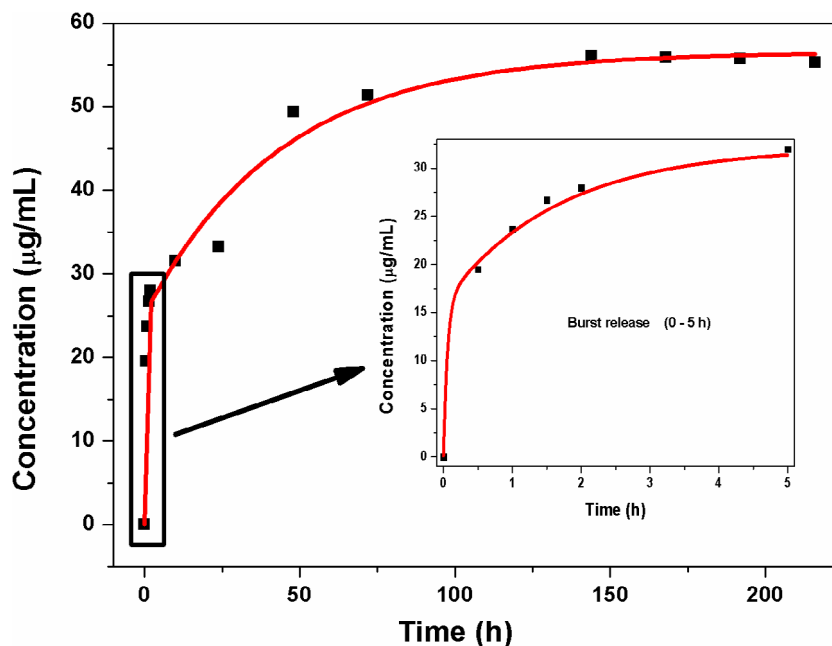


Fig. 2. Propolis extract release kinetics from NRL membranes in SBF. Insert: First 5-h release.

Download English Version:

<https://daneshyari.com/en/article/5462727>

Download Persian Version:

<https://daneshyari.com/article/5462727>

[Daneshyari.com](https://daneshyari.com)