



Contents lists available at ScienceDirect

Journal of Magnetism and Magnetic Materials

journal homepage: www.elsevier.com/locate/jmmm

On the resonant state of magnetization in array of interacting nanodots

P.D. Kim^a, V.A. Orlov^{a,b,c,*}, R.Yu. Rudenko^{a,b}, V.S. Prokopenko^c, I.N. Orlova^c, A.V. Kobayakov^{a,b}^a Kirensky Institute of Physics Federal Research Center KSC Siberian Branch Russian Academy of Sciences 660036 Krasnoyarsk, Russia^b Siberian Federal University, 660041 Krasnoyarsk, Russia^c Krasnoyarsk State Pedagogical University after V.P. Astafev, 660049 Krasnoyarsk, Russia

ARTICLE INFO

Keywords:

Nanodots
Magnetization
Dispersion law
Tiel's equation

ABSTRACT

Development of the interpretation of the phenomenon of the lift of the magnetic resonance frequencies degeneracy caused by the magnetostatic interaction in assemblies of nanodisks has been done. The difference of the resonance behavior of magnetic vortices in a round and rectangular nanodots has been studied experimentally and explained.

1. Introduction

It is known, at certain ratios between the thickness and width (diameter) of nanodots, the stable distribution of the magnetization occurs in the form of a vortex with the Bloch point in the center of a magnet. The theory for describing the dynamics of the magnetization was developed on the basis of the Thiel equation (in terms of collective variables [1–6]). It was shown that the core of magnetic vortex executes gyrotropic motion around the axis of a nanodisk similar to the Larmor motion of a charged particle around the magnetic field lines.

The experimental tools for studying nanodots are also widely developed (e.g., in [7,8]). The cited works present the results of experimental studies of the magnetic properties of the individual nanodots. However, most experiments deal with films, i.e. arrays of fairly separated nanodots. For this reason, the interaction between the magnetic subsystems of elements of an array is usually disregarded [9]. At the same time, the long-term magnetostatic interaction can affect at least collective modes of rotational motion of the core if not the static or quasistatic characteristics of magnetization [10–12].

We would like also mention the works, where the magnetostatic interaction in assemblies of magnetic nanoparticles was studied [13,14], and the problem of the oscillatory modes in a pair of coaxial magnetostatically interacting nanodisks was analytically solved [15].

2. Experimental equipment and samples

The arrays of circular and square nanodots for our studies were formed by the “lift-off” technique from a continuous film prepared with thermal sputtering from an 80HXC alloy on silicon substrate [16].

The morphology and the magnetic relief of the films surface were studied with a the “Veeco MultiMode NanoScope IIIa SPM System”. The chirality direction $q = \pm 1$ was determined from the distribution of the gradient of the magnetic forces acting on the probe of the cantilever. Diameter and thickness of the particles were 3 μm and 100 nm, correspondingly.

The magnetic resonance properties of the nanodot array were studied with the ferromagnetic resonance (FMR) spectrometer operating at the frequency of 373 MHz and 415 MHz. The sample was placed in the antinode of a magnetic field of the cavity, which was of a short-circuited quarter-wave waveguide with a 4-mm wide central strip. The differential absorption curves were obtained for the sample in dependence of the base field (Fig. 1). The absorption curves in Fig. 1 have the form of superposition of curves with different absorption widths and resonance frequencies. This means the splitting of the resonance frequency of the gyrotropic motion of vortices.

3. Magnetostatic interacting nanodisks

Below, we consider the model situation that will help us qualitatively understand the origin of the lift of the degeneracy of the resonance frequency. Here we present a refinement of the calculations from works [16] for 2D-array of nanodots. Let us consider a square 2D array of cylindrical nanodots with the centers separated by equal distance d .

It is known, one of the equilibrium magnetization distributions in circular nanocylinders is the vortex structure [17–20]. Below, we use an approximation in which the profile of the magnetization of the vortex changes rigidly at the displacement of the core from the center (rigid magnetic vortex model). The behavior of the core is described by

* Corresponding author at: Kirensky Institute of Physics Federal Research Center KSC Siberian Branch Russian Academy of Sciences, 660036 Krasnoyarsk, Russia.
E-mail address: orlhome@rambler.ru (V.A. Orlov).

<http://dx.doi.org/10.1016/j.jmmm.2016.12.125>

Received 16 August 2016; Received in revised form 3 December 2016; Accepted 18 December 2016
0304-8853/ © 2016 Elsevier B.V. All rights reserved.

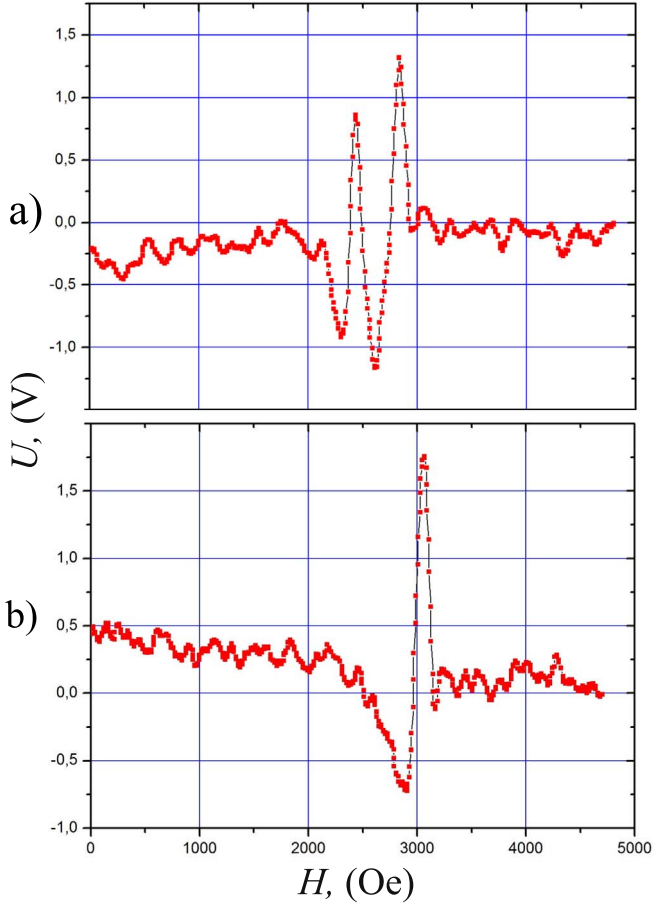


Fig. 1. Differential absorption curves obtained in the FMR experiment with the circular nanodots for arrays with the distance between the disks 2 μm (a), and 4 μm (b).

the equation of motion in the form

$$\mathbf{G} \times \mathbf{v} - \nabla U + \mathbf{F} = 0. \quad (1)$$

Here, \mathbf{G} is the gyrovector, \mathbf{v} is velocity of the core the magnetic vortex, U is the potential energy of the magnetization (its variation at the displacement of the core from the disk center is attributed, as a rule, to an increase in the magnetostatic energy). According to (1) if $\mathbf{F} = 0$, the vortex core involves in the complex motion with the gyroforce [21–26]. We added this equation with the force \mathbf{F} caused by the magnetostatic interaction between array elements.

Consider the mechanism of the magnetostatic interaction by the example of two neighboring disks. As was shown in [27], the magnetic field configuration beyond the nanodot is similar to the configuration of the field of a magnetic dipole with the satisfactor accuracy. Therefore, below we can use the dipole approximation to estimate the energy of interaction between cylinders. In [28], the collective modes were thoroughly analytically calculated using the model where only the magnetizations of identically oriented cores interact.

We approximate the interaction between nanodisks by parabolic potential well $\nabla U = \kappa \mathbf{r}$, where κ is the so-called effective rigidity of a magnetic subsystem. In this case, in the projections onto the system of coordinates, equations for n -th disk is

$$-G\ddot{y}_n - \kappa x_n + F_{x_n} = 0, \quad G\ddot{x}_n - \kappa y_n + F_{y_n} = 0. \quad (2)$$

Let us estimate the force F . In the dipole approximation, the energy of magnetostatic interaction between disks distant from each other by i periods along the x axis and by j periods along the y axis can be presented

as $W_{n,m,i,j} = (\mathbf{M}_{n,m} \mathbf{M}_{n+i,m+j} - 3(\mathbf{M}_{n,m} \mathbf{r}_{i,j})(\mathbf{M}_{n+i,m+j} \mathbf{r}_{i,j})) / (i^2 + j^2) d^2 / (i^2 + j^2)^{3/2} d^3$. Here, $\mathbf{r}_{i,j}$ is the radius vector connecting centers of nanodisks. We will

seek for the solution of system (2) in the form

$$\begin{aligned} x_{n,m} &= a_{n,m} \cos(k_x X_{n,m} + k_y Y_{n,m} - q_{n,m} p_{n,m} \omega t), \quad y_{n,m} \\ &= b_{n,m} \sin(k_x X_{n,m} + k_y Y_{n,m} - q_{n,m} p_{n,m} \omega t). \end{aligned} \quad (3)$$

Here, the parameter $q_{n,m} = \pm 1$, $p_{n,m} = \pm 1$ is the chirality and polarity of the vortex with the number (n, m) , $X_{n,m}$, $Y_{n,m}$ are the nanodots center coordinates, and k_x, k_y are the projections of the wave number onto the coordinate axes. Now, let us consider the case when one array contains disks with only two possible implementations $((q, p)$ or (q', p')), which are arranged in the staggered order.

Although the chosen model is somewhat artificial, it allows us to qualitatively explain the phenomenon of the lift of the degeneracy of the resonance frequency. Substituting the probe solutions to Eq. (2) for disks of two different kinds, we obtain biquadratic equation for the unknown ω . The solution for the modes of resonance motions

$$\omega^2 = \frac{B}{2A} \pm \sqrt{\left(\frac{B}{2A}\right)^2 - \frac{C}{A}}, \quad (4)$$

where

$$\begin{aligned} A &= G^2 G'^2, \quad B = (G^2 + G'^2)(\kappa + \varepsilon S_o^{(1)})(\kappa + \varepsilon S_o^{(2)}) + 2GG' \varepsilon^2 S_o^{(1)} S_o^{(2)}, \quad C \\ &= ((\kappa + \varepsilon S_o^{(1)})^2 - \varepsilon^2 S_o^{(1)2})(\kappa + \varepsilon S_o^{(2)})^2 - \varepsilon^2 S_o^{(2)2}). \end{aligned} \quad (5)$$

Here, we introduced the designations

$$\begin{aligned} S_o^{(1)} &= \sum_{i+j=1,3,5\dots} \left(\frac{i^2 - 2j^2}{(i^2 + j^2)^{5/2}} \cos(k_x di) \cos(k_y dj) \right), \quad S_o^{(1)} \\ &= \sum_{i+j=2,4,6\dots} \left(\frac{i^2 - 2j^2}{(i^2 + j^2)^{5/2}} \cos(k_x di) \cos(k_y dj) \right), \quad S_o^{(2)} \\ &= \sum_{i+j=1,3,5\dots} \left(\frac{j^2 - 2i^2}{(i^2 + j^2)^{5/2}} \cos(k_x di) \cos(k_y dj) \right), \quad S_o^{(2)} \\ &= \sum_{i+j=2,4,6\dots} \left(\frac{j^2 - 2i^2}{(i^2 + j^2)^{5/2}} \cos(k_x di) \cos(k_y dj) \right), \quad \varepsilon = \frac{\mu_0 M^2}{\pi R_0^2 d^3}. \end{aligned} \quad (6)$$

Parameters G , G' , and κ are taken from the works [2,8,26]:

$$G = qp \frac{2\pi M_S L}{\gamma} (1 - ph), \quad \kappa = \frac{40 \pi M_S^2 L^2}{9 R} (1 - h^2), \quad G' = q' p' \frac{2\pi M_S L}{\gamma} (1 - p'h), \quad (7)$$

Here, L is the nanodisk thickness and γ is the gyromagnetic ratio and the dimensionless field $h = H/H_S$ is applied perpendicular to the disk plane.

In the limit case $d \gg R$, when disks do not interact, Eq. (4) yields the well-known result for the core gyrotropic motion frequency in the solitary disk: $\Omega_0 = \kappa/G \rightarrow \Omega'_0 = \kappa/G'$. The presence of a multiplet in the FMR absorption curve in zero external field was predicted in [29] and confirmed in part in the experiment [27], were a system of two or four interacting disks.

Fig. 1 shows differential absorption curves obtained by us in the FMR experiment. It is seen that practically one resonance curve is observed, when the distance between disks is 4 μm (a). The splitting of this curve onto several resonance peaks occur, when the distance between the disks became 2 μm (b). We interpret this splitting as the lift of the degeneracy of the resonance frequency. The maximum splitting calculated using formula (4) in the long-wavelength limit is about $\Delta h \approx 0.2$. This is in satisfactory agreement with the experimental data presented in Fig. 1a.

The theory of the shape of the splitting resonance curve is not developed yet. That is why we describe the experimental data illustrated in Fig. 1, introducing a fitted formula. Assume the absorbed power to be determined by characteristic the sum of the independent Lorentz resonance curves

$$P(\omega, h) \sim \sum_i \frac{\rho_i \omega \Gamma(h)}{(\omega^2 - \omega_i(h)^2)^2 + 4\omega^2 \Gamma(h)^2}. \quad (8)$$

Download English Version:

<https://daneshyari.com/en/article/5490786>

Download Persian Version:

<https://daneshyari.com/article/5490786>

[Daneshyari.com](https://daneshyari.com)