

Enabling continuous capture and catalytic conversion of flue gas CO₂ to syngas in one process



Luis F. Bobadilla^{a,1}, José M. Riesco-García^b, Germán Penelás-Pérez^b, Atsushi Urakawa^{a,*}

^a Institute of Chemical Research of Catalonia (ICIQ), The Barcelona Institute of Science and Technology, Av. Països Catalans 16, 43007 Tarragona, Spain

^b Repsol Technology Center, Carretera de Extremadura A-5, km 18, 28935 Móstoles, Madrid, Spain

ARTICLE INFO

Article history:

Received 10 January 2016

Received in revised form 4 April 2016

Accepted 6 April 2016

Available online 14 April 2016

Keywords:

CO₂ capture

CO₂ reduction

Heterogeneous catalysis

Unsteady-state operation

ABSTRACT

Albeit a variety of available strategies for CO₂ conversion to useful chemicals and fuels, most technologies require relatively pure CO₂, especially without oxygen and water. This requires additional steps of CO₂ capture and purification before its efficient conversion. This necessity increases energy requirement, leading to poorer carbon footprints and higher capital expenditures lowering the viability of overall CO₂ conversion processes. We have developed an effective technology which combines CO₂ capture and conversion processes using isothermal unsteady-state operation and a catalyst consisting of earth-abundant chemical elements (FeCrCu/K/MgO–Al₂O₃). Diluted CO₂ streams common in process flue gases, even containing oxygen and water, can be fed to the process and relatively pure product stream such as syngas, i.e. carbon oxides (CO and CO₂) and hydrogen mixture, can be produced. A possible scheme of reactor integration for continuous CO₂ abatement and conversion based on a two-reactors system is presented.

© 2016 Elsevier Ltd. All rights reserved.

1. Introduction

Success in the quest for sustainable solutions to environmental threats induced by the atmospheric carbon dioxide (CO₂) accumulation largely relies on advances in chemical sciences and technological innovations [1]. One of the most promising strategies for the mitigation of anthropogenic CO₂ emission is its utilization by converting CO₂ into chemical fuels and value-added chemicals such as methanol and polymers [2]. Prior to the chemical transformation, however, CO₂ must be first captured from emission sources such as power, refinery, chemical, steel, and ceramic plants. This stage represents an increase of 40 to 80% of the total capital cost for a conventional post-combustion carbon capture and storage (CCS) process [3]. Thus, these steps drastically increase capital costs and investments for CO₂ transformation. Only the capture step is estimated to increase the energy requirements of a power plant by 25–40% [4].

Most chemical processes are designed to be operated under steady-state conditions. In case of heterogeneous catalytic processes, process performance is conventionally optimized under

a given temperature, pressure, concentration, and flow conditions. Having this approach as the main stream, over the past 50 years intensive research and development work in academia and industry was devoted to improve the overall reaction performance using so-called *unsteady-state operation*. For a number of catalytic reactions, the advantages of unsteady-state operation and improvement in catalytic process performances were shown theoretically and also demonstrated in practice by forcing external parameter(s) such as concentration, temperature, pressure, and flow direction to change. Using such operations, the profiles of the catalyst states, coverage of active surface chemical species, concentrations, and temperatures in reactors can be influenced and controlled to a great extent, thus providing more favourable conditions for better process performance [5–7]. One of the catalytic technologies based on unsteady-state operation close to our daily life is NO_x storage-reduction (NSR) catalysis pioneered by TOYOTA and widely used in automotive industry [8,9]. The major advantage of NSR technology is to chemically reduce nitrogen oxides in fuel-lean and oxygen-rich conditions. By transiently switching between NO_x storage phase and reduction phase (as a short pulse of increased fuel for the latter), efficient NO_x reduction is made possible.

Among possible strategies proposed in the literature, *chemical looping* process represents an attractive technology that offers means to effectively purify CO₂ for subsequent conversion by changing the environment of catalyst within the reactor system

* Corresponding author.

E-mail address: urakawa@iciq.es (A. Urakawa).

¹ Current address: Instituto de Tecnología Química, Universidad Politécnica de Valencia—CSIC, Avenida de los Naranjos s/n, 46022 Valencia, Spain.

[4]. Within the closed-system, the catalyst experiences unsteady-state reaction conditions. The fundamental concept of the process is based on the conversion of metal oxide sorbent to metal carbonate by *in situ* removal of flue gas CO₂ where calcium-based materials are typically used as the sorbent. The major general challenges of such processes are the required complex engineering, material resistance and drastic temperature changes for catalyst regeneration [4]. Generally this technology requires an additional reactor for CO₂ transformation unless the two conversion steps of CO₂ to CO and H₂ oxidation to H₂O are combined in one process (i.e. net reverse water-gas shift (RWGS) reaction operated under unsteady-state condition) as demonstrated by Kuhn using perovskite-type oxides [10,11]. The approach is promising although further material and process improvements are required to convert CO₂ to CO efficiently. Very recently, Farrauto has reported dual-functional materials based on ruthenium and calcium oxide which capture CO₂ from a model flue gas stream and subsequently reduce the captured CO₂ to methane at the same temperature in the same reactor [12]. Although the production of methane under the unsteady-state operation was demonstrated and even the catalyst functions in the presence of water vapour, the low CO₂ capture efficiency and high loading of previous ruthenium are the important points for further improvement.

Herein, we report a highly efficient dual-function catalyst material and process concept of catalytic CO₂ conversion strategy through CO₂ capture and subsequent reduction combined in one process, utilizing unsteady-state operation denoted here as CO₂ capture-reduction (CCR). In CCR, two distinct regimes, (i) capture of CO₂ on a storage component of a catalyst and (ii) release of CO₂ or direct catalytic reduction of stored CO₂ by reducing gas (here hydrogen) and catalyst regeneration, are operated alternately and isothermally. The important differences from the current state-of-the-art are the very high capture efficiency enabled by potassium component of the catalyst, earth-abundant metal components (Fe, Cr, Cu) and high activity and selectivity for CO₂ reduction to CO, and the same duration for the CO₂ capture and reduction phases. The last point is crucial for an advanced process integration concept,

enabling continuous and complete CO₂ capture and reduction of captured CO₂ in one process using multiple-reactors.

2. Experimental

2.1. Materials and chemicals

PURAL[®] MG 20 hydrotalcite (Mg/Al molar ratio is 0.29) provided by Sasol Germany GmbH, Inorganic Specialty Chemicals was employed as the pristine material of the support. Potassium carbonate from Panreac was used as precursor of potassium component. All the metal precursors salts used in this study were the nitrate form purchased from Sigma-Aldrich. Deionized water was used for catalyst synthesis. The gases were purchased from Linde at the quality of >99.9993% for CO₂ and >99.999% for the other gases.

2.2. Catalyst synthesis

The hydrotalcite supported FeCrCu-K catalyst was prepared by sequential impregnation using the incipient wetness method. Firstly, a thermal treatment of hydrotalcite support at 600 °C for 3 h was carried out in order to obtain the homogeneous mixed oxides of MgO and Al₂O₃. Afterwards, three metals (Fe, Cr and Cu) were impregnated using a solution prepared by adding the necessary volume of deionized water to the metal nitrates precursor salts. The resulting solid was dried overnight at 80 °C followed by calcination at 500 °C for 5 h. Finally, a solution of potassium carbonate was impregnated over the solid obtained and it was dried and calcined under identical conditions. The elemental composition of the catalyst was determined by ICP analysis (Table S1-Supplementary material).

2.3. Reaction procedure

The experimental system mainly consists of four sections; (i) gas feed system, (ii) switching valve, (iii) reactor, (iv) gas detection

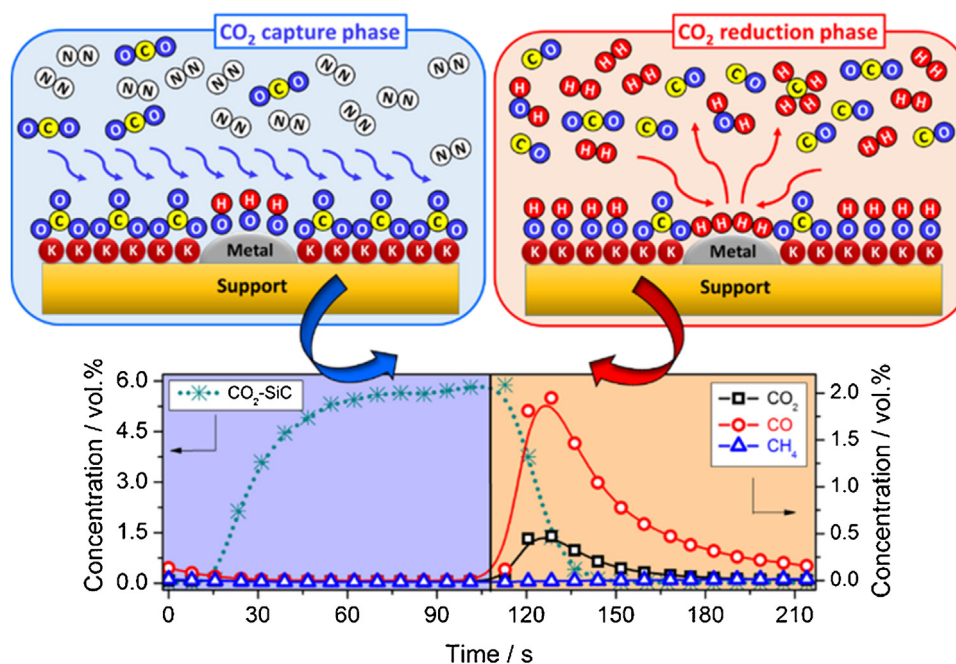


Fig. 1. A pictorial representation of the function and a possible mechanism of CCR on the catalyst material and representative concentration profiles during the unsteady-state operation. In comparison, a CO₂ concentration profile measured under the identical condition using an inert SiC material filled in the reactor is also shown.

دانلود مقاله



<http://daneshyari.com/article/63549>



- ✓ امکان دانلود نسخه تمام متن مقالات انگلیسی
- ✓ امکان دانلود نسخه ترجمه شده مقالات
- ✓ پذیرش سفارش ترجمه تخصصی
- ✓ امکان جستجو در آرشیو جامعی از صدها موضوع و هزاران مقاله
- ✓ امکان پرداخت اینترنتی با کلیه کارت های عضو شتاب
- ✓ دانلود فوری مقاله پس از پرداخت آنلاین
- ✓ پشتیبانی کامل خرید با بهره مندی از سیستم هوشمند رهگیری سفارشات