



Communication

New strategy to incorporate nano-particle sized water oxidation catalyst into dye-sensitized photoelectrochemical cell for water splitting[☆]

Peicheng Wei, Bo Hu, Li Zhou, Ting Su, Yong Na^{*}

School of Chemical Engineering & Technology, Harbin Institute of Technology, Harbin 150001, Heilongjiang, China

ARTICLE INFO

Article history:

Received 26 January 2016

Revised 7 March 2016

Accepted 8 March 2016

Available online 24 March 2016

Keywords:

Dye-sensitized photoelectrochemical cell

Water splitting

Cobalt oxide

Water oxidation

ABSTRACT

In order to develop a new strategy to deposit nano-particle sized water oxidation catalyst based on earth abundant element to the photoanode in a photoelectrochemical cell for water splitting, Co_3O_4 as water oxidation catalyst was prepared and subsequently modified by 3-aminopropyltriethoxysilane. The amino functionalized Co_3O_4 catalyst was carefully characterized and then integrated to the ruthenium dye sensitized photoelectrode through fast Schiff base reaction. Cyclic voltammetry experiments in the dark confirmed that the modified Co_3O_4 catalyst was still active toward water oxidation, which could be initiated by oxidation of the ruthenium photosensitizer. Under visible light irradiation, incorporation of the modified Co_3O_4 catalyst resulted in dramatic enhancement of the transient photocurrent density for the photoanode, which was 8 times higher than that of without Co_3O_4 catalyst.

© 2016 Science Press and Dalian Institute of Chemical Physics. All rights reserved.

Conversion of solar energy into hydrogen via visible light-driven water splitting represents a bridge towards a renewable-energy future [1]. Dye-sensitized photoelectrochemical cells (DS-PECs) for water splitting have attracted worldwide attention since they can produce hydrogen without any accumulated byproduct, making hydrogen generation and utilization to be cyclic [2,3]. The photoanode in a DS-PEC device is assembled by molecular dyes and water oxidation catalysts co-deposited onto a mesoporous TiO_2 electrode. The dye sensitizer absorbs visible light and injects an electron into the conduction band of TiO_2 , resulting in a strong oxidant to initiate the water oxidation through electron transfer from the water oxidation catalyst(s), in which most of the cases, ruthenium and iridium based catalysts are employed dominantly [3–5]. Although excellent performances have been achieved using catalysts based on ruthenium complexes [6], the development of efficient catalyst based on earth-abundant first row transition metal elements is still appealing in the long term.

Cobalt based water oxidation catalysts such as organic cobalt complexes [7–10], inorganic polyoxometalate cobalt [11], Co_3O_4 [12,13] and CoO_x analogues [14–16] have been demonstrated to be potential candidates, among which nano-particle sized Co_3O_4 is more promising from a viewpoint of easy preparation as well


as good stability. Recently, light-driven water oxidation catalyzed by Co_3O_4 nano-particles (NPs) has been successfully initiated by $\text{Ru}(\text{bpy})_3^{2+}$ photosensitizer in the presence of sacrificial electron acceptor, in which the catalytic activity of Co_3O_4 could be improved by narrowing the particle sizes [13]. Since the large surface of Co_3O_4 NPs can provide sites for chemical modification, it is possible to develop strategies to incorporate Co_3O_4 catalyst into the ruthenium dye-sensitized TiO_2 photoanodes for light-driven water splitting, but has, as far as we know, never been explored. In contrast to the reported strategies that dye molecules were attached to the nano-particle sized catalyst as stabilizers [17,18], stepwise co-sensitization was adopted since remarkable performances have been achieved by molecular components co-sensitized on the TiO_2 electrode [6]. Herein, we describe the surface modification of Co_3O_4 NPs with 3-aminopropyltriethoxysilane (3-APTES) and integration of the amino functionalized catalyst into ruthenium dye (**RuP**)-sensitized TiO_2 photoanode through Schiff base reaction (Scheme 1).

All reagents used were reagent grade without further purification. The photosensitizer $[\text{Ru}(\text{bpy})_2(4,4'-(\text{CH}_2\text{PO}_3\text{H}_2)\text{bpy})](\text{PF}_6)_2$ (**RuP**) was synthesized according to the literature [19]. Nano-structured Co_3O_4 was prepared according to the published procedure with minor modification [13]. Typically, 0.5 g of cobalt(II) acetate tetrahydrate was dissolved in 2 mL of water followed by addition of 23 mL of ethanol. The reaction solution was stirred at 45 °C for 10 min before aqueous ammonia (3.2 mL, 28%) was added dropwise. The reaction mixture was heated at 80 °C under

[☆] This work is supported by the Program for Innovation Research of Science in Harbin Institute of Technology (PIRS of HIT nos. A201418 and Q201508).

^{*} Corresponding author. Tel: +86 451 86413710; Fax: +86 451 86418270.

E-mail address: yongna@hit.edu.cn (Y. Na).

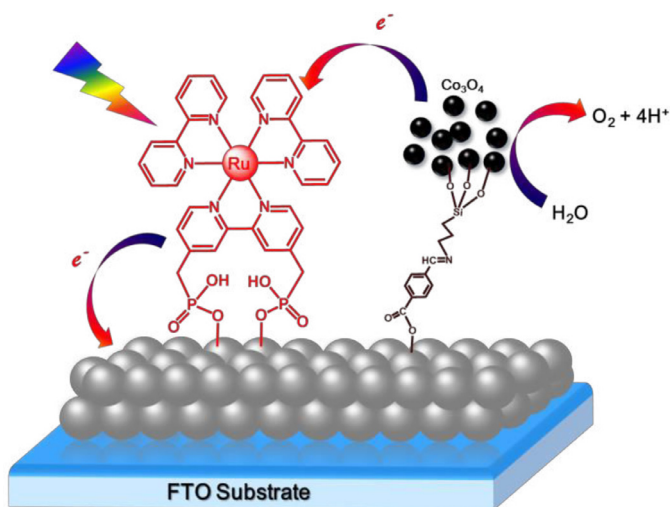

Scheme 1. Schematic illustration of the TiO_2 electrode co-sensitized by RuP and surface modified Co_3O_4 NPs.

magnetic stirring for 3 h and then cooled to room temperature, which became turbid immediately upon addition of acetone (100 mL). The precipitate of brownness Co_3O_4 was obtained by centrifugation at 4500 rpm for 20 min. The crude product was re-dispersed in 12 mL of methanol followed by addition of acetone (120 mL) and then centrifugation (4500 rpm, 20 min). The above dispersion–centrifugation wash was repeated for two times until the supernatant liquid was almost colorless. The organic solvent residue was removed under vacuum to obtain Co_3O_4 NPs powder.

In a typical surface modification procedure, 100 mg of Co_3O_4 NPs powder was dispersed in 20 mL of methanol by ultrasonication. The dispersion was degassed by bubbling with N_2 for 15 min before 360 mg of 3-aminopropyltriethoxysilane was added dropwise. The reaction mixture was stirred at room temperature for 12 h under N_2 . Solvent was removed by rotary evaporation to obtain the crude product, which was washed two times with CH_2Cl_2 to get rid of the excess 3-aminopropyltriethoxysilane by centrifugation (10,000 rpm, 10 min). The CH_2Cl_2 residue was removed under vacuum to obtain the amino-functionalized Co_3O_4 NPs that was stored under N_2 .

Mesoporous TiO_2 film was deposited to FTO substrate with active area of 1 cm^2 according to the reported procedure [20]. The TiO_2 electrode was first immersed into aqueous solution of RuP (0.15 mM) for 12 h at room temperature in the dark and rinsed with water and ethanol. This dye sensitized TiO_2 electrode was then dipped into ethanolic solution of 4-formylbenzoic acid for 2 h. The electrode was rinsed with ethanol to get rid of excess 4-formylbenzoic acid. Finally, the electrode was immersed in methanolic solution of amino-functionalized Co_3O_4 at $40\text{ }^\circ\text{C}$ for another 1 h to get the desired photoanode.

Scanning electron microscope (SEM) image and energy dispersive spectrometer (EDS) was analyzed by Hitachi SU8000 instrument. The X-ray powder diffraction (XRD) measurement was performed with $\text{Cu K}\alpha$ radiation by a Shimadzu XRD-6000 X-ray diffraction instrument. FT-IR spectra were measured on a Perkin-Elmer Spectrum 100 FT-IR Spectrometer. Electrochemistry measurements were recorded using a CHI-660E electrochemical potentiostat at a scan rate of 50 mV/s. CV experiments were carried out in a three-electrode cell under argon. The working electrode was the photoanode, and the auxiliary electrode was a platinum wire. The reference electrode was $\text{Ag}|\text{AgCl}$ (sat. KCl) electrode. The potentials versus NHE discussed in CV section were calibrated

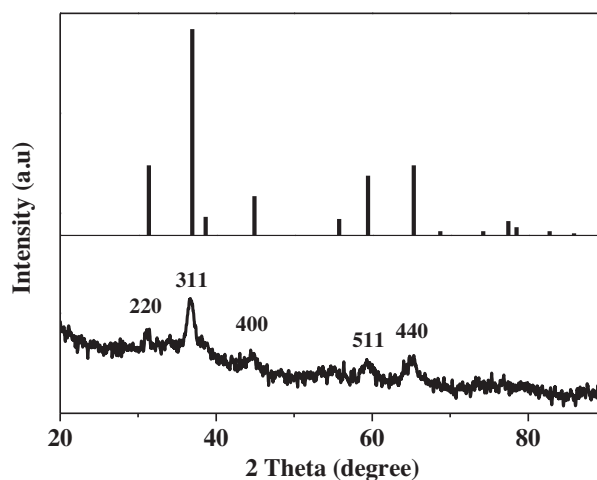


Fig. 1. X-ray powder diffraction pattern of the prepared Co_3O_4 NPs.

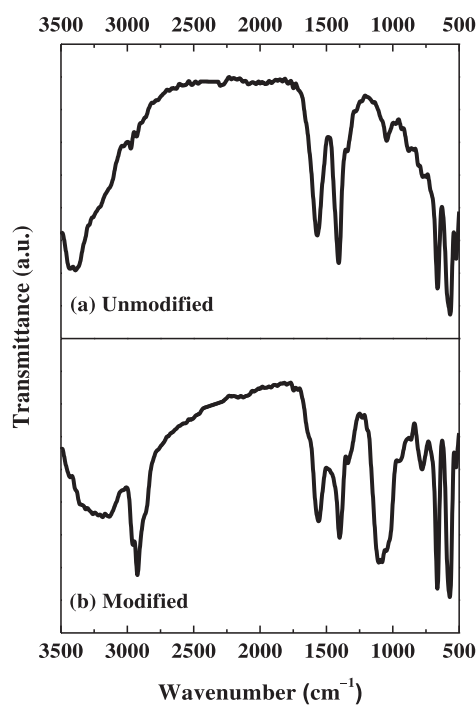


Fig. 2. FT-IR spectra of the prepared Co_3O_4 NPs before (a) and after (b) surface modification with 3-APTES.

using $\text{Ru}(\text{bpy})_3\text{Cl}_2$ as a reference with $E_{1/2}(\text{Ru}^{\text{III/II}}) = 1.26\text{ V}$. A phosphate buffer solution at pH 6.8 was used as electrolyte, which was degassed by bubbling with dry argon for 15 min before measurement.

The prepared Co_3O_4 NPs were first characterized by XRD and FT-IR spectroscopy (Fig. 1). It can be observed that all diffraction peaks are in good agreement with characteristic peaks of the standard (JCPDS-ICDD no. 42-1467), corresponding to spinel phase Co_3O_4 (Fig. 1). The most prominent diffraction peak at 37.6° can be attributed to the crystal plane (311). The particle size is calculated to be 8.9 nm according to the Scherrer equation: $d = K\lambda/\beta\cos\theta$. In the FT-IR spectrum shown in Fig. 2(a), the characteristic absorption bands at 665 cm^{-1} and 577 cm^{-1} can be ascribed to the $\nu(\text{Co}-\text{O})$ of spinel phase cobalt oxide, which is consistent with the result from XRD patterns. Moreover, the existing of hydroxyl groups on the surfaces of the prepared Co_3O_4 NPs is confirmed by the absorption bands for $\nu(\text{OH})$ at 3380 cm^{-1} and 1560 cm^{-1} , providing

دانلود مقاله



<http://daneshyari.com/article/63680>



- ✓ امکان دانلود نسخه تمام متن مقالات انگلیسی
- ✓ امکان دانلود نسخه ترجمه شده مقالات
- ✓ پذیرش سفارش ترجمه تخصصی
- ✓ امکان جستجو در آرشیو جامعی از صدها موضوع و هزاران مقاله
- ✓ امکان پرداخت اینترنتی با کلیه کارت های عضو شتاب
- ✓ دانلود فوری مقاله پس از پرداخت آنلاین
- ✓ پشتیبانی کامل خرید با بهره مندی از سیستم هوشمند رهگیری سفارشات