

Efficient conversion of renewable levulinic acid to *n*-butyl levulinate catalyzed by ammonium and silver co-doped phosphotungstic acid



Xi Zhou^{a,*}, Ze Xian Li^a, Chao Zhang^a, Xue Ping Gao^a, You Zhi Dai^a, Gong Ying Wang^b

^a Department of Biological and Chemical Engineering, Shaoyang University, Shaoyang 422000 Hunan, PR China

^b Chengdu Institute of Organic Chemistry, Chinese Academy of Sciences, Chengdu, 610041 Sichuan, PR China

ARTICLE INFO

Article history:

Received 31 January 2016

Received in revised form 2 March 2016

Accepted 2 March 2016

Available online 5 March 2016

Keywords:

Phosphotungstic acid

Co-doped

n-Butyl levulinate

Levulinic acid

Esterification

ABSTRACT

Ammonium and silver co-doped phosphotungstic acid was developed as novel efficient catalyst for the synthesis of *n*-butyl levulinate. The catalyst was characterized by element analysis, FT-IR, XRD and Hammett indicator method. Among them, $(\text{NH}_4)_{0.5}\text{Ag}_{0.5}\text{H}_2\text{PW}_{12}\text{O}_{40}$ exhibited the highest catalytic activity, and the yield of *n*-butyl levulinate could reach up to 99.0% within 2 h. The results showed that the activity of $(\text{NH}_4)_{0.5}\text{Ag}_{0.5}\text{H}_2\text{PW}_{12}\text{O}_{40}$ was higher than that of single Ag^+ or NH_4^+ doped H_3PW and other representative catalysts reported by literatures. In addition, $(\text{NH}_4)_{0.5}\text{Ag}_{0.5}\text{H}_2\text{PW}_{12}\text{O}_{40}$ performed good reusability for this reaction.

© 2016 Elsevier B.V. All rights reserved.

1. Introduction

Levulinic acid (LA) is a platform organic chemical and one of the top 12 building blocks that can be obtained from the deconstruction of lignocellulosic biomass. It can be used for preparing numerous useful chemicals such as levulinate esters, γ -valerolactone, acrylic acid, etc. Among them, levulinate esters have been widely used as additives in gasoline and biodiesel since its low toxicity, high lubricity, flash point stability and moderate flow properties under low temperature [1–3].

Generally, levulinate esters are synthesized by the esterification of LA with alcohols using mineral acid or organic sulfonic acid as catalyst [4]. However, these methods suffer from high cost separation, large energy consumption, equipment corrosion and environmental pollution. A large number of heterogeneous catalysts have been also reported for the synthesis of levulinate esters such as zeolites [5–9], sulfonic materials [10–14], MOFs [15], heteropoly acids (HPAs) and supported HPAs [16,17]. Among them, HPAs are known to be excellent catalysts for a wide range of acid-catalyzed reactions. However, HPAs have the drawbacks of high solubility in polar media, low surface area and relatively low thermal stability. Recently, Dharme and Bokade have developed dodecatungstophosphoric acid supported on K10 as catalyst for

the synthesis of *n*-butyl levulinate [16]. Although 97% LA conversion can be obtained, the activity of catalyst decreased after two cycles due to the increasing leaching of dodecatungstophosphoric acid from K10 support.

Compared to grafting HPAs onto porous supports, it is more effective to exchange H^+ of HPAs with different cations (e.g., K^+ , Cs^+ , Ag^+) to form insoluble salts, which can tune and enhance the activity of HPAs [18–20]. Different simple salts based on only one type of cation (excluding H^+) have been extensively reported [18]. For example, silver-doped phosphotungstic acid ($\text{Ag}_1\text{H}_2\text{PW}$) has been developed as efficient heterogeneous catalyst for the esterification [21], etherification [22], transesterification [23], and so on. However, different cations co-doped HPAs have been rarely reported in the literature.

Herein, ammonium and silver co-doped phosphotungstic acid was prepared and used as efficient catalyst for the conversion of renewable LA to *n*-butanol levulinate. To the best of our knowledge, there are no reports available for the esterification of LA with *n*-butanol in the presence of different cations co-doped HPAs.

2. Experimental

2.1. Preparation and characterization of catalysts

In a typical procedure for the preparation of ammonium and silver co-doped phosphotungstic acid catalysts, $\text{H}_3\text{PW}_{12}\text{O}_{40}$ (H_3PW , 0.18 mol/L) was dissolved in deionized water with vigor-

* Corresponding author.

E-mail address: z.zhouxi@163.com (X. Zhou).

ous stirring at room temperature. Then, the appropriate amount of $(\text{NH}_4)_2\text{CO}_3$ (0.03 mol/L) aqueous solution was added dropwise to the H_3PW aqueous solution, followed by the addition of AgNO_3 (0.06 mol/L) aqueous solution. The resultant mixture was further stirred for 2 h at room temperature. Finally, the solid sample was obtained by filtration, dried at 80°C overnight, and calcinated at 200°C in air for 4 h. These prepared catalysts were designated as $(\text{NH}_4)_x\text{Ag}_y\text{H}_{3-x-y}\text{PW}$ ($x=0.5, 1, 2, y=0.5, 1, 2$).

Nitrogen content was detected in a Perkin-Elmer EA 2400 II. The content of Ag and W was obtained by X-ray fluorescence in a Shimadzu EDX 720 spectrometer with a rhodium X-ray source tube. The XRF spectra were collected under vacuum conditions setting the X-ray source at 50 kV. The detection was performed on flake sample which was prepared by tableting of powder. The X-ray diffraction patterns (XRD) were collected on X-ray diffractometer (XPRT PRO) using a Cu K radiation source ($\lambda = 1.54056 \text{ \AA}$), operating at 40 kV and 45 mA. The diffractograms were recorded in the range of $10\text{--}70^\circ$ with a scan rate of $5^\circ/\text{min}$ and step size of 0.03° . FT-IR spectra were obtained by Nicolet 560 in KBr pellets. The surface areas of catalysts were measured by nitrogen adsorption and desorption on a TriStar II 3020 (Micromeritics Instrument Corporation) at 77 K and determined by using the BET methods. The acidity of catalysts was determined by means of *n*-butylamine titration using Hammett indicators. The catalyst leaching in filtration was detected by TS IRIS 1000 ICP-AES instrument.

2.2. Typical procedure for the esterification of LA with *n*-butanol

Typical procedure for the synthesis of *n*-butanol levulinate: 11.6 g (0.1 mol) LA, 14.8 g (0.2 mol) *n*-butanol and 0.174 g catalyst were charged into a 100 mL flask equipped with a magnetic stirring, a reflux condenser and a water segregator. The reaction mixture was then heated to desired temperature with continuous stirring for 2 h. After the reaction, the mixture was cooled to room temperature. Solid catalyst was separated from product by filtration. And the product was analyzed by GC (Shandong Lunan Ruihong Co., SP-6890). The structure of the product was defined by GC-MS (HP 6890/5973). In the experiment to test the reusability of catalyst, $(\text{NH}_4)_{0.5}\text{Ag}_{0.5}\text{H}_2\text{PW}$ was separated by filtration, washed by ethanol, dried at 90°C and reused for the next run.

3. Results and discussion

3.1. Characterization of catalysts

Although much care was taken to match the theoretical values during preparation, it was important to detect the actual compositions of catalysts. The element content of $\text{Ag}_1\text{H}_2\text{PW}$, $(\text{NH}_4)_1\text{H}_2\text{PW}$ and $(\text{NH}_4)_{0.5}\text{Ag}_{0.5}\text{H}_2\text{PW}$ is summarized in Table 1. The actual element content of catalysts was close to the calculated values, which indicated that the preparation methodology was effective for controlling the desired stoichiometry of above catalysts.

$\text{Ag}_1\text{H}_2\text{PW}$ and $(\text{NH}_4)_{0.5}\text{Ag}_{0.5}\text{H}_2\text{PW}$ were characterized by FT-IR spectra. It is well known that the Keggin anion of parent H_3PW consists of a central phosphorous atom tetrahedrally coordinated by four oxygen atoms and surrounded by twelve octahedral WO_6 units

Table 1
Element analysis of $\text{Ag}_1\text{H}_2\text{PW}$, $(\text{NH}_4)_1\text{H}_2\text{PW}$ and $(\text{NH}_4)_{0.5}\text{Ag}_{0.5}\text{H}_2\text{PW}$.

Catalyst	N (%)		Ag (%)		W (%)	
	Cal.	test	Cal.	test	Cal.	test
$\text{Ag}_1\text{H}_2\text{PW}$	–	–	3.62	3.56	73.86	72.52
$(\text{NH}_4)_1\text{H}_2\text{PW}$	0.62	0.57	–	–	76.15	74.37
$(\text{NH}_4)_{0.5}\text{Ag}_{0.5}\text{H}_2\text{PW}$	0.29	0.27	1.83	1.79	75.00	74.56

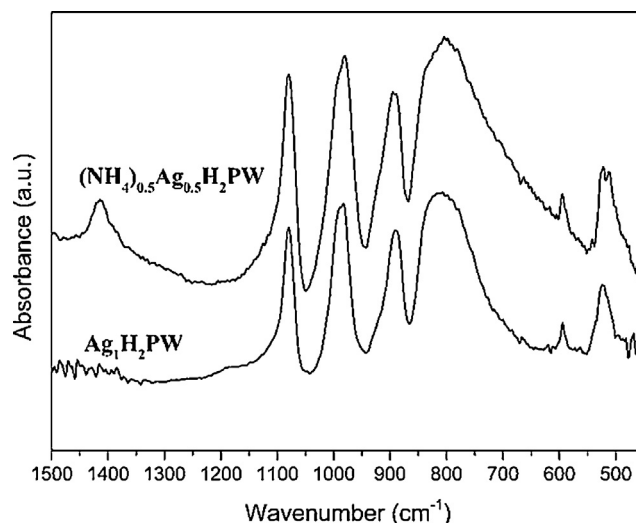


Fig. 1. FT-IR spectrum of $\text{Ag}_1\text{H}_2\text{PW}$ and $(\text{NH}_4)_{0.5}\text{Ag}_{0.5}\text{H}_2\text{PW}$.

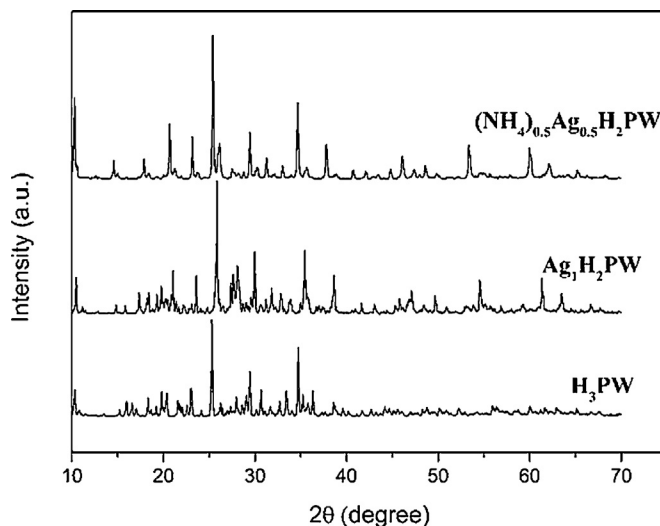


Fig. 2. XRD patterns of H_3PW , $\text{Ag}_1\text{H}_2\text{PW}$ and $(\text{NH}_4)_{0.5}\text{Ag}_{0.5}\text{H}_2\text{PW}$.

that share edges and corners in the structure. As shown in Fig. 1, the characteristic bands of typical Keggin anions can be clearly observed in the spectra of $\text{Ag}_1\text{H}_2\text{PW}$ and $(\text{NH}_4)_{0.5}\text{Ag}_{0.5}\text{H}_2\text{PW}$. They are the bands located at 1080 cm^{-1} ($\nu_{\text{as}} \text{P-O}_a$), 982 cm^{-1} ($\nu_{\text{as}} \text{W-O}_d$), 890 cm^{-1} ($\nu_{\text{as}} \text{W-O}_b\text{-W}$), and 807 cm^{-1} ($\nu_{\text{as}} \text{W-O}_c\text{-W}$), respectively. The results indicate that the Keggin structure is maintained on ammonium and silver co-doped H_3PW catalyst. In addition to these bands, there is also a band related to N–H stretching observed at 1414 cm^{-1} for $(\text{NH}_4)_{0.5}\text{Ag}_{0.5}\text{H}_2\text{PW}$. It means that NH_4^+ still exists in $(\text{NH}_4)_{0.5}\text{Ag}_{0.5}\text{H}_2\text{PW}$ even after calcinating at 200°C for 4 h.

The XRD patterns of parent H_3PW , $\text{Ag}_1\text{H}_2\text{PW}$ and $(\text{NH}_4)_{0.5}\text{Ag}_{0.5}\text{H}_2\text{PW}$ catalysts are displayed in Fig. 2. The parent H_3PW shows typical diffraction pattern of body-centered cubic secondary structure of Keggin anion, with characteristic diffraction peaks at 10.3° , 25.3° , and 34.6° [21–23]. The most intense peak for H_3PW at 25.3° is also present in the XRD patterns of $\text{Ag}_1\text{H}_2\text{PW}$ and $(\text{NH}_4)_{0.5}\text{Ag}_{0.5}\text{H}_2\text{PW}$ samples, although this peak had slightly shifted to higher 2θ values. This peak is present at 25.8° for $\text{Ag}_1\text{H}_2\text{PW}$, and 25.4° for $(\text{NH}_4)_{0.5}\text{Ag}_{0.5}\text{H}_2\text{PW}$. It is speculated that $\text{Ag}_1\text{H}_2\text{PW}$ and $(\text{NH}_4)_{0.5}\text{Ag}_{0.5}\text{H}_2\text{PW}$ catalysts possess the same symmetry as parent H_3PW but with a contracted unit cell.

For the acid-catalyzed reactions, the surface acid strength and density play important roles in determining the catalytic prop-

دانلود مقاله



<http://daneshyari.com/article/64644>



- ✓ امکان دانلود نسخه تمام متن مقالات انگلیسی
- ✓ امکان دانلود نسخه ترجمه شده مقالات
- ✓ پذیرش سفارش ترجمه تخصصی
- ✓ امکان جستجو در آرشیو جامعی از صدها موضوع و هزاران مقاله
- ✓ امکان پرداخت اینترنتی با کلیه کارت های عضو شتاب
- ✓ دانلود فوری مقاله پس از پرداخت آنلاین
- ✓ پشتیبانی کامل خرید با بهره مندی از سیستم هوشمند رهگیری سفارشات