



Featured Letter

Pectin coatings on titanium alloy scaffolds produced by additive manufacturing: Promotion of human bone marrow stromal cell proliferation



Timothy E.L. Douglas^{a,b,*}, Ute Hempel^c, Jagoda Żydek^d, Alina Vladescu^{e,f}, Krzysztof Pietryga^d, Julia A.H. Kaeswurm^g, Maria Buchweitz^g, Roman A. Surmenev^f, Maria A. Surmeneva^f, Cosmin M. Cotrut^{f,h}, Andrey V. Koptugⁱ, Elżbieta Pamuła^d

^a Engineering Dept., Lancaster University, United Kingdom

^b Materials Science Institute (MSI), Lancaster University, United Kingdom

^c Institute of Physiological Chemistry, Technische Universität Dresden, Germany

^d Dept. Biomaterials and Composites, Faculty of Materials Science and Ceramics, AGH University of Science and Technology, Kraków, Poland

^e National Institute for Optoelectronics, Dept. Advanced Surface Processing and Analysis by Vacuum Technologies, Romania

^f Physical Materials Science and Composite Materials Centre, National Research Tomsk Polytechnic University, Russia

^g Analytical Food Chemistry, Faculty of Chemistry, University of Stuttgart, Germany,

^h University Politehnica of Bucharest, Romania

ⁱ Sports Tech Research Centre, Mid Sweden University, Sweden

ARTICLE INFO

Article history:

Received 25 January 2018

Received in revised form 5 April 2018

Accepted 12 May 2018

Keywords:

Biomaterials

Thin films

Biomimetic

ABSTRACT

Ti6Al4V is a popular biomaterial for load-bearing implants for bone contact, which can be fabricated by additive manufacturing technologies. Their long-term success depends on their stable anchoring in surrounding bone, which in turn depends on formation of new bone tissue on the implant surface, for which adhesion and proliferation of bone-forming cells is a pre-requisite. Hence, surface coatings which promote cell adhesion and proliferation are desirable.

Here, Ti6Al4V discs prepared by additive manufacturing (EBM) were coated with layers of pectins, calcium-binding polysaccharides derived from citrus (C) and apple (A), which also contained alkaline phosphatase (ALP), the enzyme responsible for mineralization of bone tissue.

Adhesion and proliferation of human bone marrow stromal cells (hBMSC) were assessed. Proliferation after 7 days was increased by A-ALP coatings and, in particular, by C-ALP coatings. Cell morphology was similar on coated and uncoated samples. In conclusion, ALP-loaded pectin coatings promote hBMSC adhesion and proliferation.

© 2018 Elsevier B.V. All rights reserved.

1. Introduction

The titanium alloy Ti6Al4V is a popular biomaterial for load-bearing implants for bone contact which can be fabricated by additive manufacturing technologies [1]. The adhesion and proliferation of bone-forming cells are pre-requisites for formation of new bone tissue on the implant surface, which guarantees implant stability and long-term success. Hence, surface coatings which promote cell adhesion and proliferation are desirable. Coatings containing certain polysaccharides have improved cell adhesion and proliferation [2–4].

Pectins are a family of complex, anionic, calcium-binding polysaccharides found in the primary cell wall and intercellular regions of higher plants, composed primarily of linear D-galactopyranosyluronic acids joined via $\alpha(1 \rightarrow 4)$ glycosidic linkages (Homogalacturonan: HG). These are either partially methyl-esterified, acetylated or both. In the Rhamnogalacturonan-I (RG-I) the linear galacturonic acid (GalA) chain is disturbed by $\alpha(1,2)$ -linked L-rhamnose (L-Rha) units. Depending on plant source and isolation method, L-Rha residues are substituted with neutral saccharide side chains. The RG-II fragment is a substituted galacturonan being composed of a partially methyl esterified GalA backbone.

Commercial pectins from apple and citrus pomace are extracted under hot acidic conditions and therefore, many regions containing high proportions of neutral sugars are hydrolysed. Thus, extracted

* Corresponding author at: Engineering Dept., Gillow Avenue, Lancaster University, Lancaster, LA1 4YW, United Kingdom.

E-mail address: t.douglas@lancaster.ac.uk (T.E.L. Douglas).

pectins are mainly composed of HG containing free or genuine esterified carboxylic groups that are more acid-stable. They form hydrogels and are thus widely applied in viscous, hydrated foods such as jams. They are also inexpensive and widely available and have been applied as scaffolds for tissue regeneration [5]. Pectic RG-I nanocoatings have been used to tailor surface properties of tissue culture polystyrene (TCPS) [6,7] and titanium [8]. However, pectin coatings on Ti6Al4V remain relatively unexplored.

The enzyme alkaline phosphatase (ALP) plays an important role in hard tissue mineralization. ALP catalyses hydrolysis of organic phosphate monoesters to yield inorganic phosphates. ALP has been used as a coating material on Ti6Al4V surfaces [9,10], which has improved the osteogenic response.

Here, Ti6Al4V discs prepared by additive manufacturing (electron beam melting, EBM) were coated with pectins derived from citrus (C) and apple (A) and ALP. Coatings were characterized physicochemically and cell biologically with human bone marrow stromal cells (hBMSC). Cell adhesion and proliferation were assessed.

2. Materials and methods

All materials, including alkaline phosphatase (P7640) and BCA Assay (BCA1) were acquired from Sigma-Aldrich, unless stated otherwise. Pectins C (degree of esterification (DE) 35%, Galacturonic acid content (GalC) 86%) and A (DE 34%, GalC 74%) were obtained from Herbstreith & Fox KG Pektin-Fabriken, D. Rough Ti6Al4V discs of diameter 2 cm were prepared using additive manufacturing techniques in an ARCAM EBM A2 machine as described previously [1]. Ti6Al4V discs and 0.8% (w/w) C (degree of esterification (DE) 35%, Galacturonic acid content (GalC) 86%) and A (DE 34%, GalC 74%) pectin solutions were autoclaved (121 °C, 15 min). Sterile-filtered ALP solution (1.6% (w/v)) and pectin solution were mixed 1:1 (v/v). 250 µl of this solution was spread on Ti6Al4V and allowed to air-dry under sterile conditions (Fig. 1).

Morphologies of uncoated and coated samples were examined by digital optical microscopy (KEYENCE VHX-5000) and scanning electron microscopy (SEM, TableTop 3030PLUS, Hitachi).

Surface contact angles were determined using a drop shape analysis system (DSA 10Mk2, KRÜSS). UHQ water droplets (approximate volume 0.2 µl) were deposited on sample surfaces.

Images captured by video camera were analyzed to calculate the contact angle. Results (30 drops per sample) were expressed mean ± standard deviation.

To test coating stability, uncoated and coated samples were immersed in 4 ml ddH₂O for 1 and 15 h. ALP release was quantified by the BCA Assay according to the manufacturer's instructions. Pectin release was quantified by the method of van den Hoogen et al. [11].

For cell experiments, hBMSC from two different donors (ethical approval granted by ethics committee of Technische Universität Dresden, No. 466112016) were seeded at a density of 7000 cells/cm². Cells were seeded onto the samples in 400 µl of cell culture medium (DMEM with 10% heat-inactivated fetal calf serum, and antibiotics (penicillin and streptomycin)). After 2 h the medium was filled up to 4 ml and culture proceeded at 37 °C in a humidified CO₂ incubator. Proliferation was assessed by the MTS assay. Cells were treated with 10% dye solution in DMEM for 2 h. The formed formazan amount was measured photometrically at 490 nm. Analyses were performed 24 h and 7 days after seeding. Statistical significance was analyzed by one-way ANOVA and Bonferroni post-test (prism graph pad software). Cell morphology was assessed after 24 h. Cells were fixed with 4% paraformaldehyde and stained with Alexa488-phalloidine to visualize F-actin cytoskeleton (green fluorescence) and with DAPI to stain the nuclei (blue fluorescence). The images (three from each sample) were taken with AxioPhot microscope (Zeiss) using a digital camera and Axiovision software. Focusing of cells of samples was complicated by the roughness of the sample surfaces.

3. Results and discussion

The presence of A-ALP and C-ALP coatings was confirmed by optical microscopy (Fig. 2a) and SEM (Fig. 2b). Coatings lowered contact angle, and A-ALP coatings were more hydrophilic than C-ALP coatings (Fig. 2c). ALP release was more pronounced from C-ALP coatings (Fig. 2d) and increased from 1 to 15 h. No differences in pectin release from A-ALP and C-ALP coatings after 1 and 15 h were observed (Fig. 2e). Cells retained viability and proliferated over 24 h and 7 days (Fig. 3a). Proliferation was significantly higher on C-ALP coatings than on A-ALP coatings after 24 h, and higher than on both uncoated samples and A-ALP coatings after

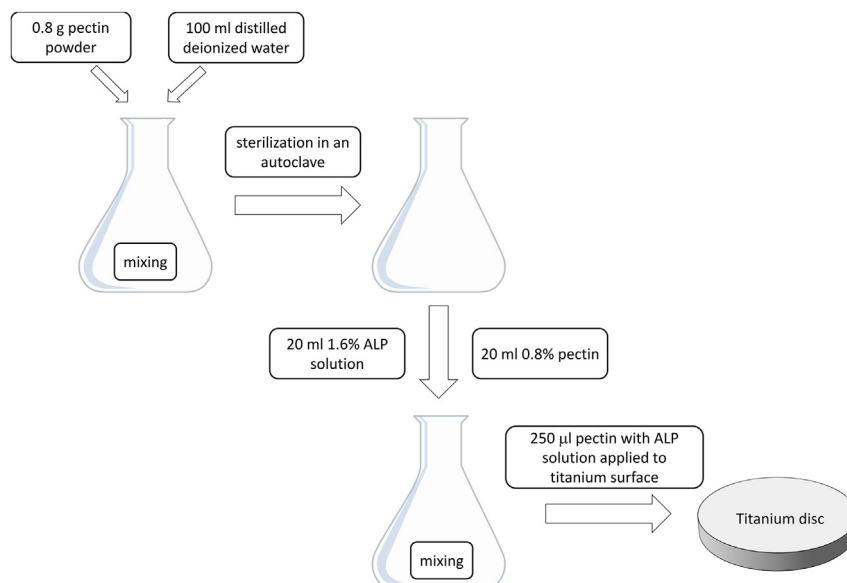


Fig. 1. Schematic description of coating of Ti6Al4V discs with pectin and ALP.

Download English Version:

<https://daneshyari.com/en/article/8012726>

Download Persian Version:

<https://daneshyari.com/article/8012726>

[Daneshyari.com](https://daneshyari.com)