

Photostability of biliverdin bound to smectite, clay mineral

Tetsuya Saito^a, Kouji Fukui^b, Yoh Kodera^b, Ayako Matsushima^b,
Hiroyuki Nishimura^b, Yuji Inada^{b,*}

^a*Spirulina Bio-Lab. Co. Ltd., Nishinakajima 1-13-6, Yodogawa-ku, Osaka 532-0011, Japan*

^b*Toin Human Science and Technology Center, Department of Biomedical Engineering, Toin University of Yokohama,
Kurogane-cho 1614, Aoba-ku, Yokohama 225-8502, Japan*

Received 14 March 2004; received in revised form 31 May 2004; accepted 1 June 2004

Available online 15 September 2004

Abstract

Biliverdin, the precursor of bilirubin, was adsorbed onto the synthetic clay mineral, smectite, in a mixed solution of benzene and methyl alcohol (7:3 v/v) to form a biliverdin–smectite conjugate. The adsorption of biliverdin to smectite followed the Freundlich equation with an adsorption coefficient of 1.0. The water-soluble conjugate had a green color with the absorbance maxima at 679 and 378 nm. The biliverdin–smectite conjugate became photostable in water to irradiation with UV, although the biliverdin in benzyl alcohol was rapidly decolorized.

© 2004 Elsevier Ltd. All rights reserved.

Keywords: Biliverdin; Porphyrin; Synthetic clay mineral; Smectite; Photostability; Bio-conjugate

1. Introduction

Study on bio-conjugate compounds has been extensively developed since the late 1970s; the chemical modification of asparaginase with polyethylene glycol (PEG) leads to the disappearance of binding ability to anti-asparaginase serum [1]. PEG-modified hydrolytic enzyme, lipase, catalyzes effectively the reverse reaction of hydrolysis in hydrophobic media, ester synthesis and ester exchange reactions, in organic solvent [2].

Recently, bio-conjugate materials of the compound porphyrin such as chlorophyll *a* and heme (or hemin) bound to clay mineral, smectite, were reported. The chlorophyll *a*–smectite conjugate became a transparent colloidal solution with a green color in water and was photostable against light irradiation [3]. The conjugate also catalyzed photoreduction and hydrogen gas


evolution by visible light [4]. Furthermore, hemin (Fe^{3+})–smectite and heme (Fe^{2+})–smectite conjugates were also soluble in water and their absorption spectra closely agreed with those of oxy- and carboxy-hemoglobins, in the presence of O_2 and CO [5]. Although porphyrin pigments have the physiological functions in the living body, the functions are easily lost by the degradation of pigments in vitro. The stabilization of pigments bound to smectite has a possibility of expanding the applications with novel functions of natural pigments.

The chemical structures of biliverdin, unfolded porphyrin ring, and smectite are shown in Scheme 1A and B, respectively. Biliverdin, tetrapyrrole, is a metabolic product from heme with a porphyrin ring and has a green color in organic solvents. In the living body, biliverdin is changed to bilirubin with biliverdin reductase. Biliverdin is degraded with high pH and/or light irradiation [6,7].

In the present study, we have made a bio-conjugate of biliverdin bound to smectite, clay mineral, with

* Corresponding author. Tel./fax: +81 45 974 5060.

E-mail address: inada@cc.toin.ac.jp (Y. Inada).

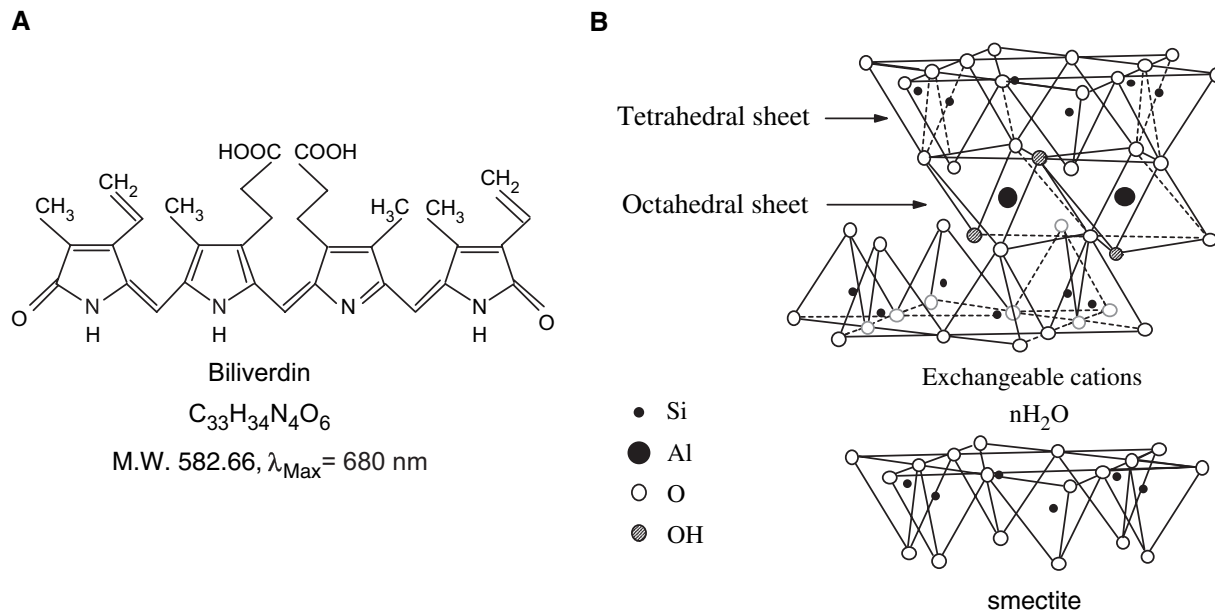

Scheme 1. The chemical structures of biliverdin (A) and smectite (B).

photostability for expanding the availability of natural pigments.

2. Experimental

Biliverdin dihydrochloride, $C_{33}H_{34}N_4O_6 \cdot 2HCl$, was purchased from ICN Biomedicals Inc. (OH, USA). Smectite powder (hectorite), which was hydrothermally synthesized, was obtained from Co-op Chemical Co., Ltd. (Tokyo, Japan). Its properties are as follows: the elemental composition with Si 8.00, Mg 5.65, Li 0.70, Na 1.05; transmittance 95% in 1% aqueous solution at 500 nm; and methylene blue adsorption 101 mequiv per 100 g [8]. The absorption spectra of pigments were measured with Multi-Purpose Spectrophotometer, MPS-2400 (Shimadzu, Kyoto, Japan).

The biliverdin–smectite conjugate was prepared as follows: smectite powder (100 mg) was added to 1.0 ml of biliverdin dissolved in a mixed solution of benzene and methyl alcohol (7:3 v/v) (0–5.5 mg/ml). The suspension was shaken for 1 h at 25 °C to establish the adsorption equilibrium and obtain the biliverdin–smectite conjugate. Then the sample solution was centrifuged and its precipitate dried under reduced pressure. The amount of biliverdin adsorbed onto smectite was spectrophotometrically determined by measuring the absorbance of biliverdin in the supernatant of the sample suspension after centrifuging. The molar extinction coefficient of biliverdin was $2.80 \times 10^4 \text{ M}^{-1} \text{ cm}^{-1}$ at 680 nm in methyl alcohol including 5% (w/v) HCl [9].

The absorption spectrum of the biliverdin–smectite conjugate in water, a transparent colloidal solution with green color, was measured by using MPS-2400.

Photostability of biliverdin–smectite conjugate was tested as follows: the conjugate in water (2 mg/ml) was irradiated by UV-rays (365 nm, 40 W) at a distance of 16 cm at room temperature. The absorbance change of biliverdin–smectite conjugate at 679 nm was measured against irradiation time. A similar test was carried out with free biliverdin in benzyl alcohol (12 $\mu\text{g/ml}$) at room temperature by the same UV irradiation at a distance of 16 cm.

3. Results and discussion

The biliverdin–smectite conjugates, in which various amounts of biliverdin (0–5.42 mg) were adsorbed onto 100 mg of smectite, were dissolved in water to form a green colored transparent solution. Absorption spectra of the conjugates (1.0% in water) are shown in Fig. 1a. The absorbance peaks at 679 nm and 378 nm are enhanced by increasing the amount of biliverdin bound to smectite as is shown in curves D, C, B and A. The absorption spectrum of smectite soluble in water (1.0%) without biliverdin is negligible at the visible region from 800 to 300 nm as is shown in curve E.

The adsorption of biliverdin onto smectite powder in a mixed solution of benzene and methyl alcohol (7:3 v/v) was spectrophotometrically measured with respect to time (insert in Fig. 1b). The adsorption proceeds efficiently with time, and reaches a constant level with adsorption equilibrium within 1 h. In this case, 0.60 mg out of 0.63 mg biliverdin is adsorbed onto 100 mg of smectite in a mixed solution of benzene and methyl alcohol (7:3 v/v). The adsorption of biliverdin onto

Download English Version:

<https://daneshyari.com/en/article/10266455>

Download Persian Version:

<https://daneshyari.com/article/10266455>

[Daneshyari.com](https://daneshyari.com)