

Modification of carboxymethyl cellulose through oxidation

Anjali Teotia

Department of Chemistry, Jamia Millia Islamia (Central University), New Delhi 110 025, India

ARTICLE INFO

Article history:

Received 2 August 2010
Received in revised form 2 August 2011
Accepted 4 August 2011
Available online 11 August 2011

Keywords:

Carboxymethyl cellulose
Dialdehyde cellulose
Periodate oxidation

ABSTRACT

The periodate oxidation reaction of carboxymethyl cellulose involve the primary and secondary hydroxyl groups of the pyranose ring. The reaction is accompanied by the opening of the pyranose ring and resulting product is dialdehyde carboxymethyl cellulose along with some hydrated forms. In this process the glucosidic bond becomes weaker; the formation of carboxyl groups induces a depolymerization, thus reducing the polymerization degree and the physical and mechanical strength of the material. The reaction has been carried out at pH 3.5, temperature 45 °C for 0.5–4 h.

© 2011 Elsevier Ltd. All rights reserved.

1. Introduction

Cellulose is the most extensively used natural polymer and represents a renewable natural source for organic materials. The main reactions acting on the structure of cellulose and causing its structure alteration are photo-degradation, acid hydrolysis, oxidation, and biodegradation. A complete analysis of them is quite complex, since these phenomena are all related to each other. In order to a better understanding of the structural changes of cellulose related to oxidation, in the present paper we will consider only the oxidation process. The oxidation reactions of cellulose involve the primary and secondary hydroxyl groups of the pyranose ring and result in carbonyl and carboxyl groups (Qingxi, Wei, Zehua, Bo, & Liangliang, 2008). This reaction can be accompanied by the opening of the pyranose ring. In this case the glucosidic bond becomes weaker; the formation of carboxyl groups induces a depolymerization, thus reducing the polymerization degree (DP) and the physical and mechanical strength of the material (Margutti, Conio, Calvini, & Pedemonte, 2001).

The conversion of dihydroxyl groups to dialdehyde by periodate oxidation is a useful method widely used in derivatization of cellulose to active the polymer at further reactions (Rahn & Heinze, 1998). Periodate oxidation is a highly specific reaction to convert 1,2-dihydroxyl (glycol) groups to paired aldehyde groups without significant side reactions and is widely used in structural analysis of carbohydrates (Bruneel & Schacht, 1993; Gal'braikh & Rogovin, 1971; Kim, Kuga, Wada, & Okano, 2000; Maekawa & Koshijima, 1984; Nevell, 1963; Schacht, Bogdanov, Bulcke, & Rooze, 1997; Uraz & Güner, 1997). When applied to glucose in the carboxymethyl

cellulose chain, this reaction cleaves the C2–C3 bond, according to the mechanism of Malaprade reaction (Cremonesi, Focher, & Angiuro, 1971, 1972). The resulting compound is the dialdehyde cellulose (DAC) (Maekawa & Koshijima, 1991; Varma & Kulkarni, 2002). The application or the quantitative understanding of this reaction has been hampered by complication arising from hemiacetal formation of aldehyde and crystalline nature of cellulose (Kuniak, Alince, Masura, & Alfödi, 1969; Rowen, Forziati, & Reeves, 1951; Spedding, 1960). The structure of dialdehyde cellulose, as shown in Fig. 1, has been suggested to include the hydrated form

$[-CH(OH)_2]$, the 2,3-hemialdal form $[-CH(OH)-O-CH(OH)-]$, the 2,6- or 3,6-hemiacetal forms $[-CH(OH)-O-CH_2-]$, as well as the reactive free aldehyde form. The former three types correspond to addition of one molecule of water per each aldehyde group, addition of one molecule of water per two aldehyde groups, and rearrangement between an aldehyde group and one of the remaining alcohol groups without addition of water. All forms act as free aldehydes under appropriate conditions. According to a kinetic study, free or hydrated aldehyde groups react about 300 times faster than hemialdal groups, and hemiacetal groups come in intermediate between both forms (Maekawa & Koshijima, 1953).

2. Experimental

2.1. Materials

Carboxymethylcellulose sodium salt (low viscosity), Sigma Aldrich was used as cellulose sample. Periodic acid, sulphuric acid, sodium bicarbonate, hydrochloric acid, potassium iodide, sodium thiosulphate, starch were of reagent grade. Distilled water was used throughout the experiments.

E-mail address: anjali333@gmail.com

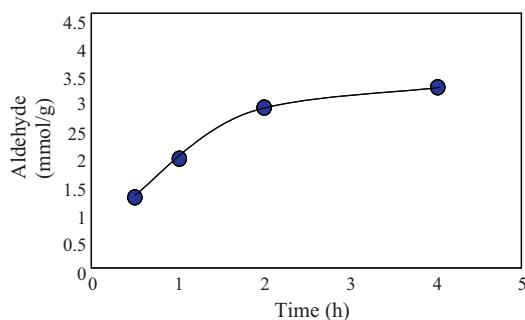


Fig. 1. Aldehyde content increasing per time.




2.2. Oxidation of carboxymethyl cellulose

Different concentrations of carboxymethyl cellulose were taken into consideration, i.e. from 0.5 wt% to 2 wt%. Finally 1 wt% was found the most suitable because of its optimum viscosity and good solubility in aqueous medium.

Added 1 g CMC in 100 ml distilled water, stirred it at room temperature for 6 h, after getting the clear solution added 3 ml of 0.45 M periodic acid. The pH of the solution was adjusted to about 3.5 using dilute sulphuric acid to decrease and sodium bicarbonate to increase the pH of the solution. The oxidation reaction conditions were carried out at temperature 45 °C (Qingxi et al., 2008). The reaction kettle was wrapped with several layers of aluminum foil to prevent exposure to light, i.e. to avoid auto oxidation. Oxidation reaction was carried out for 0.5–4 h which fulfill our requirements for detailed studies of oxidation of CMC for further experiments.

2.3. Determination of aldehyde content

The aldehyde content has been determined by iodometric titration of residual periodic acid present in the reaction mixture. Five ml of aliquot of reaction mixture was added to 10 ml 0.5 N KI and 20 ml HCl. The I₂ formed was titrated with 0.2 N sodium thiosulphate until the endpoint marked by disappearance I₂ was visualized by addition of soluble starch. The similar titration was also performed with a blank sample. All experiments were done in triplicate (Balakrishnan, Lesieur, Labarre, & Jayakrishnan, 2005; McSweeney et al., 2008). The following equations from Lange (1961) described the reactions involved in the analysis (except for the periodate cation being K):



2.4. Fourier transform infrared spectroscopy (FTIR)

FTIR spectra have been recorded for the determination of various peaks of oxidized carboxymethyl cellulose regarding aldehyde groups. Approximately 1 mg of dry sample was pressed into a pellet with 200 mg of potassium bromide and FTIR spectroscopy studies of the samples were carried out on Perkin Elmer Spectrum-BX FTIR system. FTIR of the samples were recorded in transmittance mode.

2.5. Thermogravimetric analysis (TGA)

TGA was carried out to determine the thermal stability changes occur while converting CMC to OCMC. TGA studies of the samples

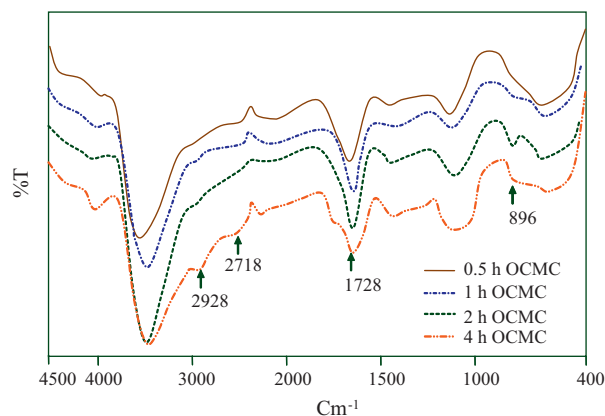


Fig. 2. FTIR spectra of 0.5 h, 1 h, 2 h and 4 h OCMC.

have been recorded with Perkin Elmer TGA-7 system. The thermograms were obtained under nitrogen atmosphere at a uniform heating rate of 20 °C/min in the temperature range of 50–600 °C.

2.6. X-ray diffraction (XRD)

X-ray diffraction has been applied to observe the crystallinity changes of CMC and OCMC. X-ray diffraction of the films was measured by the X-ray diffractometer Xpert PRO PANalytical, Holland. X-ray diffraction pattern were recorded with Cu-K α radiation ($\lambda = 1.54 \text{ \AA}$). The voltage and current were recorded 40 kV and 30 mA respectively. Samples were scanned from 5° to 60° 2 θ .

3. Results and discussion

3.1. Aldehyde content

Periodate oxidation of cellulose proceeds gradually from the amorphous to the crystalline phase, it cause the changes in the physical and chemical properties of carboxymethyl cellulose. In this study several oxidations with different time period were carried out. Increasing the reaction time degrades the sample more extensively. In Fig. 2 we can see the periodate oxidation of carboxymethyl cellulose forming dialdehyde cellulose.

Consumption of sodium thiosulphate by the sample is the measure of excess periodic acid. It is known that one periodic acid forms two aldehyde groups so by the amount of periodic acid we calculated the amount of aldehyde groups formed during periodate oxidation. We carried out our experiment from 0.5 h to 4 h. As the oxidation time is increased aldehyde content also get increase Table 1 and Fig. 1.

3.2. FTIR

In Figs. 2 and 3 the three bands, i.e. at 1728, 2928 and 2718 cm⁻¹ confirm the oxidation. The oxidation leads to the presence of one more characteristic band of OCMC in 880 cm⁻¹ regions. The broad band at 880 cm⁻¹ can be assigned to the hemiacetal and hydrated form of the dialdehyde cellulose (Bruneel & Schacht,

Table 1
Aldehyde Content (mmol/g) per time (h).

Time (h)	Aldehyde content (mmol/g)
0.5	1.2
1	1.9
2	2.8
4	3.1

Download English Version:

<https://daneshyari.com/en/article/10602250>

Download Persian Version:

<https://daneshyari.com/article/10602250>

[Daneshyari.com](https://daneshyari.com)