



# Effect of ultrasonic pretreatment on emulsion polymerization of styrene



Daichi Nagatomo<sup>a</sup>, Takafumi Horie<sup>a,\*</sup>, Chizuru Hongo<sup>b</sup>, Naoto Ohmura<sup>a</sup>

<sup>a</sup> Department of Chemical Science and Engineering, Graduate School of Engineering, Kobe University, 1-1 Rokko-dai, Nada-ku, Kobe 657-8501, Japan

<sup>b</sup> Organization of Advanced Science and Technology, Kobe University, 1-1 Rokko-dai, Nada-ku, Kobe 657-8501, Japan

## ARTICLE INFO

### Article history:

Received 26 October 2015

Received in revised form 9 January 2016

Accepted 10 January 2016

Available online 12 January 2016

### Keywords:

Emulsion polymerization

Process intensification

Function modules

Compartment reactor

Smith–Ewart theory

Partition equilibrium

## ABSTRACT

This study investigated the effect of pretreatment of ultrasonic irradiation on emulsion polymerization of styrene to propose a process intensification method which gives high conversion, high reaction rate, and high energy efficiency. The solution containing styrene monomer was irradiated by a horn mounted on the ultrasonic transducer with the diameter of 5 mm diameter and the frequency of 28 kHz before starting polymerization. The pretreatment of ultrasound irradiation as short as 1 min drastically improved monomer dispersion and increased reaction rate even under the agitation condition with low rotational speed of impeller. Furthermore, the ultrasonic pretreatment resulted in higher monomer concentration in polymer particles and produced larger polymer particles than conventional polymerization without ultrasonic pretreatment.

© 2016 Elsevier B.V. All rights reserved.

## 1. Introduction

Process intensification brings technological innovations to drastically enhance energy efficiency and process performance, thus contributing toward a sustainable society. In chemical industries, reactors, which are the heart of chemical processes, have received more attention than other unit operations in the context of intensification. Stankiewicz and Moulijn [1] divided process intensification into two areas, i.e. process-intensifying equipment and process-intensifying methods. Among the process-intensifying methods, alternative energy sources such as centrifugal fields, ultrasound, solar energy, microwaves etc. are one of the promising methods for future process intensification. Particularly, the use of ultrasound as a source of energy for chemical processing has the potential for development of an innovative chemical process. Cavitation causing the formation, growth and implosion collapse of microbubbles can create high local energy with temperature of up to 5000 K and negative pressure of up to 10,000 atm [1–3]. Furthermore, low-frequency ultrasound can exert some physical effects such as enhanced mass transport, emulsification and so on.

Emulsion polymerization which is a heterogeneous reaction system can be intensified by ultrasound irradiation. The cavitation produces radicals and emulsion polymerization can be conducted without adding initiator. Ooi and Biggs [4] showed that the monomer conversion could be achieved up to 90% without initiator using

a horn-type ultrasound device in the emulsion polymerization of styrene. Kobayashi et al. [5] evaluated performance of emulsion polymerization of styrene using a bath-type ultrasonic equipment under no initiator conditions. Although applying ultrasound is hopeful for emulsion polymerization, continuous irradiation is rather wasteful for energy consumption. Most of the input energy by ultrasound irradiation is converted to thermal energy to simply rise the liquid temperature. As Stankiewicz and Moulijn [1] pointed out, therefore, the maximum economically and technically feasible size and shape of the reactor are still unresolved issue. This problem is interfering industrial applications of ultrasound device for emulsion polymerization.

Conventional emulsion polymerization processes often encounter deceleration of reaction rate due to unstable monomer dispersion which results in enlargement of monomer droplet size and phase separation due to coalescence of monomer droplets. In order to avoid the deceleration of reaction rate, higher agitation speed is required. However, higher agitation speed causes another problem, i.e. polymer coagulation due to high shear. Yatomi et al. [6] showed that amount of coagulation in the emulsion polymerization depended on required power of an agitation impeller, and optimal required power existed. This indicates how to obtain stable monomer dispersion is a critical issue in the emulsion polymerization.

In this study, emulsification ability of ultrasound was focused on because even a short time irradiation could produce highly stable dispersion state of monomer droplets. Ultrasound irradiation for a very short time was carried out before emulsion polymerization as pretreatment. This operation leads to high energy

\* Corresponding author.

E-mail address: [horie@dragon.kobe-u.ac.jp](mailto:horie@dragon.kobe-u.ac.jp) (T. Horie).

efficiency. Monomer dispersion can be maintained even at low agitation speed by ultrasonic pretreatment. Furthermore, the effect of size and shape of reactor on emulsion polymerization are independent of ultrasound irradiation condition. This study investigated the effect of ultrasonic pretreatment on reaction kinetics of emulsion polymerization of styrene to propose a process intensification method which gives higher conversion, faster reaction rate, less coagulation and higher energy efficiency.

## 2. Experimental

Fig. 1 presents a schematic of the experimental apparatus. Styrene monomer (special grade, Wako Pure Chemical Industries, Ltd.) was washed with 10% NaOH three times to remove the inhibitor (*p*-tert butylcatechol), followed by three washes with distilled water. Distilled water of 180 mL, sodium dodecyl sulfate of 0.5 g (first grade, Wako Pure Chemical Industries, Ltd.) and the styrene monomer of 10 mL were added into a beaker. Before starting each experiment, dissolved oxygen in aqueous mixture of emulsifier and initiator was completely expelled by feeding nitrogen gas for sufficient time. The solution in a beaker was irradiated by a horn type ultrasonic device (SONAC-150, Honda Electronics Co., Ltd.) with the diameter of 5 mm diameter and the frequency of 28 kHz. After this pretreatment, the solution was poured into the cylindrical glass reactor with volume of 200 mL. The reactor was equipped with a water jacket to keep the reaction temperature  $60 \pm 1$  °C. Reaction was started by adding aqueous potassium persulfate of 10 mL (2.9 wt%) (special grade, Kanto Chemical Co., Inc.). The 2-bladed turbine impeller was used at all experiments. The rotational speed of the impeller was varied from 250 to 1000 rpm. Samples were taken for analysis at predetermined time. Polymerization in each sample was stopped by adding hydroquinone (special grade, Wako Pure Chemical Industries, Ltd.).

Monomer conversion was determined by measuring the mass of coagulated latex particles after adding an aqueous solution of aluminum (III) chloride hexahydrate ( $2.5 \text{ kg m}^{-3}$ ) (special grade, Wako Pure Chemical Industries, Ltd.), rinsing with distilled water and drying. The PSD was obtained using a laser-diffraction particle-size analyzer (ELSZ-2, Otsuka Electronics Co., Ltd.) on a number basis for percentage.

## 3. Results

### 3.1. Stability of emulsified monomer solution

Fig. 2 shows the pictures of emulsified monomer solution at different elapsed time after ultrasonic irradiation. The ultrasonic

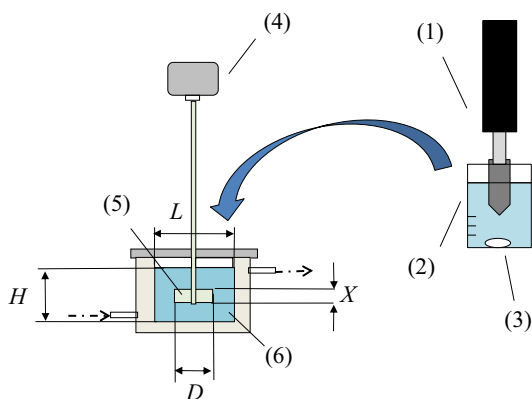


Fig. 1. Experimental apparatus (1) horn-type ultrasonic device (2) beaker of 200 mL (3) magnet stirrer (4) stirrer (5) 2-bladed turbine impeller (6) batch reactor ( $L = 60$  mm,  $D = 20$  mm,  $H = 73$  mm,  $X = 10$  mm) with a jacket.

pretreatment made fine droplets of styrene monomer and the emulsified solution became completely clouded. Although coalescence of monomer droplets occurred and phase separation between monomer and water gradually proceeded, sufficient monomer dispersion can be obtained even after 8 h since ultrasonic irradiation. Monomer droplets gradually floated on water with time courses. After about 48 h, water and monomer almost completely separated. Fig. 3 shows time variation of monomer droplets diameter,  $d_m$  [ $\mu\text{m}$ ], as a function of irradiation time. The diameter of monomer droplets slightly increased for 30 min in all cases. As shown in Fig. 3, the longer ultrasound was irradiated, the finer monomer droplets became. Consequently, the growth rate of droplet diameter in the case of longer irradiation was slower. Although slight difference of droplet diameter could be seen among three cases, even short irradiation made the droplet diameter sufficiently small to obtain stable emulsified state when reaction time of emulsion polymerization was taken into consideration.

### 3.2. Reaction rate and estimation of energy consumption

Fig. 4 shows the time variation of monomer conversion as functions of ultrasound irradiation time and rotational speed of impeller. In the case without ultrasonic pretreatment (Fig. 4a), at lower rotational speed of impeller than 750 rpm, weak shear force by the slow impeller rotation induced rapid coalescence of monomer droplets and floating layer of monomer was formed. As a result, final monomer conversion did not reach 100%. On the other hand, at higher rotational speed of impeller than 750 rpm, monomer floating layer was not formed and the monomer was completely consumed and the conversion reached 100%. Although the final conversion values were different between lower and higher rotational speed of impeller, the initial reaction rate was almost the same. One should note that reaction rate was also increased by ultrasonic pretreatment. In the case of the various ultrasonic pretreatment time (Fig. 4b), the insufficient dispersion resulted in lower conversion when the irradiation time was less than 30 s. In contrast, ultrasonic pretreatment more than 1 min led to the 100% conversion of monomer even at 250 rpm due to good dispersion of monomer, and there was little difference for the longer pretreatment than 1 min. Furthermore, in the case with ultrasonic pretreatment, the reaction rate was independent of rotational speed of impeller.

Here we measured electric power supplied to the system,  $E$  [g/J], defined as the following equation:

$$E = \frac{x}{e_u t_u + e_r t_r} \quad (1)$$

where  $x$  [g] is polymer yield,  $e_u$  [W] and  $e_r$  [W] are the electric power consumption rates required by ultrasonic irradiation and agitation respectively, and  $t_u$  [s],  $t_r$  [s] are the duration time of ultrasonic irradiation and agitation respectively. The electric power consumption rates were measured by an electrical power meter (TAP-TST5, SANWA SUPPLY). Fig. 5 shows the polymer yield per consumption energy when the monomer conversion reached 80%. As can be seen from Fig. 5, 1 min ultrasonic pretreatment gave the highest polymer yield per energy consumption. With increasing irradiation time, the polymer yield decreased due to large energy consumption of ultrasonic irradiation. On the other hand, with decreasing irradiation time from 1 min to 30 s, the polymer yield was also decreased, because it took more time to reach 80% conversion due to the formation of thin monomer floating layer. Although the growth rate of droplet diameter was fast in a case when the irradiation time was 1 min, as shown in Fig. 3, the stability of the monomer droplets was guaranteed within the time range of polymerization when the diameter was less than  $2.0 \mu\text{m}$ . Thus the optimum value of ultrasonic irradiation time could be regarded as 1 min.

Download English Version:

<https://daneshyari.com/en/article/1265679>

Download Persian Version:

<https://daneshyari.com/article/1265679>

[Daneshyari.com](https://daneshyari.com)