



Short communication

Electrochemical profile of an asymmetric supercapacitor using carbon-coated $\text{LiTi}_2(\text{PO}_4)_3$ and active carbon electrodes

Jia-Yan Luo, Yong-Yao Xia*

Department of Chemistry & Shanghai Key Laboratory of Molecular Catalysis and Innovative Materials, Fudan University, Shanghai 200433, PR China

ARTICLE INFO

Article history:

Received 14 July 2008

Received in revised form 9 September 2008

Accepted 9 September 2008

Available online 26 September 2008

Keywords:

Aqueous

Electrochemical capacitor

 Li_2SO_4

Hybrid

Battery

Energy

ABSTRACT

In this work, we reported an asymmetric supercapacitor in which active carbon (AC) was used as a positive electrode and carbon-coated $\text{LiTi}_2(\text{PO}_4)_3$ as a negative electrode in 1 M Li_2SO_4 aqueous electrolyte. The $\text{LiTi}_2(\text{PO}_4)_3/\text{AC}$ hybrid supercapacitor showed a sloping voltage profile from 0.3 to 1.5 V, at an average voltage near 0.9 V, and delivered a capacity of 30 mAh g^{-1} and an energy density of 27 Wh kg^{-1} based on the total weight of the active electrode materials. It exhibited a desirable profile and maintained over 85% of its initial energy density after 1000 cycles. The hybrid supercapacitor also exhibited an excellent rate capability, even at a power density of 1000 W kg^{-1} , it had a specific energy 15 Wh kg^{-1} compared with 24 Wh kg^{-1} at the power density about 200 W kg^{-1} .

© 2008 Published by Elsevier B.V.

1. Introduction

Supercapacitors coupled with batteries and fuel cells are considered promising mid-term and long-term for low- and zero-emission transport vehicles by providing the power peaks for start-stop, acceleration, and recovering the braking energy. Today much research in electrochemical capacitors aims to increase power and energy density as well as reduce fabrication cost while using environmental friendly materials [1–5]. One of the most useful approaches is to develop a hybrid system that typically consists of an electrochemical double-layer capacitor (EDLC) electrode and a battery electrode, such as $\text{AC}/\text{Ni}(\text{OH})_2$, AC/MnO_2 and $\text{AC}/\text{LiMn}_2\text{O}_4$ systems [6–8]. Both the increase of the working voltage and the high energy density of the battery electrode material results in a significant increase in the overall energy density of the capacitors compared with that of AC/AC system. It should be noted that, in the above aqueous hybrid supercapacitor systems, the negative electrode materials are all activated carbon, which is characterized by a high hydrogen evolution overpotential that enables a large negative cutoff potential [9,10]. However, there are no appropriate negative materials for supercapacitor to replace AC except RuO_2 until now, but the high cost detracts its application.

Recently, we have demonstrated that the carbon-coated $\text{LiTi}_2(\text{PO}_4)_3$ exhibited excellent electrochemical performance both in organic and aqueous electrolytes, and especially shown good cycling stability in aqueous electrolytes [11]. $\text{LiTi}_2(\text{PO}_4)_3$ appears to be a promising material for the novel hybrid supercapacitor negative electrode, because of the appropriate voltage plateau at 2.5 V vs. Li/Li^+ (–0.5 V vs. SHE), high theoretical specific capacity of 138 mAh g^{-1} , low cost of the raw material, and environmentally benign [12–14]. In the present work, the hybrid supercapacitor consisting of a combination of AC as cathode material, carbon-coated $\text{LiTi}_2(\text{PO}_4)_3$ as anode material, and a 1 M Li_2SO_4 aqueous solution as electrolyte was presented, and the electrochemical performance of the $\text{LiTi}_2(\text{PO}_4)_3/\text{AC}$ hybrid supercapacitor was extensively investigated by cyclic voltammetry (CV), and galvanostatic charge–discharge tests.

2. Experiment

Carbon-coated $\text{LiTi}_2(\text{PO}_4)_3$: the macroporous $\text{LiTi}_2(\text{PO}_4)_3$ was prepared by a sol–gel method [11]. An aqueous precursor containing Li_2CO_3 , $\text{NH}_4\text{H}_2\text{PO}_4$, and TiO_2 was blended with 100 ml of 2 wt.% poly-vinyl-alcohol (PVA) aqueous solution as a synthetic agent. The mixture was stirred at a constant temperature of 80°C until water has evaporated and a white solid formed. The product was placed in a porcelain boat and heated at 900°C for 12 h under N_2 flow in a tube furnace. Then the as-prepared $\text{LiTi}_2(\text{PO}_4)_3$ powder was transferred into a reaction tube to make a fluid-bed layer for reaction where

* Corresponding author. Fax: +86 21 55664177.
E-mail address: yyxia@fudan.edu.cn (Y.-Y. Xia).

a toluene vapor was carried by N_2 through the reaction tube at a flow rate of 1 l min^{-1} . The reaction temperature was maintained at 800°C for 12 h to coat the surface of $\text{LiTi}_2(\text{PO}_4)_3$ with a carbon layer about 20 nm. The carbon content of the carbon-coated $\text{LiTi}_2(\text{PO}_4)_3$ sample is about 12 wt.% by TG analysis (including both the carbon resident in the as-prepared nanostructured $\text{LiTi}_2(\text{PO}_4)_3$ and CVD coated carbon) and the carbon has been transformed to graphite to a certain extent. The particle size of the carbon-coated $\text{LiTi}_2(\text{PO}_4)_3$ is in the range of 200–300 nm. BET surface area measurement of the carbon-coated $\text{LiTi}_2(\text{PO}_4)_3$ yields a value of $0.7 \text{ m}^2 \text{ g}^{-1}$. The AC was used as received (provided by Research Institute of Chemical Defense, Beijing, China) and had a BET surface area of $1500 \text{ m}^2 \text{ g}^{-1}$.

The electrodes were formed by mixing 85 wt.% active material, 10 wt.% acetylene black and 5 wt.% PTFE as binder before pressing into a thin sheet of uniform thickness onto stainless steel grid ($1.2 \times 10^7 \text{ Pa}$) that served as a current collector (area is 1 cm^2). The typical mass load of positive (AC) and negative (carbon-coated $\text{LiTi}_2(\text{PO}_4)_3$) electrode material was 14 and 8 mg, respectively. The electrolyte was 1 M Li_2SO_4 solution. The electrochemical behavior of the individual composite electrode was characterized by cyclic voltammetry (CV). The experiments were carried out in a three-electrode glass cell. Platinum foil was used as a counter electrode, and saturated calomel electrode (SCE, 0.242 V vs. NHE) as the reference electrode. Cyclic voltammetry test was performed using a Solartron Instrument Model 1287 electrochemical interface controlled by a computer. Capacitor test was using a two-electrode glass cell, it was consisted of a AC positive electrode and $\text{LiTi}_2(\text{PO}_4)_3$ negative electrode.

3. Results and discussion

Fig. 1 shows the cyclic voltammograms (CV) of carbon-coated $\text{LiTi}_2(\text{PO}_4)_3$ and AC electrodes. The CV of the carbon-coated $\text{LiTi}_2(\text{PO}_4)_3$ electrode in aqueous 1 M Li_2SO_4 solution (Fig. 1a) is characterized by a set of oxidation and reduction peaks centered at -0.6 and -0.9 V (potential vs. SCE), respectively, which are in good agreement with the extraction/insertion reaction of $\text{LiTi}_2(\text{PO}_4)_3$ in the organic electrolyte. The hydrogen evolution reaction (HER) on the $\text{LiTi}_2(\text{PO}_4)_3$ electrode occurs under -1.0 V (potential vs. SCE), indicating that the Li^+ can be inserted into the $\text{LiTi}_2(\text{PO}_4)_3$ lattice before the evolution of H_2 . It should be noted that the carbon coating is needed to improve the stability of in aqueous electrolyte. The uncoated $\text{LiTi}_2(\text{PO}_4)_3$ shows fast capacity fading in aqueous electrolyte, which is extensively found for the electrode materials with potentials lower than 3.0 V vs. Li/Li^+ in aqueous electrolyte. It has been suggested that the capacity fading is related to transition metal ion dissolution, phase transformation of electrode materials, decomposition of water, and so on [15]. We speculate that the capacity fading mechanism of $\text{LiTi}_2(\text{PO}_4)_3$ is most likely ascribed to changes in the composition and/or phase structure because of a side reaction with water in the aqueous electrolyte. So we employed a surface carbon-coated technique to improve the stability of electrode material by preventing water from attacking the bulk phase [11]. However, the lithium insertion into the carbon generally takes place at potentials lower than 1.5 V vs. Li/Li^+ , the lithium ion intercalates $\text{LiTi}_2(\text{PO}_4)_3$ at 2.5 V vs. Li/Li^+ . It is seen that the carbon coated by CVD process spreads over the entire particle surface to form a nanometer-thick film will prevent the lithium ion from intercalating $\text{LiTi}_2(\text{PO}_4)_3$. Presently, the mechanism responsible for ionic transport in the coatings still remains unclear. Recently, Suzuki reported that the lithium ion can diffuse through a copper thin film [16]. This was further confirmed by an *ab initio* density-functional calculation contributed by Chen and co-workers [17]. They demonstrated that the ion can pass through the film by some crystal defect

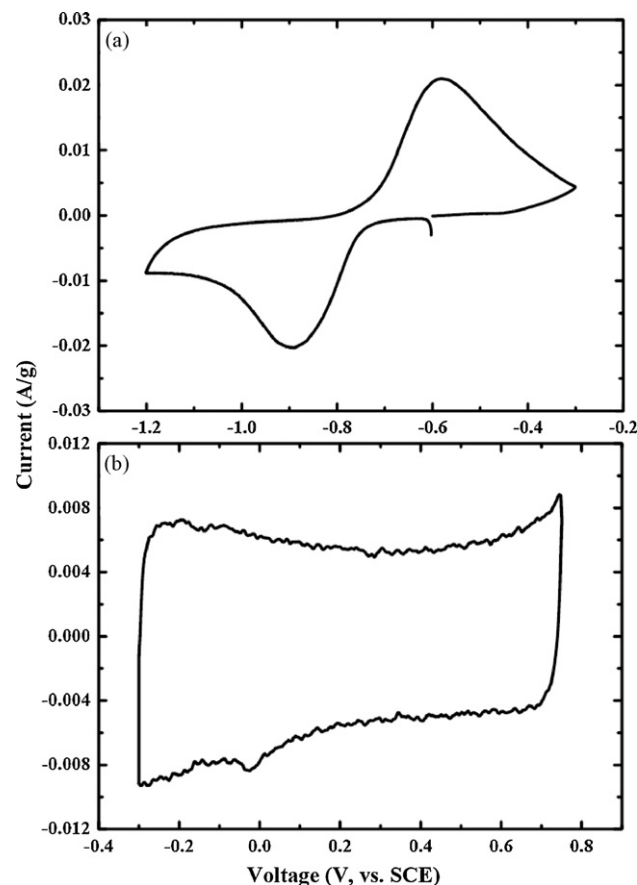


Fig. 1. CV curves of (a) carbon-coated $\text{LiTi}_2(\text{PO}_4)_3$ sample, and (b) AC sample at a scan rate of 3 mV s^{-1} .

or vacancy in the bulk substance under the ion concentration in between two phase. There are many defects present in our coated-carbon layer. It is speculated that these defects allow the Li ion to pass through the carbon layer to provide enough effective reaction areas. The AC electrode (Fig. 1b) can be cycled between -0.3 and 0.75 V (potential vs. SCE) without noticeable oxygen evolution. Within this potential window, the shape of the CV is rectangular as expected for material displaying capacitive behavior.

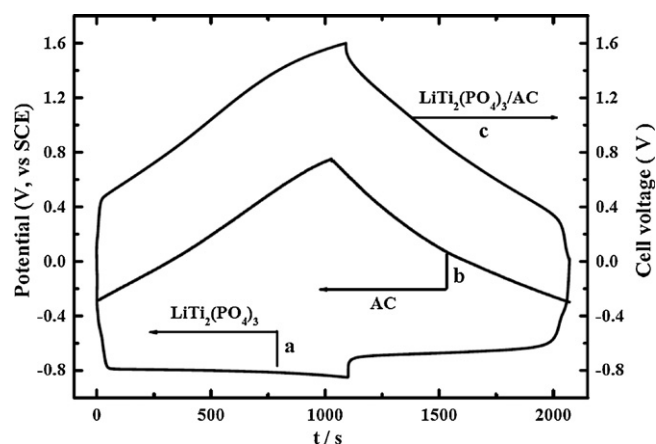


Fig. 2. Typical charge/discharge curves of individual electrode (a) carbon-coated $\text{LiTi}_2(\text{PO}_4)_3$ and (b) AC along with (c) a composite voltage profile of the $\text{LiTi}_2(\text{PO}_4)_3/\text{AC}$ hybrid aqueous capacitor at a current rate of 2 mA cm^{-2} in 1 M Li_2SO_4 .

Download English Version:

<https://daneshyari.com/en/article/1289915>

Download Persian Version:

<https://daneshyari.com/article/1289915>

[Daneshyari.com](https://daneshyari.com)