



Short communication

Microwave assisted ecofriendly recycling of poly (ethylene terephthalate) bottle waste

N.D. Pingale, S.R. Shukla *

Department of Fibres and Textile Processing Technology, Institute of Chemical Technology (Autonomous), University of Mumbai, Matunga, Mumbai 400 019, Maharashtra, India

ARTICLE INFO

Article history:

Received 4 June 2008

Received in revised form 25 August 2008

Accepted 18 September 2008

Available online 26 September 2008

Keywords:

PET bottle waste

Recycling

Glycolysis

Bis (2-hydroxyethylene) terephthalate

ABSTRACT

Glycolysis of poly (ethylene terephthalate) bottle waste was carried out using microwave energy. A domestic microwave oven of 800 W was used with suitable modification for carrying out the reaction under reflux. The catalysts used for the depolymerization in ethylene glycol (EG) were zinc acetate and some simple laboratory chemicals such as sodium carbonate, sodium bicarbonate and barium hydroxide. Comparison of results was made from the point of view of the yield of bis (2-hydroxyethylene) terephthalate (BHET) and the time taken for depolymerization. It was observed that under identical conditions of catalyst concentration and PET:EG ratio, the yield of BHET was nearly same as that obtained earlier by conventional electric heating. However, the time taken for completion of reaction was reduced drastically from 8 h to 35 min. This has led to substantial saving in energy.

© 2008 Elsevier Ltd. All rights reserved.

1. Introduction

Poly (ethylene terephthalate) (PET) finds use in a large number of utilities among which the fibers and disposable soft drink bottles predominate. Substantial solid waste generation coupled with high resistance to degradative assimilation into the environment makes it to be seen as a noxious material that demands its effective recycling [1].

Two main sources for PET recycling are the manufacturing waste and the post consumer waste [2]. Chemical recycling through depolymerization leads to the formation of materials which can react to form the polymer itself or some other secondary value added products [3]. Hydrolysis, aminolysis, methanolysis and glycolysis [4] are the routes to PET depolymerization, of which glycolysis and methanolysis have reached commercial maturity [1]. Glycolysis using ethylene glycol [5–10], diethylene and dipropylene glycol [8] and propylene glycol [11] results in the formation of oligomers or oligoester diols/polyols with hydroxyl terminal groups [5].

Microwave-assisted organic synthesis (MAOS), a new technique that has revolutionized synthesis moved to the forefront of chemical research [12,13]. Heating the material by microwave irradiation offers a number of advantages over the conventional heating, such as noncontact, instantaneous and rapid heating with high specificity. These characteristics have made it a popular technique for heating and drying materials and it is utilized in many households and industrial applications [13,14].

Microwave irradiation has been used for hydroglycolysis of PET pallets to reduce reaction time to less than 10 min in comparison with about 30 min at 100 °C heating in presence of various alcohols and alkalis. [15] The microwaves couple directly with the molecules those are present in a reaction mixture, leading to rapid but controllable rise in the temperature. Two fundamental mechanisms for transferring energy from microwaves to the substance being heated are the dipole rotation and the ionic conduction. Dipole rotation is an interaction between polar molecules, which try to align themselves with the rapidly changing electric field of the microwaves, resulting in transfer of energy. It is related to polarity of the molecules and their ability to align with the electric field. Ionic

* Corresponding author. Tel.: +91 22 2414 5616.

E-mail address: sanjeevrshukla@rediffmail.com (S.R. Shukla).

conduction results if there are free ions or ionic species present in the substance, which try to orient themselves to the rapidly changing electric field, generating ionic motion [16].

Hydrolytic depolymerization of PET in closed system under microwave irradiation with 2 MPa pressure and 90–120 min reaction time led to terephthalic acid, ethylene glycol and diethylene glycol as degradation products [17]. Similar studies were carried out by Zhang [18] using pure water at 220–230 °C at 2.0–2.5 MPa for 120–60 min. Krzan [19–21] during solvolysis in presence of zinc acetate catalyst and by using microwave (500 W) in a closed system achieved complete PET solubilization in about 5–10 min with methanol, diethylene glycol, propylene glycol and polypropylene glycol.

In the present study, we have attempted the use of microwave irradiation for PET glycolysis in EG under reflux conditions in place of conventional heating to obtain virtual monomer bis (2-hydroxyethylene) terephthalate (BHET). The catalysts used were zinc acetate, sodium carbonate, sodium bicarbonate and barium hydroxide of which the first three have been used in earlier glycolysis experiments using conventional heating source [9,10].

The results on the yield of BHET under these two sources of heating are compared through optimization of parameters (PET:EG ratio, catalyst concentration and time of glycolysis) for the yield of pure BHET.

2. Experimental

2.1. Materials

Discarded PET bottles were procured from local market. The bottles after removing caps and labels were cleaned by boiling in a weak detergent solution followed by washing and drying.

2.2. Chemicals

All the chemicals including the catalysts zinc acetate, sodium bicarbonate, sodium carbonate and barium hydroxide were of analytical reagent grade.

2.3. Glycolysis of polyester waste

A 700 W Electrolux (17L) domestic microwave oven was used at maximum power for the glycolysis reaction. A hole was made in the back panel of the oven to allow fitting of a condenser (Fig. 1). PET waste was treated with ethylene glycol using different PET:EG molar ratios (1:4 to 1:10) under reflux using microwave oven for time periods up to 60 min. The catalysts used were zinc acetate, sodium bicarbonate, sodium carbonate and barium hydroxide and their concentration was varied between 0.3% and 1% (w/w) in the reaction mixture. At the end of the reaction, distilled water was added in excess to the reaction mixture with vigorous agitation. The glycolized product was obtained as a residue after filtration. The filtrate contained unreacted ethylene glycol, bis (2-hydroxyethylene) terephthalate (BHET) and little quantities of a

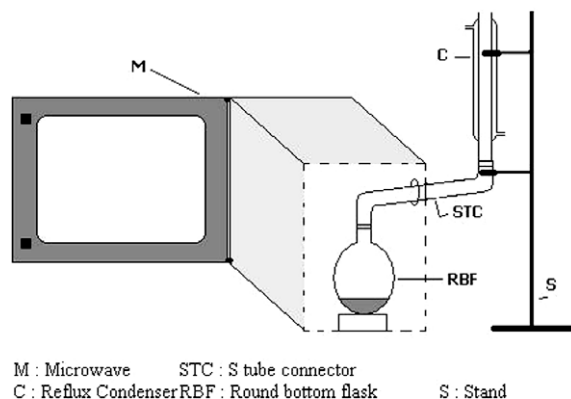


Fig. 1. Microwave reaction assembly.

few water soluble oligomer. White crystals of BHET were obtained by first concentrating the filtrate by boiling and then chilling it. The glycolized residue was then boiled with water to extract any BHET left. White crystalline powder of BHET was purified by repeated crystallization from water, dried in an oven at 80 °C and weighed for estimating the yield. It was subjected to different characterization techniques, such as FTIR, NMR, and DSC.

2.4. Characterization of BHET

Melting point of the purified monomer, BHET was determined in an open capillary. Elemental analysis was carried out by using Heraeus Combustion Apparatus. For ¹H NMR, the glycolized residue was dissolved in solvent CDCl₃. Tetramethyl silane was used as an internal standard and the spectrograph was recorded on JEOL, FT-NMR (60 MHz). FTIR spectrum was recorded using KBr disc technique on Shimadzu IR Spectrophotometer (Model 8400S). The melting characteristic was determined by differential scanning calorimeter (DSC) (Shimadzu 60) at the heating rate of 10 °C/min from 20 to 200 °C in nitrogen atmosphere.

3. Results and discussion

Earlier, we have reported that simple nontoxic chemicals like sodium carbonate, sodium bicarbonate, glacial acetic acid, lithium hydroxide, sodium sulfate and potassium sulfate can be used for PET glycolysis as catalyst in place of the conventionally used heavy metal catalysts zinc acetate and lead acetate. The experiments were conducted under reflux in EG using conventional electrical heating [9,10]. The products of glycolysis were BHET along with oligomers to a lesser extent, out of which BHET was separated by repeated crystallization. In the present communication, the study of ecofriendly glycolysis has been extended to the use of unconventional heating source of microwave radiations. The catalysts selected for this purpose were the conventional zinc acetate, sodium carbonate, sodium bicarbonate and barium hydroxide.

The glycolysis led to soluble BHET and insoluble residue of different oligomers. After filtration and repeated crystallization, pure BHET yield was measured. Each experiment

Download English Version:

<https://daneshyari.com/en/article/1402962>

Download Persian Version:

<https://daneshyari.com/article/1402962>

[Daneshyari.com](https://daneshyari.com)