



Initial anisotropy in demineralized bovine cortical bone in compressive cyclic loading–unloading

Ekaterina Novitskaya ^{a,*}, Steve Lee ^a, Vlado A. Lubarda ^b, Joanna McKittrick ^{a,b}

^a Materials Science and Engineering Program, University of California, San Diego, La Jolla, CA 92093, USA

^b Department of Mechanical and Aerospace Engineering, University of California, San Diego, La Jolla, CA 92093, USA

ARTICLE INFO

Article history:

Received 7 August 2012

Received in revised form 2 October 2012

Accepted 4 November 2012

Available online 12 November 2012

Keywords:

Anisotropy

Cortical bone

Cyclic compression

Demineralization

ABSTRACT

The mechanical properties of demineralized bovine cortical femur bone were investigated by cyclic loading–unloading compression in three anatomical directions (longitudinal, radial, transverse) within the physiological strain range. The loading responses in the radial and transverse directions were nearly linear up to 2% strain, while the response in longitudinal direction was strongly non-linear in that range. The unloading responses were non-linear for each anatomical direction, giving rise to overall loading–unloading hysteresis and cyclic dissipation of energy. The mechanical properties were observed to be anisotropic: the radial direction was found to be the most energy dissipative, while the longitudinal direction appeared to be the stiffest bone direction. The cyclic loading mostly affects the bone stiffness in the radial and transverse directions, while the longitudinal direction was found to be the least affected. These anisotropic properties can be attributed to the differences in collagen fibers alignment and different microstructural architecture in three different anatomical bone directions.

© 2012 Elsevier B.V. All rights reserved.

1. Introduction

Bone is a hierarchically structured composite material mainly composed of a biopolymer (mostly type-I collagen), a mineral phase (carbonated hydroxyapatite), and water. The internal structure and mechanical properties of bone have been investigated by many research groups, including seminal works of Currey [1,2]; Burstein et al. [3], and Rho et al. [4]. Bone is anisotropic biological material; therefore a significant effort was made in the past to investigate mechanical properties of bone in different anatomical directions (e.g., Reilly and Burstein [5]; Bonfield and Grynpas [6]; Hasegawa et al. [7]; Iyo et al. [8]; Macione et al. [9], Skedros et al. [10]).

Detailed examination of mechanical properties of the major bone constituents (mineral and protein) in different anatomical directions is important to better understand bone mechanical response. Hasegawa et al. [7] performed acoustic velocity measurements on dog femur in the longitudinal and transverse directions. The bone was demineralized by 10% ethylenediaminetetraacetic acid (EDTA) (100% protein), and deproteinized by 7% sodium hypochlorite (100% minerals). They concluded that the minerals play the major role in the anisotropic behavior of the whole bone, while the protein matrix is highly isotropic. Iyo et al. [8] examined the effect of mechanical anisotropy on the elastic modulus relaxation. They proposed the model for the relaxation of the elastic modulus of cortical bone which included a combination of two processes: a fast one, attributed to the

relaxation of protein matrix, and a slow one, attributed to the mixture of protein and mineral matrices. Furthermore, they suggested that the slower process was responsible for the anisotropic behavior of bone. Skedros et al. [10] used acoustic microscopy to evaluate elastic modulus of untreated, demineralized and deproteinized cortical bone of wild deer calcanei. They found that anisotropy ratio (AR), calculated as ratio between longitudinal and transverse elastic coefficients, was significantly different from isotropy (where $AR=1$) not only for untreated bone, but for demineralized and deproteinized bones as well, proving that not only untreated bone, but also its main constituents (mineral and protein phases alone) behave in an anisotropic manner.

Cyclic loading–unloading experiments on bone have been studied by many groups for both cortical and trabecular bones [11–14]. Keaveny et al. [11] performed compression loading up to 4% strain, followed by the immediate unloading to a zero stress level and reloading up to approximately same strain level on a human vertebral trabecular bone. They reported percent of elastic modulus and strength reduction and concluded that occasional overloading of bone can increase the probability of bone fracture because of the mechanical degradation of a trabecular network. Pattin et al. [12] measured the fatigue properties of human femoral cortical bone, investigating the changes in secant moduli and cyclic energy dissipation during the load-controlled experiments. They reported that loading in tension up to 2.5×10^{-3} and in compression up to 4×10^{-3} strain recovered to zero strain after unloading. Schaffler et al. [13] examined the fatigue properties of bovine cortical bone loaded up to strain magnitudes less than 2×10^{-3} . They found that bone can

* Corresponding author. Tel.: +1 858 534 5513; fax: +1 858 534 5698.

E-mail address: eevdokim@ucsd.edu (E. Novitskaya).

withstand several millions of cycles without fatigue failure, and, moreover, after initial stiffness degradation of about 6%, stiffness does not significantly change. These findings suggest that physiological loading conditions within the average lifetime number of cycles do not result in fatigue failure. All experiments mentioned above were performed on samples in longitudinal direction. To the best of the authors' knowledge, there are no reports on cyclic loading–unloading experiments on demineralized cortical bone (pure bone protein matrix) in the three orthogonal anatomical directions.

Anisotropic behavior of demineralized cortical bone in compression was recently investigated by Novitskaya et al. [15], who have shown that bone protein matrix (completely demineralized bone) demonstrates anisotropic properties: the longitudinal direction was found to be the stiffest bone direction due to preferential collagen fiber orientation in this direction. The preferential orientation of collagen fibers and mineral crystals along bone growth direction is one of the main reasons for bone anisotropy. Landis et al. [16] investigated the ultrasound interaction between collagen and mineral crystals in chicken bone by high voltage electron microscopic tomography, and found that individual platelet-shaped mineral crystals were periodically arranged along collagen fibrils preferentially aligned along the longitudinal direction. Martin et al. [17,18] found out that longitudinal fiber orientation in compact bone greatly contributed to increased elastic modulus and strength in four-point bending tests. The current study expands these findings by reporting the results on strain-controlled cyclic loading–unloading compression tests on demineralized bovine cortical bone in three anatomical directions. Collagen based biomaterials are widely used to construct tissue engineering scaffolds and have found many applications from artificial bone substitutes [19] to artificial skin [20]. For each of these applications, the analysis of mechanical behavior of bone collagen under different loading conditions is of great importance. This research is of medical interest since many groups have recently investigated collagen sponge structure and properties for prospective bone substitutes [21–25].

2. Materials and methods

2.1. Sample preparation

Bovine femur bone samples were obtained from a local butcher. The slaughter age of the cattle was about 18 months. The bone was thoroughly cleaned with water. Samples were cut from the mid-diaphysis region. About 60 samples for compression testing (parallelepipeds 5 mm×5 mm×7.5 mm, 20 for the each anatomical direction) were prepared from close locations in order to minimize variations in density and mineral content. The samples were first roughly cut by handsaw and then by a diamond blade under the constant water irrigation with the prospective loading surfaces as parallel as possible. Samples were cut in all three anatomical directions (Fig. 1). The longitudinal direction was chosen to be parallel to the growth direction of the bone, the transverse direction was normal to the bone growth direction, and the radial one was orthogonal to both. Samples were stored in a refrigerator ($T=4\text{ }^{\circ}\text{C}$) until chemical procedure and testing were performed.

2.2. Demineralization process

Bone samples were demineralized (DM) by aging in 0.6 N hydrochloric acid (HCl) at room temperature using the procedures outlined in Toroian et al. [26] and Chen et al. [27]. Although EDTA is frequently used to demineralize bone, we chose HCl because the process is much quicker and has been used successfully in previous works [26–29]. Acid solutions were changed daily. The whole process took 7 days. All solutions were quantitatively analyzed by inductively coupled plasma optical emission spectrometry (ICP-OES) to evaluate

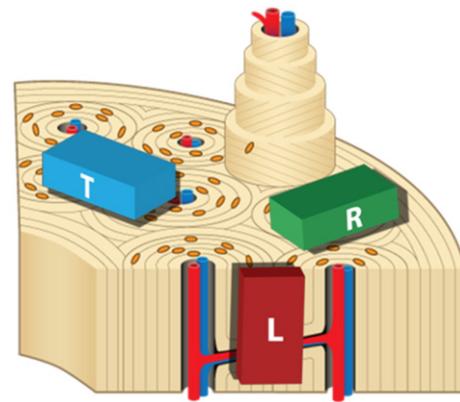


Fig. 1. Sample orientation for the three anatomical directions tested in bovine cortical bone. Samples are not shown to scale. Adapted from Ref. [15].

the Ca concentration. The completeness of demineralization was verified by the Ca absence in the solutions [29].

2.3. Compression testing

Three different sets of samples were prepared: 20 for the each anatomical direction. Specimens from all groups were submerged in Hank's balanced saline solution for 24 hours before testing, and were tested in the hydrated condition. Compression testing of DM samples was performed on universal testing machine equipped with 500 N load cell (Instron 3342 Single Column System, Norwood, MA) at a strain rate of $1\times 10^{-3}\text{ s}^{-1}$. An external deflectometer SATEC model I3540 (Epsilon Technology Corp., Jackson, WY) was used to measure the small samples displacement. Compression testing was performed in loading–unloading conditions: samples were loaded under strain-controlled loading until 1% compressive strain, then unloaded at the same rate until zero stress was reached. Three consecutive cycles up to 1% compressive strain, followed by unloading, were performed in all three anatomical directions. In addition, ten consecutive cycles up to 2% compressive strain were performed for samples in three anatomical directions. The strain levels of 1% and 2% were chosen because they are within the physiological strain region of soft biological tissues [30].

2.4. Structural characterization

Fracture surfaces of the specimens were investigated by scanning electron microscopy (SEM) using FEI-XL30 (FEI Company, Hillsboro, OR). All samples were subjected to critical point drying procedure with a purge time equal to 20 minutes, using the fully automatic critical point drier (Tousimis Autosamdri-815, Rockville, MD) before SEM imaging in order to avoid excessive shrinkage and deformation. For SEM imaging all samples were mounted on aluminum sample holders, and sputter-coated (Emitech K575X, Quorum Technologies Ltd., West Sussex, UK) with iridium for 8 seconds before imaging. Samples were observed at a 10 kV accelerating voltage.

2.5. Statistical analysis

One-way ANOVA analysis was performed to determine significant differences between the data for three anatomical bone directions. The criterion for statistical significance was $p<0.05$.

3. Results and discussion

It was previously shown that bone demineralization produced contiguous, stand-alone structure [26,28]. All microstructural features were well preserved by the demineralization process. Moreover, it

Download English Version:

<https://daneshyari.com/en/article/1428886>

Download Persian Version:

<https://daneshyari.com/article/1428886>

[Daneshyari.com](https://daneshyari.com)