

# Preparation and dielectric properties of $(\text{Sr}_{1-x}\text{Ca}_x)\text{Fe}_{0.5}\text{Nb}_{0.5}\text{O}_3$ ; $(x=0.0, 0.1, 0.2)$ ceramics

Thanatep Phatungthane, Gobwute Rujijanagul\*

Department of Physics and Materials Science, Faculty of Sciences, Chiangmai University, Huaykaw Road, Chiangmai 50200, Thailand

Available online 23 October 2012

## Abstract

In the present work, strontium calcium iron niobate  $(\text{Sr}_{1-x}\text{Ca}_x)\text{Fe}_{0.5}\text{Nb}_{0.5}\text{O}_3$  (SCFN) ( $x=0, 0.1$ , and  $0.2$ ) powders were synthesized for the first time using a molten salt technique. The pure phase perovskite obtained at a relative low calcination temperature of  $800^\circ\text{C}$  was characterized using the X-ray diffraction technique (XRD). SCFN ceramics were fabricated and their properties were investigated. The XRD data of the SCFN ceramics was consistent with an orthorhombic symmetry. However, the solubility of Ca in the SCFN ceramics had an upper limit at  $x=0.1$ . All ceramics showed a large dielectric constants. The Ca doping inhibited grain growth, but produced an improvement in dielectric–temperature stability. Furthermore, the doping reduced loss tangent, especially for the  $x=0.1$  sample. These results suggest that the SCFN ceramics prepared from molten salt synthesis exhibit a good dielectric performances, compared to many high dielectric materials that have been prepared using the conventional method.

© 2012 Elsevier Ltd and Techna Group S.r.l. All rights reserved.

**Keywords:** D. Perovskite; High dielectric; Relaxor

## 1. Introduction

Ceramics with high dielectric constants and giant dielectric constants with a perovskite structure of  $\text{AB}'\text{B}'\text{O}_3$  have been extensively developed due to their potentials for capacitor applications [1,2]. The complex structure  $\text{A}(\text{Fe}_{0.5}\text{B}_{0.5})\text{O}_3$  with  $\text{A}=\text{Sr}, \text{Ca}, \text{Pb}$ ;  $\text{B}=\text{Nb}, \text{Ta}$ , and  $\text{Sb}$  are all perovskite type ceramics which exhibit giant dielectric behavior [1,2]. For example, the ceramic  $\text{Ba}(\text{Fe}_{0.5}\text{Nb}_{0.5})\text{O}_3$  (BFN) exhibits a high value for the dielectric constant ( $\epsilon_r \sim 10^3\text{--}10^4$ ) over a wide range of temperatures [2,3]. BFN was first synthesized via a solid-state reaction by Saha and Sinha in 2002 [4,5]. Since then many authors have focused on the properties of these BFNs. Works from Yokosuka [6], Tezuka et al. [7], Raevski et al. [3], Saha and Sinha [4,5] have shown that the BFN-based ceramics have a relaxor behavior. Furthermore, Shanming et al. demonstrated that the value of  $\epsilon_r$  of the BFN ceramics depend on processing parameter [8].

$\text{Sr}(\text{Fe}_{0.5}\text{Nb}_{0.5})\text{O}_3$  (SFN) is another interesting dielectric material due to its high dielectric constant. The dielectric

properties of the SFN ceramics were first reported by Raevski et al. [3]. These materials have high dielectric constants on the order of  $10^3\text{--}10^4$  over a wide frequency and a broad temperature range [3]. The high dielectric behavior has been interpreted in terms of the Maxwell–Wagner mechanism [3]. SFN ceramics also exhibit a dielectric relaxation behavior, similar to other giant dielectric materials such as  $\text{Ba}(\text{Fe}_{0.5}\text{Nb}_{0.5})\text{O}_3$  and  $\text{Ba}(\text{Fe}_{0.9}\text{Al}_{0.1})\text{Ta}_{0.5}\text{O}_3$  [3–7,9]. The magnetic properties of the SFN at low temperatures (lower than 100 K) were reported by Tezuka et al. [7]. The ferroelectric properties of SFNs could be improved by forming a solid–solution with  $\text{PbTiO}_3$  combined with  $\text{MnO}_2$  or  $\text{Li}_2\text{CO}_3$  doping [10]. However, the effects of doping on the properties of these SFN ceramics have not been widely investigated. Furthermore, it should be noted that most  $\text{A}(\text{Fe}_{0.5}\text{B}_{0.5})\text{O}_3$  ceramics were synthesized using a solid-state reaction method (the conventional method). This method often requires a high calcination temperature which can cause particle coarsening and aggregation of the powders. Therefore, other routes including the sol–gel process, hydrothermal synthesis and molten salt synthesis have been employed produce fine powders [11–13]. Among these methods, molten salt

\*Corresponding author. Tel.: +6653943376; fax: +66533575112.

E-mail address: [rujijanagul@yahoo.com](mailto:rujijanagul@yahoo.com) (G. Rujijanagul).

synthesis is a simple and practical technique with low costs for powder preparation. In the present work, we report the effects of Ca doping on the properties SFN ceramics. The SFN powder and Ca doped SFNs were synthesized via the molten salt synthesis for the first time.

## 2. Experimental

Strontium calcium iron niobate ( $\text{Sr}_{1-x}\text{Ca}_x\text{Fe}_{0.5}\text{Nb}_{0.5}\text{O}_3$ ; ( $x=0.0, 0.1, 0.2$ ) samples were synthesized using the molten salt technique from high purity raw powders of  $\text{SrCO}_3$  (98.0%, Aldrich),  $\text{Fe}_2\text{O}_3$  (99.0%, Aldrich),  $\text{Nb}_2\text{O}_5$  (99.9%, Aldrich), and  $\text{CaCO}_3$  (98.5%, Riedel-de Haën). The raw metal oxide powders were weighed based on the stoichiometric formula of  $(\text{Sr}_{1-x}\text{Ca}_x)\text{Fe}_{0.5}\text{Nb}_{0.5}\text{O}_3$ , then ball milled in alcohol and zirconia milling media for 24 h. The mixture was dried at 110 °C for 12 h. An equal molar ratio of salt mixtures, NaCl (99.5%, Fluka) and KCl (99.5%, Riedel-de Haen) were mixed by hand-grinding for 20 min. The mixed precursors and mixed salts were weighed into a 1:1 ratio. After hand-grinding for 30 min, the obtained powders were calcined at 800 °C for 3 h with a heating rate of 100 °C/h and cooling rate of 300 °C/h. The products were washed with hot deionized water for several times until no trace of anion was detected by  $\text{AgNO}_3$  aqueous solution. The obtained powders were then added with 3% polyvinyl alcohol (PVA) and pressed into disc compact shapes with a diameter of 1.00 cm. These green compacts were then sintered at temperatures ranging from 1300 °C to 1450 °C for 3 h with the same conditions of that of the calcination rate. The phase formation was identified using the X-ray diffraction technique (XRD). The microstructures were then examined using a scanning electron microscope (SEM). To investigate the electrical properties, the sintered ceramic pellets were painted with silver paste on both sides and fired at 600 °C for 15 min. The electrical characteristics were then evaluated using an LCR meter.

## 3. Results and discussion

In the present work, the mixed raw powders were calcined over a temperature range 600–900 °C. Selected XRD patterns of the obtained powders are illustrated in the inset of Fig. 1. The XRD results indicate that the  $x=0.0$ –0.1 samples exhibited a pure perovskites structure at a calcination temperature of 800 °C. Generally, the pure phase of SFN can be synthesized at the calcination temperature of 1200 °C by using the solid-state reaction method [14,15]. Thus, the presence of pure phase SFN at 800 °C in the present work, suggests that the molten salt synthesis method can reduce the calcination temperature by 400 °C.

Fig. 1 also shows the X-ray patterns of the studied ceramics. These XRD results show that the diffraction peaks of the ceramics correspond to an orthorhombic perovskite phase. This result agrees with the work done by

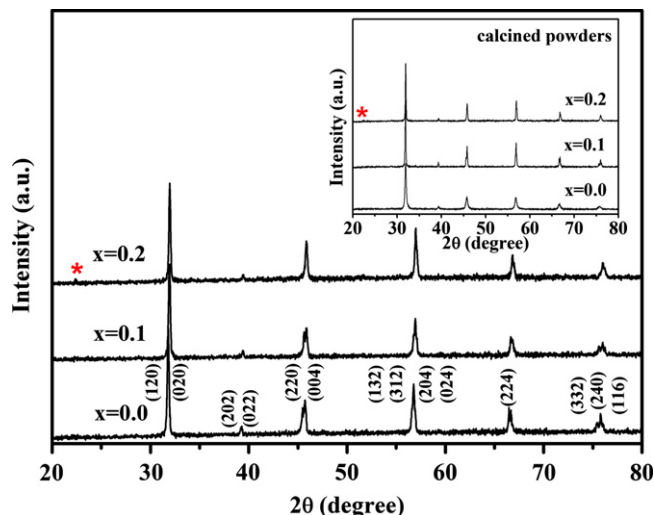


Fig. 1. XRD patterns of  $\text{Sr}_{1-x}\text{Ca}_x\text{Fe}_{0.5}\text{Nb}_{0.5}\text{O}_3$  (SCFN) powders and ceramics.

Liu et al. [15]. The appearance of three main peaks of (332), (240), and (116) with reflections at  $2\theta \sim 75$ – $77^\circ$ , confirms the presence of the orthorhombic phase for the studied samples. However, the three main peaks merged into an ambiguous peak at the higher Ca concentration ( $x=0.2$ ). Furthermore, a pure perovskite phase was observed for  $x \leq 0.1$  samples. Extra impurity peaks were observed and indexed (by \*), as seen in Fig. 1. This second phase was identified as  $\text{Ca}_2\text{FeNbO}_6$  according to the JCPDS file no. 01-089-1442. The appearance of the second phase for the  $x=0.2$  sample, indicates that the solubility of Ca in SFN had a low limit. The unit-cell volume of the samples calculated based on orthorhombic symmetry was found to decrease from 251.22 ( $\text{\AA}^3$ ) for the  $x=0.0$  sample to 249.57 ( $\text{\AA}^3$ ) for the  $x=0.2$  sample. This decrease in unit-cell volume with increasing Ca content indicates an introduction of Ca ions in the SFN lattice. In general, the solubility of a dopant in a lattice depends not only on the charge but also on the radius of the dopant. The charge of  $\text{Ca}^{2+}$  ion is the same as that of  $\text{Sr}^{2+}$  and the radius of the  $\text{Ca}^{2+}$  ion (0.134 nm) is close to that of the  $\text{Sr}^{2+}$  ions (0.144 nm). Therefore, it is possible that partial  $\text{Ca}^{2+}$  ions substituted  $\text{Sr}^{2+}$  ions in the lattice as a result in the decrease of unit-cell volume.

The SEM micrographs of the selected ceramic surfaces are illustrated in Fig. 2. The micro structural analysis revealed that Ca doping result in a change in grain size. Average values of grain size, as calculated by the linear intercept method, decreased from  $\sim 11.1 \mu\text{m}$  for the pure SFN ceramic to  $\sim 6.4 \mu\text{m}$  for the  $x=0.2$  ceramic. This result indicates that the additive inhibits grain growth. This may be due to the low solubility limit of Ca in the SFN lattice, resulting in the formation of the secondary phase which may form at the grain boundaries and prevent grain boundary movement during the sintering process [16].

The dielectric constant and loss tangent as a function of frequency at room temperatures is shown in Fig. 3.

Download English Version:

<https://daneshyari.com/en/article/1461610>

Download Persian Version:

<https://daneshyari.com/article/1461610>

[Daneshyari.com](https://daneshyari.com)