

Temperature–field phase diagrams in  $\text{Pb}(\text{Zn}_{1/3}\text{Nb}_{2/3})\text{O}_3$ –4.5% $\text{PbTiO}_3$  IIMakoto Iwata<sup>a,\*</sup>, Naoya Iijima<sup>a</sup>, Masaki Maeda<sup>a</sup>, Yoshihiro Ishibashi<sup>b</sup><sup>a</sup>Department of Engineering Physics, Electronics and Mechanics, Graduate School of Engineering, Nagoya Institute of Technology, Nagoya 466-8555, Japan<sup>b</sup>Department of Applied Physics, Nagoya University, Nagoya 464-8603, Japan

Available online 23 October 2012

## Abstract

Temperature and field dependences of the dielectric constants under the DC biasing fields along the [011]- and [111]-directions in the cubic coordinate in  $\text{Pb}(\text{Zn}_{1/3}\text{Nb}_{2/3})\text{O}_3$ –4.5% $\text{PbTiO}_3$  were investigated. The temperature–field phase diagrams were constructed in the field range below 10 kV/cm. It was confirmed that in  $\text{Pb}(\text{Zn}_{1/3}\text{Nb}_{2/3})\text{O}_3$ –4.5% $\text{PbTiO}_3$  the intermediate tetragonal phase as a ground state of the system exists even without the DC field, and the tetragonal phase disappears in the external field above 4 and 3 kV/cm along the [011]- and [111]-directions, respectively. The field-induced orthorhombic-phase in the field along the [011]-direction was also found.

© 2012 Elsevier Ltd and Techna Group S.r.l. All rights reserved.

Keywords: PZN; Relaxor; Ferroelectric; Morphotropic phase boundary

## 1. Introduction

It is well known that giant dielectric and piezoelectric responses appear in the vicinity of the morphotropic phase boundary (MPB) of solid solution systems such as  $\text{Pb}(\text{Zn}_{1/3}\text{Nb}_{2/3})\text{O}_3$ – $x\text{PbTiO}_3$  (PZN– $x\text{PT}$ ), where MPB in PZN– $x\text{PT}$  is located at  $x=9\%$  at room temperature [1–3]. Ishibashi and Iwata claimed that such giant responses essentially come from the transversal instability near MPB based on the Landau-type free energy, where the transversal instability is induced by decreasing the anisotropy of the free energy function in the order-parameter space [4]. It was also reported on the basis of first-principles calculations that a similar mechanism works for such a giant response in  $\text{BaTiO}_3$  [5]. The dielectric anisotropy near MPB in PZN– $x\text{PT}$  was experimentally confirmed to show the transversal instability [6]. Physical properties in the MPB region of PZN– $x\text{PT}$  seem to be sensitive to external fields, reflecting the giant dielectric and piezoelectric responses owing to the transversal instability [7–10]. On the other hand, it was discovered by Kutnjak et al. that a critical end point (CEP) appears in the three-dimensional concentration–temperature–field phase diagram in  $\text{Pb}(\text{Mg}_{1/3}\text{Nb}_{2/3})\text{O}_3$ – $x\text{PbTiO}_3$  (PMN– $x\text{PT}$ ); they proposed that the giant electromechanical response in

PMN– $x\text{PT}$  is the manifestation of CEP in addition to MPB [11,12]. It was also experimentally confirmed that CEP exists on the temperature–field phase diagrams in PZN– $x\text{PT}$  and PMN– $x\text{PT}$  [13–17]. A detailed and semi-quantitative analysis of such phase diagrams were presented on the basis of the Landau free energy [18]. These results imply that the essential part of giant dielectric and piezoelectric responses in relaxor ferroelectrics can be explained within the Landau theory.

It was found that a new sharp phase transition at 114 °C below the paraelectric–ferroelectric phase transition point in PZN appears only on zero-field heating (ZFH) after field cooling (FC) process [19–22], implying that decrease of heterogeneity owing to the external field on FC may make the phase transition sharp, which is usually smeared by the complex domain structures such as polar nano-regions (PNRs). We reported a new phase diagram in poled samples of PZN– $x\text{PT}$  (see Fig. 1), and found that the new sharp transition in the poled PZN and the transition at MPB are the same kind, showing that this new transition is the one between the tetragonal and rhombohedral phases [23,24]. Recently, Chang et al. reported the result of the X-ray diffraction study that the tetragonal and rhombohedral phases coexist [25,26]. It seems, however, that the existence of the intermediate tetragonal phase in the low concentration range ( $x < 5\%$ ) of PZN– $x\text{PT}$  is still controversial.

\*Corresponding author.

E-mail address: [miwata@nitech.ac.jp](mailto:miwata@nitech.ac.jp) (M. Iwata).

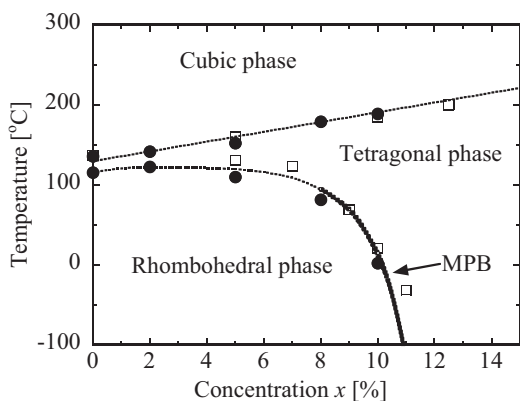


Fig. 1. Phase diagram of the poled sample in PZN- $x$ PT. Open squares and solid circles indicate the phase boundary reported by Kuwata et al. [1] and Iwata et al. [23,24], respectively. The thick curve indicates MPB.

Under these circumstances, in our previous paper, the temperature–field phase diagram under the electric fields along the [001]-direction in the cubic coordinate was clarified, and the existence of the stable tetragonal phase as an average structure in PZN-4.5%PT was experimentally confirmed [27]. In the present paper, we report our experimental results of the DC field dependences of the dielectric constants and the temperature–field phase diagrams with the electric field applied along the [011]- and [111]-directions in the cubic coordinate.

## 2. Experimental

PZN-4.5%PT single crystal plates were acquired from Microfine Technologies in Singapore. The size of the platelike sample is  $3 \times 3 \times 0.2 \text{ mm}^3$  perpendicular to the [011]-, and [111]-directions in the cubic coordinate. For the measurement of the dielectric constant, the sample plates with Au electrodes deposited on their faces were prepared. Measurements of the dielectric constant with and without the DC biasing field were carried out using an impedance/gain phase analyzer (NF ZGA5900), where an AC electric field to measure the dielectric constant is about 25 V/cm. The maximum value of the DC biasing voltage to the sample during measurement is 800 V. Complex dielectric constants were obtained at 41 frequencies in the range from 100 Hz to 1 MHz.

## 3. Results

In order to construct the temperature–field phase diagrams with the electric field applied along the [011]- and [111]-directions in PZN-4.5%PT, we measured the dielectric constant by the two methods; one is the temperature dependence of the dielectric constant under a certain biasing field, and the other is the field dependence of that under a constant temperature.

### 3.1. Dielectric constant along [011]-direction

Fig. 2 shows a typical result of temperature dependence of the dielectric constants on cooling under the DC biasing field

of 2.0 kV/cm along the [011]-direction in the cubic coordinate in PZN-4.5%PT. It is seen that three dielectric anomalies appear at 152.6, 118.1, and 77.3 °C with no significant dispersion. These phases are assigned to be the cubic, tetragonal, orthorhombic, and rhombohedral phases from the high temperature side. The electric field dependence of the dielectric constant at 128.8 °C is presented in Fig. 3 as a typical result. A sharp peak is found at 2.83 kV/cm, implying the field induced tetragonal–orthorhombic phase transition.

On the basis of our experimental results, the temperature–field phase diagram with the electric field applied along the [011]-direction in PZN-4.5%PT was obtained as shown in Fig. 4, where open and solid circles indicate the transition points on heating and cooling measurements, and upward and downward triangles show measurements of those on the field increasing and decreasing, respectively. The solid upward triangles present the dielectric anomaly points due to the polarization reversal on the field increasing measurement.

### 3.2. Dielectric constant along [111]-direction

Fig. 5 shows temperature dependences of the dielectric constants on cooling under the DC biasing field of 0.8 kV/cm

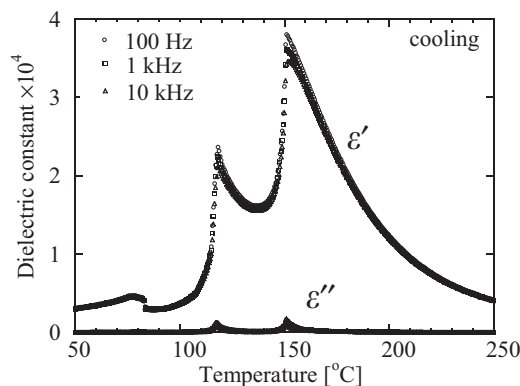


Fig. 2. Temperature dependence of the dielectric constant under the DC biasing field of 2.0 kV/cm along the [011]-direction in PZN-4.5%PT.

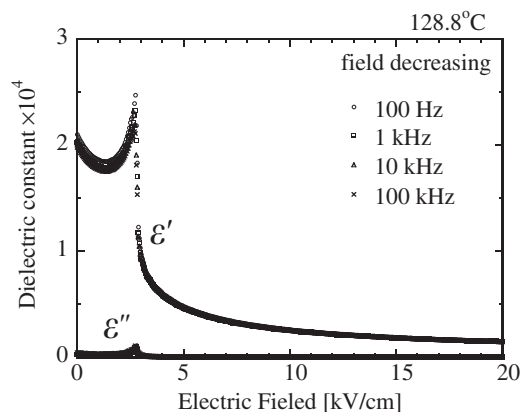


Fig. 3. Electric field dependence of the dielectric constant along the [011]-direction at 128.8 °C in PZN-4.5%PT.

Download English Version:

<https://daneshyari.com/en/article/1461616>

Download Persian Version:

<https://daneshyari.com/article/1461616>

[Daneshyari.com](https://daneshyari.com)