

Microwave sintering and grain growth behavior of nano-grained BaTiO₃ materials

Cheng-Sao Chen^{a,*}, Pin-Yi Chen^b, Chen-Chia Chou^c, Chang-Shun Chen^a

^a Department of Mechanical Engineering, Hwa-Hsia Institute of Technology, Taipei 235, Taiwan, ROC

^b Department of Mechanical Engineering, Ming-Chi University of Technology, Taipei 243, Taiwan, ROC

^c Department of Mechanical Engineering, National Taiwan University of Science and Technology, Taipei 106, Taiwan, ROC

Available online 30 April 2011

Abstract

In this paper, we investigated the effect of microwave sintering parameters on the development of the microstructure of nano-grained BaTiO₃ materials co-doped with Y and Mg species. It is observed that the materials can not only be sintered densely at a lower temperature (1150 °C) and a shorter soaking time (20 min), but also the grain growth can be suppressed by 2.45 GHz microwave heating process. However, the grain growth exhibits a unique tendency in some processing conditions such as microwave sintering for longer intervals (≥ 60 min) or at higher temperatures (1200 °C). The grain growth behavior after densification was investigated in terms of the phenomenological kinetics, and the activation energy for grain growth using microwave sintering (59.4 kJ/mol) is considerably less than that of the conventionally sintered ones (96.0 kJ/mol), which indicates that microwave sintering process can accelerate the densification rate of the BaTiO₃ materials comparing with the conventional sintering process.

© 2011 Elsevier Ltd and Techna Group S.r.l. All rights reserved.

Keywords: A. Grain growth; A. Microwave processing; B. Microstructure-final; D. BaTiO₃ and titanates

1. Introduction

Barium titanate (BaTiO₃)-based ceramics have attracted much interest and have received a favorable review, both from fundamental and from applied aspects, such as multilayer ceramic capacitors (MLCCs) and positive temperature coefficient resistors (PTCRs) etc. [1]. Pure BaTiO₃ is a typical ferroelectric material with high dielectric constant ($k \sim 10000$). Its dielectric properties can be modified by adding either acceptor or donor dopants. For instance, BaTiO₃ can co-doped with abundant Y₂O₃ and MgO species to achieve high temperature stability of dielectric constant for X7R type MLCCs applications [2,3]. With the miniaturization of MLCCs, however, high dielectric constant material with fine grains is required for thinner dielectric layer to achieve large-capacitance MLCCs with small size, and that also to improve the DC degradation and voltage breakdown strength [4]. In view of this, a sintering process which can effectively densify

the materials without inducing the growth of grains is thus demanded. Previously, many materials have been successfully sintered and fine grain size, uniform microstructure and significant energy savings were achieved by microwave sintering [3,5–7]. The advantages of microwave sintering were not only found to include higher energy efficiency, higher post sintering density and low sintering temperatures, but also reduced activation energy compared to conventional sintering [7]. At present, there are only few reports concerning the densification of BaTiO₃-based materials by using microwave sintering [3,8]. In this paper, therefore, microwave-sintering technique was adopted to densify the nano-grained BaTiO₃ materials co-doped with Y and Mg species. The effect of processing parameters on the densification behavior and the related microstructural characteristics of these BaTiO₃ materials were examined. The results were compared to that obtained by conventional sintering process.

2. Experimental procedures

Commercial BaTiO₃ (the particle size is of about 70 nm, TPL Inc, USA) were used as starting materials. Co-doped with

* Corresponding author. Tel.: +886 2 89415129x2125; fax: +886 2 29436521.

E-mail address: rickchen@cc.hwh.edu.tw (C.-S. Chen).

3 mol% yttrium nitrate ($Y(NO_3)_3 \cdot 6H_2O$) and 2 mol% magnesium acetate ($Mg(CH_3COO)_2 \cdot 4H_2O$) by chemically precipitated coating method [9]. The co-precipitated powder was mixed with 3 mol% sintering aids ($Ba_{0.6}Ca_{0.4}SiO_3$), which has stronger microwave absorptivity and does not induce marked grain growth of the $BaTiO_3$ materials [10], by ball-milling for 24 h and dried. After being calcined at 950 °C for 2 h, the as-calcined mixtures were ball-milled again for 10 min by an attritor. The mixtures were pressed at about 50 MPa into pellets using a die with 10 mm diameter and then sintered at 950–1200 °C for 0.1–30 min in a CEM MAX-7000 microwave furnace (MS series), using 2.45 GHz microwaves generated from a commercial source. The temperature profile was measured using Pt–13%Rh thermocouples placed near the sample surface. The heating rate and the cooling rate were 30 °C/min. For comparison, samples were also prepared by a conventional sintering process (CS series), that is, sintering at 1100–1250 °C for 2 h in an electrical furnace. The heating rate and the cooling rate were 10 °C/min.

The sintered density was measured using Archimedes' method. The average grain size, G , as described by Mendelson [11], is obtained as $G = 1.56L$, where L is the average grain-boundary intercept length of a series of random lines on the micrographs. In microstructural analysis, a scanning electron microscopy (SEM, Jeol 6500F) was employed to examine microstructural characteristics.

3. Results and discussion

Microwave sintering process can densify the nano-grained $BaTiO_3$ materials very efficiently. Fig. 1(a) shows that the relative density of the samples already reach 90%T.D. (theoretical density) by microwave sintering the materials at 1100 °C for 20 min. The density of the samples increases gradually with the sintering temperature, reaching 96%T.D., for 1200 °C sintered ones. Furthermore, Fig. 1(b) shows that the density of the 1150 °C-sintered samples for various soaking time. The density of the samples rises gradually with the soaking time and reaches a maximum value, 95.5%T.D., at soaking time in the 20–30 min.

To further understand how the different sintering processes influence the densification behavior of the $BaTiO_3$ materials, the samples are sintered using an electrical furnace. Fig. 2 shows a comparison of relationships between the relative density and the sintering temperature of $BaTiO_3$ materials using microwave (MS) and conventional sintering (CS) process. It reveals that, at the same sintering temperature, the density of the MS samples is much higher than that of the CS samples. Furthermore, it is evident that it needed only 1100 °C to densify the $BaTiO_3$ materials to a density of 92.5%T.D., whereas it required at least 1200 °C to reach the same density for $BaTiO_3$ materials using conventional sintering. This indicates that the microwave sintering process is more easy to achieve higher densification at lower temperature. Besides, it is noticed that the density of the samples microwave sintered for only 20 min (refer MS-20 curve) is superior to that of the samples conventionally sintered for 2 h when the sintering temperature

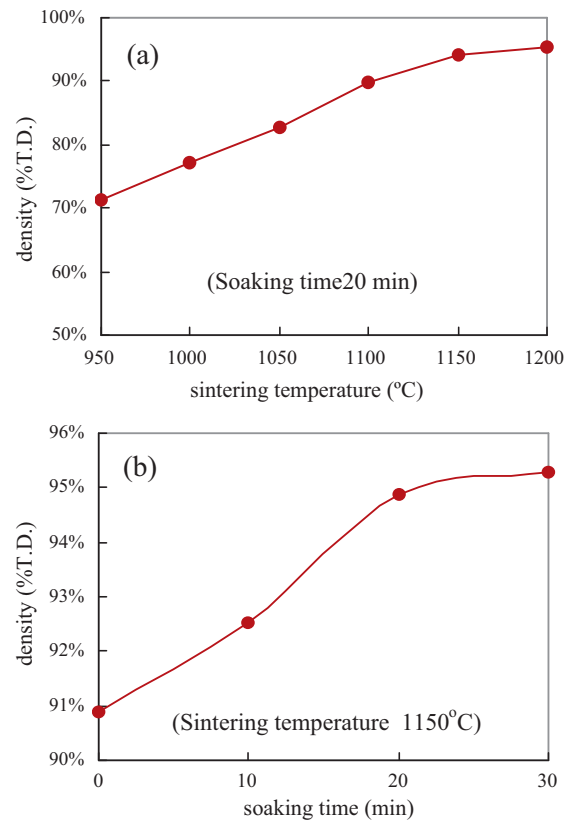


Fig. 1. Effect of (a) sintering temperature and (b) soaking time on the densification behavior of microwave-sintered $BaTiO_3$ materials which were co-doped with 3 mol% Y and 2 mol% Mg species.

is the same. For example, at 1200 °C, the density of the $BaTiO_3$ materials for microwave and conventional sintering processes are found to be 96%T.D. and 92%T.D., respectively. The result implies that the microwave sintering process substantially enhances the densification rate of $BaTiO_3$ materials such that the sintering time needed is markedly shortened.

SEM micrograph shown Fig. 3(a) indicates that, typically, the MS samples contain very fine grains and the grain size

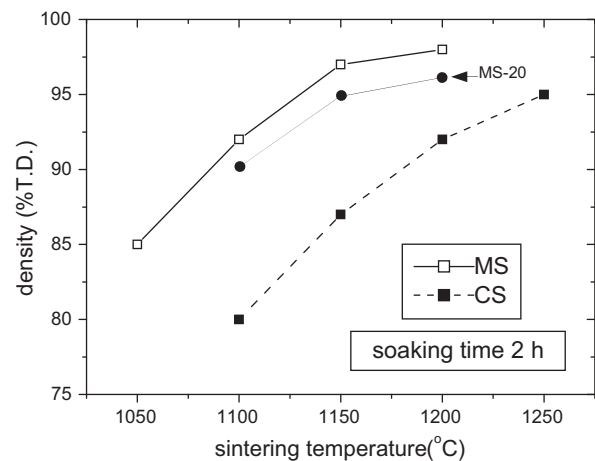


Fig. 2. Relative density as a function of sintering temperature of microwave-sintered (MS) and conventionally sintered (CS) $BaTiO_3$ materials which were co-doped with 3 mol% Y and 2 mol% Mg species materials (MS & CS: soaking time of sintering is 2 h; MS-20: soaking time of sintering is 20 min).

Download English Version:

<https://daneshyari.com/en/article/1462045>

Download Persian Version:

<https://daneshyari.com/article/1462045>

[Daneshyari.com](https://daneshyari.com)