

Effects of K nonstoichiometry in bismuth layer-structured $\text{K}_{0.5+x}\text{Bi}_{4.5}\text{Ti}_4\text{O}_{15}$ ceramics

T.H. Lee^a, Y.S. Sung^a, J.H. Cho^a, T.K. Song^a, M.H. Kim^{a,*}, T.G. Park^b, H.G. Cho^c

^a School of Nano & Advanced Materials Engineering, Changwon National University, Changwon, Gyeongnam 641-773, Republic of Korea

^b Department of Electrical Engineering, Changwon National University, Changwon, Gyeongnam 641-773, Republic of Korea

^c Advanced Material & Application Research Division, Korea Electrotechnology Research Institute, Changwon, Gyeongnam 642-120, Republic of Korea

Available online 12 May 2011

Abstract

The effects of K nonstoichiometry on phase formation, grain morphology, dielectric and piezoelectric properties of $\text{K}_{0.5+x}\text{Bi}_{4.5}\text{Ti}_4\text{O}_{15}$ (KBT) were studied in the range of excess up to +2 mol% and deficient down to −8 mol% of $\text{K}_{0.5}$. The relative densities of the sintered KBT ceramics with various K contents prepared by a solid state reaction method were all higher than 95%. In all samples, a bismuth layer-structured phase was confirmed, although a secondary phase appeared as K deficiency became larger than −6 mol%. Piezoelectric coefficient (d_{33}) increased, showing a high of 16 pC/N at $x = -3$ mol%, and then decreased with further K deficiency while Curie temperature (T_C) decreased showing a low of 540 °C at $x = -8$ mol% from 551 °C at $x = 0$ mol%. Mechanical quality factor (Q_m) of all samples was in the range of 900–1860.

© 2011 Elsevier Ltd and Techna Group S.r.l. All rights reserved.

Keywords: C. Piezoelectric properties; Bismuth layer-structured ferroelectrics; KBT; Nonstoichiometry

1. Introduction

Pb containing perovskites such as PbTiO_3 – PbZrO_3 (PZT), $\text{Pb}(\text{Mg}_{1/3}\text{Nb}_{2/3})\text{O}_3$ – PbTiO_3 (PMN-PT), and $\text{Pb}(\text{Zn}_{1/3}\text{Nb}_{2/3})\text{O}_3$ – PbTiO_3 (PZN-PT) have been the materials used for various ferroelectric and piezoelectric applications [1]. However, the use of Pb-based ceramics has caused serious human health and environmental problems due to the PbO vaporization during processing and the waste from products containing Pb. Those problems can only be resolved by banning Pb containing ceramics. It is, therefore, necessary to develop health and environment friendly Pb-free piezoelectric materials with compatible properties to those of Pb-based ceramics [2,3].

The Aurivillius family of bismuth (Bi) layer-structured ferroelectrics (BLSF) such as $\text{SrBi}_2\text{Ta}_2\text{O}_9$, $\text{Bi}_4\text{Ti}_3\text{O}_{12}$, $\text{Na}_{0.5}\text{Bi}_{4.5}\text{Ti}_4\text{O}_{15}$, $\text{SrBi}_4\text{Ti}_4\text{O}_{15}$, and $\text{CaBi}_4\text{Ti}_4\text{O}_{15}$ has been intensively studied [4–7], because they are potential candidates for piezoelectric and pyroelectric sensor applications requiring large anisotropy and stability at high working temperature. The structural formula of BLSF is generally described as $(\text{Bi}_2\text{O}_2)^+$

layers and $(\text{A}_{m-1}\text{B}_m\text{O}_{3m+1})^{2-}$ perovskite layers. A is a mono-, di-, or tri-valent cation (Na^+ , K^+ , Ba^{2+} , Ca^{2+} , Sr^{2+} , Bi^{3+} , etc.) and B is a transition element (Ti^{4+} , Nb^{5+} , Ta^{5+} , W^{6+} , etc.). Various combinations of cations are also allowed and m is usually from 1 to 5, indicating a number of perovskite layers sandwiched between the $(\text{Bi}_2\text{O}_2)^+$ layers.

A well-known merit of BLSF materials over other lead-free materials is that they are suitable for resonators especially at high frequency and temperature utilizing high mechanical quality factor (Q_m) in piezoelectric device applications. However, piezoelectric coefficients (d_{33}) of typical BLSF ceramics are relatively very low, usually under 20 pC/N. To improve piezoelectric d_{33} , various special processing techniques, such as template grain growth (TGG) and hot-forging (HF) have been applied to improve orientation and density. Some improvements have been obtained, but those unconventional processing techniques are not practical for production. Another approach for high d_{33} is a conventional one, controlling composition via extrinsic doping, substitution, and addition [8–11] of foreign components.

$\text{K}_{0.5}\text{Bi}_{4.5}\text{Ti}_4\text{O}_{15}$ (KBT) was first fabricated in the 1960s by Subbarao. It was reported to be difficult to achieve dense ceramics by conventional sintering until Wang et al. successfully prepared a dense KBT compound by ordinary firing [12].

* Corresponding author. Tel.: +82 55 213 3711; fax: +82 55 262 6486.

E-mail address: mhkim@changwon.ac.kr (M.H. Kim).

It is still not easy to obtain dense ceramics because of their highly anisotropic crystal shape ($a \sim b \sim 5.4 \text{ \AA}$, $c \sim 41.2 \text{ \AA}$ for $m = 4$). In addition, potassium carbonate (K_2CO_3), a typical raw powder for K component, is very hygroscopic and bismuth oxide (Bi_2O_3) is known to be volatile during processing. Therefore, KBT ceramics can easily off-stoichiometric from the beginning of powder processing unless suitably handled. Nevertheless, compositions of KBT ceramics are often assumed to be stoichiometric. In order to clarify any intrinsic effects of compositional variation in K content in KBT ceramics, the effects of K nonstoichiometry on phase formation, grain morphology, dielectric and piezoelectric properties were investigated in this study.

2. Experimental

KBT ceramics with K nonstoichiometry, $\text{K}_{0.5+x}\text{Bi}_{4.5}\text{Ti}_4\text{O}_{15}$, were prepared by a conventional solid state reaction method. The starting raw materials used were Bi_2O_3 (Aldrich, 99.9%), K_2CO_3 (Aldrich, 99.995%), and TiO_2 (Aldrich, 99.9%). Hygroscopic K_2CO_3 powder was thoroughly dried at 200°C for 2 h in a dry oven, and then weighed in a glove box. The compositions of samples were controlled to be $x = -8$ to $+2$ mol% of $\text{K}_{0.5}$. The weighed powders were wet milled with yttria-stabilized zirconia balls in anhydrous ethanol for 2 h. After milling, the powders were calcined first at 780°C , then 800°C , for 2 h in air with an intermediate milling and drying to make homogeneous powders. The twice calcined powders were mixed with polyvinylalcohol (PVA) binder, and then pressed to pellets of 10 or 18 mm in diameter and ~ 1 mm in thickness at a uniaxial pressure of 150 MPa. The pellets were covered with sacrificial powders of the same compositions and sintered in an Al_2O_3 crucible with a lid at 1120°C for 2 h in air.

The X-ray diffraction (XRD) patterns for the ceramic powders were obtained using an X-ray diffractometer (X'pert MPD 3040 system, Philips, Netherlands) with $\text{Cu K}\alpha$ radiation. It is not easy to take an accurate measurement because diffractometers always have systematic and random errors such as misalignment of the instrument and displacement of the specimen. Therefore, 5 N (99.999%) silicon powder (Alfa Aesar, USA) was used as an internal standard to calibrate XRD patterns from those errors. The microstructure of the sintered ceramics was inspected using a scanning electron microscope (SEM, JMS-5610, Jeol, Japan). For the measurement of dielectric and piezoelectric properties, both sides of pellets were polished down to 0.4 mm in thickness and painted with Ag paste then fired at 650°C for 0.5 h in air. The specimens were poled in silicone oil at 120°C under a dc field from 7.5 kV/mm and field-cooled to room temperature for 0.5 h. Temperature dependence of dielectric constant (ϵ) and loss tangent ($\tan \delta$) was measured using an impedance analyzer (4192A, Agilent Technologies, USA) in the temperature range from room temperature to 650°C . Composition dependence of d_{33} was measured at room temperature using a piezo- d_{33} meter (ZJ-6B, IACAS, China). Electromechanical coupling factor (K_p) and mechanical quality factor (Q_m) were calculated from resonant and antiresonant frequencies and capacitances measured at

1 kHz using an impedance analyzer (4194A, Agilent Technologies, USA).

3. Results and discussion

The changes incurred in weight loss by sintering were below 1 wt% in all samples, resulting mostly from PVA burning and moisture evaporation. The relative apparent densities of KBT ceramics were all higher than 95% after sintering. XRD patterns of KBT ceramics are shown in Fig. 1. The formation of a bismuth layer-structured phase with $m = 4$ was identified by analyzing XRD patterns. The intensity of (1 1 9) diffraction peak was the highest among the peaks in the XRD patterns. This is consistent with the report that the most intense reflection of BLSF occurs at the type of $(112m + 1)$ [13]. This bismuth layer-structured phase was maintained at all compositions but a secondary phase started forming in the samples with K deficiency over than -6 mol%. Fig. 2 shows SEM images of the KBT ceramics with various $x = -8$ to $+2$ mol%. Due to highly anisotropic shape of KBT crystal, grains grew plate-like but grain sizes did not appear to be changed much with x . In other words, in terms of grain shape and size, KBT ceramics were not much influenced by K nonstoichiometry within the range of $x = -8$ to $+2$ mol%.

Fig. 3 shows ϵ and $\tan \delta$ of the KBT ceramics measured at 100 kHz as a function of temperature. Dielectric peaks occurring above 540°C corresponded to the Curie temperature (T_C), which decreased with K deficiency from 551°C at $x = 0$ mol% to 540°C at $x = -8$ mol%. Considering dielectric properties of BLSF materials, distortion of oxygen octahedra [14] that could occur by K nonstoichiometry would be a cause for the decrease from the nominally stoichiometric sample. Similar relations between T_C and lattice distortion were observed in PZT [15] and Bi-based titanate ceramics [8,9]. Note $\tan \delta$ was quite low especially below 350°C . In other words, there was not much variation in either ϵ or $\tan \delta$ in the temperature range of 30 – 350°C indicating temperature stability of KBT ceramics.

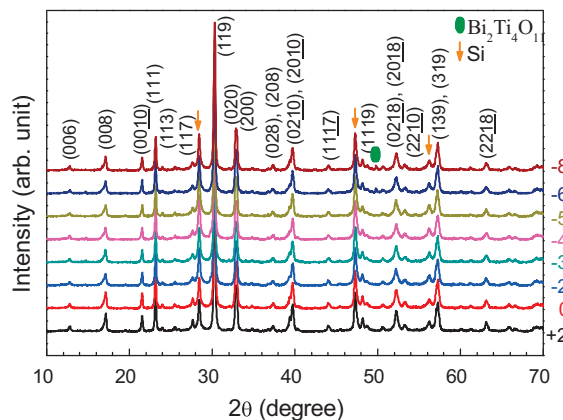


Fig. 1. XRD patterns of $\text{K}_{0.5+x}\text{Bi}_{4.5}\text{Ti}_4\text{O}_{15}$ ceramics with various x after sintering at 1120°C for 2 h in air. In all samples, a bismuth layer-structured phase was formed. Indicated as arrows were peaks from 5 N Si used as an internal standard. An impurity phase $\text{Bi}_2\text{Ti}_4\text{O}_{11}$ was also shown.

Download English Version:

<https://daneshyari.com/en/article/1462097>

Download Persian Version:

<https://daneshyari.com/article/1462097>

[Daneshyari.com](https://daneshyari.com)