

In situ TEM observation of crack propagation in LiTaO₃ particle toughened Al₂O₃ ceramics

Y.G. Liu^a, D.C. Jia^b, Y. Zhou^b, M.H. Fang^a, Z.H. Huang^{a,*}

^a School of Materials Science and Technology, China University of Geosciences (Beijing), Beijing 100083, PR China

^b School of Materials Science and Engineering, Harbin Institute of Technology, Harbin 150001, PR China

Received 28 May 2010; received in revised form 6 August 2010; accepted 4 October 2010

Available online 28 October 2010

Abstract

Direct observation of crack propagation in LiTaO₃/Al₂O₃ composite ceramics was carried out using *in situ* transmission electron microscopy (TEM). Domain switching induced by crack propagation, crack deflection and branching at domain boundaries and ripples similar to the contrasts of 180° domains at the microcrack tip inside LiTaO₃ grains were detected evidently. Domain switching, crack deflection, branching and energy dissipation resulting from the formation of contrasts similar to the 180° domains at the microcrack tip, were proposed as the toughening mechanisms in LiTaO₃/Al₂O₃ ceramics.

© 2010 Elsevier Ltd and Techna Group S.r.l. All rights reserved.

Keywords: LiTaO₃/Al₂O₃ composite ceramics; Crack propagation; Domain switching; Toughening mechanism; Transmission electron microscopy (TEM)

1. Introduction

For advanced ceramics, a series of toughening approaches has been proposed and developed [1–13]. Recently, a new approach for the toughening of ceramics, in which a piezoelectric secondary phase was incorporated into the matrix ceramic, was proposed [14–23]. For example, BaTiO₃/Al₂O₃ [14], Nd₂Ti₂O₇/Al₂O₃ [15], Sr₂Nb₂O₇/3Y-TZP [16], LiTaO₃/Al₂O₃ [17–19], Nd₂Ti₂O₇/8Y-FSZ [20], PZT/glass [21] and BaTiO₃/MgO [22,23] have been found to exhibit improved mechanical properties. It was suggested that the toughening was achieved through energy dissipation due to the piezoelectric effect or/and domain switching [14–21]. However, toughening mechanisms in ceramics with the piezoelectric second phase have not been experimentally determined overall.

The Vickers indentation technique is commonly used to study the fracture toughness resistance of materials. But, since the domain size of piezoelectric ceramics ranges from nanometers to micrometers [24], and the fracture process zone is limited to a few micrometers for most ceramics, transmission electron microscopy (TEM) would be an ideal technique for

observation purposes. *In situ* TEM observation on crack propagation paths is often adopted to investigate the fracture resistance of metal materials, but has seldom been used for that of ceramics due to its brittleness. On the basis of our previous investigations [17–19], in this paper, *in situ* TEM observation was employed to examine crack propagation in Al₂O₃ ceramics with the LiTaO₃ piezoelectric second phase. Toughening mechanisms of the composite have been illustrated experimentally.

2. Experimental

Commercially available alumina, Al₂O₃, powder (High Tech Ceramic Institute, Beijing, China) and lithium tantalate, LiTaO₃, powder (Dongfang Tantalum Joint-stock Corporation, Ningxia, China) were used as the starting powders. The average particle sizes of Al₂O₃ and LiTaO₃ powders were ~0.3 μm and 3.0 μm, respectively. The amount of LiTaO₃ was 15 vol%. Al₂O₃ and LiTaO₃ were weighed accurately and then ball milled for 24 h with Al₂O₃ balls. Ethanol was used as a medium for the ball milling. The slurry was stirred and dried slowly to remove the ethanol. The sintering was performed by hot pressing at 1300 °C with a graphite die for 90 min under a pressure of 25 MPa in a vacuum atmosphere.

In situ TEM observation was carried out to study the crack propagation paths in the composite. The sintered specimens

* Corresponding author. Tel.: +86 10 82322186; fax: +86 10 82322186.

E-mail address: huang118@cugb.edu.cn (Z.H. Huang).

were sliced to 0.5 mm in thickness and polished down to less than 30 μm using 600# SiC abrasives. The thin foil specimens were then cut to 3 mm in width and 5 mm in length and prepared by ion beam thinning at 6 kV, and then examined using TEM (TECNAI 20) at an accelerated voltage of 120 kV and under a slowly increased tensile load [25,26].

3. Results and discussion

In our previous study [18], co-existent $\text{LiTaO}_3/\text{Al}_2\text{O}_3$ (denoted as LTA) ceramic composites with high density of more than 99.5% were prepared by hot pressing at 1300 °C. It was found that the fracture toughness of the composites containing 15 vol% LiTaO_3 (denoted as 15LTA) particles was improved over that of monolithic Al_2O_3 . That is to say, weak LiTaO_3 particles have toughening effects on Al_2O_3 ceramics. An observation on the indentation crack propagation paths showed that the crack penetrated into the LiTaO_3 particles and particle debonding or pullout was negligible. The crack did not propagate in an undisturbed manner but produced large deflection through the LiTaO_3 particles. SEM observation showed that many steps, strips and layers or river patterns, which were all in the size of the domains, were observed on the fracture surface of the LiTaO_3 particles in the Al_2O_3 matrix [27]. It is ascertained that the intrinsic microstructure of LiTaO_3 particles should be helpful to counteract the crack growing.

A visible phenomenon was detected during *in situ* TEM observation on the crack propagation in LiTaO_3 grains. It was found that several 90° domains similar to daggers were produced on both sides of the crack growing path, as shown in Fig. 1. The crack growing direction is indicated by a white arrow in the figure. These domains were less than 0.1 μm in length. It is well known that domains in ferroelectric ceramics can be switched either by an electric field or by a mechanical stress [28–30]. When the crack propagates, high stress concentration will be caused at the crack tip. When the total stress concentration reaches the threshold for the domain to switch, domain switching will occur. In fact, domain switching is a process of nucleating, growing and amalgamating of new domains. According to the location and the shape of the domains in Fig. 1, they seemed to be domain nuclei of domain

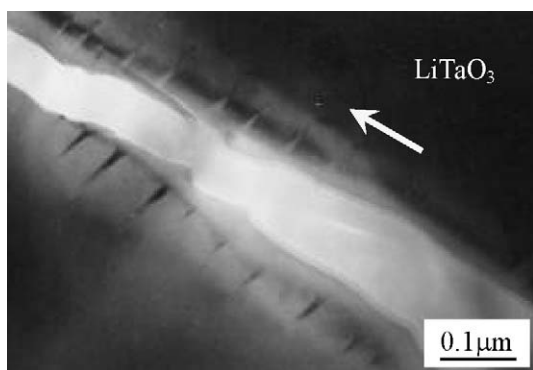


Fig. 1. TEM micrographs of domain nuclei located along a crack due to domain switching caused by crack propagation in LiTaO_3 grains.

switching caused by crack propagation. It was found that these domain nuclei did not grow into bigger domains. For pure ferroelectric ceramics, domain switching induced by an electric field or mechanical stress has been widely investigated both theoretically and experimentally. But, direct observation on domain switching by crack propagation in ceramic composites with a ferroelectric second phase has seldom been reported to date. This study provides direct experimental evidence for 90° domain switching caused by crack growing in Al_2O_3 ceramics with a LiTaO_3 second phase.

It was confirmed by *in situ* TEM observation [27] that deflections and branching both occurred at the boundaries of the 90° domains. That is to say, the domain boundary was in favor of crack propagation because of its high energy. In this study, various crack deflections at the domains in the composite were detected, as shown in Fig. 2. Crack deflections of about 90° in Fig. 2(a) produced at the other domain boundary occurred after cutting across the domain. This is different in Fig. 2(b) and (c), where the cracks produced deflections of less than 90° at the former domain boundary and then grew into the domain and continued to extend. When the cracks reached the other domain boundary, they produced another deflection of less than 90° and then developed along the other domain boundary or another domain boundary entirely. Crack branching was also observed in Fig. 2(b). A crack deflection with a large angle of more than 90° occurred in Fig. 2(d). The propagating crack cut across the domain and reached the interface between the LiTaO_3 and Al_2O_3 grains. But the crack did not continue to propagate along the interface between them. Instead, it produced a deflection at an angle of more than 90° and then developed along another domain boundary entirely. This result indicated that the domain boundary assisted crack propagation more than the interface between the LiTaO_3 and Al_2O_3 grains. It was concluded that the domain structures in the LiTaO_3 grains greatly affected the crack development.

Besides crack deflection and branching, several ripples were produced at or near the crack tips [18]. It can be seen from Fig. 3 that mass ripples were induced right before or on one side of the microcrack tip and extended for a long distance, as indicated by the white arrows. It seemed that these ripples had regular intervals and were different from stacking dislocations often observed in the study on metal ductile materials. The stacking dislocations have smaller intervals near the crack tip and larger intervals far from the crack tip. *In situ* TEM observation showed that it was common for the propagating crack in the LiTaO_3 grains in the as-hot-pressed LTA ceramic composite to cause ripples ahead of it. From the observation, these ripples were similar to contrasts of the 180° domains. According to the previous studies [31], mechanical stress can only produce 90° domain switching. 180° domain switching is irrelevant of stress and activated only by an electric field. It remains to be seen whether these ripples are also contrasts of other domain structures.

Domain switching under an electric field or/and a mechanical field in ferroelectric ceramics has been widely studied for ferroelectric materials. It is reported that polarization switching occurs only when a switching criterion is satisfied [31]. That is to say, there exists a threshold energy for

Download English Version:

<https://daneshyari.com/en/article/1462602>

Download Persian Version:

<https://daneshyari.com/article/1462602>

[Daneshyari.com](https://daneshyari.com)