

Short communication

## Co-firing behavior of ZnTiO<sub>3</sub> dielectric ceramics/Ag composites for MLCCs

Chunlin Miao<sup>a</sup>, Mao Wang<sup>a</sup>, Zhenxing Yue<sup>a</sup>, Ji Zhou<sup>a,\*</sup>, Qi Li<sup>b</sup>

<sup>a</sup> State Key Laboratory of New Ceramics and Fine Processing, Department of Material Science and Engineering, Tsinghua University, Beijing 100084, China

<sup>b</sup> Department of Materials Science and Engineering, University of Illinois at Urbana-Champaign, Urbana, IL 61801, USA

Received 30 August 2004; received in revised form 7 February 2005; accepted 15 March 2005  
Available online 8 June 2005

### Abstract

Ag is frequently used as an internal electrode in multilayer ceramic capacitors (MLCCs). Controlling the co-firing process and interface between the electrode and ceramic is of great importance to obtain highly reliable MLCCs. In this paper, the sintering behavior of the co-firing system of ZnTiO<sub>3</sub> dielectric and Ag internal electrode material is studied. Chemical reaction, interfacial microstructure and inter-diffusion are discussed, respectively, based on XRD, SEM and EDS analysis. It is shown that the introduction of Ag can affect the dielectric properties of the ceramic matrix heavily based on dielectric property measurements.

© 2005 Elsevier Ltd and Techna Group S.r.l. All rights reserved.

**Keywords:** B. Interfaces; C. Diffusion; Dielectrics; ZnTiO<sub>3</sub>; Microstructure; Co-firing

### 1. Introduction

Current trends towards smaller size, better performance, higher reliability and lower cost have led to a revolution on manufacturing techniques of multilayer ceramic capacitors (MLCCs) based on advanced tape-casting and surface mounting technologies, which is characterized by the development of MLCCs with base metal internal electrode and thinner dielectric layers [1].

MLCCs, with alternative ceramic layers and electrode layers, may include many defects, such as delaminations, cracks, and holes. Interfacial inter-diffusions as well as chemical reactions would inevitably exist, caused by unsuitable sintering processes and structural design [2–4]. Great efforts have been made to optimize the sintering process and adjust the dielectric ceramic composition, which are considered as two key processes for acquiring advanced MLCC components with high quality and reliability. Unfortunately, the effect of interaction between the internal

electrode and the dielectric ceramic layers on the component properties has not yet been fully understood.

ZnTiO<sub>3</sub>, with relatively low sintering temperature (below 945 °C) and good dielectric properties, have been considered as a suitable candidate for low-temperature co-firing compatibility [5–7]. In this paper, we investigated the co-firing compatibilities of ZnTiO<sub>3</sub> dielectric and Ag. The effect of diffusion of Ag addition on the co-firing step, electrical and dielectric properties is also discussed.

### 2. Experimental procedure

ZnTiO<sub>3</sub> was prepared by solid-state reaction method with the chemical reagent powders of ZnO and TiO<sub>2</sub>. In order to investigate the effect of Ag on the co-firing behavior, ZnTiO<sub>3</sub> powder was mixed with different amount of Ag powder and ball milled for 24 h so as to get uniform mixture. Appropriate amount of B–Pb glass (3 wt.%) was introduced into ZnTiO<sub>3</sub> as sintering aids to improve the densification. The ground powder mixture was dried and finally pressed into discs (10 mm in diameter and 1.5 mm thick) and pellet

\* Corresponding author. Tel.: +86 10 62772975; fax: +86 10 62772975.  
E-mail address: zhouji@mail.tsinghua.edu.cn (J. Zhou).

samples. The composite samples were sintered at 900 °C for 4 h for microstructure and electrical property measurements.

Phase identification on the sintered discs was performed using X-ray diffraction (XRD, Model D/max-RB, Rigaku, Japan). The microstructure and element diffusion at the interface of silver/ceramic composites were examined by a scanning electron microscopy (SEM, Model JEOL JSM-6301F, Tokyo, Japan) and energy dispersive X-ray spectroscopy (EDS), respectively. The dielectric measurements were performed using HP4292A Impedance/Gain Phase Analyzer controlled by a PC.

### 3. Results and discussion

#### 3.1. Shrinkage behavior

The sintering curves of pure Ag, ZnTiO<sub>3</sub>, and the mixture of ZnTiO<sub>3</sub> and Ag powders (20 wt.% Ag) were measured, respectively, by TMA technique in order to study their densification characteristics. Powders were pressed into pellets about 10 mm in diameter and 5 mm thick under 4 MPa. Then, the three samples were heated up at 10 °C/min to 900 °C, 1150 °C and 1050 °C for Ag, ZnTiO<sub>3</sub> and the composite of them, respectively.

Figs. 1 and 2 show the shrinkage curves and shrinking rate curves of pure Ag, ZnTiO<sub>3</sub>, and the mixture of ZnTiO<sub>3</sub> with Ag powders (20 wt.% Ag), respectively. It can be seen that the sintering temperature of Ag (about 500 °C) is far below that of ZnTiO<sub>3</sub> (nearly 880 °C). Ag finishes its densification at around 700 °C, while at that temperature ZnTiO<sub>3</sub> is just starting to densify. For the composite of ZnTiO<sub>3</sub>/Ag, one can observe at low temperature an expansion of the material, which is unfavorable to the combination of the ZnTiO<sub>3</sub> and Ag interfaces. Furthermore, the associated differential shrinkage of the composite would result in interfacial defects like deformations, cracks, and warps [8,9].

Densities of samples sintered at 900 °C for 4 h were measured by Archimedes method. The measured density of ZnTiO<sub>3</sub> was 5.08 g/cm<sup>3</sup>, and Ag's density was 10.43 g/cm<sup>3</sup>.

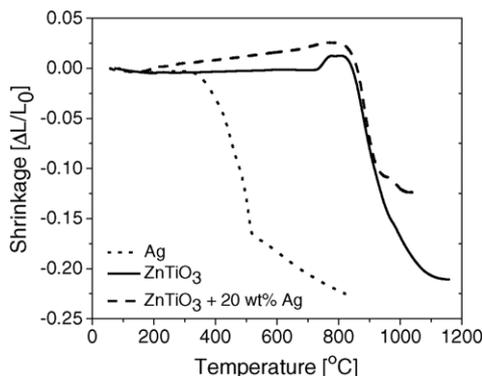


Fig. 1. Shrinkage curves of Ag, ZnTiO<sub>3</sub> and their composite.

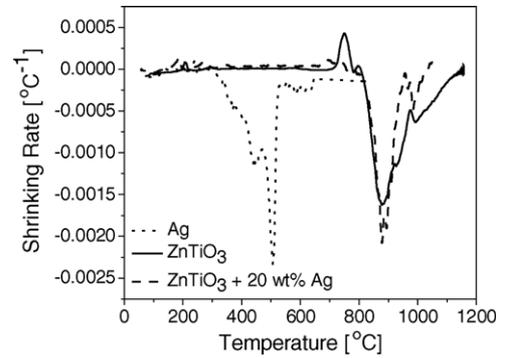


Fig. 2. Shrinking rate curves of Ag, ZnTiO<sub>3</sub> and their composite.

The measured, theoretical and relative density of the composite samples, abbreviated as  $\rho_M$ ,  $\rho_T$  and  $\rho_R$  hereafter, are all given in Table 1. Here,  $\rho_T$  and  $\rho_R$  are calculated by the following equations:

$$\rho_T = \rho_{Ag} \frac{\rho_{ZnTiO_3}}{\rho_{Ag} + (\rho_{ZnTiO_3} - \rho_{Ag})x} \quad (1)$$

$$\rho_R (\%) = \frac{\rho_M}{\rho_T} \times 100\% \quad (2)$$

where  $\rho_{Ag}$ ,  $\rho_{ZnTiO_3}$  is the measured density of pure Ag and ZnTiO<sub>3</sub>, and  $x$  is the weight content of silver in the Ag/ZnTiO<sub>3</sub> composites. On the one hand, the density ( $\rho_M$ ) of the composite increases with the increasing amount of Ag, which partly results from the higher density of Ag. On the other hand, the relative density of the composite also increases with the addition of Ag. This means that Ag addition could lead to an increase of the densification of ZnTiO<sub>3</sub>.

#### 3.2. Interfacial reaction

To study the interfacial reactions during sintering process, ZnTiO<sub>3</sub> dielectric powder was mixed with different weight proportion of Ag powder. The reference was pure ZnTiO<sub>3</sub>. All the samples were sintered at 900 °C for 4 h. XRD was performed on the sintered discs to characterize the phase transformation of the composite according to the content of Ag addition (samples A–D). The results are shown in Figs. 3 and 4.

It can be seen from Fig. 3 that the XRD patterns of the sintered mixtures are similar to that of ZnTiO<sub>3</sub> dielectric. Consequently, there is no significant chemical reaction between ZnTiO<sub>3</sub> and Ag to form new compounds, and one

Table 1  
The density for a series of samples sintered at 900 °C for 4 h

Sample	(1 - x)ZnTiO <sub>3</sub> + xAg				
Composition (x, wt.%)	0.000	0.005	0.010	0.050	0.100
Measured density ( $\rho_M$ ) (g/cm <sup>3</sup> )	4.60	4.82	4.84	4.86	5.12
Theoretical density ( $\rho_T$ ) (g/cm <sup>3</sup> )	5.08	5.09	5.11	5.21	5.35
Relative density ( $\rho_R$ ) (%)	90.55	94.70	94.79	93.28	95.62

Download English Version:

<https://daneshyari.com/en/article/1464874>

Download Persian Version:

<https://daneshyari.com/article/1464874>

[Daneshyari.com](https://daneshyari.com)