

Short communication

# A Si–SiC oxidation protective coating for carbon/carbon composites prepared by a two-step pack cementation

Fu Qian-Gang<sup>\*</sup>, Li He-Jun, Wang Yong-Jie, Li Ke-Zhi, Wu Heng

*C/C Composites Technology Research Center, Key Laboratory of Ultrahigh Temperature Composites, Northwestern Polytechnical University, Xi'an, Shaanxi 710072, PR China*

Received 23 September 2008; received in revised form 1 December 2008; accepted 22 January 2009

Available online 6 February 2009

## Abstract

To prevent carbon/carbon (C/C) composites from oxidation, a Si–SiC coating has been prepared by a two-step pack cementation technique. X-ray diffraction (XRD) and scanning electron microscopy (SEM) analysis show that the coating obtained by the first step pack cementation is a porous  $\beta$ -SiC structure, and a dense structure consisting  $\alpha$ -SiC,  $\beta$ -SiC and Si is obtained after heat-treatment by the second step pack cementation. By energy dispersive spectroscopy (EDS) analysis, a gradient C–SiC transition layer can be formed at the C/C-coating interface. The as-received coating has excellent oxidation protection ability and can protect C/C composites from oxidation for 166 h at 1773 K in air. The weight loss of the coated C/C is due to the formation of bubble holes on the coating surface and through-coating cracks in the coating.

© 2009 Elsevier Ltd and Techna Group S.r.l. All rights reserved.

*Keywords:* D. Carbon; D. SiC; Oxidation

## 1. Introduction

Carbon/carbon (C/C) composites have been attracting extensive attention due to their excellent mechanical properties at high temperature, such as high strength-to-weight ratio and high retention of mechanical properties at high temperatures, which makes them promising materials used in aircraft and aerospace fields [1]. However, these composites will be oxidized during their exposure to an oxidizing atmosphere above 723 K [2]. Their oxidation will result in an obvious decrease of their mechanical properties and limit their applications as high temperature structural materials [3]. SiC ceramic coating is an efficient method for protecting C/C composites at high temperature due to its excellent anti-oxidation property and good compatibility with C/C composites [4,5]. In addition, the glassy SiO<sub>2</sub> film will be formed on the surface of the coating while the SiC coated C/C composites are placed in air at high temperature, which can efficiently prevent oxygen from diffusing into the C/C matrix.

However, the mismatch of thermal expansion coefficient between SiC coating and C/C composites usually leads to cracking of SiC coating [6,7]. The through-coating cracks will offer entrance channels for oxygen and result in the failure of the coating. The free silicon distributed in the SiC coating can relax the stress at the end of the cracks and heal up the cracks [8]. It is also expected to decrease the frequency of cracks and improve the oxidation protection ability of SiC coating to some extent. Pack cementation has been used to prepare porous or dense SiC coating by adjusting its preparation conditions [5].

To obtain a dense Si–SiC coating, a two-step pack cementation was designed in the present work. The first step was to prepare a porous SiC inner layer, and the second step was to fill Si and SiC in the holes and cracks in the SiC inner layer. The microstructure and anti-oxidation property of the coating were investigated.

## 2. Experimental

Small specimens (10 mm × 10 mm × 10 mm) used as the substrates were cut from bulk 2D C/C composites with a density of 1.75 g/cm<sup>3</sup>. These specimens were hand-polished using 300 grit SiC paper, then cleaned with distilled water and dried at 393 K for 2 h. Powder compositions for the two-step pack

<sup>\*</sup> Corresponding author. Tel.: +86 29 88494197; fax: +86 29 88495764.

E-mail address: [fuqiangang@nwpu.edu.cn](mailto:fuqiangang@nwpu.edu.cn) (F. Qian-Gang).

cementation process were as follows: 65–80% Si, 10–25% graphite and 5–15%  $\text{Al}_2\text{O}_3$  for the first step, and 70–85% Si, 5–15% SiC, 7–15% graphite and 2–15%  $\text{Al}_2\text{O}_3$  for the second step. The role of  $\text{Al}_2\text{O}_3$  added in the pack powders was to increase the rate of diffusing reaction. All the above powders, with the granularities of 300 meshes, were analytical grade and were mixed by a blender for 2 h. The first pack mixtures and C/C specimens were put in a graphite crucible, and then were heated to 1873–2073 K and held at that temperature for 2 h under slight argon flow to form a porous SiC coating. Subsequently, the as-received SiC coated C/C were immersed in the second pack mixtures. The second pack cementation process was performed at 2173–2373 K for 2 h to obtain a dense Si–SiC coating.

The oxidation test was carried out at 1773 K in air in a furnace. The sample was weighed at room temperature by electronic balance with a sensitivity of  $\pm 0.1$  mg during oxidation at 1773 K. The morphology and crystalline structure of the coating were analyzed by JSM-6460 scanning electron microscopy (SEM), Rigaku D/max-3C X-ray diffraction (XRD) and energy dispersive spectroscopy (EDS).

### 3. Results and discussion

#### 3.1. Microstructure of the coating

Fig. 1 shows X-ray patterns of the surfaces of the as-received coatings. It can be seen that the inner layer obtained by the first step pack cementation is  $\beta$ -SiC. After the second step pack cementation, the coating is composed of Si,  $\alpha$ -SiC and  $\beta$ -SiC.  $\alpha$ -SiC was primarily resulted from the transition of  $\beta$ -SiC as the pack temperature was up to 2273–2373 K.

Fig. 2(a) displays the SEM micrograph of the surface of the coating produced by the first step pack cementation. Obviously, the  $\beta$ -SiC inner layer is of a porous structure, which might be incapable for protection of C/C composites against oxidation at high temperature. After the second pack cementation process, the coating becomes dense and crack-free, shown from Fig. 2(b), which is expected to have good oxidation protection ability.

Fig. 3 displays the backscattering electron image of the coated sample. The thickness of the coating is about 100  $\mu\text{m}$ ;

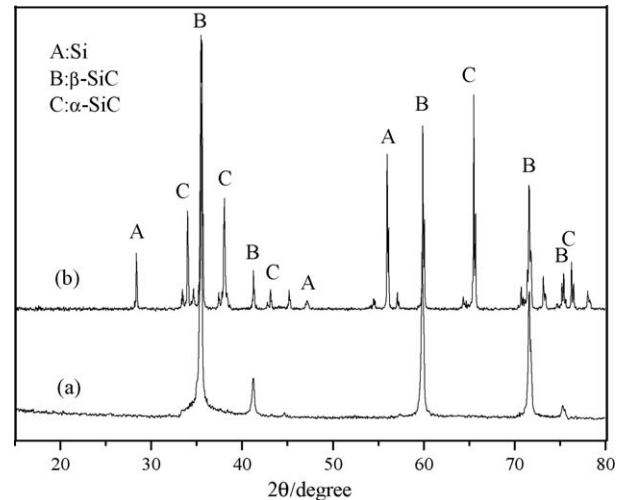


Fig. 1. X-ray patterns on the surfaces of the coatings obtained by (a) first step pack cementation and (b) two-step pack cementation process.

little penetration cracks or holes can be found in the coating. Moreover, there is no obvious interface between the coatings obtained by the two different pack cementation processes. There are two kinds of crystalline particles characterized as white (spot 1) and grey (spot 2) in the coating. By EDS analysis (Fig. 3), the white and grey phases can be distinguished as free Si and SiC, respectively.

Fig. 4 shows of the SEM image of the C/C-coating interface and its element line scanning results. From the C/C substrate to the coating at their interface, the concentration of the Si element increased gradually in the range of almost 10  $\mu\text{m}$ , implying that a gradient C–SiC bonding layer was obtained during the pack cementation process, which is advantageous to improve the thermal shock resistance of the coating.

#### 3.2. Oxidation protection ability of the coating

The isothermal oxidation curve of the coated C/C composites at 1773 K in air is shown in Fig. 5. It can be seen that the weight loss of the SiC inner layer coated sample was up to 21% after 10 h oxidation at 1773 K in air. The poor

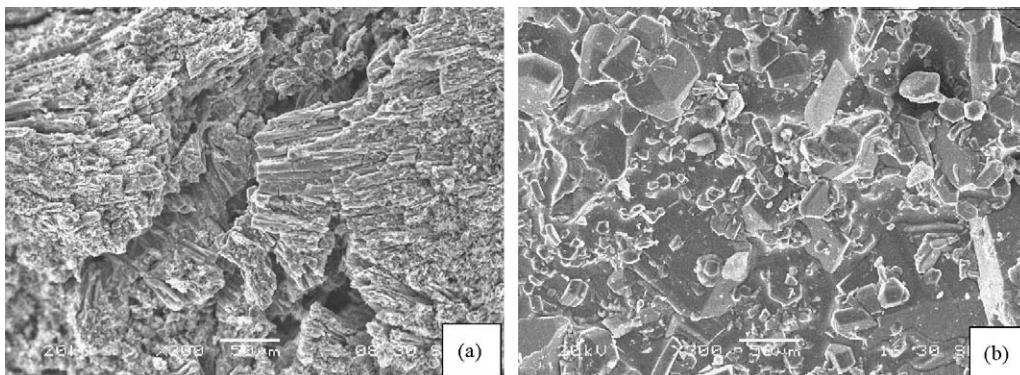


Fig. 2. SEM micrographs of the surfaces of the coatings obtained by (a) first step pack cementation and (b) two-step pack cementation process.

Download English Version:

<https://daneshyari.com/en/article/1465259>

Download Persian Version:

<https://daneshyari.com/article/1465259>

[Daneshyari.com](https://daneshyari.com)