

Technique for recovering rare-earth metals from spent sintered Nd-Fe-B magnets without external heating

Ryo Sasai*, Naohiro Shimamura

Interdisciplinary Graduate School of Sciences and Engineering, Shimane University, 1060 Nishi-kawatsu-cho, Matsue 690-8504, Japan

ARTICLE INFO

Article history:

Received 18 December 2015
Received in revised form 11 January 2016
Accepted 26 January 2016
Available online 15 February 2016

Keywords:

Spent sintered Nd-Fe-B magnets
Resource recovery
Mechano-chemical treatment
Rare-earth oxalate salt

ABSTRACT

To selectively recover rare-earth metals with higher purity from spent sintered Nd-Fe-B magnets without external heating, we investigated the mechano-chemical treatment of spent sintered Nd-Fe-B magnet powder with a reaction solution of HCl and $(\text{COOH})_2$ at room temperature. The results of various experiments showed that the mechano-chemical treatment with HCl and $(\text{COOH})_2$ is very effective for recovering the rare-earth metals contained in spent sintered Nd-Fe-B magnet powder; the recovery rate and purity of the rare-earth metals were 95.3 and 95.0 mass%, respectively, under optimal conditions ($[\text{HCl}] = 0.2 \text{ mol/dm}^3$ and $[(\text{COOH})_2] = 0.25 \text{ mol/dm}^3$).

© 2016 The Ceramic Society of Japan and the Korean Ceramic Society. Production and hosting by Elsevier B.V. This is an open access article under the CC BY-NC-ND license (<http://creativecommons.org/licenses/by-nc-nd/4.0/>).

1. Introduction

Sintered Nd-Fe-B magnets, originally researched and developed by Sagawa et al. [1–3], have the strongest coercive force among currently available magnets. Nowadays, sintered Nd-Fe-B magnets are employed as one of the essential components of the micro-motor of hard-disk drives and DVD recorders. In addition, they are used in compact speakers, watches, smartphones, automobiles, hybrid vehicles, and electrical appliances. The future demand for Nd-Fe-B magnets is expected to grow rapidly, especially because of the need for miniaturized and high-performance manufactured goods. In view of this expectation, the securement of rare-earth ores, which are essential for manufacturing Nd-Fe-B magnets, has been proposed as a high-priority national policy. However, it is extremely difficult for Japan to secure such ores because of its extremely low self-sufficiency rate. Therefore, the Japanese government and industries are devoting considerable effort toward the development of novel and independent industrial processes for stably securing rare-earth ores, which will be relatively unaffected not only by the international economic situation, but also by the diplomatic relations between Japan and rare-earth metal producing countries or the domestic situation in such countries. Toward this end, there is an urgent requirement for an effective industrial

system for recovering rare-earth metals from solid waste, such as spent sintered Nd-Fe-B magnets, as industrial raw materials for obtaining rare-earth metals of higher purity.

To expedite the establishment of such high-efficiency industrial processes, techniques for recovering rare-earth metals from various types of solid waste containing such elements have been investigated by many researchers from different fields such as metallurgy, applied chemistry, and chemical engineering. Machida et al. [4] reported that Nd could be recovered as NdCl_3 in around 90% yield by calcination of Nd-Fe-B magnet scrap and NH_4Cl at 573 K for 3 h. Moreover, they showed the possibility of obtaining residues containing Fe as an electro-microwave absorbent. Okabe et al. [5,6] reported that pure Nd metal (97.7% purity) could be recovered by treating Nd-Fe-B magnet scrap at temperatures above 1000 K. In this process, Nd metal can be directly collected using Mg alloy as the extraction medium. However, this process suffers from high energy costs and low product purity. Mochizuki et al. [7] reported that the rare-earth metals contained in oxidized Nd-Fe-B magnet scrap could be selectively recovered by chlorination under a Cl_2 gas stream at temperatures up to 1273 K. However, this process has a high energy cost; in particular, the maintenance cost is extremely high owing to the corrosive nature of Cl_2 gas. Liao et al. [8] reported that Nd from Nd-Fe-B magnet scrap could be selectively leached by H_2SO_4 based on the results of leaching experiments using four leaching reagents: NaOH, HCl, HNO_3 , and H_2SO_4 . The recovery rate of Nd was 75.41 mass%, which was not sufficiently high. Shibayama et al. [9] reported higher recover rates of Nd and Dy (up to 98% and 81%, respectively) via a hydrometallurgical process using a mixed solution of HNO_3 and H_2O_2 . Nd and Dy dissolved in the acid

* Corresponding author.

E-mail address: rsasai@riko.shimane-u.ac.jp (R. Sasai).

Peer review under responsibility of The Ceramic Society of Japan and the Korean Ceramic Society.

solution could be collected in oxalate form. Although these recovery rates are higher than those of reported dry processes such as chlorination and metallurgical process, they remain insufficient. To address the various problems faced by current and reported techniques for recovering rare-earth metals, the authors had previously reported a hydrothermal technique for recovering rare-earth metals from spent Nd-Fe-B magnets [10]. Thus, rare-earth oxalate salt with very high purity (≥ 99 mol%) could be selectively recovered from spent sintered Nd-Fe-B magnets without degaussing via hydrothermal treatment in a mixed aqueous solution of HCl and $(\text{COOH})_2$ at 383 K for 6 h. The proposed hydrothermal technique makes it possible to recover rare-earth metals from spent Nd-Fe-B magnets as oxalate salts at a lower temperature and with a shorter treatment time than other techniques. However, this approach involves external heat treatment. Thus, it is not sufficient yet eco-friendly.

The authors have previously reported that mechano-chemical treatment with reaction solvents is an eco-friendly technique for recovering valuable metal resources from solid waste without external heating. For example, when spent Pb-glass powder is subjected to mechano-chemical treatment with ethylenediaminetetraacetic acid (EDTA) aqueous solution, Pb and Ba can be extracted as EDTA complexes [11]. Similarly, lead sulfate crystals can be effectively collected in solid form from lead zirconate titanate [12–14] and lead lanthanum zirconate titanate [15] sintered compacts via mechano-chemical treatment with sulfuric acid. In the present study, we investigated the recovery of rare-earth metals such as Nd and Dy from spent sintered Nd-Fe-B magnets via mechano-chemical treatment with a mixed aqueous solution of HCl and $(\text{COOH})_2$ without external heating.

2. Experiment

2.1. Pretreatment of spent sintered Nd-Fe-B magnets

Spent sintered Nd-Fe-B magnets (chemical composition summarized in Table 1), which were acquired from a recycling company (ARBIZ Corporation) in Japan, were degaussed by heating at 573 K for 1 h in an electric furnace (SSFT-1520, Yamada Denki Co., Ltd.). The degaussed magnets were crushed into coarse grains using the planetary milling method at 300 rpm for 24 h with zirconia balls (diameter, 10 mm) and grinding bowl fasteners (P-5/2, Fritsch Japan Co., Ltd.). The degaussed and crushed magnet (hereafter, D&C/Nd-mag) powder was used as the sample powder for mechano-chemical treatment.

2.2. Mechano-chemical treatment of D&C/Nd-mag powder

Next, 0.5 g of D&C/Nd-mag powder was sealed in a polypropylene bottle (100 cm^3) with around 130 g of zirconia balls (diameter, 5 mm) and 20 cm^3 of HCl– $(\text{COOH})_2$ mixed aqueous solution with appropriate concentration. For determining the optimal mechano-chemical conditions, the molar concentrations of HCl and $(\text{COOH})_2$ were set in the range of 0.0125 – 0.2 mol/dm^3 and 0.005 – 0.85 mol/dm^3 , respectively. Mechano-chemical treatment of D&C/Nd-mag powder was performed using a rotary ball-milling

Table 1
Chemical composition of spent sintered Nd-Fe-B magnets.

	Nd	Dy	Fe	B	Ni ^a	Cu ^a
Content (mg/g)	152.9	42.4	332.8	1.4	12.3	1.2

^a From plating.

apparatus (UB-32, YAMATO Scientific Co., Ltd.) at 120 rpm for 6–24 h. After the mechano-chemical treatment, the produced precipitates adhered on the zirconia balls were collected by sonication for 3 min in 300 cm^3 of 0.02 mol/dm^3 HCl. The produced precipitates were completely collected by filtration under reduced pressure, and then, the collected precipitate was dried at 333 K overnight.

2.3. Characterization

Quantitative analysis of the metals (Nd, Dy, Fe, Ni, Cu, and B) in the filtrate and acid aqueous solution obtained by fully dissolving the collected powder into HCl after mechano-chemical treatment was carried out via inductively coupled plasma-atomic emission spectroscopy (ICP-AES, Optima 2000DV, PerkinElmer Co., Ltd.). From this elemental analysis, both the recovery rate of each metal (R) and the purity of the rare-earth metals (P) were calculated as follows:

$$R(\text{mass}\%) = \frac{(m^{\text{solid},M})}{(m^{\text{solid},M}) + (m^{\text{liquid},M})} \times 100 \quad (1)$$

$$P(\text{mass}\%) = \frac{(m^{\text{rare-earth}})}{(m^{\text{total}})} \times 100 \quad (2)$$

where $m^{\text{solid},M}$ and $m^{\text{liquid},M}$ are the weight of each metal, M , in the collected solid and liquid, respectively, and $m^{\text{rare-earth}}$ and m^{total} are the weight of the rare-earth metals and all the metals in the collected solid, respectively. Here, the experimental errors of both R and P values were about 1% of each value. The precipitates collected after mechano-chemical treatment were identified via X-ray diffraction (XRD) analysis (MiniFlex-II, RIGAKU Corporation) using Mo-filtered $\text{FeK}\alpha$ radiation (30 kV and 15 mA). The precipitate collected by mechano-chemical treatment under optimal condition was measured by thermal gravimetry-differential thermal analysis (TG-DTA: ThermoPlus II, RIGAKU Corporation).

3. Results and discussion

3.1. Effect of HCl concentration

The R value of each metal is plotted against the HCl concentration in Fig. 1, when the D&C/Nd-mag powder was treated via the mechano-chemical method with HCl– $(\text{COOH})_2$ mixed reaction solution. Here, the concentration of $(\text{COOH})_2$ was constant (0.1 mol/dm^3). The R values of the rare-earth metals did not change with increase in HCl concentration; they were nearly constant (around 60 mass%). Furthermore, the R values of Fe, B, and Ni did not

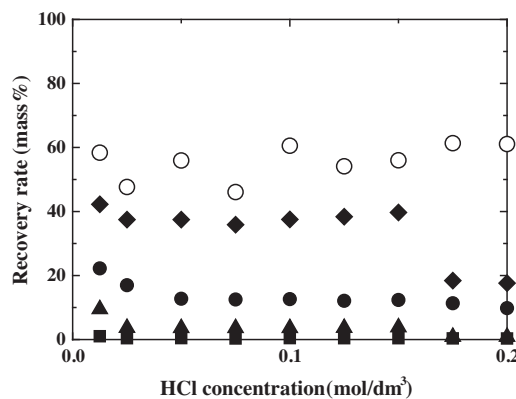


Fig. 1. Dependence of the R value of each metal on HCl concentration; $[(\text{COOH})_2] = 0.1 \text{ mol/dm}^3$. The symbols represent the following: rare-earth (○), Fe (■), B (●), Ni (▲), and Cu (◆).

Download English Version:

<https://daneshyari.com/en/article/1473153>

Download Persian Version:

<https://daneshyari.com/article/1473153>

[Daneshyari.com](https://daneshyari.com)