

New LTCC-hexaferrites by using reaction bonded glass ceramics

R. Karmazin^{a,*}, O. Dernovsek^a, N. Ilkov^a, W. Wersing^a, A. Roosen^b, M. Hagymasi^b

^a SIEMENS AG, CT MM 2, Otto-Hahn-Ring 6, D-817 30 Munich, Germany

^b University of Erlangen-Nuremberg, Glass and Ceramics, Martensstr. 5, D-91054 Erlangen, Germany

Available online 25 March 2005

Abstract

Hexaferrites are usually prepared according to the standard mixed oxide method with high sintering temperatures of up to 1350 °C, which are not suitable for low temperature cofired ceramics (LTCC) technology. In this work, the sintering temperature of BaFe₁₂O₁₉ was reduced to 900 °C by the development of reaction-bonded glass ceramics systems for LTCC-hexaferrites. Low amounts of reactive glasses (<7 vol.%) based on boron and zinc oxide were used as sintering additives to achieve full densification at 900 °C. The influence of variation in glass–ceramics compositions, different processing parameters, advanced powder preparation by using high-energy milling and the calcination temperature on achieving high- μ ferrites at 900 °C was studied. The magnetic properties of these LTCC-hexaferrites were characterized by a coaxial airline method and impedance measurements in the frequency range of 0.1–10 GHz. The influence of phase composition and microstructure on magnetic properties was also discussed.

© 2005 Elsevier Ltd. All rights reserved.

Keywords: LTCC; Ferrites; Glass ceramic; Magnetic properties

1. Introduction

Advanced low temperature cofired ceramics (LTCC) including Ba-hexaferrites with the concept of reactive bonded glass ceramics are of high interest for high frequency applications, e.g. phase-shifters, circulators, antennas and wireless technologies for the next generation of miniaturized electronic modules. One of the favoured candidates which combine high permeability (μ) at high frequencies is the group of hexaferrites, which are usually prepared according to the conventional mixed oxide method with high sintering temperatures of up to 1350 °C in air.

Development trends in LTCC magnetics using a small amount of additives and glass–ceramics systems, including low softening glasses and high melting magnetic ceramic. A typical additive for low temperature sintered ferrites, prepared with low cost mixed oxide method, is Bi₂O₃.^{1,2} Addition of lithium borosilicate glass³ or B₂O₃–Sb₂O₃⁴ was also reported. The main problem with low temperature fired polycrystalline magnetic phases, e.g. Ba₁₂Fe₁₉ is the high

porosity. Due to a high content of a non-magnetic phase (>10 vol.%), e.g. glass or pores the permeabilities are dramatically reduced. A novel technique to solve this problem and achieve the densification of samples below 900 °C at the same time was developed using the sintering process of hexaferrites with the addition of a small amount of reactive glasses which is based on Bi–B–Zn–Si–O (BBSZ).⁵

The influence of variation in glass–ceramics compositions, different processing parameters, advanced powder preparation by using high-energy milling and the calcination temperature on achieving high- μ ferrites at 900 °C was investigated in this paper.

2. Experimental

2.1. Powder preparation

M-Type modified 0hexaferrites with the phase composition BaFe₁₂O₁₉ were prepared using the mixed oxide method. The mixed precursor was calcinated at 1200 °C and then ball milled. Milled powder was mixed with a low content of reactive glass frits based on boron and zinc-oxide (3, 5, and

* Corresponding author. Tel.: +49 636 48039; fax: +49 636 48131.

E-mail address: Process1-CTMM2@mchp.siemens.de (R. Karmazin).

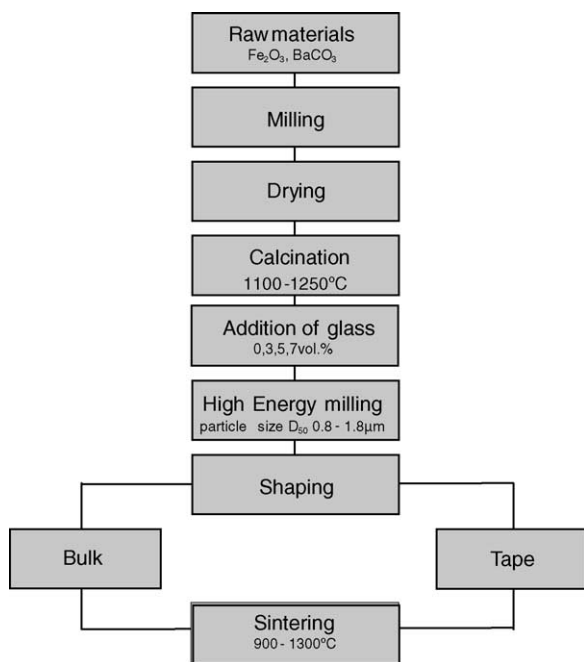


Fig. 1. Flow chart of synthesis of LTCC compatible hexaferrites.

7 vol.%) and then high energy milled using an attritor mill (Dispermat SL-C, WMA-Getzmann, Germany). To achieve densification at temperatures below 900 °C it was necessary to reduce the average particle size of the composite powder to 1.8 and 0.8 µm. The prepared powder was pressed into pellets or tape-casted and sintered at a temperature range of 900–1350 °C for 5 h. Fig. 1 displays the entire procedure.

2.2. Characterization method

Phase composition of calcinated hexaferritic powders was characterized by high-temperature X-ray diffraction. Measurements from 600 to 1300 °C with step 200 °C were done in order to describe evolution of hexaferritic phase in the mixture. Obtained diffractograms were compared with low temperature diffractogram (50 °C). Temperature and time-controlled sintering behaviour was investigated using dilatometer (Model STA 409C, Netzsch, Germany). The density of the sintered hexaferrites was measured using helium pycnometry (Accupyc 1330, Micrometrics, Germany). Phase composition of the glass–ceramic composites was examined by X-ray analysis (Siemens Diffract 500, Siemens, Germany) and the microstructure of the sintered ceramic bodies was investigated using a SEM (Jeol 840, Jeol, Japan).

2.3. Permeability measurements

Permeability measurements based on broadband results up to 5 GHz using a coaxial transmission–reflection (TR) was employed. The coaxial line had an inner and an outer diameter of 3 and 7 mm, respectively. The thickness of hexaferrites toroid ranged from 3 to 4 mm. The test fixture of the TR



Fig. 2. Test fixture for transmission–reflection measurements of cylindrical hexaferrites.

measurement and prepared samples are shown in Fig. 2. The basic magnetic parameters were measured using an HP4291A analyzer in the range of 0.1–3 GHz.

3. Results and discussion

3.1. Phase composition

High temperature X-ray diffraction was employed to find the suitable temperature for the BaFe₁₂O₁₉ phase creation. The resulting spectra are shown in Fig. 3. The first traces of BaFe₁₂O₁₉ were observed at temperatures around 1000 °C, but a pure hexaferrite phase was obtained at 1200 °C. Thus, this temperature was used for the calcination of the mixed oxide precursor.

3.2. Sintering behaviour of glass–hexaferrite composite

A dilatometric study of heat treatment of samples with different amounts of BBSZ glass was done in order to determine shrinkage on densification of the reactive sintered ceramic–glass composites. The results are shown in a graph (Fig. 4). The shrinkage increases with the increase of the amount of BBSZ glass. The porosity, evalu-

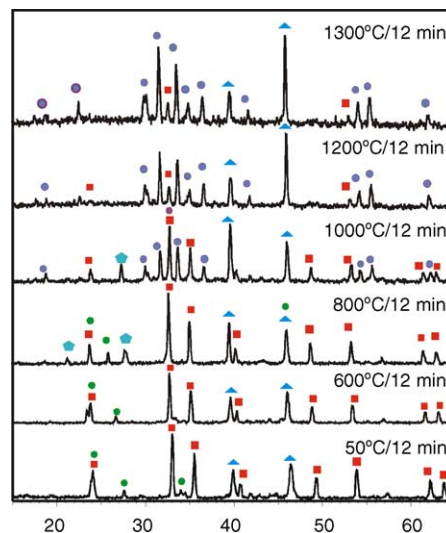


Fig. 3. High temperature X-ray diffractogram of heat treatment of mixture of BaCO₃ and Fe₂O₃.

Download English Version:

<https://daneshyari.com/en/article/1478951>

Download Persian Version:

<https://daneshyari.com/article/1478951>

[Daneshyari.com](https://daneshyari.com)