

10th Eco-Energy and Materials Science and Engineering
(EMSES2012)

Relaxation Analysis of Electrode Crystal Materials for Secondary Lithium Ion Batteries

Takeshi Yao *

*Graduate School of Energy Science, Kyoto University
Sakyo-ku, Yoshida-Honmachi, Kyoto 606-8501, Japan*

Abstract

Relaxation analysis, I have invented first in the world, makes transition of electrode material from kinetic state to equilibrium state clear. I would like to introduce the relaxation analysis for some electrode materials here, and make discussions about the behavior of Li ion and the crystal structure of the electrode material.

© 2013 The Authors. Published by Elsevier B.V. Open access under [CC BY-NC-ND license](#).

Selection and peer-review under responsibility of COE of Sustainable Energy System, Rajamangala University of Technology Thanyaburi (RMUTT)

Keywords: Li ion; Electrode Material; Kinetic state; Equilibrium state

1. Introduction

When lithium is inserted into $\gamma\text{-Fe}_2\text{O}_3$ electrochemically, prolonged potential change is observed after termination of the insertion (Fig.1). It is considered that this phenomenon reflects some continuing crystal structure change even after lithium insertion. We inserted lithium into $\gamma\text{-Fe}_2\text{O}_3$, then made the circuit open and analyzed the material. We named the analysis “Relaxation Analysis”, because material is analyzed at relaxation process. We are now applying relaxation analysis to so many materials such as $\gamma\text{-Fe}_2\text{O}_3$ [1-3], LiFePO_4 [4], LiMn_2O_4 [5,6], $\text{Li}_{4/3}\text{Ti}_{5/3}\text{O}_4$ [7], LiCoO_2 [8], and so on.

* Corresponding author. Tel.: +81-75-753-4865; fax: +81-75-753-4734.

E-mail address: yao@energy.kyoto-u.ac.jp

2. Experimental

We charged or discharged the cell electrochemically with electrode material. When the required conditions were attained, we opened the circuit and removed the working electrode from the cell immediately in a glove box to avoid the local cell action between the electrode material and the current collector or the supplemental conductor. Then, we obtained the sample for XRD measurement. XRD patterns were measured with various relaxation time. The XRD patterns were analyzed by the Rietveld method using RIEVEC program coded by T. Yao[9-10].

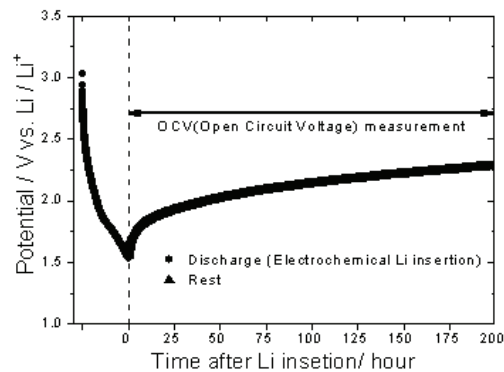


Fig. 1. Result of OCV (Open Circuit Voltage) measurement after lithium insertion (Sample : $\text{Li}_{1.5}\text{Fe}_2\text{O}_3$)

3. Results and Discussion

We measured crystal structure change of $\gamma\text{-Fe}_2\text{O}_3$ with spinel structure after termination of lithium insertion by using the X-ray Rietveld analysis and had a result that the iron occupancy of 8a site decreased and that of 16c site increased with lithium insertion process and after the lithium insertion, the iron occupancy of 8a site increased and that of 16c site decreased gradually at the relaxation process (Fig.2). And we concluded that this indicates that lithium prefer 8a site to occupy kinetically, on the other hand, prefer 16c site thermodynamically.

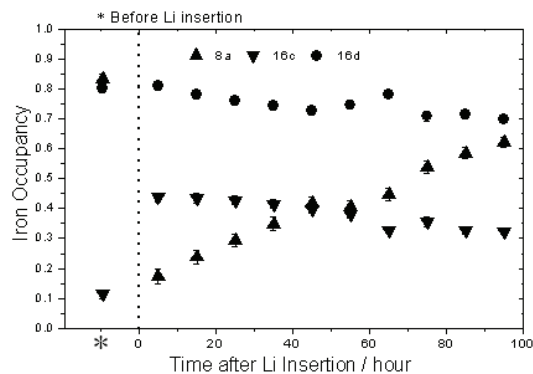


Fig. 2. Relaxation of crystal structure of $\gamma\text{-Fe}_2\text{O}_3$ with elapsed time after lithium insertion: Site occupancy changes of iron at 8a, 16c and 16d sites. Asterisk mark (*) indicates the sample before lithium insertion.

Download English Version:

<https://daneshyari.com/en/article/1512480>

Download Persian Version:

<https://daneshyari.com/article/1512480>

[Daneshyari.com](https://daneshyari.com)