



Improved thermal stability of $[001]_c$ poled $0.24\text{Pb}(\text{In}_{1/2}\text{Nb}_{1/2})\text{O}_3$ – $0.47\text{Pb}(\text{Mg}_{1/3}\text{Nb}_{2/3})\text{O}_3$ – 0.29PbTiO_3 single crystal with manganese doping



Yuling Wang^{a,b}, Enwei Sun^a, Wei Song^a, Wanchong Li^a, Rui Zhang^{a,*}, Wenwu Cao^{a,c}

^a Condensed Matter Science and Technology Institute, Harbin Institute of Technology, Harbin 150080, China

^b Physical and Electrical Information Engineering Institute, Daqing Normal University, Daqing 163712, China

^c Materials Research Institute, The Pennsylvania State University, University Park, Pennsylvania 16802, USA

ARTICLE INFO

Article history:

Received 3 November 2013

Received in revised form 25 February 2014

Accepted 26 February 2014

Available online 7 March 2014

Keywords:

Piezoelectric

PIN–PMN–PT

Thermal stability

ABSTRACT

The temperature dependence of dielectric, piezoelectric, and electromechanical coupling properties of 0.5 wt.% manganese-doped and undoped $[001]_c$ -poled $0.24\text{Pb}(\text{In}_{1/2}\text{Nb}_{1/2})\text{O}_3$ – $0.47\text{Pb}(\text{Mg}_{1/3}\text{Nb}_{2/3})\text{O}_3$ – 0.29PbTiO_3 (0.24PIN–0.47PMN–0.29PT) single crystals has been investigated. Compared to the undoped single crystal, the Mn-doped 0.24PIN–0.47PMN–0.29PT demonstrated higher level of coercive field (9.8 kV/cm), increased Curie temperature (187 °C), improved mechanical quality factor Q_m (196), decreased piezoelectric constant d_{33} and comparable electromechanical coupling factor k_{33} , indicating hardening effects caused by the manganese ion substitution. More importantly, it was found that the Mn substitution significantly enhanced temperature stabilities of k_{33} , d_{33} and Q_m , leading to 30–40 °C improvement of the usage temperature range. These results show the application potential of Mn-doped ternary PIN–PMN–PT single crystals for the high-temperature and high-power electromechanical devices.

© 2014 Elsevier B.V. All rights reserved.

1. Introduction

Ternary relaxor-based ferroelectric $x\text{Pb}(\text{In}_{1/2}\text{Nb}_{1/2})\text{O}_3$ – $(1-x-y)\text{Pb}(\text{Mg}_{1/3}\text{Nb}_{2/3})\text{O}_3$ – $y\text{PbTiO}_3$ (PIN–PMN–PT) single crystals, with compositions near the morphotropic phase boundary, demonstrate much higher coercive fields and Curie temperature with comparably high-level piezoelectric and electromechanical properties compared to their binary counterpart $(1-x)\text{Pb}(\text{Mg}_{1/3}\text{Nb}_{2/3})\text{O}_3$ – $x\text{PbTiO}_3$ (PMN–PT) single crystals [1–6]. However, its mechanical quality factor is still far lower than that of hard PZT ceramics [7], which limits its applications for high power ultrasonic transducers, sensors and actuators.

Recently, numerous efforts have been conducted to “harden” relaxor–PT single crystals through the addition of acceptor dopants, such as manganese (Mn) [8–13]. Through X-ray photoelectron spectroscopy (XPS) [8] and X-ray absorption fine structure (XAFS) analysis [9], the formation of oxygen vacancy dipole defects ($\text{Mn}^{II} - \text{V}_O$) is observed in Mn-doped PMN–PT single crystals, which indicates the “harden effect” from Mn doping [10]. In ternary PIN–PMN–PT single crystals, Mn modification induces enhanced ferroelectric and pyroelectric properties [11], improved mechanical quality factor Q_m , and higher coercive field E_c , but a decrease in

the piezoelectric and dielectric properties at room temperature [12,13]. In practical applications, the change of piezoelectric coefficient, electromechanical coupling factor, and mechanical quality factor with temperature will influence the performance of electro-mechanical devices. Therefore, understanding the temperature dependence of properties of Mn-doped ternary PIN–PMN–PT single crystals is very important.

In this work, we systematically investigated the temperature behavior of piezoelectric, dielectric, electromechanical properties and mechanical quality factor for both undoped and Mn-doped $[001]_c$ -poled 0.24PIN–0.47PMN–0.29PT single crystals. Our results are useful for future development of high-power and high-temperature electromechanical devices based on these Mn-doped ternary single crystals.

2. Experimental

$[001]_c$ -oriented undoped and 0.5 wt.% Mn-doped 0.24PIN–0.47PMN–0.29PT single crystals were supplied by H.C. Materials Corp, USA, which were grown by the modified Bridgman method [14,15]. X-ray diffraction (XRD) analysis was performed on both types of crystals. The dopant amount of Mn was determined to be ~0.5 wt.% by the scanning electron microscopy (SEM) with energy-dispersive X-ray spectroscopy, and the samples were oriented by the Laue machine with an accuracy of $\pm 0.5^\circ$. Each sample was cut and polished into a parallelepiped with orientations of $[100]_c \times [010]_c \times [001]_c$ for $[001]_c$ -poled crystals. In order to fill in the oxygen vacancies, the samples were annealed at 600 °C for 10 h, which also reduced the residual stress from crystal growth and mechanical processing.

* Corresponding author. Tel/fax: +86 0451 86402797.

E-mail address: ruizhang_ccmst@hit.edu.cn (R. Zhang).

Afterwards, gold electrodes were sputtered onto the $[001]_c$ and $[00\bar{1}]_c$ samples surfaces. The samples were poled at a field of 15 kV/cm for 20 min in silicone oil at room temperature. The poling completeness of each sample was checked by a JZ-2 piezo d_{33} meter.

The temperature dependence of dielectric properties was measured from room temperature up to 250 °C at a rate of 1 °C/min at the frequencies of 1 kHz, 10 kHz, and 100 kHz for both types of single crystals using an Agilent E4980A precision LCR meter. The dielectric constant was calculated from the measured capacitance based on the parallel capacitance approximation. The P – E hysteresis loops were measured on $[001]_c$ -oriented plate samples from room temperature to 210 °C by the Precision Premier II (Radiant Technologies). In the thermal behavior measurements, a small amount of high-temperature conductive silver was employed as the electrode, and thin silver wires were attached for minimizing clamping effects on the samples. The thermal characteristics of piezoelectric, electromechanical characteristics and mechanical quality factor were determined by combining the Agilent 4294A Precision Impedance Analyzer with a heating-cooling optical stage (Thmsee600, Linkam).

3. Results and discussion

The main properties of $[001]_c$ -poled undoped and Mn-doped 0.24PIN–0.47PMN–0.29PT single crystals at room temperature are listed in Table 1. The dielectric constant ϵ_{33}/ϵ_0 and piezoelectric coefficient d_{33} decrease in Mn-doped samples, but the electromechanical coupling factor k_{33} of Mn-doped ternary samples maintains comparable level with that of the undoped crystal. More importantly, Mn-doped single crystal has much higher mechanical quality factor Q_m than the undoped sample (196 vs. 66).

Fig. 1 shows the temperature dependent P – E hysteresis loops of the two specimens. At room temperature, the Mn addition leads to the increase in both the remnant polarization P_r (from 23.6 $\mu\text{C}/\text{cm}^2$ to 26.5 $\mu\text{C}/\text{cm}^2$) and coercive field E_c (from ~ 5.8 kV/cm to ~ 9.8 kV/cm). Moreover, Mn doped PIN–PMN–PT single crystal also has better ferroelectric properties than that of undoped single crystal. This implies that the introduction of Mn ions into the 0.24PIN–0.47PMN–0.29PT single crystal produces a “hardening” effect [16]. As a result, the Mn-doped single crystal is more suitable for high-power electromechanical devices, such as underwater projectors and piezoelectric motors [17].

The XRD spectrum of undoped and Mn-doped 0.24PIN–0.47PMN–0.29PT single crystals, with corresponding diffraction indices, is shown in the inset of Fig. 2a. Clearly, both single crystals have rhombohedral symmetry with perovskite structure. In addition, Fig. 2 presents the dielectric constants (ϵ_{33}/ϵ_0) and dielectric loss as a function of temperature for $[001]_c$ poled undoped and Mn-doped 0.24PIN–0.47PMN–0.29PT single crystals at the frequencies of 1 kHz, 10 kHz and 100 kHz. The ferroelectric phase transition temperature T_{R-T} (rhombohedral to tetragonal) and Curie temperature T_C (tetragonal to cubic) were determined according to the locations of the dielectric permittivity peaks (at 1 kHz). For undoped single crystal, the T_{R-T} and T_C were found to be 102 °C and 145 °C, respectively, while in Mn-doped crystal, both transition temperatures increased noticeably ($T_{R-T} \sim 109$ °C and $T_C \sim 187$ °C, respectively). In addition, the dielectric loss is obviously lower for the Mn modified crystal, especially in the range from room temperature to T_{R-T} . In acceptor doped crystals, Mn ions substitute the B sites ($\text{Zr}^{4+}/\text{Ti}^{4+}$) of the perovskite structure due to the match of ionic radius, while oxygen vacancies can be generated due to valance mismatch. Thus, defect dipole pairs are developed inside the modified crystal, which leads to domain wall pinning and suppression of the dielectric and piezoelectric responses

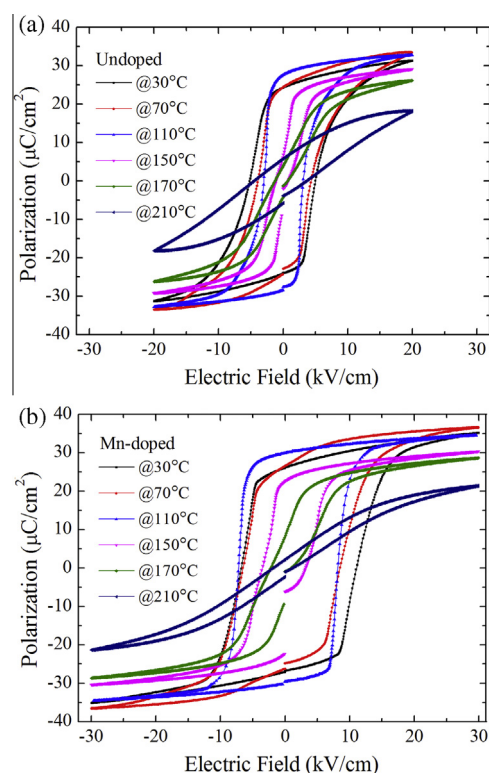


Fig. 1. Temperature dependence of P – E hysteresis loops in (a) undoped and (b) Mn-doped $[001]_c$ -oriented 0.24PIN–0.47PMN–0.29PT single crystals.

[18,19]. These dipolar defects can provide nucleation centers for the ferroelectric phases, so that the phase transition temperatures are increased. At the same time, the suppression of the mobility of domain walls by the dipolar defects enhances the relaxation time, which lowers the losses [10,18].

Temperature stabilities of the longitudinal electromechanical coupling factor k_{33} for the undoped and Mn-doped crystals are shown in Fig. 3. The k_{33} value was determined based on the impedance spectrum at each temperature, and four representative impedance spectra are shown in the inset of Fig. 3. Clearly, the frequency difference between the resonant peak and the anti-resonant peak is reduced as the temperature increases. The k_{33} values in both crystals show little change when the temperature is lower than their respective T_{R-T} . In the undoped sample, k_{33} decreases sharply after T_{R-T} (~ 102 °C) due to the partial depolarization in the tetragonal phase, and reduces to zero at 170 °C. On the contrary, only a slow decrease was observed for the Mn-doped crystal even at temperatures higher than its T_{R-T} (close to 110 °C). The k_{33} value decreases to 0.73 at 140 °C, which is still higher than that of hard piezoelectric ceramics [20]. These results indicate a more stable electromechanical coupling characteristic for Mn-modified PIN–PMN–PT single crystal.

The temperature behaviors of the piezoelectric coefficient d_{33} in these two crystals are shown in Fig. 4. One can see that the d_{33} increases with temperature and reaches the peak value at T_{R-T} in the undoped crystal. The Mn-doped crystal shows a much slower

Table 1

Important physical properties of undoped and Mn-doped 0.24PIN–0.47PMN–0.29PT single crystals at room temperature.

PIN–PMN–PT	d_{33} (pC/N)	k_{33}	$\epsilon_{33}^T/\epsilon_0$ at 1 kHz	$\tan \delta$ (%) at 1 kHz	s_{33}^D (10^{-12} m ² /N)	s_{33}^E (10^{-12} m ² /N)	E_c (kV/cm)	Q_m
Undoped	1215	0.90	4553	0.56	10.95	48.33	5.8	66
Mn-doped	836	0.87	2635	0.40	12.20	36.64	9.8	196

Download English Version:

<https://daneshyari.com/en/article/1611251>

Download Persian Version:

<https://daneshyari.com/article/1611251>

[Daneshyari.com](https://daneshyari.com)