



Preparation and characterization of $\text{Li}_5\text{ReSi}_4\text{O}_{12}$ (Re = Nd, Gd) solid electrolyte

Chenghuan Huang, Kelong Huang*

School of Chemistry and Chemical Engineering, Central South University, Changsha 410083, China

ARTICLE INFO

Article history:

Received 7 May 2010

Received in revised form 7 July 2010

Accepted 8 July 2010

Available online 15 July 2010

Keywords:

Solid electrolyte

Solid-state reaction

Conductivity

Electrochemical impedance spectroscopy

ABSTRACT

Dense $\text{Li}_5\text{ReSi}_4\text{O}_{12}$ (Re = Nd, Gd) ceramic materials with densities of $3.0\text{--}3.1\text{ g/cm}^3$ were synthesized by a solid-state reaction method. The samples were characterized by X-ray diffraction (XRD), scanning electron microscopy (SEM) and electrochemical impedance spectroscopy (EIS). The conductivity of $\text{Li}_5\text{NdSi}_4\text{O}_{12}$ was $1.2 \times 10^{-2}\text{ mS/cm}$ at 550°C and $2.5 \times 10^{-4}\text{ mS/cm}$ at 350°C , respectively, with activation energy of 0.84 eV . $\text{Li}_5\text{GdSi}_4\text{O}_{12}$ with activation energy of 0.90 eV had conductivities similar to $\text{Li}_5\text{NdSi}_4\text{O}_{12}$, suggesting that neither rare earth ion significantly affected the properties of $\text{Li}_5\text{ReSi}_4\text{O}_{12}$.

© 2010 Elsevier B.V. All rights reserved.

1. Introduction


Li-ion conducting solids are materials of increasing interest because of their possible use as solid electrolytes in high-energy solid-state batteries [1–4]. Liquid-free batteries have various advantages over currently commercialized ones. These include safety issues caused by flammable organic electrolytes and irreversible capacity loss during cycles and storage originated by the solid electrolyte interface [5–7]. Therefore, solid-state electrolytes with chemical stability and high ionic conductivity have been considered as candidates to substitute liquid organic electrolytes in Li-ion batteries.

A wide variety of inorganic materials, such as sulfides [4,8,9], hydride-based materials [10–12], and perovskite-type (ABO_3) oxides (A = Li, La and B = Ti) [1,13], have been found to exhibit high lithium ionic conductivity for low temperature application. On the other hand, recent studies on high temperature Li-ion conductors are also attracting attention in order to develop high temperature batteries [14–16] and other electrochemical devices [17]. Some lithium rare earth silicates (LiLnSiO_4 , Ln = La–Dy) with apatite structure have thermal stability and relatively high conductivity at over 500°C [18]. Furthermore, NASICON-type alkali rare earth silicates, such as $\text{Na}_5\text{ReSi}_4\text{O}_{12}$ (Re = rare earth metal) [19,20] and $\text{Na}_{3+3x-y}\text{Re}_{1-x}\text{PySi}_{3-y}\text{O}_9$ [21,22], show excellent ionic conductivity. For instance, the ionic conductivity of $\text{Na}_5\text{ReSi}_4\text{O}_{12}$ is over 10^{-2} S/cm at 300°C [20]. Such a structure consists of $\text{Si}_{12}\text{O}_{36}$ metasilicate rings stacked along the threefold axes of the rhom-

bohedral space group. Na^+ ions in the sites between the rings are mobile, resulting in the super ionic conductivity [19]. For this reason, we attempted to synthesize Li-substitution $\text{Na}_5\text{ReSi}_4\text{O}_{12}$ -type of materials ($\text{Li}_5\text{ReSi}_4\text{O}_{12}$, Re = Nd, Gd), and characterized their properties.

2. Experimental

$\text{Li}_5\text{NdSi}_4\text{O}_{12}$ powder was synthesized by a solid-state reaction method. Stoichiometric amounts of high-purity Li_2CO_3 , Nd_2O_3 and SiO_2 powders were mixed by ball milling in ethanol for 48 h, followed by drying in an oven and calcination at 850°C for 12 h in air. The calcinated powder was ground and mixed again, followed by the second calcination under the same conditions as the first time. The sample was cooled to room temperature, ground and manually pelletized using a disk-shaped mold. The pellets were sintered at 960°C for 6 h in air to get dense ceramic materials. The final products of $\text{Li}_5\text{NdSi}_4\text{O}_{12}$ were blue. The overall reaction for formation of $\text{Li}_5\text{NdSi}_4\text{O}_{12}$ is given by the following reaction:



A similar synthesis method was applied to prepare $\text{Li}_5\text{GdSi}_4\text{O}_{12}$ powder and ceramic. However, the final products of $\text{Li}_5\text{GdSi}_4\text{O}_{12}$ were white.

The morphology of the samples was revealed by using scanning electron microscopy (SEM, LEO 1530). The crystal structure and phase purity was analyzed by using X-ray diffraction pattern (XRD, X'Pert PRO Alpha-1). Conductivity measurements from 300 to 550°C were carried out with AC electrochemical impedance spectroscopy (EIS) by using a Solarton 1255 impedance analyzer with a Solartron 1287 electrochemical interface in the frequency range of 10 Hz to 5 MHz , with an AC perturbation voltage of 10 mV . Conductive silver paint was used as electrodes. Ionic conductivity values were calculated with $\sigma = d/(R \times S)$, where d denotes the sample thickness, S the area of the electrodes and R the sample resistance, which can be obtained from complex impedance plots.

* Corresponding author. Tel.: +86 73188879850; fax: +86 73188879850.

E-mail address: huangkelong@yahoo.com.cn (K. Huang).

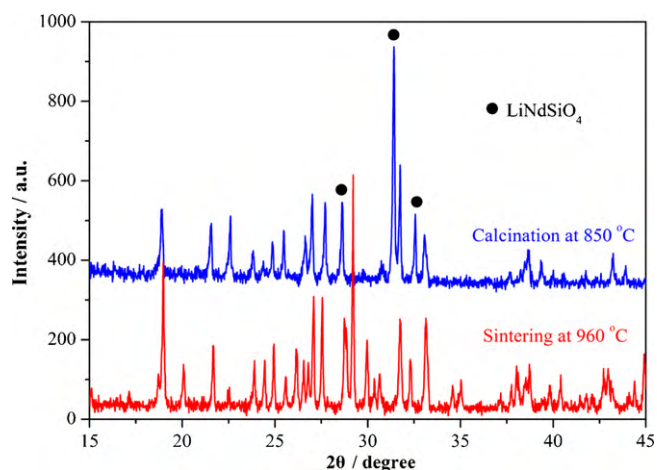


Fig. 1. XRD patterns of $\text{Li}_5\text{NdSi}_4\text{O}_{12}$ after calcination and sintering.

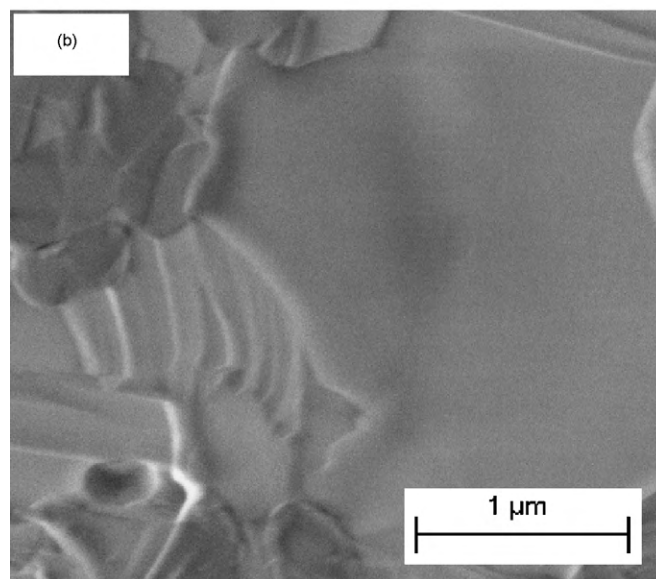
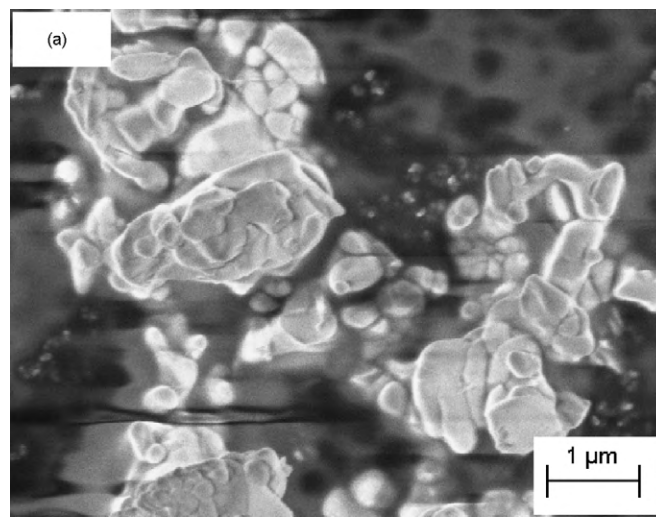


Fig. 3. SEM images of $\text{Li}_5\text{GdSi}_4\text{O}_{12}$ after (a) calcination at 880 °C and (b) sintering at 980 °C, respectively.

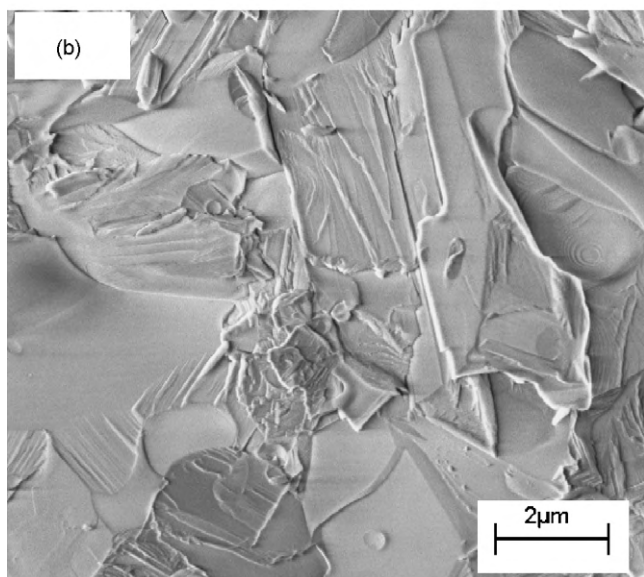
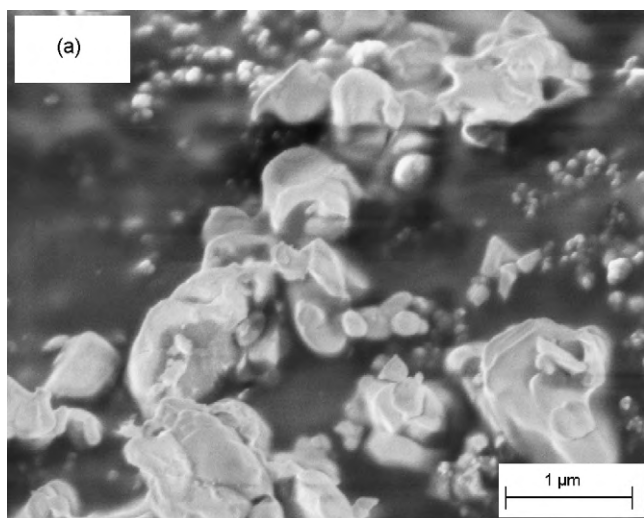


Fig. 2. SEM images of $\text{Li}_5\text{NdSi}_4\text{O}_{12}$ after (a) calcination at 850 °C and (b) sintering at 960 °C, respectively.

3. Results and discussion

Fig. 1 shows the XRD pattern of $\text{Li}_5\text{NdSi}_4\text{O}_{12}$ after calcination and sintering. No peak of Li_2O , Nd_2O_3 , or SiO_2 was found. However, the peaks of LiNdSiO_4 were detected after the first calcination, indicating that the solid-state reaction was not completed. Repeating grinding and mixing of the sample would facilitate the solid reaction. After the sample sintered at 960 °C, the peaks of LiNdSiO_4 disappeared. Fig. 2 shows SEM images of the $\text{Li}_5\text{NdSi}_4\text{O}_{12}$ powder and pellet, respectively. The grain sizes of $\text{Li}_5\text{NdSi}_4\text{O}_{12}$ after calcination at 850 °C were 200 nm to 1 μm. The cross-section image shows that the pellet was dense after sintering. The density of the ceramic was 3.0 g/cm³. Fig. 3 shows that the grain size distribution of $\text{Li}_5\text{GdSi}_4\text{O}_{12}$ powder was also in the range of 200 nm to 1 μm. Likewise, the $\text{Li}_5\text{GdSi}_4\text{O}_{12}$ pellet was dense after sintering, with a density of 3.1 g/cm³.

Fig. 4 shows typical AC impedance spectra of both $\text{Li}_5\text{NdSi}_4\text{O}_{12}$ and $\text{Li}_5\text{GdSi}_4\text{O}_{12}$ pellets at different temperatures. In Fig. 4(a), the impedance of $\text{Li}_5\text{NdSi}_4\text{O}_{12}$ is associated with the large semicircle starting from the origin and ending at about $1.6 \times 10^4 \Omega$, implying that the resistance of the $\text{Li}_5\text{NdSi}_4\text{O}_{12}$ specimen was about $1.6 \times 10^4 \Omega$ at 550 °C. The impedance of the specimen increased

Download English Version:

<https://daneshyari.com/en/article/1617912>

Download Persian Version:

<https://daneshyari.com/article/1617912>

[Daneshyari.com](https://daneshyari.com)