



Formation of $\text{Ti}_2\text{AlC}_{0.5}\text{N}_{0.5}$ solid solutions by combustion synthesis of Al_4C_3 -containing samples in nitrogen

C.L. Yeh*, C.W. Kuo, F.S. Wu

Department of Aerospace and Systems Engineering, Feng Chia University, 100 Wenhwa Road, Seatwen, Taichung 40724, Taiwan

ARTICLE INFO

Article history:

Received 8 July 2010

Accepted 20 August 2010

Available online 27 August 2010

Keywords:

Ceramics

X-ray diffraction

SEM

$\text{Ti}_2\text{AlC}_{0.5}\text{N}_{0.5}$

Combustion synthesis

ABSTRACT

Preparation of the solid solution $\text{Ti}_2\text{AlC}_{0.5}\text{N}_{0.5}$ from the powder compacts composed of Ti, Al_4C_3 , and Al or AlN was investigated by self-propagating high-temperature synthesis (SHS) under gaseous nitrogen. The molar proportion of three reactant powders was formulated as $\text{Ti}:\text{Al}_4\text{C}_3:\text{Al}$ (or AlN) = 2:1/6:1/3. For both types of the samples, the increase of nitrogen pressure from 0.45 to 1.82 MPa augments the combustion temperature and thus accelerates the reaction front. In contrast to the inertness of AlN, Al particles reacted energetically with Ti and N_2 during the SHS process, which resulted in the higher reaction exothermicity for the sample containing Al than that adopting AlN. The solid solution $\text{Ti}_2\text{AlC}_{0.5}\text{N}_{0.5}$ was identified as the dominant phase in the final products from the Ti– Al_4C_3 –Al powder compacts. However, the increase of nitrogen pressure adversely affected the evolution of $\text{Ti}_2\text{AlC}_{0.5}\text{N}_{0.5}$, because Ti was over-nitrified and Al also reacted with nitrogen. When AlN was used to replace Al in the reactant compacts, the formation of $\text{Ti}_2\text{AlC}_{0.5}\text{N}_{0.5}$ was deteriorated due to weak exothermicity and deficiency of TiAl. In addition, the products synthesized from the Ti– Al_4C_3 –AlN samples under nitrogen of 1.48 and 1.82 MPa were dominated by titanium carbonitride $\text{Ti}(\text{C},\text{N})$. This implies that the use of AlN in place of Al is unfavorable for the formation of $\text{Ti}_2\text{AlC}_{0.5}\text{N}_{0.5}$ through combustion synthesis involving gaseous nitrogen.

© 2010 Elsevier B.V. All rights reserved.

1. Introduction

Ternary compounds $\text{M}_{n+1}\text{AX}_n$, where $n = 1, 2$, or 3, M is an early transition metal, A is an A-group (mostly IIIA and IVA) element, and X is either C or N, are a class of materials with a unique combination of metallic and ceramic properties [1–3]. In general, the MAX phases are relatively soft, readily machinable, good thermal and electrical conductors, elastically stiff, and highly resistant to thermal shock, oxidation, and corrosion [1–3]. Extensive studies were performed on many MAX compounds, such as Ti_3SiC_2 , Ti_3AlC_2 , Ti_2AlC , Cr_2AlC , and Ti_2AlN [4–10]. Fabrication of the MAX phases has been conducted through a variety of processing routes; for example, hot pressing (HP) [2,4,5], hot isostatic pressing (HIP) [6,7], in situ hot pressing/solid–liquid reaction synthesis [10–15], pulse discharge sintering (PDS) [16–19], and self-propagating high-temperature synthesis (SHS) [20–25].

Furthermore, solid solutions based on the MAX phases can be formed on either the M, A, or X site, which renders great potential for tailoring and/or optimizing the material properties. Various MAX-based solid solutions, like $(\text{Ti},\text{Nb})_2\text{AlC}$, $(\text{Cr},\text{V})_2\text{AlC}$, $(\text{Cr},\text{V})_2\text{GeC}$, $\text{Ti}_3(\text{Si},\text{Al})\text{C}_2$, $\text{Ti}_3(\text{Si},\text{Ge})\text{C}_2$, and $\text{Ti}_2\text{Al}(\text{C},\text{N})$, were prepared

and their mechanical and thermal properties were studied [26–35]. Of particular interest for this work is $\text{Ti}_2\text{AlC}_{0.5}\text{N}_{0.5}$, which possesses enhanced properties when compared with two related end members Ti_2AlC and Ti_2AlN [7,32–34]. According to Barsoum and co-workers [7,32–35], $\text{Ti}_2\text{Al}(\text{C},\text{N})$ was produced from the stoichiometric mixtures of Ti, Al_4C_3 or Al, AlN, and graphite powders by hot isostatic pressing at 1300–1400 °C and 40–100 MPa for 10–15 h.

As a promising alternative, combustion synthesis in the SHS mode takes advantage of the self-sustaining merit from highly exothermic reactions, and hence, has the benefits of low energy requirement, short reaction time, and simple facilities [36–39]. The SHS technique has been effectively utilized to produce a number of the MAX carbides, like Ti_3SiC_2 [20], Ti_3AlC_2 [21], Ti_2AlC [22], Ta_2AlC [23], Nb_2AlC [24], and Ti_2SnC [25]. Recently, Yeh et al. [40] first prepared $\text{Ti}_2\text{AlC}_{0.5}\text{N}_{0.5}$ from TiC- and TiN-diluted Ti–Al–C powder compacts by combustion synthesis in either solid–gas or solid state mode. Formation of $\text{Ti}_2\text{AlC}_{0.5}\text{N}_{0.5}$ with three minor phases TiC, TiN, and Ti_3Al was achieved by solid–gas combustion of the TiC-diluted samples in nitrogen [40]. For the TiN-added samples, the SHS process executed in the solid state was beneficial to reduce the secondary phases, which yielded $\text{Ti}_2\text{AlC}_{0.5}\text{N}_{0.5}$ with trivial amounts of TiC and TiN [40].

As an extension of the previous effort [40], this study makes the first attempt to employ Al_4C_3 -containing powder compacts for the preparation of $\text{Ti}_2\text{AlC}_{0.5}\text{N}_{0.5}$ through the SHS process under gaseous

* Corresponding author. Tel.: +886 4 24517250x3963; fax: +886 4 24510862.
E-mail address: clieh@fcu.edu.tw (C.L. Yeh).

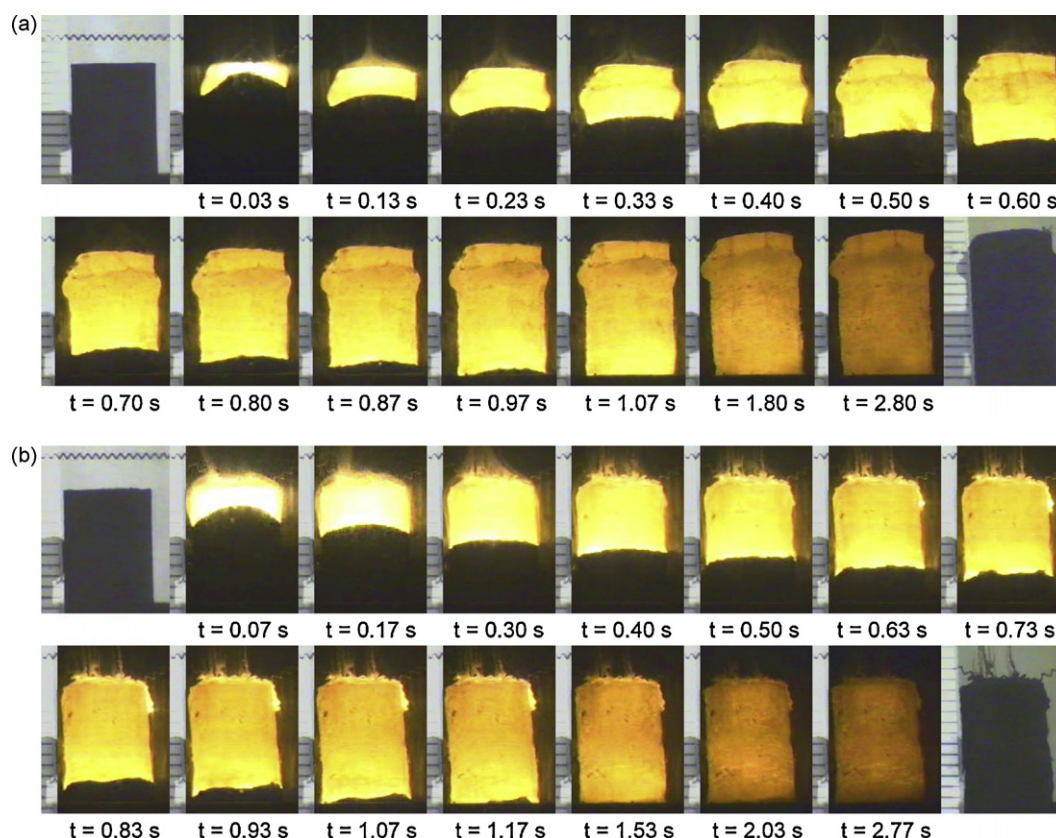


Fig. 1. Typical SHS sequences in nitrogen of 0.45 MPa associated with powder compacts of different initial compositions: (a) $2\text{Ti} + 1/6\text{Al}_4\text{C}_3 + 1/3\text{Al}$ and (b) $2\text{Ti} + 1/6\text{Al}_4\text{C}_3 + 1/3\text{AlN}$.

nitrogen. Effects of the sample stoichiometry and nitrogen pressure are investigated on the phase composition of the final product, as well as on the combustion temperature and propagation velocity of the reaction front. Moreover, the reaction mechanism describing the formation of $\text{Ti}_2\text{AlC}_{0.5}\text{N}_{0.5}$ from the $\text{Ti}-\text{Al}_4\text{C}_3-\text{Al}$ sample in nitrogen is proposed on the basis of the phase composition of the final product.

2. Experimental methods of approach

The starting materials adopted in this study are inspired by those (Ti , Al , Al_4C_3 , AlN , and carbon) used by Barsoum and co-workers [7,32–35] in the process of hot isostatic pressing. In order to assure self-sustaining combustion in nitrogen, this work employs two types of the Al_4C_3 -containing samples. One is composed of titanium (Strem Chemicals, $\leq 45\ \mu\text{m}$, 99% purity), aluminum (Showa Chemical Co., $\leq 40\ \mu\text{m}$, 99% purity), and Al_4C_3 (Strem Chemicals, $\leq 45\ \mu\text{m}$, 98% purity) at a molar proportion of $\text{Ti}:\text{Al}_4\text{C}_3:\text{Al} = 2:1/6:1/3$. The other replaces elemental aluminum with AlN (Strem Chemicals, $2.5\text{--}4.0\ \mu\text{m}$, 99% purity) to form an initial stoichiometry of $\text{Ti}:\text{Al}_4\text{C}_3:\text{AlN} = 2:1/6:1/3$. The reactant powders were well mixed in a ball mill and then cold-pressed into cylindrical compacts with a diameter of 7 mm, a height of 12 mm, and a compaction density of 55% relative to the theoretical maximum density (TMD).

The SHS experiments were conducted in a stainless-steel windowed chamber filled with high-purity nitrogen (99.999%) from 0.45 to 1.82 MPa. Details of the experimental setup and measurement approach were reported elsewhere [41,42]. The microstructure of synthesized products was examined under a scanning electron microscope (Hitachi S-3000N), and the phase composition was analyzed by an X-ray diffractometer (Shimadzu XRD-6000) with CuK_α radiation.

3. Results and discussion

3.1. Observation of combustion characteristics

Fig. 1(a) and (b) illustrates typical SHS images recorded from combustion of two different types of powder compacts in nitrogen of 0.45 MPa. It is evident that upon ignition a distinct reaction

front forms and propagates downward in a self-sustaining manner, which transforms the cold reactant into an incandescent combustion product. Because nitrogen is normally insufficient within the sample compact for combustion synthesis involving gaseous reagent, continuous infiltration of nitrogen proceeds after the passage of the combustion wave, which leads to subsequent nitridation and prolonged combustion luminosity. As indicated in Fig. 1(a) and (b), a shorter propagation period of the combustion wave is noticed for the $\text{Ti}-\text{Al}_4\text{C}_3-\text{Al}$ powder compact than the $\text{Ti}-\text{Al}_4\text{C}_3-\text{AlN}$ sample. This is most likely due to the fact that combustion of the sample adopting Al is more exothermic than that of the AlN -containing sample.

3.2. Measurement of flame-front propagation velocity and combustion temperature

Fig. 2 presents the influence of nitrogen pressure on the propagation velocity of the combustion front (V_f). The combustion velocity increases with increasing pressure of nitrogen for both types of the samples, on account of a higher concentration of nitrogen in the reaction front. As mentioned above, the use of AlN instead of Al in the reactant compact lowers the flame-front velocity, because AlN is essentially inert during the SHS process. On the contrary, Al reacts with nitrogen and Ti to form nitrides and aluminides, respectively, and both reaction paths are exothermic. Therefore, the higher overall reaction exothermicity is anticipated for the $\text{Ti}-\text{Al}_4\text{C}_3-\text{Al}$ sample, which thereby accelerates the combustion wave.

Three temperature profiles recorded from combustion of the $\text{Ti}-\text{Al}_4\text{C}_3-\text{Al}$ samples under nitrogen of different pressures are depicted in Fig. 3. The abrupt rise in temperature signifies the rapid arrival of the combustion wave. The peak value corresponds

Download English Version:

<https://daneshyari.com/en/article/1619245>

Download Persian Version:

<https://daneshyari.com/article/1619245>

[Daneshyari.com](https://daneshyari.com)