



Effect of 6.25 at% Al addition on structural stability of magnesium under high pressure: A first-principles study

Qiuxiang Liu, Ruijun Zhang*

State Key Laboratory of Metastable Materials Science and Technology, Yanshan University, Qinhuangdao 066004, China

ARTICLE INFO

Article history:

Received 27 April 2010

Received in revised form 25 August 2010

Accepted 27 August 2010

Available online 6 September 2010

Keywords:

First-principles

High pressure

Metals and alloys

Structural stability

ABSTRACT

The structural stability of pure Mg and Mg–6.25 at% Al under hydrostatic pressures at zero temperature was investigated by employing first-principles total energy calculations. The results show that the adding Al leads to higher enthalpy of forming for all structures of Mg with the increase in the enthalpy for the bcc structure being the highest. The structural stability order does not get affected by the application of hydrostatic pressure. However, compared with pure magnesium, the magnesium with added 6.25 at% Al shows higher hcp \rightarrow bcc phase transformation pressure point, but lower hcp \rightarrow fcc pressure point.

© 2010 Elsevier B.V. All rights reserved.

1. Introduction

Magnesium has great potential in many important industrial fields, such as aerospace, automobile, computers and mobile communication, due to its low density, highly specific stiffness, excellent castability and easy recycling capability [1–7]. However, the comparatively poor mechanical performance has greatly obstructed its application in more important fields [8–10]. Addition of aluminum element has been proved to be an effective method to improve the mechanical properties of magnesium. Up to now, many Mg–Al system alloys such as AZ91, AZ71 and AZ61 have been developed.

It is well known that microstructure plays a critical role in determining the properties of materials and can be adjusted by means of structural phase transformation. High pressure can lead to the structural transformation of materials, and many previous studies have been focused on the structural stability of magnesium under high pressure. For instance, McMahan and Moriarty [11,12] predicted the possible sequence of structures hcp \rightarrow bcc \rightarrow fcc in magnesium by first-principle calculations and predicted a hcp to bcc transformation under 50 ± 6 GPa at zero temperature. These transformations have been confirmed by experimental or calculation methods [13,14]. The crystal structures of magnesium have been examined after adding Zn and Y atoms, which was studied by Datta et al. [15,16]. In addition, the influence of alloying Al and Li

elements on the lattice parameters and mechanical properties of Mg have been studied [17,18]. However, the effect of adding aluminum atoms on the structural stability of magnesium under high pressure has not yet been examined.

In this paper, therefore, the structural stabilities for the hcp, bcc and fcc structures of magnesium with added 6.25 at% Al (chemical component similar to a typical Mg–Al system alloy – AZ71) and pure magnesium under hydrostatic pressures are studied by first-principles total energy calculations, respectively. The present work is expected to be beneficial to the further improvement of mechanical property for more widely use of magnesium alloy – Mg–Al series alloy.

2. Computational methods

The first-principle calculation is performed with the CASTEP code based on the density-functional and pseudopotential methods. Vanderbilt-type ultrasoft pseudopotentials [19] are employed to describe the electron–ion interactions. The exchange and correlation terms are described with generalized gradient approximations (GGA) in the scheme of Perdew–Burke–Erzerhof (PBE) [20]. The geometric optimization of unit cell is carried out with the BFGS minimization algorithm [21] provided in this code.

The hexagonal-close-packed (hcp) structure belongs to hexagonal crystal system, space group $P6_3/MMC$, with cell parameter: $a = b = 3.20940$ Å, $c = 5.21050$ Å. The unit cell of the hcp structure of magnesium has two atoms. However, the primitive cells of the bcc and fcc structures of magnesium belongs to cubic crystal system, with the lattice constant $a = 3.10379$ Å and $a = 3.19872$ Å, and

* Corresponding author.

E-mail address: qx0813@126.com (R. Zhang).

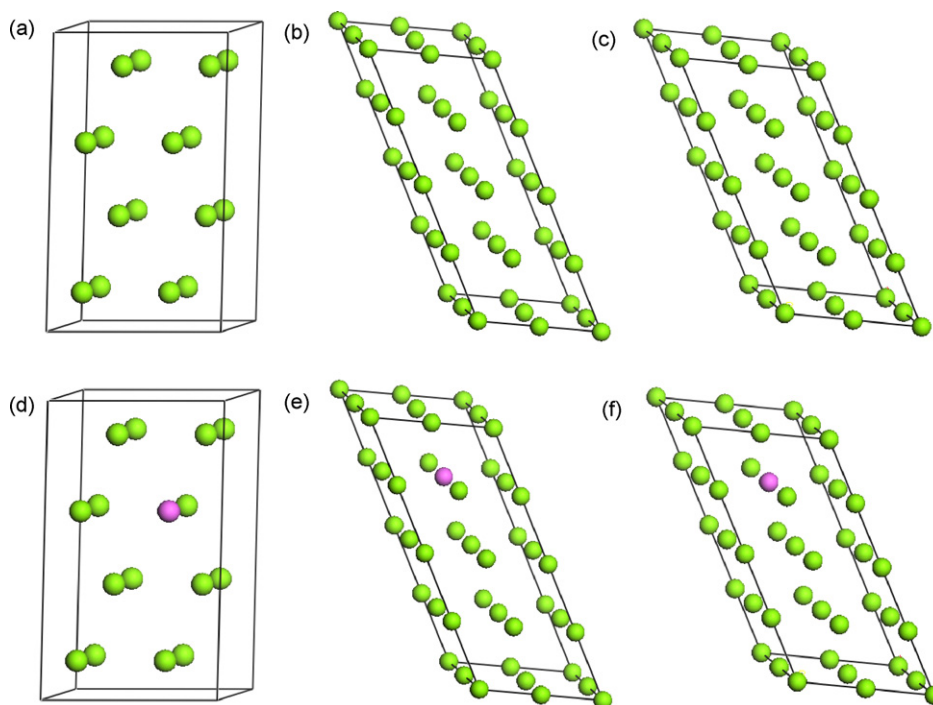


Fig. 1. Crystalline structure models of Mg and Mg-6.25 at% Al. (a) Hexagonal-close-packed of Mg. (b) Body-centered cubic of Mg. (c) Faced-centered cubic of Mg. (d) Hexagonal-close-packed of Mg-6.25 at% Al. (e) Body-centered cubic of Mg-6.25 at% Al. (f) Faced-centered cubic of Mg-6.25 at% Al.

space groups $IM-3M$ and $FM-3M$, respectively. In order to study the effect of adding 6.25 at% Al atoms on the structures structural stability of pure magnesium under high pressure, calculations are performed with hcp structure of magnesium, using $2 \times 2 \times 2$ supercells, while, for the bcc and fcc structures of magnesium, using $2 \times 2 \times 4$ supercells. The hcp, bcc and fcc structures of pure Mg and Mg-6.25 at% Al are shown in Fig. 1. In order to confirm the convergence of our calculations, we investigate the total energy on the dependence on the energy cutoff from 280 eV to 600 eV. At last, we choose energy cutoff 450 eV, 400 eV and 400 eV for the hcp, bcc and fcc structure of magnesium, respectively. The k -point set mesh parameters are (6, 6, 3), (8, 8, 4) and (10, 10, 5) respectively. Each calculation is considered to be converged when the maximum force on the atom is below $0.01 \text{ eV } \text{\AA}^{-1}$ and the maximum displacement between cycles is below $5 \times 10^{-4} \text{ \AA}$. The self consistent field (SCF) calculations are converged when the energy threshold is lower than $5.0 \times 10^{-7} \text{ eV/atom}$.

In our work, hydrostatic pressure is applied to three structures of pure magnesium and magnesium with 6.25 at% Al added to investigate the effect of pressure on their structural stability. The geometry optimization is performed at a fixed value 200 GPa for the three structures.

3. Results and discussion

The ground state properties of the hcp, bcc and fcc structures of pure magnesium and magnesium with 6.25 at% Al added are investigated from their total energy. Meanwhile, the geometry optimization is performed for the crystal lattice constant and atomic coordinates of the three structures under hydrostatic pressures ranging from 0 GPa to 200 GPa. According to the calculation results, the calculated P - V dates are fitted to the third-order Birch–Murnaghan equation of state [22–24]. The corresponding equilibrium lattice constant a_0 , bulk modulus B_0 , and pressure derivative of bulk modulus B_0' for the hcp, bcc and fcc structure of magnesium with 6.25 at% Al added and pure magnesium at zero pressure are presented in Table 1.

Furthermore, we calculate the relative volume (v/v_0) at various pressures for the three structures of magnesium with 6.25 at% Al added and pure magnesium, as shown in Fig. 2. It can be seen that 6.25 at% Al addition leads to larger relative volume for three structures of magnesium and the increase in the relative volume for the bcc structure is the most, then followed by hcp and fcc structure. Therefore, we can conclude that the compressibility of three structures of magnesium with 6.25 at% Al added is poorer than magnesium's. The results are consistent with the B_0 , which are fitted by the EOS. Obviously, the increase of strength for magnesium with 6.25 at% Al should be related with 6.25 at% Al addition, since aluminum can result in structural distortion of Mg crystal when dissolved in the pure Mg.

Moreover, the enthalpy for the three structures of Mg and Mg-6.25 at% Al under different pressures is shown in Fig. 2. The calculated results have shown that, under zero pressure, 6.25 at% Al addition leads to higher enthalpy for the hcp, bcc and fcc structures of magnesium. The enthalpy for the hcp, bcc and fcc structure increase 57.55314 eV/atom, 57.59124 eV/atom and 57.58781 eV/atom, respectively. Clearly, the increase in the enthalpy for the bcc structure is the most, then followed by the fcc and hcp structures. As the pressure becomes larger, the enthalpy for both pure magnesium and magnesium with added 6.25 at% Al increases. In this case, the average enthalpy increment for magnesium with 6.25 at% Al relative to that of the similar structure

Table 1

Calculated equilibrium lattice constants a_0 , cell volume (V) and bulk modulus B_0 and B_0' .

Structure	a_0 (Å)	V (Å ³)	B_0 (GPa)	B_0' (GPa)
Mg-6.25 at% Al-hcp	6.471998	359.937027	37.95572	3.83900
Pure Mg-hcp	—	—	36.03834 ^a	3.83117 ^a
Mg-6.25 at% Al-bcc	7.109092	359.287916	37.35587	3.85234
Pure Mg-bcc	—	—	35.05696 ^a	3.84977 ^a
Mg-6.25 at% Al-fcc	9.305891	725.750354	36.70761	3.83202
Pure Mg-fcc	—	—	35.52171 ^a	3.81513 ^a

^a Ref.[25].

Download English Version:

<https://daneshyari.com/en/article/1619297>

Download Persian Version:

<https://daneshyari.com/article/1619297>

[Daneshyari.com](https://daneshyari.com)