



Martensitic transformation and thermal cycling effect in Cu–Co–Zr alloys

F.A. Javid^{a,*}, N. Mattern^a, S. Pauly^a, J. Eckert^{a,b}

^a IFW Dresden, Institut für Komplexe Materialien, Postfach 27 01 16, D-01171 Dresden, Germany

^b TU Dresden, Institut für Werkstoffwissenschaft, D-01062 Dresden, Germany

ARTICLE INFO

Article history:

Received 2 July 2010

Received in revised form 14 January 2011

Accepted 27 January 2011

Available online 5 February 2011

Keywords:

Cu–Co–Zr

Rapid solidification

Martensitic transformation

Thermal analysis

ABSTRACT

Cu_{50-x}Co_xZr₅₀ ($x=0, 0.5, 1, 2, 3, 4$ and 5 at.%) alloys were cast in a cylindrical copper mold by a suction casting device. In order to investigate the thermal behavior of the as-cast rods, the samples were heated from 313 to 573 K and then cooled down to about 253 K. The structure of the samples was studied by X-ray diffraction and optical microscopy. Thermal cycling measurements were also done for alloys with $2, 3, 4$ and 5 at.% cobalt. It was found that increasing the cobalt content decreases martensite (M_s) and austenite (A_s) start temperatures, while it increases the temperature region in which austenite is stable. Thermal cycling measurements revealed that by increasing the number of cycles, the austenite start temperature increases while martensite start temperature shifts to lower temperatures.

© 2011 Elsevier B.V. All rights reserved.

1. Introduction

Martensitic transformations (MT) are the phase transformation with a cooperative atomic movement and they are diffusionless solid–solid transition, which were the interesting point of many researches due to their unique properties such as shape memory effect and superelasticity [1]. The shape memory effect was first known in 1938 in Cu–Zn alloys and Cu–Sn alloys [2], but not widely used until 1963 when Ni–Ti alloys were studied. Among the various alloy systems studied so far, NiTi-based alloys are the most attractive materials with superior shape memory and super plastic properties [3–5]. On the other hand Cu–Zr-based quasi-binary intermetallics [6] show quite high MT temperature. As an example of Cu–Zr-based alloys, phase transformations in Cu–Zr–Ni alloy were studied by [7]. The MT in CuZr intermetallic and the twined nature of the martensite were first studied by Carvalho and Harris [8] and Nicholls et al. [9]. In Cu–Zr-based alloys, Cu₅₀Zr₅₀ intermetallic compound has a B2 structure which is stable above 988 K. Below this temperature and in the equilibrium state this phase decomposes into Cu₁₀Zr₇ and CuZr₂ phases; but rapid cooling to the temperatures lower than 413 K leads to a transformation of CuZr–B2 into metastable monoclinic structure. This phase has martensitic characteristics and shape memory effect [10,11]. On the other hand Co₅₀Zr₅₀ composition also has a simple cubic B2 structure which is stable at room temperature. It seems with the addition of proper amount of cobalt to CuZr, CuZr–B2 phase can be stabilized at room

temperature. The purpose of the current paper is to investigate MT in the Cu–Co–Zr ternary system in which copper is replaced by cobalt while the atomic ratio of (Cu+Co):Zr is kept one. The effect of cobalt on the transformation temperatures is studied. Finally thermal cycling of some selected alloys is evaluated.

2. Experimental

Master alloys of Cu_{50-x}Co_xZr₅₀ compositions with different Co contents ($x=0, 0.5, 1, 2, 3, 4$ and 5 at.%) were prepared by arc-melting using high-purity metals (99.99) of Cu, Zr and Co in a Ti-gettered argon (>99.999) atmosphere. The ingots were remelted several times in order to reach a good chemical homogeneity. Subsequently, cylindrical rods with a diameter of 3 mm were produced from the ingots by an Edmund Bühler suction casting device using a water-cooled copper mold. The transmission geometry STOE STADIP diffractometer with Mo-radiation ($K\alpha_1$) was used to identify the phases of the samples. Using Nikon EPIPHOT 300 optical microscopy the microstructure of the samples was characterized. Differential scanning calorimetry was used to investigate the martensitic transformation. These experiments were performed on a PerkinElmer Pyris differential scanning calorimeter at a constant heating and cooling rates of 5 K/min from 253 to 573 K and using graphite crucibles. In order to study the effect of thermal cycling on Cu–Co–Zr alloys, Cu_{50-x}Co_xZr₅₀ compositions with $x=2, 3, 4$ & 5 at.% cobalt were 3 times cycled with the mentioned DSC device and the same temperature regime.

3. Results and discussion

Fig. 1(a) shows the X-ray patterns of the samples with 0, 2 and 5 at.% cobalt. The main constituent for all Cu–Co–Zr samples is CuZr monoclinic phase with $pm-3m$ space group and here we show some selected compositions. As reported in [10,11], in the as-cast situation, monoclinic structure is the main crystallographic structure for the Cu₅₀Zr₅₀ composition. In the X-ray pattern of the samples picks of the low temperature equilibrium phases (i.e. Cu₁₀Zr₇ and CuZr₂) also were found. Increasing the cobalt content to 5 at.%, the

* Corresponding author. Tel.: +49 351 4659 739; fax: +49 351 4659 452.
E-mail address: f.a.javid@ifw-dresden.de (F.A. Javid).

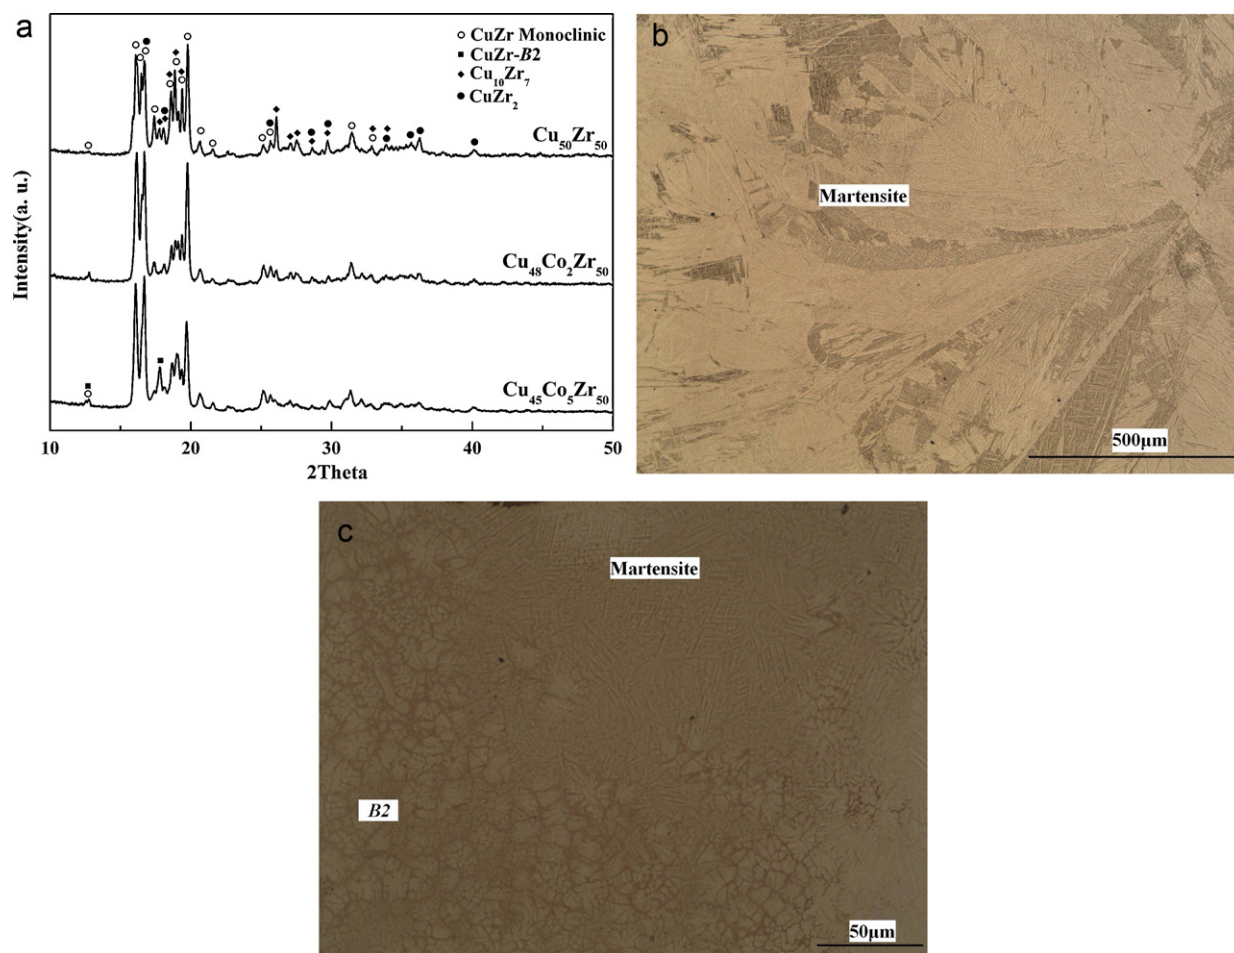


Fig. 1. (a) X-Ray patterns of $\text{Cu}_{50-x}\text{Co}_x\text{Zr}_{50}$ alloys ($x=0, 2$ and 5 at.%), micrograph of (b) $\text{Cu}_{48}\text{Co}_2\text{Zr}_{50}$ with martensite laths and (c) $\text{Cu}_{45}\text{Co}_5\text{Zr}_{50}$ which has CuZr-B2 phase beside martensite structure.

intensity of equilibrium phases decrease and the peak of CuZr-B2 phase starts to become intense mostly at around 2θ less than 18° . On the other words in samples with 5 at.% cobalt CuZr-B2 is directly solidified from the melt and coexists with CuZr monoclinic phase. Due to 100% solubility of Co in Cu, when copper is replaced by cobalt, it forms a solid solution of $(\text{Cu}, \text{Co})\text{Zr}$. Fig. 1(b and c) shows the micrographs of $\text{Cu}_{48}\text{Co}_2\text{Zr}_{50}$ and $\text{Cu}_{45}\text{Co}_5\text{Zr}_{50}$ compositions at room temperature. In $\text{Cu}_{48}\text{Co}_2\text{Zr}_{50}$ composition CuZr monoclinic is the main phase and Fig. 1(b) shows the martensite laths clearly, while by increasing the cobalt content to 5 at.%, in a higher magnification we can see the CuZr-B2 phase with dendritic structure coexisting with martensite.

Fig. 2(a and b) shows the heating and cooling curves of the samples respectively. For the sake of an easier comparison of all samples, all DSC curves of the heating process (from 313 to 573 K) are plotted together, and also the same for cooling curves (from 573 to 253 K). The DSC curves of Fig. 2 show an obvious martensitic transformation. For $\text{Cu}_{50}\text{Zr}_{50}$ the austenite start (A_s) and the austenite finish (A_f) temperatures are around 528 and 553 K respectively. Also for this composition martensite start (M_s) and martensite finish (M_f) temperatures are 448 and 410 K. Adding cobalt to the binary Cu–Zr system shifts the transformation temperatures. Increasing the cobalt content decreases the A_s and A_f temperatures and also M_s and M_f temperatures are decreased. For example the addition of 2 at.% cobalt shifts A_s and A_f to 485 and 503 K, respectively, while the M_s and M_f reach 410 and 387 K. It means that by adding cobalt to the binary Cu–Zr system, the temperature range in which martensite is stable decreases and austenite will be stable in a wider temper-

ature range. With respect to the Cu–Zr phase diagram, $\text{Cu}_{50}\text{Zr}_{50}$ phase is a B2 type phase which is stable above 988 K and as mentioned previously decomposes to two low temperature equilibrium phases; On the other hand, in the Co–Zr binary system, $\text{Co}_{50}\text{Zr}_{50}$ intermetallic compound has a B2 structure which is stable at room temperature. Therefore the addition of cobalt to Cu–Zr system shifts the stability temperature of CuZr-B2 phase to the lower temperatures. It means that this phase is established at lower temperatures compared to $\text{Cu}_{50}\text{Zr}_{50}$ and as the X-ray results show in $\text{Cu}_{45}\text{Co}_5\text{Zr}_{50}$ composition B2 phase coexists with monoclinic phase in the as-cast situation. Consequently A_s and A_f appear at lower temperatures in DSC curves; also in the reverse transformation M_s and M_f start later at lower temperatures.

In order to investigate the reversibility of the transformation and to find out if any new phases are being formed, all the samples were characterized with X-Ray device after DSC. The results (not shown here) show that after DSC each composition has the same phases as it had in the as-cast mode. It means that the transformation is reversible. Fig. 3 shows the MT temperatures plotted versus cobalt content and as it was discussed the addition of cobalt shifts the martensitic transformation temperatures to lower temperatures and stabilizes the B2 temperature range to lower ranges. Extrapolating the data shows that by increasing the cobalt up to 7.5 at.%, M_s decreases to room temperature.

In order to investigate the effect of thermal cycling on $\text{Cu}_{50-x}\text{Co}_x\text{Zr}_{50}$ ($x=2, 3, 4$ and 5 at.% Co) compositions, 3 thermal cycles were performed on the samples. Fig. 4 shows the thermal cycling

Download English Version:

<https://daneshyari.com/en/article/1619521>

Download Persian Version:

<https://daneshyari.com/article/1619521>

[Daneshyari.com](https://daneshyari.com)