



## Antiferromagnetic Kondo lattice behaviour of YbNiAl<sub>2</sub> alloy

D.P. Rojas\*, J. Rodríguez Fernández, J.I. Espeso, J.C. Gómez Sal

DCITIMAC, Facultad de Ciencias, Universidad de Cantabria, Av de los Castros S/N, Santander, 39005, Spain

### ARTICLE INFO

#### Article history:

Received 8 March 2010

Received in revised form 20 April 2010

Accepted 24 April 2010

Available online 5 May 2010

#### Keywords:

Yb compounds

Antiferromagnetic

Electrical transport

Kondo effect

Magnetoresistance

Heat capacity

### ABSTRACT

We report measurements on the thermal and electronic transport properties for the YbNiAl<sub>2</sub> compound. At low temperatures, the electrical resistivity exhibits a logarithmic increase below a local minimum at 23 K, followed by a sharp decrease into the coherent/magnetically ordered state below 4.8 K. From the magnetic contribution to the specific heat ( $c_{mag}$ ), a Kondo temperature  $T_K = 5$  K and an entropy value of  $0.8R\ln 2$  at the transition are estimated. The extrapolation of  $c_{mag}/T$  vs  $T$  plot to lower temperatures gives an estimate of the electronic coefficient  $\gamma_0 = 300$  mJ/mol K<sup>2</sup>, which classifies this compound as a moderate heavy-fermion system. The magnetoresistance shows a single impurity Kondo scaling, with a single-ion characteristic temperature  $T^* = -1.2$  K. This negative sign implies the presence of strong ferromagnetic correlations, as suggested from the previously reported magnetization data. The results indicate that the YbNiAl<sub>2</sub> alloy is an antiferromagnetic Kondo lattice system with a similar energy scales of the Kondo and RKKY interactions.

© 2010 Elsevier B.V. All rights reserved.

### 1. Introduction

Ce, Yb and U compounds display a variety of ground states as intermediate valence, heavy-fermion behaviour and Kondo effect [1–3]. Among them, a special attention have been paid to the study of magnetically ordered Kondo lattices, which is a current topic of great interest because the observed phenomenology near to the quantum critical point [4]. The nature of the ground state in Kondo lattice materials depends on the competition between the Kondo effect and the Ruderman–Kittel–Kasuya–Yosida (RKKY) interactions [5,6]. When RKKY interaction dominates, the system orders magnetically, for comparable strength of these two interactions, the system shows Kondo-type behaviour but still orders magnetically. In this intermediate situation an enhanced density of electronic states at the Fermi energy is possible and a magnetically heavy-fermion state could be observed. Finally, when the Kondo-type interaction dominates, the ground state is nonmagnetic. It is worth noticing that most of the studies on Kondo lattice systems have been devoted to Ce and U compounds, whereas only few examples in Yb compounds has been reported. In this sense, YbNiAl was characterized as a heavy-fermion ( $\gamma = 350$  mJ/mol K<sup>2</sup>) with antiferromagnetic order at  $T_N = 2.9$  K and a characteristic Kondo behaviour below 100 K, and down to 3 K. In YbPtAl a local minimum was observed at  $T = 35$  K, followed by a maximum at 10 K, and a step decrease below  $T_N = 5.8$  K indi-


cating the onset of antiferromagnetism [7,8]. In YbPtIn, YbRhSn and YbNiGa a typical logarithmic increase with the decrease of the temperature was also observed [9]. In the other hand, other antiferromagnetic Kondo lattice compounds also display additional interesting features as quenched superconductivity by the Kondo effect in Yb<sub>2</sub>Fe<sub>3</sub>Si<sub>5</sub> [10] and antiferromagnetic fluctuations in YbNiB<sub>4</sub> [11]. The magnetic properties of YbNiAl<sub>2</sub> alloy, crystallizing in orthorhombic MgCuAl<sub>2</sub>-type of structure were reported very recently [12]. An antiferromagnetic behaviour below  $T_N = 4.8$  K, and a field-induced ferromagnetic order above 9.3 kOe were observed. In view of this, we present in this work a more detailed study of this alloy with the thermal and electronic transport properties. The measurements were performed in a Quantum Design PPMS in the temperature range 0.35–300 K and magnetic fields up to 90 kOe.

### 2. Results and discussion

In Fig. 1, the temperature dependence of the specific heat of YbNiAl<sub>2</sub> is presented. Above the magnetic transition, for  $T > 15$  K, the data was analyzed considering the electronic, phononic and crystal field contributions, the last one with three doublets according to the splitting of the Yb<sup>3+</sup> ion in orthorhombic symmetry. The result of the fitting procedure yields  $\gamma = 33$  mJ/mol K<sup>2</sup>,  $\theta_D = 364$  K,  $\Delta_1 = 101$  K,  $\Delta_2 = 205$  K and  $\Delta_3 = 227$  K, and the result is depicted by a solid line in Fig. 1. In the inset of this figure, details of the field dependence of the specific heat at low temperatures around the magnetic transition are shown. At zero magnetic field, a local maximum at 4.1 K, associated to the magnetic transition, is observed.

\* Corresponding author. Tel.: +34 942 202069; fax: +34 942 201402.


E-mail addresses: [rojasd@unican.es](mailto:rojasd@unican.es), [dpupo@yahoo.com.br](mailto:dpupo@yahoo.com.br) (D.P. Rojas).

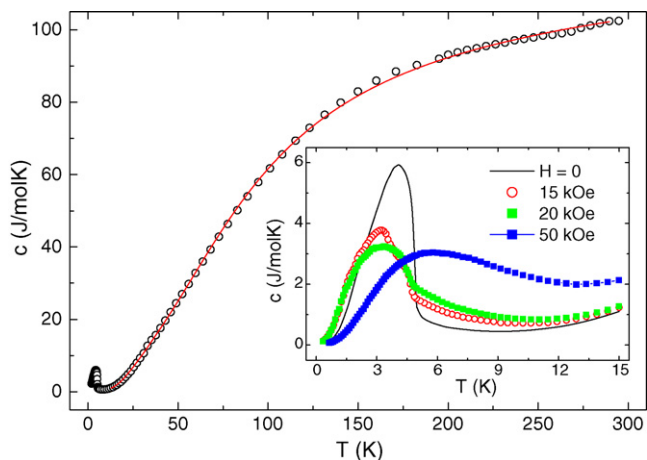


**Fig. 1.** Temperature dependence of the specific heat of the YbNiAl<sub>2</sub> intermetallic. The solid line is the result of the fitting considering the electronic, phononic, and crystal field contributions. In the inset, details of the magnetic field dependence of the specific heat around the magnetic transition are presented.

This peak shifts to lower temperatures (3.3 K) when the magnetic field increases up to 15 kOe, and to higher temperatures (5.8 K) with its further increase, as presented for 50 kOe, which is consistent with an antiferromagnetic behaviour and a field-induced ferromagnetic order, as observed from the DC-magnetic susceptibility measurements [12].

The magnetic contribution to the specific heat ( $c_{mag}$ ) can be obtained by subtraction of the electron–phonon contribution, using the values of  $\gamma = 33$  mJ/mol K<sup>2</sup> and  $\theta_D = 364$  K extracted from the fitting of the high temperature data, as presented in Fig. 2. Using the  $S = 1/2$  resonant level model which relates the jump  $\Delta c_{mag}$  with the  $T_N/T_K$  ratio, and the value of the jump at the magnetic transition of 5.4 J/mol K, a Kondo temperature  $T_K = 5$  K can be estimated [13]. The magnetic entropy ( $S_{mag}$ ) at several magnetic fields can also be calculated, using the expression  $S_{mag} = \int (c_{mag}/T) dT$ , and the result is presented in Fig. 2. It reaches a value of  $0.8R \ln 2$  at the magnetic transition, as expected from the magnetic ground state doublet with a reduced value from  $R \ln 2$  due to the Kondo effect, which is in agreement with the estimated value of  $T_K$  [13]. Another visible feature is that with the increase of the magnetic field, the magnetic entropy smears out, which is consistent with the ferromagnetic order. The analysis of the  $c_{mag}/T$  vs  $T$  dependence at low temperatures gives an estimate of the electronic

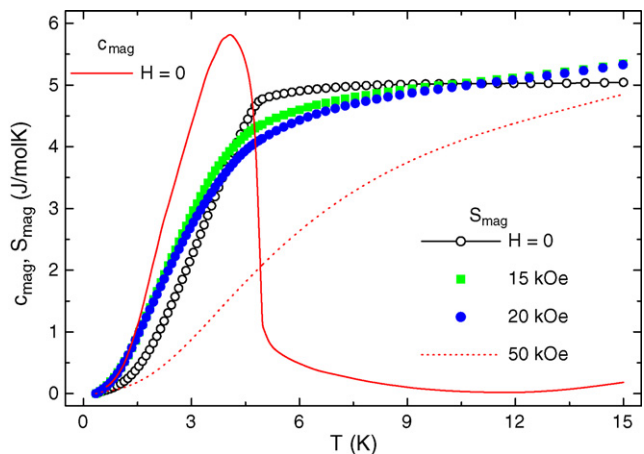

**Fig. 2.** Magnetic contribution to the specific heat and field dependence of the magnetic entropy. At zero field, the magnetic entropy reaches a value near to  $R \ln 2$  characteristic of a doublet ground state.

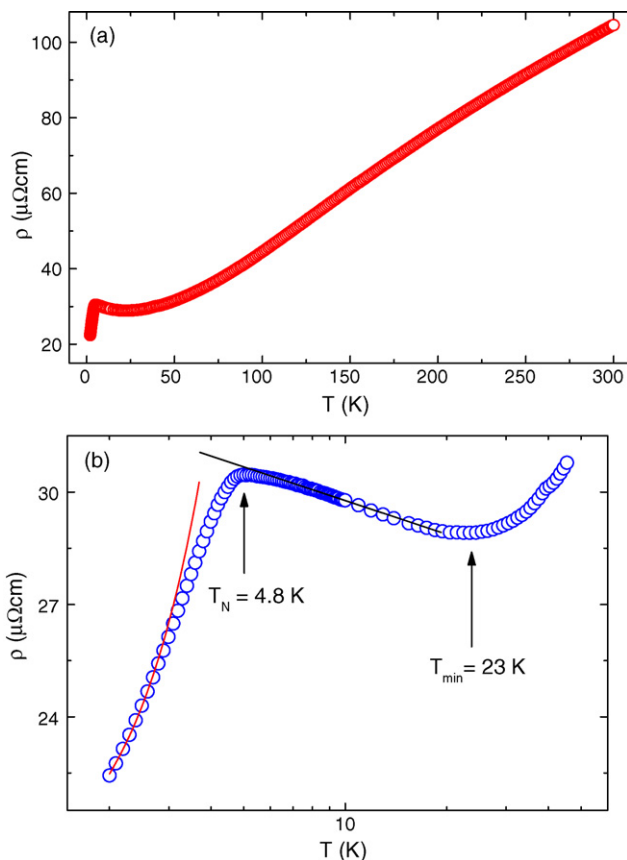

**Fig. 3.** (a) Temperature dependence of the electrical resistivity. (b) Details of low temperature region with a local minimum around 25 K and a logarithmic dependence characteristic of the Kondo effect down to 5 K. The solid line below  $T_N$  is a fit with a  $\rho_0 + AT^2$  dependence.

coefficient  $\gamma_0 = 300$  mJ/mol K<sup>2</sup>, thus indicating, a moderate heavy-fermion behaviour of the YbNiAl<sub>2</sub> compound.

Measurements of the electrical resistivity also give useful information about the magnetic and Kondo interactions. In Fig. 3a, the temperature dependence of the electrical resistivity is shown. At high temperatures, well above the magnetic transition, a typical metallic behaviour is observed. However, a deviation from this behaviour is clearly seen below 40 K. Fig. 3b displays details of the low temperature region. A local minimum at 23 K and a maximum near to the magnetic transition at  $T_N = 4.8$  K, are observed. At low temperatures below the transition the data is well described considering the  $\rho_0 + AT^2$  dependence with  $\rho_0 = 19 \mu\Omega \text{ cm}$  and  $A = 0.81 \mu\Omega \text{ cm K}^{-2}$ . The first term can be ascribed to the residual resistivity, due to impurities and lattice faults (in a magnetic or nearly magnetic metal this term includes a spin fluctuation contribution) and the second term is related to electron–electron and/or electron–magnon scattering [14].

In Fig. 4, the temperature dependence of the electrical resistivity at different magnetic fields is presented. In the high temperature region for  $T > 20$  K, above the magnetic transition, the electrical resistivity rises with the increase of the magnetic field, which is consistent with a metallic behaviour [15]. However, the opposite behaviour is observed for lower temperatures where the scattering of electrons with the spin waves is relevant with the appearance of magnetic correlations. In addition, the Kondo scattering mechanism may also play an important role [16], as follows from inspection of Fig. 3b. In order to analyze the magnetic field dependence of  $\rho(T)$  below the magnetic transition, a fitting of the data with the  $\rho_0 + A(H)T^2$  dependence was carried out, and the results are presented in the inset of Fig. 4. This last result indicates that

Download English Version:

<https://daneshyari.com/en/article/1619751>

Download Persian Version:

<https://daneshyari.com/article/1619751>

[Daneshyari.com](https://daneshyari.com)