



# Synthesis and magnetic properties of iron nanoparticles confined in highly ordered mesoporous carbons

Tai-Ming Zhang, Dong-Lin Zhao\*, Li Yin, Zeng-Min Shen

State Key Laboratory of Chemical Resource Engineering, Beijing University of Chemical Technology, Beijing 100029, China

## ARTICLE INFO

### Article history:

Received 20 June 2010

Received in revised form 5 August 2010

Accepted 6 August 2010

Available online 19 August 2010

### Keywords:

Magnetically ordered materials

Chemical synthesis

Transmission electron microscopy

X-ray diffraction

Magnetic measurements

## ABSTRACT

The iron nanoparticles confined in highly ordered mesoporous carbons (OMCs) have been directly synthesized through a simple soft templating method by using resorcinol–formaldehyde (RF) as a carbon precursor, triblock copolymer Pluronic F127 as a template agent and hydrated iron nitrite as an iron source. This synthesis was carried out by the carbonization of the F127/[Fe(H<sub>2</sub>O)<sub>9</sub>](NO<sub>3</sub>)<sub>3</sub>/RF composites self-assembled in an acidic medium, which was generated from the self-hydrolysis of precursory salt. The effects of iron loading contents on the morphology, pore feature and magnetic properties of the iron nanoparticles confined in OMCs were characterized by the X-ray diffraction, transmission electron microscopy, nitrogen sorption and vibrating-sample magnetometer measurement. It was found that Fe<sup>3+</sup> was captured by the network of F127/RF and further reduced into metallic Fe nanoparticles during the carbonization. The results showed that the carbon material exhibited highly ordered mesoporous structure, and the iron nanoparticles were uniformly confined in the OMC walls when the Fe/R molar ratio was around 0.1. The saturation magnetization *M<sub>s</sub>*, remanent magnetization *M<sub>r</sub>*, and coercivity *H<sub>c</sub>* of the Fe/OMC composites increased with the increasing of Fe/R molar ratio. The Fe/OMC composites exhibited the soft ferromagnetic behavior and the magnetization parameters could be adjusted by the content of iron.

© 2010 Elsevier B.V. All rights reserved.

## 1. Introduction

Ordered mesoporous carbons (OMCs) reported in 1991 [1] have attracted significant interest [2–11] due to their structural regularity, large specific surface area, thermal stability, chemical inertness, biocompatibility, and many potential applications in the fields of absorption [12], separation [13], hydrogen storage [14], catalyst supports [15,16], biomedical engineering [17] and energy storage [18–22]. For further applications of OMCs, metal nanoparticles were employed into the OMCs to modify their properties and broaden applications in the fields of adsorption, catalysis, lithium-ion batteries, electrochemical capacitors and magnetic separation, etc. [23,24]. There are three possible locations of guest particles in the OMCs. The guest particles may be located inside the mesochannels, within the walls or at the external surfaces of the OMCs. The metal nanoparticles confined inside the mesochannels and within the walls of OMCs are effectively protected by OMCs from oxidation and consequently showing long-term stability. When the metal nanoparticles stay inside the mesochannels, they will cause

the reduction of surface area and pore volume. Incorporation of guest nanoparticles inside the walls of OMCs is an effective way to overcome this drawback. Moreover, in such structure, the guest nanoparticles are embedded in carbon walls, so they are accessible to gas and liquid molecules which enter the mesochannels from outside media [25].

So far, there are generally two routes to insert nanoparticles into the OMCs. One route is incorporating metal and compound nanoparticles (Pt [26,27], Ru [28], SnO<sub>2</sub> [29,30], MnO<sub>2</sub> [31,32]) into the pre-synthesized OMCs using impregnation, adsorption or ion exchange methods. Another route is infiltration of an appropriate carbon precursor and metal source into the mesopores of the silica template, followed by thermal polymerization, carbonization and subsequent removal of the silica framework with HF or NaOH solution [33–38]. Nevertheless, the above routes are fussy, time-consuming and high cost multi-step synthesis procedures, including repeated impregnation with carbon and metal precursors and the removal of hard templates [23]. Meanwhile, the mesoporous materials containing Fe, Co, Ni magnetic nanoparticles have fascinating magnetic properties, and many applications including magnetic storage media, ferrofluids, and as magnetic carriers for drug targeting [36,39–42]. Yao et al. synthesized the magnetically separable Ni/OMCs with a highly ordered cubic structure by the carbonization of the F127/[Ni(H<sub>2</sub>O)<sub>6</sub>](NO<sub>3</sub>)<sub>2</sub>/RF composites self-assembled in an alkaline medium [23]. Li et al. prepared the

\* Corresponding author at: State Key Laboratory of Chemical Resource Engineering, Beijing University of Chemical Technology, No.15 Bei Sanhuan East Road, Beijing 100029, China. Tel.: +86 10 64434914; fax: +86 10 64454912.

E-mail address: [dlzhao@mail.buct.edu.cn](mailto:dlzhao@mail.buct.edu.cn) (D.-L. Zhao).

highly ordered Fe/OMCs using a soft templating route [24]. Xing et al. synthesized  $\alpha$ -Fe-incorporated nanoporous carbon through nanocasting strategy by using ordered mesoporous silica as a hard template and sugar as a carbon source [39].

Herein, we employed a simple soft templating method to synthesize magnetic Fe nanoparticles confined in OMCs (Fe/OMCs) under an acidic medium generated from the self-hydrolysis of precursory salt. The magnetic Fe/OMCs were fabricated through the self-assembly of F127, resorcinol–formaldehyde (RF) polymer and  $[\text{Fe}(\text{H}_2\text{O})_9](\text{NO}_3)_3$ . Wherein, RF was used as a carbon precursor, triblock copolymer Pluronic F127 as a template agent and  $[\text{Fe}(\text{H}_2\text{O})_9](\text{NO}_3)_3$  as an iron source. The effects of Fe loading contents on the morphology, pore feature and magnetic properties of Fe/OMCs were investigated.

## 2. Experimental

### 2.1. Chemicals

Triblock poly(ethylene oxide)-*b*-poly(propylene oxide)-*b*-poly(ethylene oxide) copolymer Pluronic F127 ( $M_w = 12,600$ ,  $\text{PEO}_{106}\text{PPO}_{70}\text{PEO}_{106}$ ) was purchased from Aldrich Corp., and resorcinol, formaldehyde and hydrated iron nitrate ( $[\text{Fe}(\text{H}_2\text{O})_9](\text{NO}_3)_3$ ) were purchased from Beijing Chemical Corp. All chemicals were analytical pure grade and were used as received without any further purification.

### 2.2. Synthesis

The synthesis compositions were in the range of resorcinol/formaldehyde/F127/ $[\text{Fe}(\text{H}_2\text{O})_9](\text{NO}_3)_3$  (molar ratio) = 1:2:0.013:0.05–0.20. The resulting composite was designated as Fe/OMC–M, M denoted the molar ratio of  $[\text{Fe}(\text{H}_2\text{O})_9](\text{NO}_3)_3$  to resorcinol (Fe/R) at the beginning of polymerization. In a typical preparation, 2.45 g F127 and 1.65 g resorcinol were dissolved absolutely in 14 g of ethanol/water (1/1 vol%) solution under magnetic stirring at room temperature (signed A). An appropriate amount of hydrated iron nitrate corresponding to Fe/resorcinol molar ratio equal to 0.05, 0.10, 0.15, 0.20 was dissolved in 7 g of ethanol/water (1/1 vol%) solution (signed B). When solution B turned to be a light brown solution, it was dropped into solution A. After stirring for 2 h, 2.3 mL of formaldehyde (37%) was subsequently added dropwise to the above solution containing F127, resorcinol and  $[\text{Fe}(\text{H}_2\text{O})_9](\text{NO}_3)_3$ . Followed by an additional 2 h stirring, the mixture was kept standing until it turned cloudy and began to separate into two layers. This two phase mixture was further kept aging for two days. Subsequently, the upper light layer was discarded while the lower dark phase was stirred overnight until a sticky monolith was formed. Finally, the monolith was dried in an oven at 90 °C for 12 h and carbonized at 800 °C for 2 h, with a heating rate of 1 °C/min from 25 to 400 °C and 5 °C/min from 400 to 800 °C under a nitrogen atmosphere, to obtain the Fe/OMCs.

### 2.3. Characterization

Powder X-ray diffraction (XRD) patterns were recorded on a Rigaku D/max-2500B2+/PCX system operating with  $\text{Cu K}\alpha$  radiation ( $\lambda = 1.5406 \text{ \AA}$ ). For small-angle XRD measurement with  $2\theta \leq 5^\circ$ , the step width and acquisition time were 0.002° and 0.24 s, respectively, and for wide-angle XRD measurement 0.02° and 0.15 s were employed.

The transmission electron microscope (TEM) images were obtained using a Hitachi H-800 transmission electron microscope operating at 200 kV. The high resolution TEM (HRTEM) images were recorded on a JEOL JEM-3010 microscope operating at 300 kV. Before TEM observations, the samples were prepared by dispersing the products in ethanol with an ultrasonic bath for 10 min and then one drop of the resulting suspension was placed on a copper grid.

Nitrogen adsorption–desorption isotherms were measured with an ASAP 2010 Micromeritics Instrument at 77 K. Before the measurement, the samples were degassed at 473 K for 12 h. The specific surface areas were calculated using the Brunauer–Emmett–Teller (BET) equation in a relative pressure range between  $P/P_0 = 0.05$ –0.3. The pore size distribution was estimated from the desorption branch of the isotherm using the Barrett–Joyner–Halenda (BJH) method.

The magnetic properties of Fe/OMCs were measured at room temperature with a vibration sample magnetometer (VSM, Lakeshore, Model 7307).

## 3. Results and discussion

The small-angle XRD patterns of Fe/OMC composites with different iron loadings are presented in Fig. 1. As shown in Fig. 1, the Fe/OMC-0.05, Fe/OMC-0.10 and Fe/OMC-0.15 samples exhibit intense diffraction peaks at  $2\theta$  range of 0.8–1°, which can be

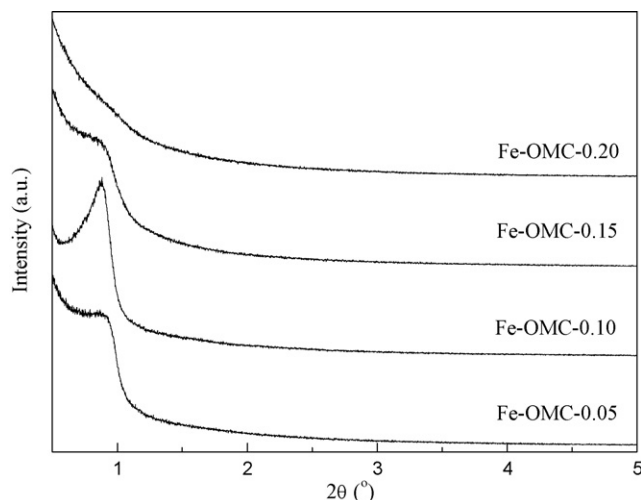


Fig. 1. Small-angle XRD patterns of Fe/OMC composites with different iron loadings.

indexed to [100] reflection of hexagonal mesostructure [24]. A sharp and narrow diffraction peak at  $2\theta = 0.89^\circ$  can be observed for Fe/OMC-0.10, which indicates that this sample possesses well-ordered mesostructure. However, no obvious diffraction peak was detected in the Fe/OMC-0.20 sample, implying that the optimal ordering of the hexagonal mesostructure can be obtained when Fe contents around Fe/R = 0.1 and the ordering decreased as the Fe content was either greater or smaller than this ratio. In the Fe/OMCs synthesis, when iron precursor  $[\text{Fe}(\text{H}_2\text{O})_9](\text{NO}_3)_3$  was added into the reaction mixture containing resorcinol–formaldehyde (RF) and F127, the acid was generated due to the hydrolysis of precursory salt. And it could be used as the catalyst for cross-linking between resorcinol and formaldehyde. The excess iron loading might disturb the self-assembly process and thus influence the final ordering of the mesostructure [24].

Fig. 2 shows the wide-angle XRD patterns of Fe/OMC composites with different iron loadings. The wide-angle XRD patterns exhibit resolved diffraction peaks at  $2\theta = 44.7^\circ$  for all samples, which are in accordance with the (110) diffraction of body-centered cubic (bcc)  $\alpha$ -Fe (JCPDS card No. 06-0696). It indicates that  $\text{Fe}^{3+}$  was captured by the network of F127/RF and further reduced into metallic Fe nanoparticles during the carbonization. The weak diffraction peaks at  $35.8^\circ$  of Fe/OMC-0.05 and Fe/OMC-0.10 samples are in accordance with the (311) diffraction of  $\gamma$ - $\text{Fe}_2\text{O}_3$  (JCPDS card No.

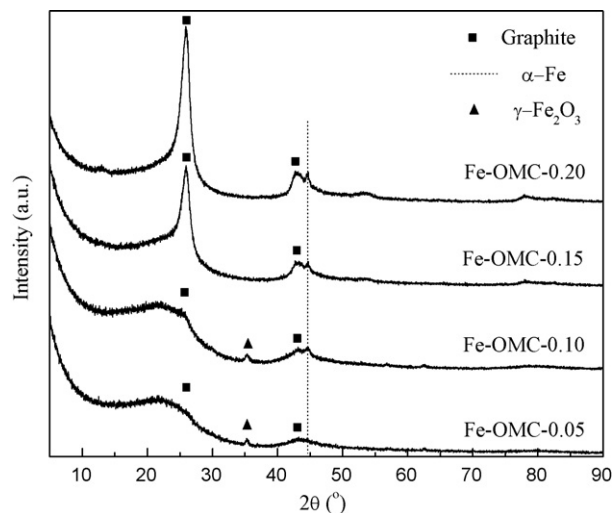


Fig. 2. Wide-angle XRD patterns of Fe/OMC composites with different iron loadings.

Download English Version:

<https://daneshyari.com/en/article/1619835>

Download Persian Version:

<https://daneshyari.com/article/1619835>

[Daneshyari.com](https://daneshyari.com)