



Letter

Effect of hafnium carbide on the grain refinement of Mg–3 wt.% Al alloy

Ling Wang^a, Young Min Kim^{b,*}, Jehyun Lee^a, Bong Sun You^b^a School of Nano and Advanced Materials Engineering, Changwon National University, 9 Sarimdong, Changwon, Gyeongnam, 641773, Republic of Korea^b Light Metals Research Group, Korea Institute of Materials Science, 66 Sangnam dong, Changwon, Gyeongnam, 241010, Republic of Korea

ARTICLE INFO

Article history:

Received 16 November 2009

Received in revised form 22 March 2010

Accepted 25 March 2010

Available online 2 April 2010

Keywords:

Magnesium alloys

Grain refinement

Heterogeneous nucleation

Hafnium carbide

Casting

Scanning electron microscopy

ABSTRACT

This study investigates how different amounts of hafnium carbide (HfC) powder affect the grain refinement of Mg–3 wt.% Al alloys. Even though HfC and Mg have a similar crystallography, the use of HfC powder is not a very effective means of refining pure magnesium with typical columnar grains. However, Mg–3 wt.% Al alloy can be successfully refined by the addition of HfC due to the in situ formation of Al₄C₃. The addition of 0.7 wt.% of HfC into Mg–3 wt.% Al alloy leads to the smallest grain size, and its average grain size is refined from 365 μm to 145 μm .

© 2010 Elsevier B.V. All rights reserved.

1. Introduction

The last decade has witnessed a significant increase in the use of magnesium alloys for engineering components in the automotive industry. Magnesium alloys are promising structural light materials due to their high specific strength and high specific stiffness. However, poor ductility and workability have limited the application of magnesium alloys. Improvements in ductility and workability are therefore desirable [1]. Grain refinement is an effective method of improving the microstructural homogeneity, mechanical properties, and workability of magnesium alloys.

Magnesium alloys can be divided into two groups: aluminum-free alloys and aluminum-bearing alloys. Zirconium is an effective grain refiner for magnesium alloys that contain little or no Al, Mn, Si, and Fe (because Zr forms stable compounds with these elements) [2]. The most commonly accepted mechanism of grain refinement by Zr is the lattice registry between Zr (hcp structure, $a=0.323\text{ nm}$, $c=0.514\text{ nm}$) and Mg (hcp structure, $a=0.320\text{ nm}$, $c=0.520\text{ nm}$). Therefore, Zr particles are believed to provide efficient nucleation sites. Large numbers of grain refining methods have been proposed in aluminum-containing magnesium alloys. However, there are few available commercial grain refiners for magnesium alloys. Adding chlorinated hydrocarbons (C₂Cl₆) is an effective method in industry, however, its use should be restricted

due to the emission of toxic gases which are detrimental to the workplace and environment. In the recent years, many researches have been conducted on seeking alternative of C₂Cl₆. The addition of compounds, such as ZnO [3], AlN [4], Al₂Y [5] and MgCO₃ [6], exhibits good grain refinement effect and some master alloys, such as Ni–C [7], Al–Ti–C–Si–B [8], Al–B [9], Mg–TiB₂ [10], Al–C [11] and Mg–Sr [12] can also refine Mg–Al alloys effectively.

One new grain refiner that is not harmful to the environment is HfC (FCC structure, $a=0.4641\text{ nm}$). It was selected by means of an edge-to-edge matching crystallographic model [13–15]. Due to the absence of any detailed observations about HfC characteristics in the literature, the effect of HfC powders on the grain refinement of aluminum-bearing magnesium alloy was investigated in this study.

2. Experimental procedures

The HfC powders (with an average particle size of 2 μm) wrapped in a pure magnesium capsule were added into the molten metal of pure magnesium and Mg–3 wt.% Al alloy at 740 °C in an electrical furnace by using a mild steel crucible in a protecting gas atmosphere (10% SF₆ and 90% CO₂). Different amounts of the HfC powder were used; that is, 0.20 wt.%, 0.70 wt.%, and 1.20 wt.%. The melt was kept at 740 °C for 30 min and then poured into a mild steel mold with a size of 25 mm × 80 mm × 125 mm coated with BN and preheated to 200 °C. The 12.5 mm × 25 mm samples for microstructure observation were sectioned on the plane as shown in Fig. 1. They were then heat-treated at 380 °C for 8 h and subsequently air-cooled to delineate the grain boundaries. Finally, microstructure characterization and qualitative analysis were carried out for the selected specimens of pure magnesium and Mg–3 wt.% Al alloys with HfC. For the measurement of grain size, a Nikon EPIPHOT 200 optical microscope and an I-solution software program were used in this study.

* Corresponding author. Tel.: +82 55 2803537; fax: +82 55 2803599.
E-mail address: ymkim@kims.re.kr (Y.M. Kim).

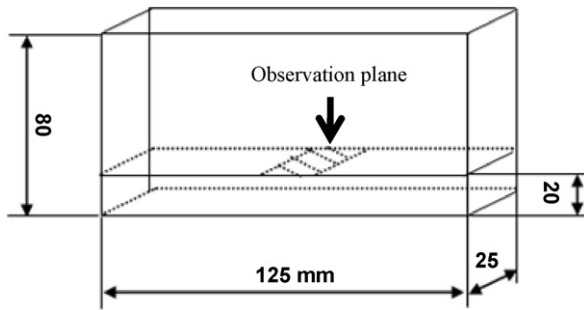


Fig. 1. Schematic illustration of sections from ingots selected for microscopy observations.

3. Results and discussion

Fig. 2 shows the macrostructures of the pure magnesium with HfC powder (for the entire observation plane in Fig. 1). The left and right-hand side of the images in Fig. 2 and Fig. 3 correspond to two edges of each specimen. As 0.2 wt.% of HfC was added into the pure magnesium, coarse columnar grains still remained, but their size tends to decrease as the amount of added HfC increases. The decrease in the size of the columnar grains indicates that HfC does have a grain refining effect on pure magnesium, though the effect is less significant than that observed in Mg-3 wt.% Al alloys.

Fig. 3 shows the optical macrostructure of a heat-treated Mg-3 wt.% Al alloy with different amounts of HfC powder. The columnar

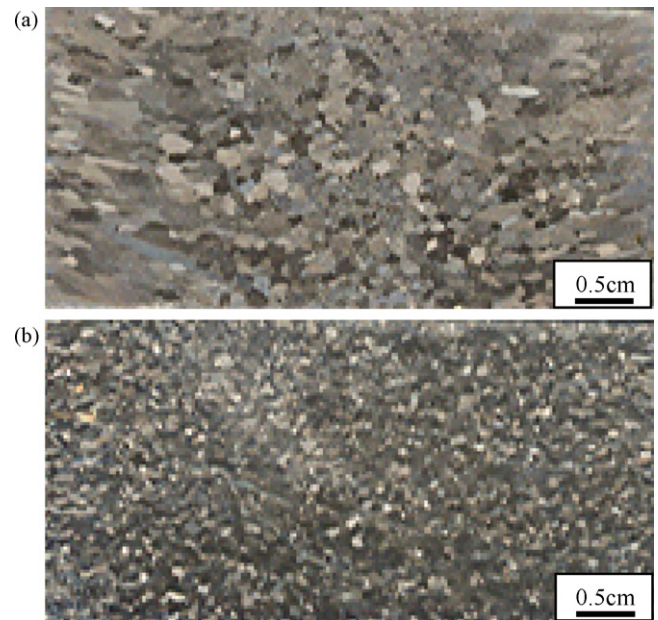


Fig. 3. Macrostructure of Mg-3 wt.% Al-x wt.% HfC. (a) $x = 0$; (b) $x = 0.7$.

grains at the edge of the optical microscope plane and equi-axed grains at the center of the plane can be found in Fig. 3(a). As 0.7 wt.% of HfC was added to the Mg-3 wt.% Al melt, the columnar grains were replaced by homogeneous fine equi-axed grains. It is obvious that the grains were successfully refined by adding HfC powder to the Mg-3 wt.% Al melt, as shown in Fig. 4. Fig. 5 shows the average grain size of the Mg-3 wt.% Al alloys with the addition of HfC. The grains of Mg-3 wt.% Al alloy without addition of HfC have an average size of about 365 μm , and they become smaller as the amount of HfC increases. The smallest grain size (145 μm) was obtained when 0.70 wt.% of HfC powders were added into the Mg-3 wt.% Al alloy. Any excess amount of HfC over 0.70 wt.% cannot contribute to the refining effect of the powders.

In order to elucidate the effect of HfC addition on grain refinement, the refined microstructure under a scanning electron microscope was examined. Besides $\text{Mg}_{17}\text{Al}_{12}$ and Al-Fe phases (not shown in Fig. 6 but commonly observed at the alloys with the same alloy compositions), the particle with high content of Fe, Al and Hf formed in the Mg-3 wt.% Al alloy with the addition of HfC, indicating that the new particle in Fig. 6 formed after the HfC powder was added to Mg-3 wt.% Al alloy.

According to the classical theory of grain nucleation and growth, the final grain structure of as-cast polycrystalline materials is determined by the nucleation and growth conditions that prevail during phase transformations. The growth restriction factor (Q) is often used to quantify the role of solutes in controlling grain growth. The quantification is based on the segregation behavior of the solutes at the advancing solid-liquid interface. Thus,

$$Q = mC_0(k - 1) \quad (1)$$

where m is the gradient of the liquidus line of the Mg-X binary system, C_0 is the bulk concentration of the solute of interest (X), and k is the equilibrium partition coefficient of the solute (X) between the solid and liquid [16]. A solute with a higher value of Q is expected to have a stronger impact on grain restriction. However, the bulk concentration of HfC or its components (C and Hf), which are almost insoluble in molten magnesium, is close to zero. Thus, from the viewpoint of growth restriction, the addition of HfC appears to have poor grain refining efficiency.

Besides the growth restriction mechanism, heterogeneous nucleation is another important mechanism for refining the

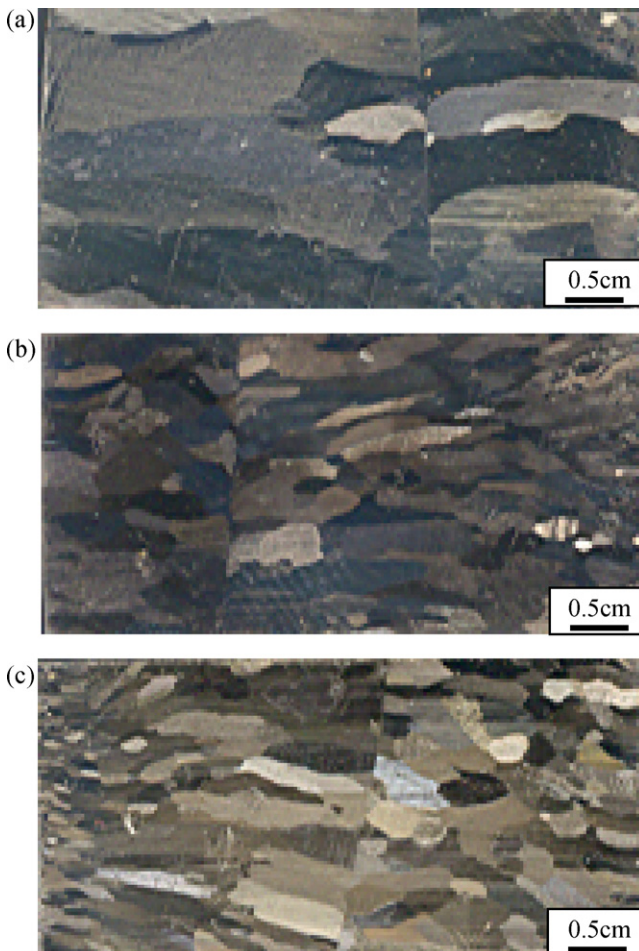


Fig. 2. Macrostructure of pure Mg-x wt.% HfC. (a) $x = 0.2$; (b) $x = 0.7$; (c) $x = 1.2$.

Download English Version:

<https://daneshyari.com/en/article/1620235>

Download Persian Version:

<https://daneshyari.com/article/1620235>

[Daneshyari.com](https://daneshyari.com)