



Green synthesis of silver nanoneedles using shallot and apricot tree gum

Mohammad Mahdi TAHERI^{1,2}, Mohammed Rafiq ABDUL KADIR², Noor Kamila AHMAD SHAFIAI²,
Tolou SHOKUH FAR^{3,4}, Mahtab ASSADIAN¹, Mostafa Rezazadeh SHIRDAR¹

1. Materials Engineering Department, Faculty of Mechanical Engineering,
Universiti Teknologi Malaysia, 81310 Johor Bahru, Johor, Malaysia;

2. Medical Devices & Technology Group, Faculty of Bioscience and Medical Engineering,
Universiti Teknologi Malaysia, 81310 Johor Bahru, Johor, Malaysia;

3. Department of Mechanical Engineering–Engineering Mechanics,
Multiscale Technologies Institute, Michigan Technological University, Houghton, MI 49931, USA;

4. Department of Bioengineering, University of Illinois at Chicago, Chicago, IL 60607, USA

Received 5 November 2014; accepted 6 May 2015

Abstract: A green synthesis method to produce silver nanoneedles was described using shallot and apricot tree gum (ATG). A fast, simple, and low cost method was used to synthesize silver with nanoparticle and nanoneedle shape from the silver nitrate solution. Shallot as a reducing agent and apricot tree gum (ATG) as a stabilizer and a capping agent were utilized to reduce and form silver ions into silver atoms with needle and particle shape. Moreover, high crystalline structures of silver nanoparticles (AgNPs) with diameters of 8–20 nm and silver nanoneedles with average diameters of 50–60 nm and lengths of 5–10 μm were consequently synthesized by shallot and the mixture of shallot and ATG. A self-assembly mechanism was proposed to indicate the formation of needle-like structures of spherical AgNPs via carbon chains of ATG. The results indicate that the presence of ATG with shallot can transfer the reduced AgNPs into the silver nanoneedle. The findings were characterized using X-ray diffraction (XRD), ultra violet visible (UV-Vis) spectrometry, field emission scanning electron microscopy (FESEM), and transmission electron microscopy (TEM) techniques.

Key words: green synthesis; silver; nanoneedle; nanoparticle; shallot; apricot tree gum; self-assembly

1 Introduction

AgNPs have received a great deal of interest and have been used in many products such as optical sensors [1], semiconductors [2], and antibacterial agents [3]. Several methods to synthesize AgNPs such as laser ablation [4], electrochemical method [5], wet-chemical [6], mechanochemical [7], and green synthesis by plant extraction [8,9] have been described. Green synthesis is environmentally friendly, cost effective and therefore most likely to be massively produced [10]. Several studies [8–10] have reported the use of natural materials such as garlic and plant leaves extract as reduction agents to form spherical AgNPs [11]. Although, different surfactant and template agents such as nano-carbon [12], risodium citrate dehydrate and potassium tartrate [13] are utilized to prevent any agglomeration of synthesized

AgNPs. However, it is more desirable to have green template or surfactant agents for AgNPs synthesis.

Recently, the nanoneedle and nanowire structures of silver with its great optical and electrical properties enable many applications such as chemical and biological sensors, airborne water-soluble molecules in military sensors, SERS micro-detection devices and restorative dental materials [14–17]. YANG et al [11] reported that silver nanoneedle structures can be synthesized by using CVD, PVD, electrical sputtering and other techniques. Because complex processes are needed to obtain needle structure of silver, the use of simple, eco-friendly, and environmentally friendly techniques are necessary to synthesize the needle structure of silver. The use of certain reducing and capping agents in suitable condition are desirable to eliminate the need for these complex processes. DARROUDI et al [18] reported that certain sugars such

as furostanol saponins and flavonoids are potential good reducing agents, which can be found in shallots in high quantities [19]. However, the use of shallot as a reducing agent has not been previously described.

The present study was thus conducted to synthesize AgNPs from silver nitrate using shallot as a reducing agent and ATG as a stabilizer and a capping agent. Moreover, it was illustrated that ATG contains polysaccharides; therefore, it can help the formation of silver nanoneedles from AgNPs. Characterization of the nanoneedles and AgNPs were performed using XRD, UV-Vis, FESEM, and TEM.

2 Experimental

2.1 Materials

Silver nitrate (AgNO_3 , 99.9%) was purchased from Sigma Aldrich Company. ATG (*Prunus Armenia*) was obtained from the city of Taleghan, Iran, and shallots (*Allium ascalonicum*) were purchased from a local market.

2.2 Shallot extraction

Shallots were peeled and washed several times using deionized water. 5 g of shallot was ground and immediately centrifuged at 6000 r/min for 2 min. 5 mL of the extracted solution was added to 10 mL of double deionized water. The concentration of the solution (35 $\mu\text{g/mL}$) was measured by evaporating 5.0 mL of the solution in a vacuum oven at 40 °C. The remaining solid particles were then weighed.

2.3 Synthesis of AgNPs

To prepare silver nitrate solution with concentration of 35 mmol/L, 0.6 g of silver nitrate was dissolved in 100 mL of double deionized water. The silver nitrate solution was then used to prepare 3 different samples: 2, 4, and 8 mL of shallot solution. The combined solutions were then stirred using a magnetic stirrer for 15 min. As time passes, the colour of solutions changed, indicating the formation of solid AgNPs. The solutions were centrifuged at 4000 r/min for 20 min to ensure no agglomerations or large particles present inside the solutions. 0.2 and 0.4 g ATG were added to the solutions using an ultrasonic device, respectively. Additionally, the sample without ATG was used as the control.

3 Results and discussion

It was reported that the shallot bulb (*Allium ascalonicum*) contains the flavonoids and volatile sulfur compounds while the extraction of shallot was composed of polar compounds like quercetine, isorhamnetin and glucose [19]. In addition, it was demonstrated that

certain glucose, once oxidized into gluconic acid, reduced silver ions into silver atoms, which was the reason why shallot was chosen in the present study [18]. By adding extracted shallot solution as reducing agent to the silver nitrate solution, the color of solution will be changed. It is directly related to the reduction of silver ions to silver atoms. As a result, the color changes of solutions were observed over time, possibly due to the change in the surface resonance of AgNPs, i.e., due to changes in the size and shape of AgNPs. Moreover, it was reported by ROSIK [20] that 80% of chemical composition of ATG contained polysaccharide which is composed of methyl-*D*-glucuronic acid, *D*-xylose, and *D*-galactose. The ATG which acts as a stabilizer and capping agent was added to prevent the agglomeration of AgNPs. It has been suggested that the increase in the bright yellow color indicates the decrease of obtained silver particles size [21–23].

Figure 1 demonstrates the UV-Vis result of AgNPs, which corresponds to the spectrum band of 300–570 nm. The addition of extracted shallot solution to AgNO_3 solution changed the color of the solution from transparent to yellow due to the reduction of silver ions and the production of AgNPs. The existence of AgNPs also increased the excitation of surface plasmon vibration. The surface plasmon resonances peaked sharply at 320 nm, which indicated a particle size of less than 50 nm, which was also confirmed by TEM.

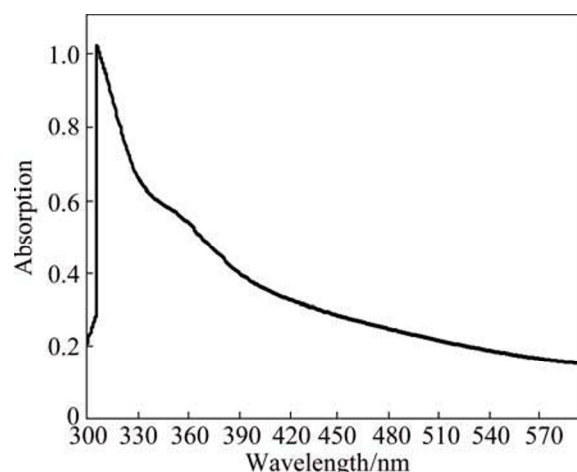


Fig. 1 UV-Vis spectrum of AgNPs

Figure 2 illustrates the X-ray diffraction pattern which demonstrates the crystallinity of AgNPs. The comparison between XRD standard patterns with the synthesized silver in this study confirmed the formation of nanocrystals, as proved by the peaks at 38°, 44°, 64° and 77° (2θ) corresponding to (111), (200), (220), and (311) planes, respectively [24]. Moreover, this pattern illustrates the face centered cubic (FCC) crystal structure of the AgNPs. In addition, sharp peaks of AgNPs reveal

Download English Version:

<https://daneshyari.com/en/article/1636479>

Download Persian Version:

<https://daneshyari.com/article/1636479>

[Daneshyari.com](https://daneshyari.com)