



Investigation of the effect of different oxygen partial pressure to LaAlO₃ thin film properties and resistive switching characteristics

Kou-Chen Liu ^{a,*}, Wen-Hsien Tzeng ^b, Kow-Ming Chang ^{b,c}, Jiun-Jie Huang ^b, Yun-Ju Lee ^d, Ping-Hung Yeh ^d, Pang-Shiu Chen ^e, Heng-Yuan Lee ^f, Frederick Chen ^f, Ming-Jinn Tsai ^f

^a Institute of Electro-Optical Engineering, Chang Gung University, Tao-Yuan 33302, Taiwan, ROC

^b Institute of Electronics, Department of Electronics Engineering, National Chiao Tung University, HsinChu 30010, Taiwan, ROC

^c Department of Electronic Engineering, I-Shou University, No. 1, Sec. 1, Syuecheng Rd., Kaohsiung 840, Taiwan, ROC

^d Department of Physics, Tamkang University, Tansui 251, Taiwan, ROC

^e Department of Material Science and Engineering, Minghsin University of Science and Technology, Hsinchu 340, Taiwan, ROC

^f Electronics and Optoelectronics Research Laboratory, Industrial Technology Research Institute, Hsinchu 310, Taiwan, ROC

ARTICLE INFO

Available online 4 May 2011

Keywords:

Lanthanum aluminate
Resistive switching
Switching memory
Oxygen partial pressure
LaAlO₃
Pulsed laser deposition

ABSTRACT

The pulsed laser deposition and growth of a high-k dielectric lanthanum aluminate LaAlO₃ (LAO) thin film on indium tin oxide/glass substrate at different oxygen partial pressure was studied. Based on the pulsed laser deposition growth mechanism, we explain how a difference in the oxygen partial pressure influences the surface roughness, formation of an interfacial layer, and the transparent resistive switching characteristics of LAO thin films. The micro-structure and oxygen concentration difference inside LAO thin films may be the main reason for the difference in electrical and resistive switching properties. Films grown at higher oxygen partial pressure displayed more reliable resistive switching performance, due to the formation of the interfacial layer and a lower concentration of oxygen vacancies. The interfacial layer serves as a good oxygen reservoir and the involvement of more oxygen ions ensures the switching reliability. The migration of oxygen ions between the interfacial layer and the LAO film under applied bias may be the switching mechanism.

© 2011 Elsevier B.V. All rights reserved.

1. Introduction

The high demand for nonvolatile memory (NVM) with low power consumption, high density, and compatibility with conventional complementary metal oxide semiconductor (CMOS) technology has led to increased research. As a result, resistive random access memory (RRAM), which is based on the concept of resistance switching (RS), has emerged as one of the prime candidates for next generation NVM [1–3]. Several materials have been shown to exhibit RS characteristics, including transition metal oxide [4–6], perovskite oxides [7–9], and some organic materials [10]. Various models such as the filamentary model [11,12] and the charge trapping model [13,14] have been proposed to explain the RS mechanism. Most of these materials show polycrystalline structures, and the existence of the grain boundaries may facilitate the formation of the conducting filaments and determine the electrical properties [15]. In recent years, amorphous materials have also attracted attention since they are free from grain boundaries which improve film uniformity and avoid detrimental pad-to-pad variations in switching characteristics, in contrast to polycrystalline cells. However, the resistive switching mechanism in

amorphous films might be different from that in polycrystalline films due to the absence of these grain boundary defects in amorphous thin films.

In this study, we investigate the use of amorphous LaAlO₃ (LAO) thin films for RRAM devices. The ternary oxide LaAlO₃, is one of the materials that has been identified by the semiconductor industry as a potential replacement for SiO₂ in gate dielectric layers. It has a high dielectric constant of 25 [16] and has large band offsets (over 2 eV) with silicon [17]. Furthermore, the thin film of LAO is amorphous at temperatures up to 800 °C [18], the band gap is predicted to be 6.2 eV [19], and it is theoretically thermally stable in contact with silicon at up to 1000 °C [20]. Since the LAO thin film exhibits reliable RS properties, it is a good choice for 1T1R integration applications. However, the use of a lanthanum-based dielectric layer for the RRAM applications has not received great attention. In lanthanum-based films, the oxygen vacancy density is critical for determining the resistance values. The influence of oxygen partial pressure during pulsed laser deposition (PLD) on the thin film morphology and resistive switching properties of LAO is the subject of our study.

2. Experimental method

The PLD process was used to deposit the LAO films using an LAO target as the resistive layer of transparent RRAM (T-RRAM) device on

* Corresponding author.

E-mail address: jacobliu@mail.cgu.edu.tw (K.-C. Liu).

an indium tin oxide (ITO)/glass substrate. A KrF excimer laser ($\lambda = 248$ nm) was used as the light source for PLD with a pulse duration of 25 ns, a repetition rate of 3 Hz, and laser energy of 500 mJ. The distance from the target to the substrate was 10 cm and the target rotation rate was 5 rpm. The ambient oxygen pressure, which is the most important parameter of the PLD process, was varied, taking values of 0.93, 1.87, and 3.73 Pa. We use ITO as a top electrode (TE). A 100 nm ITO film was deposited using the dc sputter system using a shadow mask with a diameter of 1200 μm . The electrical characterization was carried out using an Agilent 4156C semiconductor parameter analyzer (SPA) at room temperature. The surface morphology, LAO film thickness and chemical composition of LAO thin films was characterized by atomic force microscopy (AFM), a surface profiler and X-ray photoelectron spectroscopy (XPS). Cross-sectional high resolution transmission electron microscopy (HR-TEM) was employed to examine the microstructure. The current flow from the top to the bottom electrode was defined as a positive sweep.

3. Results and discussion

The surface roughness of LAO thin film with oxygen partial pressure of 0.93 (L1), 1.87 (L2), and 3.73 (L3) Pa was measured by AFM. The root mean square (RMS) surface roughness of L1, L2, and L3 samples was about 3.66, 4.00, and 4.38 nm, respectively, as shown in Fig. 1(a)–(c). The thicknesses of the L1, L2, and L3 samples were about 25, 28, and 40 nm, as measured using the surface profiler and TEM analysis. The PLD process parameter such as oxygen pressure [21] or substrate temperature [22], can influence the thin film growth mechanism and the nucleation reaction—the LAO thin film thickness and surface roughness increased linearly with oxygen content. This increase may be related to some physical properties of thin film growth conditions. The cross sectional structures of the stacked ITO/LAO/ITO devices were characterized by HR-TEM, as shown in Fig. 2(a)–(c). A very clear interfacial layer (IL) with a rougher surface between the ITO substrate and the LAO film deposited in the L3 sample is clearly observed, while no IL can be observed in L1. This indicates that LAO thin film deposition at a higher oxygen pressure aids the formation of the IL. The three LAO samples were all in the amorphous phase due to the high crystallization temperature of about 800 °C [18].

To explain how the oxygen pressure influences the thin film growth during the PLD process, we need to examine the mechanism of the PLD fabrication process. The PLD-deposited thin film properties show a high correlation with the conditions in the chamber. The oxygen gas has two effects expected to influence the film formation. It alters the evaporated plume length, and provides a high flux of background gas particles bombarding the surface during the deposition. The evaporated plume is a critical factor to determine the deposited thin film quality during PLD. According to Dyer et al. [23], the deposited thin film quality was influenced by the specific effect of the plume length and ambient pressure. The plume length L and the oxygen pressure P_o follow $L \propto (E/P_o)^{1/3\gamma}$, where E is the laser-pulse energy, and γ is the ratio of specific heats of the elements in the plume. From the above equation, high oxygen pressure has a corresponding shorter plume length L . They mentioned that as the target-to-substrate distance is located beyond the plume length L , the concentration of smaller clusters decreases and larger clusters appear, indicating that with a longer transfer time, the clusters merge via reaction [24]. Therefore, the vaporized species undergo more collisions and form larger clusters during transformation from plume to the substrate surface. Ionized atomic oxygen is quite reactive and tends to interact easily with the vaporized species. A continuous source of atomic oxygen can contribute on oxygen activity and arrival adatoms to the substrate surface, thus leading to higher deposition rate and thicker LAO thin film. The quality of the vacuum is a major practical consideration for the determination of the deposition rate [25,26]. Therefore, the thicker thin film was observed under the

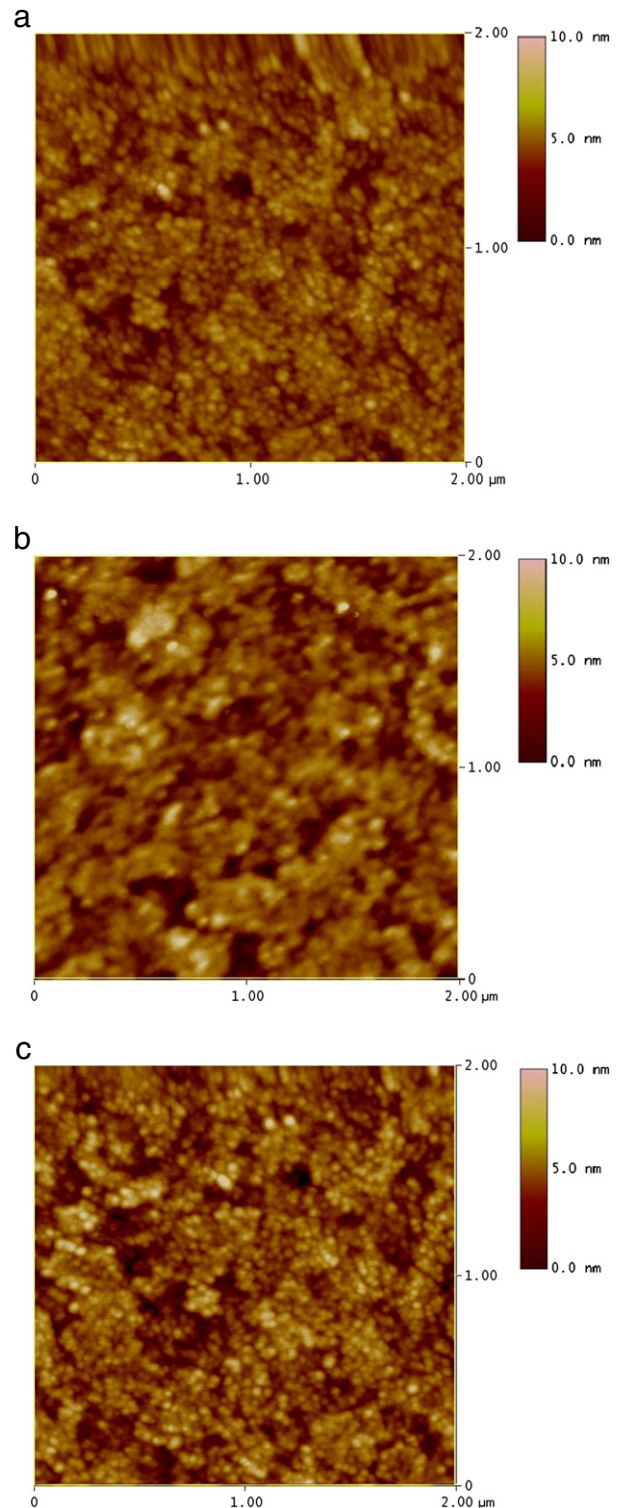


Fig. 1. AFM images of the LAO films grown with oxygen partial pressures of (a) 0.93, (b) 1.87, and (c) 3.73 Pa.

same deposition time as shown in Fig. 2. The deposition rate alternation may lead to different thin film nucleation and growth mechanism. For a high oxygen pressure circumstance, the vaporized species tend to form clusters before arriving at the substrate surface. Large clusters have the additional effect of decreasing the surface diffusion coefficient of the adsorbed vapor atoms, therefore, the adhesion of the ejected matter is poor, the shape size growth follows a random distribution, and a rougher

Download English Version:

<https://daneshyari.com/en/article/1667588>

Download Persian Version:

<https://daneshyari.com/article/1667588>

[Daneshyari.com](https://daneshyari.com)