

7th HPC 2016 – CIRP Conference on High Performance Cutting

## Fractal analysis of cutting force and acoustic emission signals during CFRP machining

Xavier Rimpault<sup>a\*</sup>, Jean-François Chatelain<sup>b</sup>, Jolanta-Ewa Klemberg-Sapieha<sup>c</sup>, Marek Balazinski<sup>a</sup>

<sup>a</sup>Department of Mechanical Engineering, Polytechnique Montréal, Montréal, QC H3T 1J4, Canada

<sup>b</sup>Department of Mechanical Engineering, École de Technologie Supérieure, Montréal, QC H3C 1K3, Canada

<sup>c</sup>Department of Engineering Physics, Polytechnique Montréal, Montréal, QC H3T 1J4, Canada

\* Corresponding author. Tel.: +1-514-627-8794; fax: +1-514-340-5170. E-mail address: [xavier.rimpault@polymtl.ca](mailto:xavier.rimpault@polymtl.ca)

### Abstract

Cutting forces and acoustic emissions signals while machining Fiber Reinforced Plastics (FRP) depends strongly on the tool wear. Fractal analysis can be adapted to those signals to characterize their variations. This tool wear monitoring technique is presented herein for the carbon FRP (CFRP) orbital drilling. Fractal parameters, characterizing the signal complexity and ruggedness, are very efficient for machining quality estimation and to follow the tool wear evolution.

© 2016 The Authors. Published by Elsevier B.V. This is an open access article under the CC BY-NC-ND license (<http://creativecommons.org/licenses/by-nc-nd/4.0/>).

Peer-review under responsibility of the International Scientific Committee of 7th HPC 2016 in the person of the Conference Chair Prof. Matthias Putz

*Keywords:* fiber reinforced plastic; orbital drilling; fractal analysis; cutting force; acoustic emission; tool wear

### 1. Introduction

Carbon fiber reinforced plastics (CFRPs) have been increasingly used in the aerospace industry over the past decades due to its lightweight vs mechanical properties. CFRP is constituted of two very different materials (carbon fiber and epoxy resin). The CFRP machining usually involves only finishing operations, thanks to its manufacturing, allowing CFRP components to be produced close to their final shape. To evaluate the machining quality, surface integrity is examined. Several problems may occur during fibre reinforced plastic (FRP) machining, e.g. uncut fibres, pulled fibres, delamination and burnt resin [1-4]. Due to the abrasiveness and hardness of the carbon fibres, abrasion is considered as the main tool wear mechanism [5, 6]. With the tool wear increase, keeping sufficient machining quality is challenging, and the surface quality should be examined through the tool life. Hamedanianpour et al. found that, even if the tool wear is still considered as functional, the resin may be burnt during the CFRP machining leading to a lower surface quality [7].

New techniques of tool wear monitoring can emerge due to the FRP heterogeneity. With the tool wear increase, the cutting tool edge radius increases resulting in lower surface quality and the signals' change of cutting forces and acoustic emissions (AEs). In addition to statistical parameters to extract quantitative data from such signals, fractal analysis was used to estimate the complexity of the signal [8, 9]. Therein, cutting force and vibratory signals were analyzed during homogeneous materials machining. However, the changes of the signal complexity through the tool life seem to be relatively low during the machining of homogeneous materials. Nevertheless, the cutting force and AE signals observed while machining CFRP show relatively high signal complexity variations for different tool wear. Thus, performing the fractal analysis of such signals would be relevant. In this study, the orbital drilling of composite/metal stack is investigated. The drilling of such stack is a major concern in the aerospace industry, which is part of the last assembly process of current airplanes' structural parts. In addition to issues specific to each material of the stack, machining stacks constituted of very different characteristics

materials leads to further problems. So, process monitoring is crucial to maintain sufficient machining quality.

## 2. Materials and methodology

### 2.1. Machining setup

The machined part was a stack composed of a quasi-isotropic CFRP, prepared using 24 pre-impregnated plies, with a 3.3 mm thickness, and Ti-6Al-4V titanium alloy, with a 3.0 mm thickness. The K2X10 Huron® high-speed machining center was used to conduct the machining tests. A dust extraction system was mounted onto the machine for health and safety purposes. The stack was machined by orbital drilling with different cutting parameters for each material of the stack. The cutting parameters, used to drill the 5.85 mm diameter holes, are presented in Table 1. The tool was a four flutes uncoated carbide shoulder mill with a 4 mm diameter, 30° helix angle and 11 mm maximum depth of cut. The composite/metal stack was drilled using the same setup until the complete tool failure. A total of 44 holes was achieved even though the tool had already reached the end of its tool life.

Table 1. Cutting parameters

Material	Helix step (mm)	Feed (mm/min)	Speed (RPM)
CFRP	0.7	800	11 000
Titanium	0.35	300	3 200

### 2.2. Measurements

The cutting force and AE signals were acquired during the tests using a dynamometer table and an AE sensor. The experimental setup is presented in Fig. 1. The input signal from both systems were acquired using the same amplifier and DAQ system at the 48 kHz frequency rate. The cutting force and AE signals from the CFRP machining were analyzed. The machining of titanium allowed generating a faster tool wear.

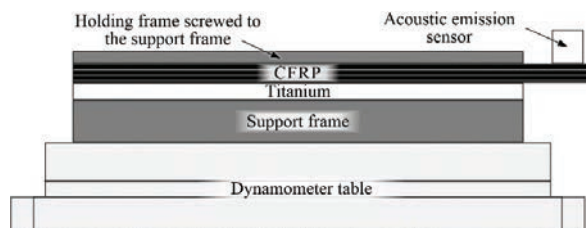


Fig. 1. Experimental setup representation

The tool wear was estimated between each drilling in order to evaluate the fractal parameters along the tool life. The tool wear was estimated using VHC 600+500F Keyence® optical microscope pictures which were taken on the clearance face of the tool tip edges. The maximum tool wear  $VB_{max}$  was estimated according to ISO standard recommendations [10]. The tool wear  $VB$  is introduced as the  $VB_{max}$  average of the four tool cutting edges.

Fig. 2 depicts the acquired signals (the cutting forces signals, the total cutting force signal and the AE signal) during the first drilling. The signal section analyzed corresponds to the area between the dash lines (Fig. 2), which is the relatively stable part of the CFRP machining using CFRP cutting parameters.

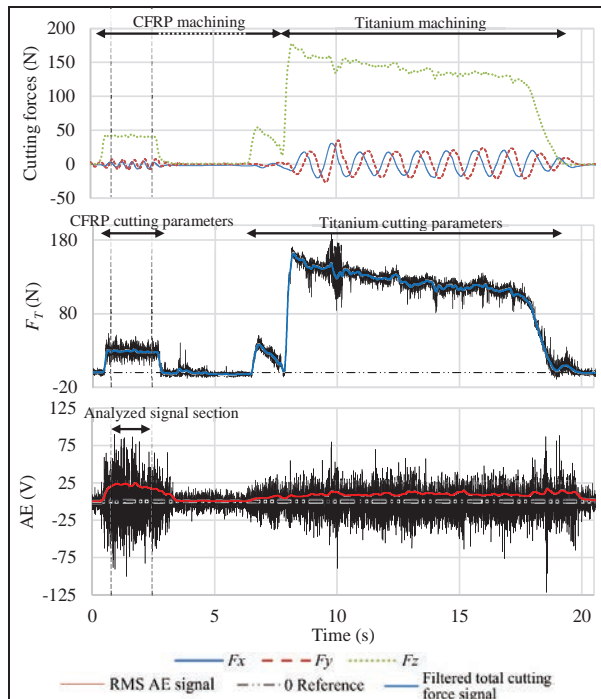


Fig. 2. Filtered cutting forces (top), total cutting force (center) and filtered and root mean square (RMS) acoustic emission (AE - bottom) signals

To highlight the changes of the signals' shape through the tool life, Fig. 3 show magnified signal samples from the analyzed section for different tool wear. In Fig. 3, the signal sample of the total cutting force  $F_T$  is relatively steady for a new tool. Then, the passes due to the cutting edges, can be identified on the cutting force signal with higher tool wear.

The signal samples from the AE sensor acquisition for different tool wear show similar trends (Fig. 3), in comparison with the cutting force signal samples. However, the periodic oscillation in those samples is more distinct with the tool wear increase.

From the signals observation of the AE and the cutting force, two outlines can be identified. At high frequency (so at low scale) the signal seems affected with noise for the first holes and becomes sharper with the tool wear increase. At a higher scale (around the tool rotation frequency), both signal types turns from a steady signal for the first holes, to increasingly clearer periodic oscillations for higher tool wear. The period corresponds to the tool rotation time per tooth.

### 2.3. Fractal analysis

Fractal analysis allows quantifying the signal complexity by a single value, the fractal dimension. Adapted to the

Download English Version:

<https://daneshyari.com/en/article/1698392>

Download Persian Version:

<https://daneshyari.com/article/1698392>

[Daneshyari.com](https://daneshyari.com)