



# Preparation of stable core–shell dye adsorbent Ag-coated silica nanospheres as a highly active surfaced-enhanced Raman scattering substrate for detection of Rhodamine 6G

Shijia Long, Li Li, Hao Guo, Wu Yang\*, Feng Lu

College of Chemistry and Chemical Engineering, Key Lab of Eco-Environmental Related Polymer Materials of MOE, Northwest Normal University, Lanzhou 730070, PR China

## ARTICLE INFO

### Article history:

Received 27 February 2012

Received in revised form

20 May 2012

Accepted 22 May 2012

Available online 26 June 2012

### Keywords:

Ag-coated silica nanospheres

Electrostatic assembly

Surface-enhanced Raman scattering

Rhodamine 6G

Core-shell structure

determination

## ABSTRACT

Silica spheres are used as a template to prepare Ag-coated silica nanospheres through electrostatic interaction, using a technique of homogeneous shaking instead of magnetic stirring. Pre-synthesized spherical Ag nanoparticles are firstly adsorbed onto silica spheres through bifunctional linking molecule, the silane reagent 3-aminopropyltrimethoxysilane, to form thin silver shells. These monodispersed Ag-coated silica nanospheres are assembled onto the glass substrates, which have been functionalized by 3-aminopropyltrimethoxysilane, to form close-packed three-dimensional Ag-coated silica nanosphere arrays by electrostatic interaction. The Ag-coated silica nanospheres were investigated as substrates for surface-enhanced Raman scattering using Rhodamine 6G as a probe molecule, and the enhancement factor of the Raman signal obtained on the Ag-coated silica nanospheres is about  $1.74 \times 10^9$  for R6G. Compared with pure silver hydrosols, the prepared Ag-coated silica nanospheres have a higher Raman enhancing effect. The hybrid nanosphere substrates can be used as a highly sensitive chemical and biological sensor for Rhodamine 6G dye.

© 2012 Elsevier Ltd. All rights reserved.

## 1. Introduction

The conventional Raman spectra often suffer from weak signal strength, however, the discovery of surface-enhanced Raman scattering (SERS) gave birth to a convenient and sensitive technique for detecting surface adsorbates [1–3]. Noble metal nanoparticles, such as Au and Ag, exhibit locally enhanced electric fields when illuminated at their localized surface plasma wavelengths. The SERS effect is observed when probe molecules are adsorbed on noble metal surfaces. However, only probe molecules in close proximity to these surfaces, which surface plasma resonances are coupled together, could produce large electric-field enhancement in the gap between neighboring nanoparticles, that is so-called “hot spots” [4,5]. In SERS, the localized Raman signals can be enhanced a million-fold or more when the molecules were adsorbed on aggregates of colloidal metal particles or roughened metal surfaces [6,7]. In virtue of a higher sensitivity than the usual analytical techniques, many efforts have been made to prepare new SERS-active substrates, including colloidal dispersions of metal

particles [8,9], metal island films [10–12], electrochemically roughened metal electrodes [13]. Among the useful substrates, silver is the most commonly used.

For solid metal substrates, the stability of the metal surfaces often influences the efficiency of the SERS substrates, but it can be significantly improved by the addition of a silica support for the noble metal [14]. The support of silica can be not only applied to disperse noble metal but also to stabilize the metallic phase. Therefore, silver nanoparticles can be uniformly distributed on the silica-supported substrate, where silica can also preserve the aggregation state of silver nanoparticles, making it possible to stabilize the SERS effect. So far, there have been core–shell structured nanoparticles to be prepared and applied as SERS-active substrates [15,10,15,16]. Bao and co-workers [17] prepared a new SERS substrate based on vapor deposition of silver nanoparticles on silica spheres. But although this type of substrates exhibited good stability and sensitivity, it is too complex to be fabricated conveniently, so that the substrate is not practical for SERS detection. While a large number of efforts have been focused on the study of SERS properties of different noble metal or their compounds, there have been only a few reports on the fabrication of silica-supported metal substrates.

In recent years, SERS, as a kind of highly sensitive determination technology of dyes, has attracted wide interests [18,19]. In the

\* Corresponding author. Tel./fax: +86 931 7971989.

E-mail addresses: [yangw@nwnu.edu.cn](mailto:yangw@nwnu.edu.cn), [yangwu\\_nwal@yahoo.com.cn](mailto:yangwu_nwal@yahoo.com.cn) (W. Yang).

present work, a fabrication and application on recognition of Rhodamine 6G dye (R6G) of Ag-coated silica nanosphere, as highly SERS-active substrates was described. The results show that the surface morphology of the substrate was extremely favorable to the enhancement of Raman signals and it can be used for highly sensitive determination of R6G.

## 2. Experimental

### 2.1. Materials

Tetraethoxysilane (TEOS, 98%), 3-aminopropyltrimethoxysilane ( $\text{NH}_2(\text{CH}_2)_3\text{Si}(\text{CH}_3\text{O})_3$ , APTMS, 99%), Rhodamine 6G (R6G, 98%) were purchased from Aldrich Chemical Company. Silver nitrate ( $\text{AgNO}_3$ ), sodium borohydride ( $\text{NaBH}_4$ ), ammonium hydroxide ( $\text{NH}_4\text{OH}$ , 25–28%) were obtained from Shanghai Chemical Reagents Company (Shanghai, China). All other reagents were used without further purification. Glass plates were prepared by cutting fresh microscope slides into  $1 \times 1$  cm pieces and were cleaned using freshly prepared 98%  $\text{H}_2\text{SO}_4/30\%$   $\text{H}_2\text{O}_2$  (v:v) at  $90^\circ\text{C}$  for at least 1 h and then rinsed with distilled water followed by ethanol and dried under a stream of clean nitrogen. All of the glassware was washed with freshly prepared aqua regia (volume ratio  $\text{HCl}:\text{HNO}_3 = 3:1$ ).

#### 2.1.1. Caution

$\text{H}_2\text{SO}_4/\text{H}_2\text{O}_2$  solution and aqua regia are very toxic chemicals and should be handled carefully!

### 2.2. Characterization

UV–Vis spectra were recorded on a Shimadzu UV-3100 spectrophotometer. Morphological images of Ag nanoparticles were obtained with a Japan Seiko SPI-3800N atomic force microscope (AFM) in a tapping mode with a commercial  $\text{Si}_3\text{N}_4$  probe. The X-ray photoelectron spectroscopy (XPS) analysis was carried out on a PHI-5702 multifunctional XPS spectrometer, using Al  $K\alpha$  radiation (1486.6 eV) as the exciting source, and all peak positions were normalized to the binding energy of C 1s (284.6 eV). Scanning electronic microscopy (SEM) was used to visualize the surface morphologies of silica nanospheres and Raman-active substrate on a JSM-5600LV/KVEX scanning electron microscope. Surface-enhanced Raman measurements were performed using a FT-Raman spectrometer (RFS 100/s, Bruker) with 200 mw of 1064 nm radiation from an Nd:VO<sub>4</sub> laser. The scan times were 50 times.

### 2.3. Preparation of the substrate

Uniform 200–250 nm silica spheres were synthesized by base-catalyzed hydrolysis of TEOS with the Stöber method [20]. Briefly, a mixture of ethanol (100 mL), ammonia water (5 mL), distilled water (3 mL) and TEOS (2 mL) was stirred overnight at room temperature. The resulting silica spheres were then washed and centrifuged three times in ethanol. Subsequently, the surface of the silica spheres was functionalized with amino groups by APTMS treatment in ethanol. Spherical Ag nanoparticles were prepared by reducing  $\text{AgNO}_3$  with  $\text{NaBH}_4$  in the presence of citrate as a stabilizer. In a typical preparation, a sodium citrate solution (0.2 mL, 1%) was first added to  $\text{AgNO}_3$  solution (20 mL, 0.01%) under homogeneous shaking for 1 min, and then, a freshly prepared ice-cold  $\text{NaBH}_4$  solution (1 mL, 0.075%) was injected all at once under vigorous shaking, the solution immediately turned yellow, indicating the formation of Ag nanoparticles. These nanoparticles were used within 24 h of their preparation. To assemble these Ag nanoparticles onto silica spheres, APTMS-functionalized silica

spheres (20 mg) were dispersed into the Ag nanoparticle solution (10 mL) by sonication, and then shaking for 12 h, this Ag-coated silica nanospheres were collected by centrifugation and then redispersed into a citrate solution (10 mL, 1%) for 30 min in order to enhance further adsorption of the Ag nanoparticles onto the silica spheres. Then, the Ag-coated silica nanospheres (5 mg) were dispersed into water (10 mL), APTMS-functionalized glass plates were immersed in the solution for 6 h to assemble Ag-coated silica nanospheres on them, forming close-packed three-dimensional Ag-coated silica nanosphere arrays by electrostatic interaction. Typically, clean glass plates were functionalized with APTMS by immersing them in an acetone solution of APTMS (10 mmol) for 30 min, rinsing them with acetone, and then drying at room temperature. Finally, different concentrations of R6G were adsorbed onto such obtained SERS-active substrates for detecting their Raman signals. The preparation procedure of SERS-active Ag-coated silica nanospheres was illustrated in Fig. 1.

### 2.4. Adsorption of R6G on Ag-coated silica substrates

R6G sample solutions were prepared in the concentration range of  $1 \times 10^{-4}$  mol  $\text{L}^{-1}$  to  $1 \times 10^{-7}$  mol  $\text{L}^{-1}$  for SERS measurements. And then respectively immerse SERS-active substrates in R6G solutions with different concentrations for 3 h to adsorb R6G molecules on the surface of the substrate. The SERS substrate plates were removed from the R6G solution and the solvent was allowed to evaporate.

## 3. Results and discussion

### 3.1. Characterization of SERS-active Ag-coated silica substrates

To synthesize SERS substrates, silica spheres with a diameter of 200–250 nm were prepared using the well-known Stöber method, as shown in Fig. 2. These silica spheres were then functionalized with APTMS to introduce amino groups onto their surfaces to acquire positively charged surfaces.

Fig. 3 shows thermogravimetry of APTMS modified  $\text{SiO}_2$  nanospheres. There are two obvious weight loss peaks. Loss of adsorbed water occurs before  $100^\circ\text{C}$  and oxidation and decomposition of grafted APTMS starts  $250^\circ\text{C}$  with an approximate 10% of weigh loss. These results indicate that about 10% APTMS of  $\text{SiO}_2$  mass has been grafted on the surface of silica nanospheres.

Silver nanoparticles with an average size of  $\sim 15$  nm obtained by reduction by  $\text{NaBH}_4$  are adsorbed onto the APTMS-functionalized silica surface by electrostatic interaction to form a thin silver shell. It is known that alkylamines exist predominantly as positively charged  $\text{R-NH}_3^+$  groups at values of  $\text{pH} < 10$  [21], and reduction of  $\text{Ag}^+$  with excess  $\text{NaBH}_4$  was helpful to forming small silver nanoparticles with a net negative interfacial charge [22]. Fig. 4 shows the AFM image of the obtained silver nanoparticles, it can be seen that the silver nanoparticles are uniform and the approximately diameter is 15 nm.

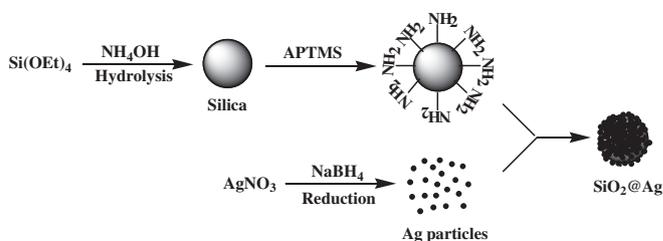


Fig. 1. Preparation procedure of a silver nanoshell on the silica sphere.

Download English Version:

<https://daneshyari.com/en/article/176827>

Download Persian Version:

<https://daneshyari.com/article/176827>

[Daneshyari.com](https://daneshyari.com)