



Short communication

In situ microwave-enhanced electrochemical reactions at stainless steel: Nano-iron for aqueous pollutant degradation

Gema Cabello ^{a,*}, Murilo F. Gromboni ^a, Ernesto C. Pereira ^a, Frank Marken ^{b,1}^a Department of Chemistry, Federal University of São Carlos, 13565-905 São Carlos, SP, Brazil^b Department of Chemistry, Bath University, Bath BA2 7AY, UK

ARTICLE INFO

Article history:

Received 7 October 2015

Received in revised form 9 November 2015

Accepted 10 November 2015

Available online 26 November 2015

Keywords:

Iron nanoparticles

Steel electrode

Microwave

Pollutant degradation

ABSTRACT

Iron nanoparticle deposition and stripping are observed from aqueous Fe^{2+} solution at pH 3 on stainless electrodes in the presence of focused microwave activation. The effects of Fe^{2+} concentration and microwave power are evaluated. It is shown that the resulting iron nanoparticle deposit (i) gives well-defined anodic stripping responses, (ii) is readily released into the solution phase, and (iii) is highly reactive towards chlorinated hydrocarbons such as trichloroacetate. The combined effects of increased mass transport and localized microwave heating improve pollutant degradation treatments.

© 2015 Elsevier B.V. All rights reserved.

1. Introduction

Iron nanoparticles are highly reactive and elusive species in aqueous media. The size and properties of iron particles are highly dependent on the preparation conditions and electrochemical reducing methods seem to lead to high purity nanoparticles with specific size range controlled by the current [1,2]. Most work has been focused on the synthesis of iron oxide nanoparticles, but iron nanoparticles are much more reactive and useful, for example, as reducing agents or in pollutant treatment.

Direct electrochemical reduction methods have been applied for the degradation of aqueous chloroacetic acids [3–5] (often employed as model chlorinated hydrocarbons), with special attention to the use of iron, or iron-modified electrodes. The main source of chloroacetates is the oxidation of chlorine compounds during the disinfection of water supplies. Iron is the main component of pipes for water supply [6], and iron has been extensively used to dehalogenate compounds [7]. A remaining problem is that reductive dehalogenation of chloroacetic acids requires high overpotentials since the reaction takes place at potentials more negative than -1.0 V vs. SCE, concurrently with hydrogen evolution, which diminishes the efficiency of the process [5]. Stainless steel has previously been used as cathode material in environmental treatment processes [8,9] since it is a fairly robust material at negative potentials, resistant to adsorption of impurities, and relatively cheap.

Microwave radiation can be focused into the region close to the electrode surface to give locally enhanced temperatures (with superheating)

at the electrode/electrolyte interface [10,11]. A combination of heating (with inverted temperature gradient) and strong mass transport can be achieved in particular at microelectrodes. In this study, the behavior of stainless steel electrodes in aqueous solution and with self-focused microwave activation is investigated. It is shown that Fe^{2+} can lead to well-defined deposition at stripping reactions consistent with the Fe(0)/Fe(II) conversion [12]. Nanoparticle deposits are confirmed by microscopy. In situ microwave radiation is proposed to enhance the formation of iron nanoparticles and the electrocatalytic reduction of chloroacetic acids in aqueous media.

2. Experimental methods

2.1. Chemicals

All solutions were prepared using analytical-grade reagents (purchased from Aldrich in the purest commercially available grade) and demineralised and filtered water ($18.2\text{ M}\Omega\text{ cm}$) from an Elgastat water purification system (Elga, Bucks, UK). Solutions were partially degassed using a flow-through vacuum system (ca. 15 Torr achieved with a membrane pump) with electrolyte solution flux of typically 2 mL min^{-1} .

2.2. Instrumentation

Microwave-activated cyclic voltammetry experiments were performed on a Bio-Logic SP-300 electrochemical workstation (Bio-Logic, France). The working electrode was a $50\text{ }\mu\text{m}$ diameter stainless steel wire (AISI 316 L) from Advent, embedded in a glass tube with epoxy

* Corresponding author.

E-mail address: g.cabello@ufscar.br (G. Cabello).¹ ISE Member.

resin (SP 106, from Gurit). All potentials were measured using a KCl-saturated calomel electrode (SCE), and the auxiliary electrode was a platinum wire. The electrochemical cell (Fig. 1A) was placed inside a modified domestic multimode microwave oven (Panasonic NN-3456) with modified power supply (Oxford Electronics). Details of the cell design and application of microwaves have been described previously [13]. Scanning electron microscopy (SEM) images were obtained with a JEOL JSM6480LV SEM system.

3. Results and discussion

3.1. Microwave effects on electrochemical processes at stainless steel I.: $\text{Fe}(\text{CN})_6^{3-}/\text{Fe}(\text{CN})_6^{4-}$ calibration

Electrochemical processes in the presence of self-focused microwave radiation experience both faster mass transport and elevated temperatures. Therefore, a temperature calibration is required since the operating temperature is controlled by changing the anode current of the microwave magnetron. It is well known [13] that the $\text{Fe}(\text{CN})_6^{3-}/\text{Fe}(\text{CN})_6^{4-}$ redox system is a suitable system for quantifying the effect of thermal activation since an increase of the temperature at the electrode surface will provoke a linear shift of the equilibrium potential due to the reaction entropy associated with the redox process [14]. The shift in the equilibrium potential for a solution containing 10 mM $\text{Fe}(\text{CN})_6^{3-}$ and 10 mM $\text{Fe}(\text{CN})_6^{4-}$ in 1 M KCl, recorded with microwave pulses and under non-isothermal heating conditions, with an electrolyte flow rate of 2 mL min^{-1} , as a function of the temperature can be assumed to follow $dE_{\text{equilibrium}}/dT = -1.7 \pm 0.05 \text{ mV K}^{-1}$ [15]. Fig. 1B shows the local electrode temperature data (which may be lower than the adjacent solution temperature) as a function of the applied microwave power (expressed as magnetron current). As expected, the

equilibrium potential shifts to more negative potentials in the presence of microwave radiation and similar temperatures are obtained at stainless steel compared to those reported in previous works for other electrodes [15].

3.2. Microwave effects on electrochemical processes at stainless steel II.: reduction of aqueous Fe^{2+}

Self-focused microwave radiation has been previously proven to be suitable to enhance electrochemical processes such as deposition and stripping detection of heavy metals [16,17] and, typically, platinum, gold, and glassy carbon electrodes have been employed [18,19]. There are no previous records of the direct application of self-focused microwave radiation at stainless steel electrodes or for the electrosynthesis of metal nanoparticles.

Aqueous Fe^{2+} can be easily reduced to Fe^0 at the surface of a stainless steel microelectrode under microwave conditions, from 1 mM Fe^{2+} solution at pH 3 [12], as shown in the scanning electron microscopy images (Fig. 2). Fig. 2a shows the featureless polished stainless steel surface; Fig. 2b shows the surface of the steel electrode after exposure to microwave radiation for 5 minutes (10 mA magnetron current) in a solution containing 0.1 M Na_2SO_4 (pH 3). It can be observed that the epoxy resin around the steel wire has been damaged by the action of the heat, causing some melting/leaching or swelling to partially cover the electrode surface. Fig. 2c and d show the surface after Fe^0 deposition, which turns into iron oxide in contact with air. It can be inferred that Fe^0 nanoparticles have been formed at the electrode surface and that, due to the high electrolyte flow, they have been dislodged or expelled from the surface towards the edge between the electrode and the resin that is porous probably due to the high temperatures reached at the vicinity of the electrode surface. Consequently, the electrode surface seems to be continuously generating Fe^0 nanoparticles.

Iron deposition onto the stainless steel surface was characterized voltammetrically by studying the evolution of the iron stripping peak under different conditions, i.e., Fe^{2+} concentration, temperature, and deposition time. The effect of the iron concentration on the Fe^0 formation at the steel microelectrode was evaluated studying the stripping peak under microwave radiation. Fig. 3A shows cyclic voltammograms obtained for solutions of FeSO_4 with different concentrations. The iron stripping peak is absent when a solution containing just 0.1 M Na_2SO_4 is used (Fig. 3A-a). On the other hand, in solutions containing Fe^{2+} from 0.5 mM to 4 mM, the stripping response for the iron re-dissolution is clearly observed. The stripping response starts at around -0.8 V and the stripping peak markedly increases with the Fe^{2+} concentration (0.5 mM Fe^{2+} being the lower limit concentration for the formation of Fe^0 under microwave constant power of 8 mA) (Fig. 3A-b–e). Peaks become narrower and more intense as the concentration increases until 4 mM Fe^{2+} and there is a clear shift in the peak position for the stripping process. However, peaks broaden at higher concentrations (data not shown). Cathodic currents increase with increasing the Fe^{2+} concentration as well, leading to sigmoidal cathodic currents typical of enhanced mass processes.

The influence of the temperature, measured as the magnetron anode current, in the iron deposition can be characterized by the iron stripping peak (Fig. 3B). The reductive deposition of iron at steel electrodes necessarily requires high temperatures, as shown by the absence of the stripping peak when no microwave radiation is applied (Fig. 3B, dotted line) or under microwave conditions but at low temperatures (Fig. 3B-a, 6 mA magnetron current, corresponding to ca. 343 K). At higher temperatures, the stripping peaks are better defined and become narrower since higher microwave radiation levels enhance the iron dissolution process, until the limit higher temperature is reached (at which the iron stripping peak no further changes), when 16 mA magnetron currents are applied and corresponding to ca. 440 K (Fig. 3B-f). Higher microwave power provokes an increase in the limiting current, attributed to the generation of a high-temperature region at the

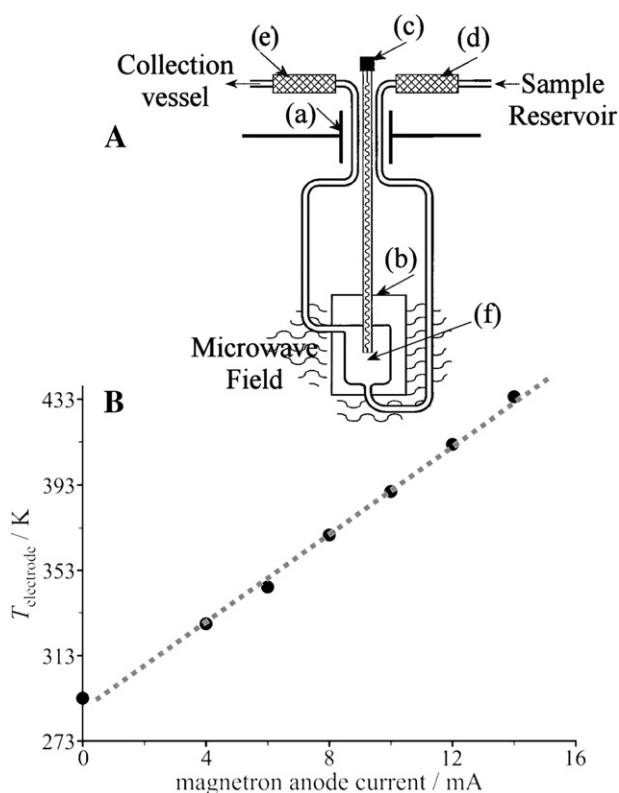


Fig. 1. (A) Schematic drawing of the flow-through microwave-electrochemical cell: (a) cavity port, (b) Teflon cell, (c) working electrode, (d) reference electrode, (e) counter electrode, and (f) location where microwave energy is focused. (B) Plot of the variation of the temperature of a $50 \mu\text{m}$ stainless steel electrode as a function of the applied microwave intensity (magnetron anode current), calculated from the equilibrium potential of 10 mM $\text{Fe}(\text{CN})_6^{3-}/10 \text{ mM } \text{Fe}(\text{CN})_6^{4-}$ in 1 M KCl.

Download English Version:

<https://daneshyari.com/en/article/178720>

Download Persian Version:

<https://daneshyari.com/article/178720>

[Daneshyari.com](https://daneshyari.com)