

# Crystal growth and properties of the non-centrosymmetric superconductor, $\text{Ru}_7\text{B}_3$

R.P. Singh<sup>1</sup>, N.A. Parzyk, M.R. Lees, D.McK. Paul, G. Balakrishnan<sup>\*</sup>

Department of Physics, University of Warwick, Coventry CV4 7AL, UK

## ARTICLE INFO

### Article history:

Received 13 January 2014

Received in revised form

28 February 2014

Accepted 2 March 2014

Communicated by K. Jacobs

Available online 10 March 2014

### Keywords:

A2. Floating zone technique

A2. Single crystal growth

B1. Inorganic compounds

B2. Superconducting materials

## ABSTRACT

We describe the crystal growth of high quality single crystals of the non-centrosymmetric superconductor,  $\text{Ru}_7\text{B}_3$  by the floating zone technique, using an optical furnace equipped with xenon arc lamps. The crystals obtained are large and suitable for detailed measurements, and have been examined using X-ray Laue patterns. The superconducting properties of the crystals obtained have been investigated by magnetization and resistivity measurements. Crystals have also been grown starting with enriched  $^{11}\text{B}$  isotope, making them suitable for neutron scattering experiments.

© 2014 Elsevier B.V. All rights reserved.

## 1. Introduction

In recent years, experimental and theoretical studies of the non-centrosymmetric superconductors (NCS) have attracted much attention due to their complex superconducting properties [1,2]. Following the first report of the observation of superconductivity in the non-centrosymmetric heavy fermion compound  $\text{CePt}_3\text{Si}$  [3], there has been a lot of interest in NCS. In NCS, the crystal structure lacks a center of inversion, which implies that in these superconductors parity is no longer a conserved quantum number and a mixed singlet–triplet superconducting wave function is possible [4,5]. As a result, NCS show significantly different properties from conventional superconducting systems such as large Pauli-limiting fields and helical vortex states. Theoretical predictions also suggest that NCS can be candidates for topological materials [6] due to their strong asymmetric spin–orbit interaction. Despite the theoretical predictions, there are very few experimental studies reported on single crystals of NCS due to the lack of high quality single crystals of several of these materials.

$\text{Ru}_7\text{B}_3$  forms in a non-centrosymmetric hexagonal  $\text{Th}_7\text{Fe}_3$ -type crystal structure with the space group  $P6_3mc$  (No. 186) [7,8]. The superconducting transition temperatures reported for  $\text{Ru}_7\text{B}_3$  in the literature vary from  $\sim 2.5$  to  $\sim 3.4$  K. For polycrystalline samples, reported values of superconducting transition temperature  $T_c$

range from  $\sim 2.58$  to  $3.38$  K [9]. Previous attempts to obtain single crystals of this material have been successful using the Czochralski method in a tetra-arc furnace [10]. Kase and Akimitsu report the superconducting transition temperature for their crystals to be different to their polycrystalline starting material [10]. The Ru–B binary phase diagram suggests that the  $\text{Ru}_7\text{B}_3$  phase melts congruently at  $\sim 1600$  °C [11]. In this paper, we report the growth of large single crystals of the non-centrosymmetric superconducting compound,  $\text{Ru}_7\text{B}_3$  by the floating zone technique using an optical mirror furnace [12] and present magnetization and resistivity measurements made on these crystals to determine their superconducting properties. We have used a four mirror optical furnace equipped with high power xenon arc lamps ( $4 \times 3$  kW) to grow these single crystals. This furnace has the capability of melting materials with melting points of up to a maximum of  $2800$  °C. The crystals obtained by this technique are large enough for most physical property measurements and are ideal for neutron scattering experiments, where large volumes of single crystal are essential. We have also produced single crystals starting with the isotopically enriched  $^{11}\text{B}$ , which has a much reduced absorption cross section for neutrons in comparison to the normally abundant boron. These crystals can be used to investigate the vortex state of this superconductor using neutron scattering techniques.

## 2. Experimental procedure

Polycrystalline samples of  $\text{Ru}_7\text{B}_3$  were prepared by arc melting stoichiometric quantities of high purity powders of Ru (99.99%),

<sup>\*</sup> Corresponding author.

E-mail address: [G.Balakrishnan@warwick.ac.uk](mailto:G.Balakrishnan@warwick.ac.uk) (G. Balakrishnan).


<sup>1</sup> Present address: Department of Physics, IISER Bhopal, MP 462023, India.

and either B (99.9%) or enriched boron isotope  $^{11}\text{B}$  (99.52 At%), on a water cooled copper hearth under a high purity argon gas (5N) atmosphere in a tri arc furnace (Centorr, USA). To ensure phase homogeneity, the resulting buttons were remelted and flipped several times. The observed weight loss during the melting was negligible. The phase purity of the polycrystalline buttons was checked by powder X-ray diffraction. Several polycrystalline buttons obtained in this manner were used to cast rods ( $\sim 40$  mm in length and  $\sim 6$  mm in diameter) under flowing argon gas in a tri-arc furnace. Two different types of feed rods were made, one set of rods starting with B and another set made starting with  $^{11}\text{B}$ . These rods were used as feed rods for the crystal growth in a high temperature optical furnace equipped with four 3 kW xenon arc lamps (CSI Model FZT-1200-X-VI VP). The first crystal growth was carried out using a tungsten rod as the seed rod and a crystal obtained from the initial growths was used as the seed for subsequent growths. Prior to starting the crystal growth, the growth chamber was flushed several times with high purity argon gas and then evacuated to a vacuum of  $\sim 10^{-6}$  mbar and finally filled with argon gas to a pressure of 0.3 MPa for the growth. The crystal growth was carried out under a flow (1 l/min) of high purity argon gas. The feed and seed rods were counter rotated at 25–30 rpm and crystal growths were carried out at speeds of 3–6 mm/h. Crystals of  $\text{Ru}_7\text{B}_3$  with the isotopically enriched boron were grown under similar growth conditions.


The crystal boules produced were first examined using Laue X-ray (Cu) diffraction to check the quality of the crystals. Spark erosion was used to cut slices from the grown boule for subsequent measurements. Temperature and field dependent magnetization measurements were made in the temperature range 1.8–300 K, using a Quantum Design MPMS-5S SQUID magnetometer. AC resistivity measurements in the temperature range 1.8–300 K were carried out on rectangular bar shaped samples ( $\sim 4$  mm in length and  $2 \times 1$  mm<sup>2</sup> in cross section) by the standard four-probe technique using a Quantum Design Physical Property Measurement System (PPMS).

### 3. Results and discussion

$\text{Ru}_7\text{B}_3$  melts congruently and therefore lends itself to crystal growth by the floating zone method. The crystals obtained starting with both the  $^{11}\text{B}$  as well as the  $^{10}\text{B}$  were identical in appearance and both the boules had shiny surfaces with a golden lustre. Crystals about 40–50 mm long and roughly 4–6 mm in diameter were obtained. As the melting temperature for this material is around 1600 °C, the power of the xenon lamps required to

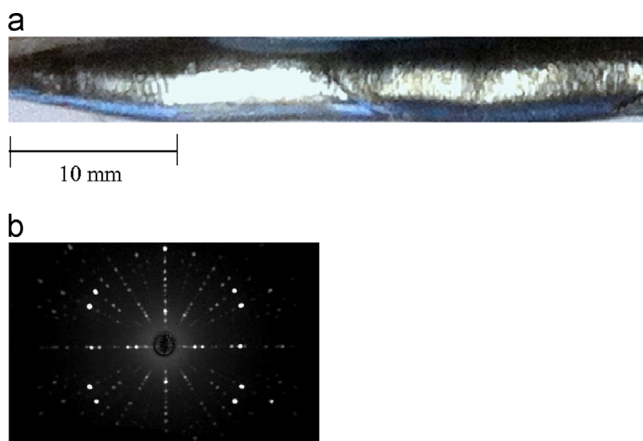

**Fig. 1.** (a) Single crystal of  $\text{Ru}_7\text{B}_3$ . (b) Laue X-ray diffraction pattern of a piece cut out of the as grown boule along the [100] direction.

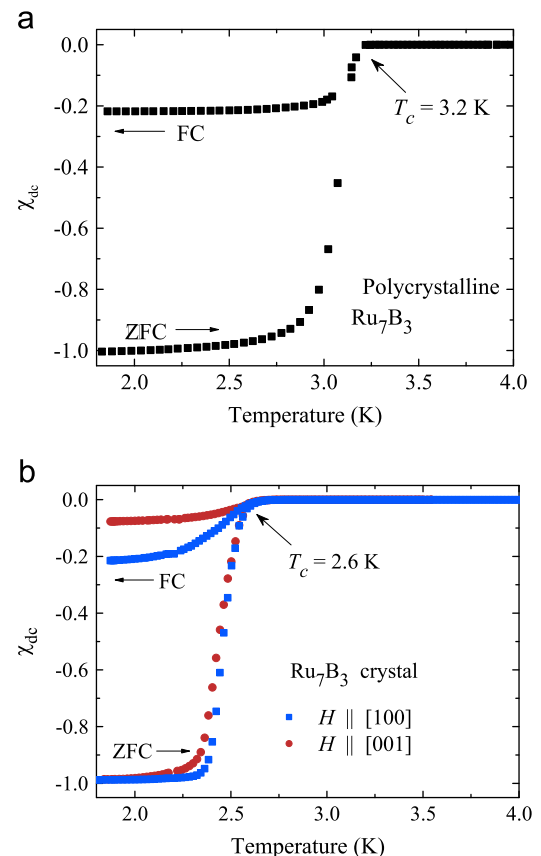

**Fig. 2.** Temperature dependence of the magnetic susceptibility ( $\chi_{dc}$ ) of (a) polycrystalline  $\text{Ru}_7\text{B}_3$ , and (b) single crystal  $\text{Ru}_7\text{B}_3$ . The magnetic susceptibility was measured in an applied field of 10 Oe. For the single crystal, the field was applied parallel to the [001] (red circles) or [100] (blue squares) directions of the crystal. Measurements were carried out in both zero field cooled (ZFC) and field cooled (FC) modes. (For interpretation of the references to color in this figure caption, the reader is referred to the web version of this paper.)

maintain a stable molten zone was in the region of 15–20%. We found that in order to obtain the best crystals, slow growth rates of around  $\sim 3$  mm/h were necessary. There was evidence of boron evaporation during the growth process in all the growths conducted. The crystals were cut using a spark cutter. Prior to cutting, the crystals were examined using Laue X-ray back reflection. Laue X-ray photographs were taken along the length of each crystal on several faces to confirm the crystal quality. A photograph of the as grown  $\text{Ru}_7\text{B}_3$  crystal is shown in Fig. 1(a). The Laue X-ray pattern obtained on a piece of the crystal cut out of the boule for measurements along the [100] direction is shown in Fig. 1(b). By use of the Laue X-ray diffraction, crystals oriented along particular crystallographic axes were cut from the as-grown boules for measurements.

Fig. 2 shows the dc magnetic susceptibility as a function of temperature for a crystal of  $\text{Ru}_7\text{B}_3$  as well as for a piece of polycrystalline sample of  $\text{Ru}_7\text{B}_3$ . The onset of the superconducting transition  $T_c^{\text{onset}}$  for the single crystal, determined from the dc magnetic susceptibility measurements, is 2.6 K. This is different to the  $T_c^{\text{onset}}$  of 3.2 K measured on the polycrystalline ingots used as the starting material for the crystal growth. Similar differences have also been reported between the  $T_c$ s of single crystal and polycrystalline material by Kase and Akimitsu [10] for crystals grown by the Czochralski technique. In borides, this is often associated with loss of boron during the crystal growth procedure and the presence of boron vacancies in the resultant crystals [13]. In general there is good agreement between the observed transition temperatures and those reported on both polycrystalline samples as well as single crystals grown by the Czochralski

Download English Version:

<https://daneshyari.com/en/article/1790541>

Download Persian Version:

<https://daneshyari.com/article/1790541>

[Daneshyari.com](https://daneshyari.com)