

Effects of magnetic interparticle coupling in the blocking temperature of granular Co multilayers

J.C. Denardin^{a,*}, W.C. Nunes^b, M. Knobel^b

^a*Departamento de Física, Universidad de Santiago de Chile, USACH, Santiago, Chile*

^b*Departamento de Física da Materia Condensada, Instituto de Física “Gleb Wataghin”, UNICAMP, Campinas (SP), Brazil*

Abstract

In order to study the influence of magnetic interactions on the blocking temperature of magnetic nanoparticles, magnetization measurements were carried out on a discontinuous Co/SiO₂ multilayer. The observed field dependence of the blocking temperature does not fit any of the non-interacting laws commonly used to describe this behavior. We applied a generalized model which considers a field-dependent magnetic correlation length. This model explains well the experimental results and can be used in other nanoparticulate systems.

© 2006 Elsevier B.V. All rights reserved.

PACS: 75.50.Tt; 75.20.-g; 75.75.+a

Keywords: Magnetic nanoparticles; Dipolar interactions

1. Introduction

The synthesis of magnetic nanoparticle systems with controlled morphology is very important in view of their interest for device and storage information applications. Moreover, ordered arrays of magnetic nanoparticles deposited on two-dimensional substrates constitute ideal geometry for device applications [1]. The study of the magnetic properties of such systems, with controlled sizes of particles, is particularly interesting because the effect of size distribution is minimized and the effect of magnetic interactions can be controlled. The development of a detailed understanding of the effects of interparticle interactions represents one of the most important challenges to the renewed interest in magnetic nanoparticles [2–4]. The problem is extremely complex because these systems display a rich variety of magnetic configurations, resulting from different contributions to their total energy. The interparticle interactions compete with the magnetic

anisotropy in determining the orientation of the particle moments. If strong enough, the interactions can make a collection of individual superparamagnetic moments that behaves like a collective magnetic system. A disordered collective state, or spin cluster glass, is expected when the system is dominated by dipolar interactions. Also, a ferromagnetic state can be formed in the case that the interactions are dominated by exchange coupling, for example, which appears in systems with particles that are in direct contact or dispersed in ferromagnetic amorphous matrix. However, many recent works have indicated the presence of a ferromagnetic correlation length larger than the size of the particles in systems with concentration of particles lower than the percolation, both in insulating [5,6] and metallic (paramagnetic) matrix [7], leading to the so-called superferromagnetism. This fact opens the possibility to analyze the interaction-induced variations of the superparamagnetic properties using the random anisotropy model (RAM). In this paper, we present a quantitative analysis of the field dependence of the blocking temperature in magnetic nanoparticles immersed in an insulating matrix. We apply a phenomenological model that takes

*Corresponding author. Tel.: +56 2 7763322; fax: +56 2 7769597.

E-mail address: jdenardin@usach.cl (J.C. Denardin).

into account particle coupling effects [8]. The model explains the experimental results with accuracy and, in principle, can be used in other nanostructured magnetic systems.

2. Experiment

The study of the influence of magnetic interactions on the blocking temperature was carried out in samples of discontinuous Co/SiO₂ multilayers, grown by DC (Co) and RF (SiO₂) sputtering on Si substrates held at room temperature. The sample consists of almost periodically arranged Co nanoparticles immersed in a SiO₂ matrix. More details on the production method can be found elsewhere [9]. Cross-section transmission electron microscopy (TEM) characterization was performed using a Jeol JEM-3010 ARP microscope. Magnetization properties were measured in the Quantum Design MPMS XL7 system in the temperature range 5–300 K.

3. Results and discussion

The TEM image of Fig. 1 shows that the sample is composed of almost periodically arranged Co nanoparticles. The particle size distribution (see also Fig. 1) was obtained by measuring the particle sizes in images of several different regions of the sample, and it is well fitted by a Gaussian distribution, leading to an average diameter of 3 nm. Fig. 2 shows the zero-field cooling/field cooling curves (ZFC/FC), measured for different applied DC magnetic fields H . One can observe that the maximum of the ZFC curves, which is related to the mean blocking temperature, displaces toward lower temperatures for increasing H , as expected.

The effect of external magnetic field on the blocking temperature has been considered for uniaxial magnetic systems by several authors [10,11]. A simple analytical expression is usually employed

$$T_B(H) = \frac{KV}{k_B \ln(\tau_m/\tau_0)} \left[1 - \left(\frac{H}{H_k} \right)^\alpha \right], \quad (1)$$

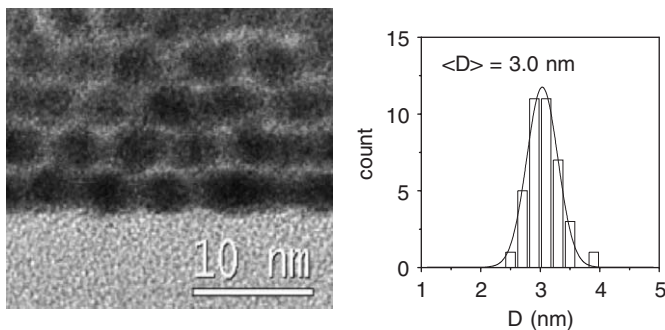


Fig. 1. Cross-section TEM image of the granular multilayer (left). The average diameter of the particles is 3 nm, as shown in the size distribution (right).

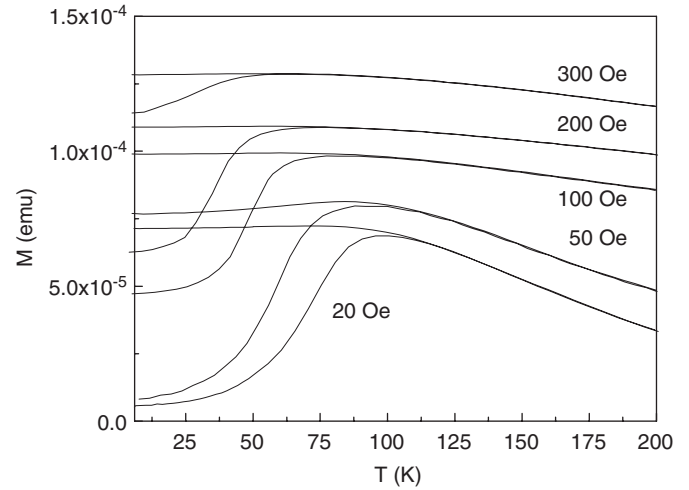


Fig. 2. ZFC, FC magnetization curves, measured at five different fields H .

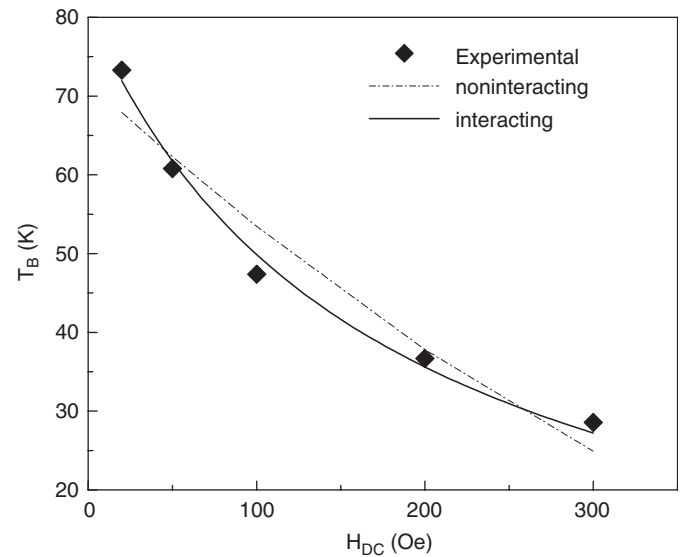


Fig. 3. The field dependence of the blocking temperature. Fits by using Eq. (1) (dashed-dotted line) and the modified RAM expression, given by Eq. (2) (solid line).

where K is the uniaxial anisotropy constant, V the particle volume, k_B is the Boltzmann's constant, and τ_0 is a constant related to gyromagnetic precession, and may be considered to be of the order of 10^{-9} – 10^{-10} s. The relaxation time $\tau = \tau_0 \exp(KV/k_B T)$ is a fundamental quantity of these systems that describes how rapidly the magnetization reversal of the particles occurs by thermal activation [12], and the blocking temperature T_B , for a system of particles with mean volume V , is defined as the temperature at which $\tau = \tau_m$, the measurement time (typically in the order of 100 s for DC measurements). H_k is the anisotropy field ($H_k = 2K/M_S$, M_S being the saturation magnetization) and the exponent α is close to 1.5 [13].

Download English Version:

<https://daneshyari.com/en/article/1815313>

Download Persian Version:

<https://daneshyari.com/article/1815313>

[Daneshyari.com](https://daneshyari.com)