



Effects of dilute columnar defects on the vortex matter in $\text{Bi}_2\text{Sr}_2\text{CaCu}_2\text{O}_{8+\delta}$ near the disorder-driven phase transition

D. Levi^{a,*}, A. Shaulov^a, T. Tamegai^b, Y. Yeshurun^a

^a Center for High- T_c Superconductivity and Institute for Nanotechnology, Department of Physics, Bar-Ilan University, Ramat-Gan 52900, Israel

^b Department of Applied Physics, The University of Tokyo, Hongo, Bunkyo-ku, Tokyo 113-8656, Japan

ARTICLE INFO

Article history:

Received 8 February 2010

Accepted 25 April 2010

Available online 29 April 2010

Keywords:

Vortex phase

Metastable disordered vortex state

Columnar defects

ABSTRACT

Magneto-optical measurements are employed to characterize the disorder-driven vortex phase transition and the metastable disordered vortex state in heavy-ion irradiated and pristine regions of the same $\text{Bi}_2\text{Sr}_2\text{CaCu}_2\text{O}_{8+\delta}$ crystal. We find that dilute columnar defects, while hardly affect the disorder-driven phase transition line, significantly increase the lifetime of the metastable state created in the vicinity of this line. Study of flux injection from the pristine region into the irradiated region suggests that in presence of columnar defects a metastable disordered state may be created in the bulk, in addition to being injected from the edges.

© 2010 Elsevier B.V. All rights reserved.

1. Introduction

Experimental and theoretical studies have revealed remarkable effects of columnar defects (CD) on the dynamic and thermodynamic properties of the vortex matter in high- T_c superconductors [1–15]. Early investigations, focused on the limit of high density of CD, have shown that in this case the vortex matter forms a Bose glass phase that melts through a continuous transition [1,2]. Recent studies have concentrated on the opposite limit of dilute CD, where vortices outnumber CD at the relevant fields [3–15]. In this case the vortex matter can no longer be regarded as a homogenous pinned medium. Instead, two distinct subsystems of vortices are created: vortices pinned on the CD forming a rigid disordered array, and interstitial vortices which are relatively ordered at low temperatures and fields [5–7]. Investigations of the melting process have shown that the melting line of the interstitial vortices subsystem is shifted upwards with respect to the pristine melting line [5]. At the delocalization transition line, which is located further up, the rigid matrix of the vortices residing at the CD delocalizes and the vortex liquid becomes homogenous [5].

While the effect of dilute CD on the melting process is well established, their effect on the dynamic and thermodynamic properties of the vortex matter near the disorder-driven solid–solid transition is yet unclear. The present paper addresses this issue using magneto-optical measurements and analysis of the local magnetic response to external fields ramped at different rates. Presumably, upon increasing the field at low temperatures, only the

interstitial vortices undergo the solid–solid transition, while the vortices trapped in the randomly distributed CD remain unaffected. Thus, the separate melting and delocalization lines are supposed to merge at low temperatures into a single solid–solid transition line. Realizing that the melting and the solid–solid transition lines are two segments of the same order–disorder phase transition line [16,17], one may expect that dilute CD also shift the thermodynamic solid–solid transition line upwards. By contrast, our results indicate that dilute CD hardly affect the solid–solid transition line, tending to shift it slightly downward rather than upward.

The present paper also addresses the question of how CD affect the metastable disordered state (MDS) generated below the solid–solid transition line [18–29]. This metastable state is believed to be created by injection of vortices through inhomogeneous surface barriers while the external magnetic field increases [18–20]. As the induction of the transition is approached, the free energies of the quasi-ordered and the disordered states become comparable, and therefore the lifetime of the transient disordered phase becomes longer, diverging at the transition induction [19]. The effect of dilute CD on the MDS was investigated in NbSe_2 , revealing enhancement of the MDS as compared to the pristine material, in contrast to the expectation that CD stretch the entangled vortices of the MDS and assist their annealing [11]. In the present work we characterize this effect quantitatively by measuring the lifetime, $\tau(B,T)$, of the MDS in the pristine and irradiated parts of the same $\text{Bi}_2\text{Sr}_2\text{CaCu}_2\text{O}_{8+\delta}$ crystal. The existence of the MDS in our local magnetic measurements is manifested by a shift of the onset of the second magnetization peak to lower inductions as the sweep rate of the external field increases [22]. Utilizing this shift to determine

* Corresponding author. Tel.: +972 3 5318607; fax: +972 3 7369599.
E-mail address: ph100@mail.biu.ac.il (D. Levi).

τ [28] reveals that the CD significantly increase the lifetime of the MDS, allowing the MDS to exist in the sample at low inductions, far below the transition, where in a pristine sample their lifetime is practically zero.

The configuration of our sample also allowed studying the generation of MDS as a result of injection of ordered vortices through an interface separating the pristine and the irradiated regions of the same sample. Our measurements show that such MDS are in fact created and that their lifetime matches that of the MDS injected through the natural sample edges. The injection of MDS within the bulk of the sample challenges the commonly accepted view that edge contaminations are the sole source responsible for the creation of MDS.

2. Experimental

Measurements were performed on a $2.3 \times 1 \times 0.04 \text{ mm}^3$ $\text{Bi}_2\text{Sr}_2\text{CaCu}_2\text{O}_{8+\delta}$ single crystal ($T_c = 92 \text{ K}$) grown by the floating zone method [30]. Part of the sample (right to the white dotted line in Fig. 1) was irradiated at the GSI Helmholtz Centre for Heavy Ion Research (Darmstadt, Germany), with 2.2 GeV Au ions (fluence of 10^8 ions/cm^2) resulting in the formation of columnar defects of diameter 7–12 nm [31] with density corresponding to a matching field of 80 G. The range of the ion tracks was large enough to completely penetrate the 40 μm thick crystal. The irradiation was performed at room temperature and under normal beam incidence. Local magnetization curves were extracted from magneto-optical images of the induction distribution, taken using an iron-garnet indicator with in-plane anisotropy and a 12 bit Hamamtsu CCD camera with a frame rate between 0.1 and 25 Hz. In a typical magneto-optical measurement, the sample was zero-field cooled to a target temperature between 24 and 32 K and was then subjected to external field parallel to the crystallographic c -axis of the sample. The external magnetic field was ramped up at a constant rate between 2.5 and 160 Oe/s, from 0 to about 700 Oe. Camera integration time used for image acquisition was 14–36 ms.

3. Results and discussion

Fig. 1 depicts magneto-optical images of the sample at $T = 28 \text{ K}$ after exposing it to an external magnetic field ramped up from zero at a rate of 5 Oe/s. Flux penetration (brighter tone in the figure) is shown 7 s (a), 12 s (b) and 19 s (c) after the application of the field.

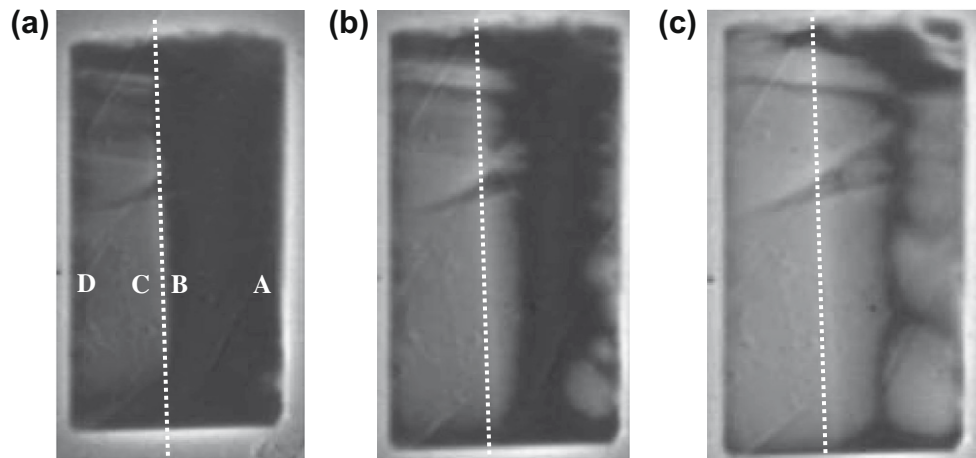


Fig. 1. Magneto-optical images of flux penetration through the edges of a partially irradiated $\text{Bi}_2\text{Sr}_2\text{CaCu}_2\text{O}_{8+\delta}$ sample subjected to external field ramped at 5 Oe/s, 7 (a) 12 (b) and 19 (c) seconds after the application of the field. The dotted line marks the border between the irradiated (right hand side) and pristine parts of the sample. The color tone is brighter for larger inductions. Points A, B, C and D mark locations where magnetization curves in Figs. 2 and 9 were extracted.

One clearly sees that flux penetrating through the sample edges advance in the pristine region (right hand side in each image) at a much higher rate, allowing flux injection from the pristine into the irradiated part through the sharp border between them. Thus, the partially irradiated sample allows simultaneous study and comparison of the metastable vortex state created by flux injection through both the sample edges and the border between the irradiated and pristine parts of the sample.

Fig. 2 exhibits local magnetization curves, $m = \text{Bloc} - H$ versus the applied field H , measured at points A and D near the sample edges at 28 K, in the pristine (a) and the irradiated (b) region, respectively (see Fig. 1 for the location of these points). The different curves in each figure correspond to different ramping rate of the external field from 2.5 to 160 Oe/s. Notable differences in the local magnetic response of the pristine and the irradiated parts are evident: In the irradiated part the second magnetization peak is smeared, exhibiting onset at lower fields, and stronger dependence of the onset field on the ramping rate dH/dt of the applied field. As discussed below, the onset field, H_{on} , signifies the first field at which MDS is injected into the sample. In the pristine region H_{on} can be accurately determined; in this region the difference between the persistent current of the ordered state, j_{low} , and the metastable disordered state, j_{high} , is large. As a result, the natural increase with field of the local magnetization, m , is disrupted abruptly by penetration of a metastable disordered vortex state (MDS) through the edges, creating an SMP with a well defined onset. A difficulty in accurate determination of H_{on} arises in the irradiated region where the difference between j_{low} and j_{high} is smaller. As a result, the natural increase of m is competing with a decrease of m at a comparable rate, creating a smeared onset. In this case we define H_{on} as the field where the increase and decrease in m are exactly compensated, i.e. at the maximum point of m . We note that this definition of H_{on} underestimates the shift down of the onset field in the irradiated region.

Fig. 3 shows the onset field, H_{on} , as a function of dH/dt in the pristine and irradiated regions. As expected, both curves exhibit accelerated approach of H_{on} to the thermodynamic order–disorder transition field B_{od} for dH/dt approaching zero [28]. However, the curve corresponding to the irradiated region is far below that corresponding to the pristine region, indicating longer lifetime of the MDS in the irradiated part, enabling it to persist at lower fields.

It is important to note that H_{on} is independent of the measuring location, in both the pristine and the irradiated regions. The reason for it is well understood; as stated above, H_{on} signifies the first field

Download English Version:

<https://daneshyari.com/en/article/1818778>

Download Persian Version:

<https://daneshyari.com/article/1818778>

[Daneshyari.com](https://daneshyari.com)