



Electrochemistry and spectroelectrochemistry of a novel selenophene-based monomer

Przemysław Data^{a,b}, Mieczysław Lapkowski^{a,b,*}, Radosław Motyka^a, Jerzy Suwinski^a

^a Faculty of Chemistry, Silesian University of Technology, 44-100 Gliwice, Poland

^b Center of Polymer and Carbon Materials, Polish Academy of Sciences, 41-819 Zabrze, Poland

ARTICLE INFO

Article history:

Received 8 July 2011

Received in revised form 3 November 2011

Accepted 4 November 2011

Available online 15 November 2011

Keywords:

Synthesis

Properties

Spectroelectrochemistry

X-ray analysis

ABSTRACT

A stereocontrolled synthesis of a novel selenophene-based monomer namely (*E,E*)-1,4-dimethoxy-2,5-bis[2-(selenophen-2-yl)ethenyl]benzene has been successfully performed starting from 1,4-dimethoxybenzene. Its spectra, electrochemistry and polymerization have been studied.

© 2011 Elsevier Ltd. All rights reserved.

1. Introduction

In recent years there has been a rapid development of studies related to the production of new materials for electrochromic devices [1], electronic papers, sensors, radio frequency identification tags [2], polymeric light emitting diodes, organic photovoltaic devices [3,4], and organic single crystal field-effect transistors [5]. An important group of compounds that may have potential application are oligomers [6,7] or polymers of thiophene and their derivatives [8]. Oligomers of thiophene are well known to possess good electrodonating properties [9], considerable mobility of charges and substantial crystallinity [10]. Surprisingly, up to 2005 only little attention has been given to polymers of selenophene and its derivatives even though selenophene has lower oxidation potential in compare to its sulfur or oxygen analogs. In the last few years a number of papers on polymers bearing selenophene have grown rapidly [11–17] and first electrochromic device where a selenophene-containing polymer was used as an active layer was described in 2009 [18]. Few years ago, regioregular poly(3-hexylselenophene) (P3HS) [19,20] have been reported for organic electronic applications, with

higher mobility than analog of polythiophenes (P3HT) [21,22] Poly(9,90-n-dioctylfluorene-alt-biselenophene) (F8Se2) [23] and poly(5,50-bis(3-dodecylthiophene-2-yl)2-20-biselenophene) (PDT2Se2) [24] revealed an order of magnitude larger field-effect mobility than their sulfur analogs, when used as active layers in OFETs. For this reason, in recent years an increasing interest in oligomers, polymers and copolymers containing selenophene moiety has been observed. Of the many compounds synthesized and studied may be mentioned: 1,3-diarylbenzo[c]selenophenes [25], benzo[1,2-b:4,5-b']diselenophenes [26], selenopheno[3,2-b]thiophene [27] or 9,9-dialkylfluorene capped benzo[c]thiophene/benzo[c]selenophene derivatives [28]. Attracted much interest: poly(3,4-ethylenedioxy-selenophene) (PEDOS; PEDOT analog) [29–31], poly(fluorene-co-selenophene) [13] and poly(9,9'-dioctylfluorene-alt-biselenophene) [21]. Very recent review on poly(selenophene) and its derivatives was done by Patra and Bendikov [32]. Selenophene derivatives have a lower oxidation potentials than the thiophenes but higher than tellurophenes analogs in series $\text{Te} < \text{Se} < \text{S}$ [33,34]. In comparison with tellurophene analogs selenophene derivatives are more stable [35,36].

Formerly, it was shown that monomers with conjugated system of multiple bonds bearing two terminal residues of chalcogens (furan or thiophene) with free positions in C5 (Fig. 1, structure 1) are able to electropolymerize leading to linear PPV-type conducting systems that show strong electroluminescence [37–40]. Now we present a synthesis and some properties

* Corresponding author at: Faculty of Chemistry, Silesian University of Technology, 44-100 Gliwice, Poland.

E-mail address: mieczyslaw.lapkowski@polsl.pl (M. Lapkowski).

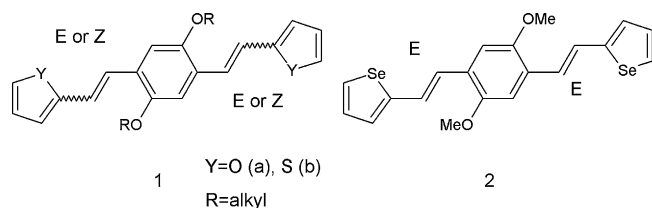


Fig. 1. Structures of monomers with conjugated system of multiple bonds and two terminal residues of furan (**1a**), thiophene (**1b**) or selenophene (**2**).

of compound **2** being (EE) selenophene analog of compounds **1**.

2. Experimental

2.1. Synthesis

2.1.1. General

All solvents were dried and then distilled before the use. Other commercial substances and reagents were used without purification. Melting points (not corrected) were determined on Boetius HMK apparatus. NMR spectra were taken in CDCl_3 with TMS as an internal reference by Varian XL-300 at 300 MHz for ^1H and at 75.5 MHz for ^{13}C . EA results were obtained using Perkin-Elmer CHN automatic analyzer. X-ray structural data have been obtained on the Gemini A Ultra diffractometer. The structures were determined by means of direct methods and refined by the full-matrix least squares technique.

2.1.2. Preparation details

2.1.2.1. (E,E)-1,4-dimethoxy-2,5-bis[2-(selenophen-2-yl)ethenyl]benzene (2). This compound was synthesized following a slightly modified procedure known for the synthesis of (E,E)-2,5-bis(2,5-dihexylstyryl)-1,4-dimethoxybenzene [39,40]. Preparation procedures of intermediate materials (selenophene-2-carboxyaldehyde and tetraethyl [2,5-dimethoxy-1,4-bis(methylene)]diphosphonate) can be obtained on request from authors as an supplementary additional material.

A cold solution of selenophene-2-karboxyaldehyde (0.36 g, 2.28 mmol) and tetraethyl [2,5-dimethoxy-1,4-bis(methylene)]diphosphonate (0.50 g, 1.14 mmol) in dry DMF (5 mL) was added dropwise to a solution of *t*-BuOK (0.79 g, 7.05 mmol) in DMF (10 mL) at 0°C . The mixture was stirred without cooling for 2.5 h and then poured into cold water (50 mL) acidified with conc. HCl (1 mL). The obtained solution was extracted with dichloromethane (3×25 mL) and organic extracts were dried over MgSO_4 . The solvents were evaporated under diminished pressure and the residue purified by column chromatography over silica gel using hexane:benzene (4:1) as eluent to give (E,E)-1,4-dimethoxy-2,5-bis[2-(selenophen-2-yl)ethenyl]benzene (0.15 g, 0.34 mmol, 30%) as orange crystals (m.p. $224\text{--}226^\circ\text{C}$). ^1H NMR δ (300 MHz, CDCl_3): 3.91 (6H, s, CH_3); 7.04 (2H, s, ArH), 7.13 (2H, d, $J = 15.9$ Hz, CH vinyl); 7.20–7.24 (4H, m, $\text{C}_4\text{H}_3\text{Se}$, C^4H , C^3H); 7.33 (2H, d, $J = 15.9$ Hz, CH vinyl); 7.83–7.85 (2H, m, $\text{C}_4\text{H}_3\text{Se}$, C^5H). ^{13}C NMR (75 MHz, CDCl_3): δ 56.42 (OCH_3); 109.38 (Ar, CH); 124.51 (C vinyl); 124.96 (C vinyl); 126.28 (ArCCH); 128.84 ($\text{C}_4\text{H}_3\text{Se}$, C^5); 129.00 ($\text{C}_4\text{H}_3\text{Se}$, C^4); 130.27 ($\text{C}_4\text{H}_3\text{Se}$, C^3); 150.00 ($\text{C}_4\text{H}_3\text{Se}$, C^2); 151.59 (Ar, COAlk). UV (CH_2Cl_2): $\lambda = 414.5$ nm; $\epsilon = (4.66 \pm 0.29) \times 10^4$; $\lambda = 355.0$ nm; $\epsilon = (1.77 \pm 0.12) \times 10^4$; $\lambda = 293.0$ nm; $\epsilon = (0.82 \pm 0.07) \times 10^4$ [$\text{dm}^3/\text{mol cm}$].

The structure of product was additionally proved by X-ray measurements of a monocrystal of (E,E)-1,4-dimethoxy-2,5-bis[2-(selenophen-2-yl)ethenyl]benzene (**2**). Crystallographic data (excluding structure factors) for the structure of **2** has been deposited with the Cambridge Crystallographic Data Centre as

supplementary publication nos. CCDC 812456. Copies of the data can be obtained, free of charge, on application to CCDC, 12 Union Road, Cambridge CB2 1EZ, UK (fax: +44 01223 336033 or e-mail: deposit@ccdc.cam.ac.uk).

2.2. Electrochemical measurement

The solutions of compound **2** with the concentration of 1.0 mM were used for cyclic voltamperometry measurements. Electrochemical studies were conducted in 0.1 M solution of Bu_4NBF_4 (Sigma Aldrich 99%) in anhydrous dichloromethane at room temperature. The electrochemical investigations were carried out using Eco Chemie Company's AUTOLAB potentiostat "PGSTAT20". The results were collected using GPES (General Purpose Electrochemical System) software. The electrochemical cell comprised of platinum wire with 1 mm diameter of working area as working electrode, Ag wire – calibrated versus ferrocene/ferrocinium redox couple – as a quasi-reference electrode and platinum coil as auxiliary electrode. Cyclic voltamperometry measurements were conducted at 50 mV/s potential rate.

3. Results and discussion

A stereocontrolled three steps synthesis of a novel selenophene-based monomer namely (E,E)-1,4-dimethoxy-2,5-bis[2-(selenophen-2-yl)ethenyl]benzene (**2**) has been successfully performed starting from 1,4-dimethoxybenzene (**3**) as it is shown in Scheme 1. Compound **3** was treated with paraformaldehyde and gaseous hydrogen chloride in the solution of glacial acetic acid and concentrated hydrochloric acid to give 2,5-bis(chloromethyl)-1,4-dimethoxybenzene (**4**). The latter compound on heating at with ca 20% excess of triethoxyphosphine 150°C afforded 2,5-bis(diethylphosphonomethyl)-1,4-dimethoxybenzene as a white powder in 30% yield.

During our former work on preparation of several compounds of type **1**, we treated bis(chloromethyl)-1,4-dialkoxybenzenes with triphenylphosphine (instead of triethoxyphosphine used here); the respective substitution products obtained in form of salts, were then condensed with appropriate 2-chalcogenecarbaldehydes. Such method in all cases lead to mixtures of stereoisomers differing in configuration of substituents at the double bonds. Separation of stereoisomers was always troublesome [37–41]. After all, ZZ isomers were rather unstable and in solutions quickly isomerized to give equilibrium mixtures. All separated stereoisomers underwent electropolymerization showing two oxidation peaks. For the stereoisomers, first oxidation peaks appeared at different potentials decreasing in the following order ZZ, EZ, EE. Only small differences in oxidation potentials could be spotted for the second peaks what might suggest isomerization prior to oxidation. Polymers obtained from the stereoisomers did not show distinct differences what seemed to support the former suggestion [39]. Therefore, a stereocontrolled condensation of **5** with 2-selenophenecarbaldehyde leading to the most stable EE isomer was a method of choice for the synthesis of **2** even if yields achieved would be lower in comparison with reaction using triphenylphosphine derivatives. Indeed, the reaction afforded the expected EE isomer as the only product. Its structure was proved by ^1H NMR spectrum analysis (two doublets 2H , $J = 15.9$ Hz at 7.13 and 7.33 corresponding to two pairs of vinyl groups of E configuration). This finding was confirmed by X-ray crystallography of **2** monocrystal (crystal dimensions $0.38 \text{ mm} \times 0.27 \text{ mm} \times 0.12 \text{ mm}$). 3058 reflections were collected using Cu K α radiation within 3 h 13 min at 100 K. Program used to solve structure was: SHELXS97 (Sheldrick [42]); program used to refine structure: SHELXL97 (Sheldrick [43]). ORTEP projection is shown in Fig. 2. The shape of molecules of

Download English Version:

<https://daneshyari.com/en/article/189382>

Download Persian Version:

<https://daneshyari.com/article/189382>

[Daneshyari.com](https://daneshyari.com)