



# Chitosan-coated liposomes for enhanced skin permeation of resveratrol



Soo Nam Park\*, Na Rae Jo, So Ha Jeon

Department of Fine Chemistry, Nanobiocosmetic Laboratory, and Cosmetic R&D Center, Seoul National University of Science and Technology, 232 Gongneung-ro, Nowon-gu, Seoul 139-743, Republic of Korea

## ARTICLE INFO

### Article history:

Received 28 January 2013

Accepted 23 July 2013

Available online 1 August 2013

### Keywords:

Resveratrol

Liposome

Chitosan coating

Skin permeation

## ABSTRACT

In this study, chitosan-coated liposomes were investigated for use in enhanced transdermal delivery of resveratrol. Particle size, entrapment efficiency, stability, and skin-permeation efficiency were evaluated. The particle size was seen to increase on coating with chitosan, with higher concentrations of coating solution forming larger particles. The zeta potential of the liposomes also followed the same trend, *i.e.*, it changed from a negative value for uncoated liposomes to increasingly positive values for the chitosan-coated ones. The chitosan coating was seen to increase the stability of the liposomes by preventing their aggregation. Transdermal delivery of uncoated and 0.1% chitosan-coated liposomes containing 0.1% resveratrol was investigated using Franz diffusion cells. The proportions of resveratrol that permeated the animal skin were 40.42% and 30.84% for the coated and uncoated liposomes, respectively. This increased skin-permeation efficiency with the coating could be explained by the tendency of positively charged liposomes to interact more strongly with the skin surface. These results indicate that chitosan-coated liposomes could be an effective transdermal delivery system for delaying skin aging using resveratrol.

© 2013 The Korean Society of Industrial and Engineering Chemistry. Published by Elsevier B.V. All rights reserved.

## 1. Introduction

Resveratrol (3,5,4'-trihydroxy-trans-stilbene, Fig. 1) belongs to a class of polyphenolic compounds called stilbenes found in the skin of grapes [1]. It is beneficial for cardiovascular health as it prevents oxidative damage and platelet aggregation, promotes vasodilatation, and exhibits antimicrobial activity against dermatophytes and the herpes simplex virus [2–5]. Such beneficial effects of resveratrol have highlighted its potential applications throughout the world [6]. However, it has some limitations owing to its poor solubility in water, and its instability [7]. These shortcomings therefore need to be overcome if resveratrol is to fulfill its potential.

Human skin is a layered structure composed of three main layers: epidermis, dermis, and subcutaneous tissue. The outermost layer, the epidermis, which forms a barrier for protection of the underlying tissue from the environment, is known as the stratum corneum. This same structure, however, also provides a barrier to therapeutic agents that need to permeate the skin in order to achieve their objectives. Therefore, a major focus of transdermal drug delivery research is the development of methods to overcome this barrier and allow the active agents to permeate the skin.

Liposomes are spherical structures that consist of one or more phospholipid bilayers, and have been used as a transdermal drug delivery system owing to their interaction with the cell surface [8]. When the liposome reaches the cell surface, drug delivery is achieved *via* the fusion of the liposome to the cell membrane, protein-mediated transfer, or phagocytosis and pinocytosis [9]. However, the poor liposome stability can result in degradation, aggregation, and fusion, thereby leading to the leakage of the entrapped drug [10].

Polymer coating is a promising way to modify the surface characteristics of liposomes in order to improve their applicability. This can be achieved by simply mixing a liposome suspension with a polymer solution without chemically linking the two components [11]. On coating the liposomes with the polymers, long-range mutual repulsion between the adjacent bilayers arise, which improves their stability. In addition, coating with a positively charged polymer can improve the skin permeation because of the increased interaction between the liposomes and the skin [12,13].

Chitosan is a hydrophilic, biocompatible, biodegradable, and positively charged polysaccharide polymer. It has been previously used as a coating material for carrying hydrophilic drugs across the skin barrier, thereby enhancing the drug delivery [14,15]. Accordingly, coating the liposomes with chitosan can significantly improve skin permeation.

In this study, we investigated the particle size, zeta potential, entrapment efficiency, and skin permeation of chitosan-coated

\* Corresponding author. Tel.: +82 29706451; fax: +82 29729585.  
E-mail address: [snpark@seoultech.ac.kr](mailto:snpark@seoultech.ac.kr) (S.N. Park).

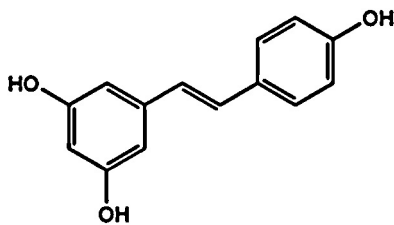


Fig. 1. Structure of resveratrol.

liposomes containing resveratrol in order to improve the application of this compound in cosmetics.

## 2. Experimental

### 2.1. Materials

1- $\alpha$ -Phosphatidylcholine (egg PC, ~60%) and chitosan (low molecular weight, viscosity 20–300 cP) were purchased from Sigma–Aldrich (USA). Resveratrol was purchased from TCI (Japan). All other chemicals were of analytical grade.

### 2.2. Preparation of liposomes

Egg PC (2%, w/v) and resveratrol (0.1%, w/v) were dissolved in a mixture of chloroform (10 mL) and methanol (5 mL). The solution was then poured into a round-bottom flask, and the solvent was removed by rotary evaporation (Buchi, Switzerland), resulting in the formation of a thin layer of lipid film on the walls of the flask. Distilled water (10 mL) was then added to the flask and the solution was sonicated using a probe-type sonicator (Branson, USA) to obtain uniformly sized submicron particles.

### 2.3. Preparation of chitosan-coated liposomes

Chitosan was dissolved in 1% v/v solution of acetic acid in water in various concentrations (0.1%, 0.3%, and 0.5%, w/v). The liposome suspension was then added dropwise to an equal volume of the chitosan solution with stirring. The mixture was incubated for 1 h with continuous stirring and then left overnight at 4 °C. The resulting chitosan-coated liposomes were harvested from the suspension by centrifugation at 15,000 rpm for 30 min at 4 °C (Labogene 2236HR, Korea), which was then resuspended in distilled water.

### 2.4. Particle size and determination of zeta potential

The particle size and zeta potential of the chitosan-coated liposomes were measured using an ELSZ analyzer (Otsuka Electronics, Japan).

### 2.5. Entrapment efficiency of resveratrol in liposomes

Free resveratrol was removed from the liposome or chitosan-coated liposome suspension by filtering through 1.2  $\mu$ m cellulose acetate filters (Minisart, CA, 26 mm). The liposome vesicles were resuspended in ethanol (15 mL) and the solvent was then removed by rotary evaporation. The remaining resveratrol was redissolved in ethanol and its content was measured using HPLC (Shimadzu, Japan). The following equation was used to calculate the entrapment efficiency:

$$\text{Entrapment efficiency (\%)} = \frac{P}{T} \times 100$$

$T$  is the initially added resveratrol content;  $P$  is the content of resveratrol passed through the 1.2  $\mu$ m filter.

### 2.6. In vitro skin-permeation study

The *in vitro* skin-permeation study was carried out using Franz diffusion cells (PermeGear, USA). Full-thickness skin was removed from the dorsal side of a freshly excised ICR albino mouse (8 weeks, female). Subcutaneous fat and bristles were carefully removed from the skin, which was then stored at -70 °C. A specimen of the skin was sandwiched between the two halves of the Franz cell, with stratum corneum facing the donor compartment. The receptor compartment had a volume of 5 mL and was filled with a receptor phase (HCO-60:ethanol:phosphate buffered saline (PBS) = 2:20:78, w/w/w). The compartment was kept at 37 °C by circulating water through it. An aliquot (0.2 mL) of the sample was introduced into the donor compartment, which was then covered with parafilm to prevent the evaporation of the solvent. The receptor phase was continuously stirred by a spinning bar magnet. Receptor phase samples (0.5 mL) were withdrawn through the sampling port of the receptor compartment at intervals of 4 h throughout the 24 h experimental period, and the receptor compartment was refilled with the receptor phase to maintain a constant volume. The test samples were concentrated, dissolved in 100% ethanol, and then analyzed for resveratrol content (Fig. 7, Transdermal) using HPLC equipped with a UV detector and computer integrating apparatus. The column was a Shim-pack VP-ODS C18 (250 mm  $\times$  4.6 mm). The skin surface was then washed on each side with 3 mL PBS solution to remove the residual donor sample. The stratum corneum was subsequently removed by the stripping method using three strips of 3M scotch tape (3M, Korea). The tape strips were dissolved in 100% ethanol at 70 °C, and analyzed for resveratrol content using HPLC. The remaining skin was cut into small pieces and dissolved in 100% ethanol at 70 °C and analyzed for resveratrol content using HPLC.

### 2.7. Statistical analysis

All reported data are presented as mean  $\pm$  S.E.M. Statistical significance was determined by Student's *t*-test.

## 3. Results and discussion

### 3.1. Particle size of chitosan-coated liposomes containing resveratrol

The effects of chitosan addition on the physical properties of liposomes containing 0.1% resveratrol were investigated. Liposomes containing 0.1% resveratrol were coated with 0.1%, 0.3%, and 0.5% chitosan solution (w/v). The particle size of uncoated (typical) liposomes was found to be 212.83 nm. After coating with chitosan solution, this increased to 279.85, 432.58, and 558.35 nm, for 0.1%, 0.3%, and 0.5% chitosan solutions, respectively (Fig. 2). These significant increases in the size of liposomes were attributed to the adhesion of the chitosan to the liposome surface via strong interactions, thereby forming a layer on the surface [16,17]. In addition, the particle size was found to be highly dependent on the concentration of chitosan. These results suggest that large aggregated structures self-assembled on the liposome surface, with higher chitosan concentrations forming a thicker layer [18].

### 3.2. Zeta potential of chitosan-coated liposomes containing resveratrol

Zeta potential measurements are commonly used to investigate certain physical properties of colloidal drug delivery systems. They give an indication of the surface electrical charge of the particles,

Download English Version:

<https://daneshyari.com/en/article/227638>

Download Persian Version:

<https://daneshyari.com/article/227638>

[Daneshyari.com](https://daneshyari.com)