



Outstanding room-temperature capacitance of biomass-derived microporous carbons in ionic liquid electrolyte



Edurne Redondo^a, Wan-Yu Tsai^{b,c}, Barbara Daffos^{b,c}, Pierre-Louis Taberna^{b,c}, Patrice Simon^{b,c,*}, Eider Goikolea^a, Roman Mysyk^{a,**}

^a CIC Energigune, Arabako Teknologia Parkea, Albert Einstein 48, 01510 Miñano, Spain

^b Université Paul Sabatier Toulouse III, Institut Carnot CIRIMAT, UMR CNRS 5085, 118 route de Narbonne, 31062 Toulouse, France

^c Réseau sur le Stockage Electrochimique de l'Energie (RS2E), FR CNRS 3459, France

ARTICLE INFO

Keywords:

Supercapacitors
Activated carbon
Micropores
Ionic liquids

ABSTRACT

A remarkable capacitance of $180 \text{ F}\cdot\text{g}^{-1}$ (at $5 \text{ mV}\cdot\text{s}^{-1}$) in solvent-free room-temperature ionic liquid electrolyte, 1-ethyl-3-methylimidazolium bis(trifluoromethylsulfonyl)imide, was achieved in symmetric supercapacitors using microporous carbons with a specific surface area of ca. $2000 \text{ m}^2\cdot\text{g}^{-1}$ calculated from gas sorption by the 2D-NLDFT method. The efficient capacitive charge storage was ascribed to textural properties: unlike most activated carbons, high specific surface area was made accessible to the bulky ions of the ionic liquid electrolyte thanks to micropores (1–2 nm) enabled by fine-tuning chemical activation. From the industrial perspective, a high volumetric capacitance of ca. $80 \text{ F}\cdot\text{cm}^{-3}$ was reached in neat ionic liquid due to the absence of mesopores. The use of microporous carbons from biomass waste represents an important advantage for large-scale production of high energy density supercapacitors.

1. Introduction

Electrical double layer capacitors (EDLCs) store charge by electrostatic interaction between electrolyte ions and electrode surface charges [1]. Room temperature ionic liquids (RTILs) [2] have been proposed as electrolytes for advanced and safe EDLCs for their wide stable electrochemical window, wide operational temperature range and non-volatility. However, RTILs exhibit high viscosity and low ionic conductivity at room temperature; hence, electrolyte ions have hindered access into the narrow micropores of commercial activated carbons (ACs). Thus, RTIL-based supercapacitors often show low capacitance and high resistance compared to those using conventional electrolytes, based on organic solvents (acetonitrile or propylene carbonate) [3,4,5,6]. In this regard, two different approaches have been pursued to circumvent the drawbacks of RTILs and make them efficient in supercapacitors: i) dissolving RTILs in small amounts of organic solvents to increase ionic conductivity [7], and ii) employing electrode materials with fully electrolyte-accessible (open) surface, such as exohedral carbons [8] or mesoporous carbons [9]. The first approach is achieved detrimentally to the maximum cell voltage. The second cannot provide high capacitance (due to the low specific surface area (SSA) of such materials), and also requires complex synthetic procedures and/or

expensive synthetic precursors. Recent investigations demonstrated improvements in gravimetric capacitance by combining RTILs containing 1-ethyl-3-methylimidazolium (EMI^+) ion and micro/mesoporous carbons with high pore volume ($\sim 2 \text{ cm}^3\cdot\text{g}^{-1}$) [10,11]. However, high mesopore volume is detrimental to the density of materials. Thus, volumetric capacitance, the most industry-demanded metric, can be adversely affected with such carbons.

In this work, a series of ACs derived from low-cost green precursors (olive pits) was synthesized [12] and tested as electrode materials in neat 1-ethyl-3-methylimidazolium bis(trifluoromethanesulfonyl)imide (EMI-TFSI) at room temperature. These carbons contain only micropores that can be easily fine-tuned through synthesis parameters. The results showed high gravimetric and volumetric capacitance using such mesopore-free materials and EMI-TFSI within 3 V, thus offering interesting opportunities for industrial development since ACs come from cheap and abundant natural precursors.

2. Experimental

ACs were prepared by chemical KOH activation of olive pits, as reported elsewhere [12,13]. Briefly, the precursor was carbonized in a tubular furnace under an Ar flow of $100 \text{ mL}\cdot\text{min}^{-1}$ by heating at

* Correspondence to: P. Simon, Université Paul Sabatier Toulouse III, Institut Carnot CIRIMAT, UMR CNRS 5085, 118 route de Narbonne, 31062 Toulouse, France.

** Corresponding to: R. Mysyk, CIC Energigune, Arabako Teknologia Parkea, Albert Einstein 48, 01510 Miñano, Spain

E-mail addresses: simon@chimie.ups-tlse.fr (P. Simon), rmysyk@cicenergigune.com (R. Mysyk).

5 °C·min⁻¹ and dwelling for 2 h at 700 °C. The samples of carbon char were mixed with different amounts of KOH and heated up under the same conditions described in the first step. Last, the ACs were washed off with diluted HCl and water until neutral pH, and dried at 120 °C under vacuum overnight.

N₂ adsorption was conducted using an ASAP2460 instrument (Micromeritics). The samples were outgassed under vacuum at 250 °C for 24 h before analysis. N₂ isotherms were measured at 77 K for relative pressures (P/P₀) between 10⁻⁷ and 0.995. The SSA and pore size distribution (PSD) were calculated using the SAIEUS software with 2D-NLDFT [14]. The differential pore volume (dV/dlgL) was calculated as:

$$dV/dlgL = dV/dL \ln 10 \quad (1)$$

Average pore size was calculated as the weighted average from PSD, according to Eqs. (2) or (3):

$$L_0 = \int_{V_{\min}}^{V_{\text{tot}}} L dV / (V_{\text{tot}} - V_{\min}) \quad (2)$$

$$L_i = \int_{V_{\text{is}}}^{V_{\text{tot}}} L dV / (V_{\text{tot}} - V_{\text{is}}) \quad (3)$$

where L₀ and L_i correspond to the average pore size and the average ion-inaccessible pore size, L the pore size, V_{is} the ion-inaccessible pore volume, and V_{tot} the total pore volume from the cumulative DFT distribution [12].

The electrodes were made by mixing 95 wt% of ACs with 5 wt% of polytetrafluoroethylene (PTFE) binder from a 60 wt% aqueous dispersion. The mixture was stirred in ethanol to form a dough further rolled to a thickness of ~170 μm and dried under vacuum at 120 °C overnight. Disk electrodes of 11 mm diameter were cut out with the electrode mass between 7 and 8 mg·cm⁻². Two-electrode symmetric supercapacitors were assembled in Swagelok® cells using two identical activated carbon electrodes, a borosilicate glass fiber separator (Whatman GF/B) and EMI-TFSI, 99.9% (Solvionic) as electrolyte. Cell assembly was conducted in a glove box under Ar atmosphere with < 1 ppm of water and oxygen.

Electrochemical measurements were done at room temperature, 20 °C, using a multichannel potentiostat/galvanostat VMP3 (Biologic): cyclic voltammetry (CV) at a scan rate of 5 mV·s⁻¹, galvanostatic cycling (GC) at 0.1–30 A·g⁻¹ of active material per electrode and electrochemical impedance spectroscopy (EIS) from 1 MHz to 10 mHz.

Gravimetric and volumetric electrode capacitance (C) was calculated using Eqs. (4) and (5), respectively:

$$C = 2 \cdot \int Idt / (U \cdot m) \quad (4)$$

$$C = 2 \cdot \int Idt / (U \cdot \pi \cdot r^2 \cdot h) \quad (5)$$

where I is the current, t the discharge time, U the voltage, m the active material mass per electrode, r the radius and h the electrode thickness.

Series resistance was evaluated from the intercept of the real axis at high frequency of the Nyquist plot, and in-pore ionic resistance from the intercept of quasi-vertical line at low frequency with the real axis after excluding the series resistance [15].

3. Results and discussion

Textural properties are shown in Fig. 1 and Table 1. Since the maximum capacitance of carbide-derived porous carbons was found at pore size of ~0.72 nm using neat EMI-TFSI [16], pores narrower than 0.70 nm are considered poorly accessible to electrolyte ions due to the ion-sieving effect. Ion-accessible pore volume and surface area calculated using this cut-off (> 0.70 nm), d₅₀ and d₉₀ are listed in Table 1. d₅₀ and d₉₀ are the pore widths corresponding to 50 and 90% of the

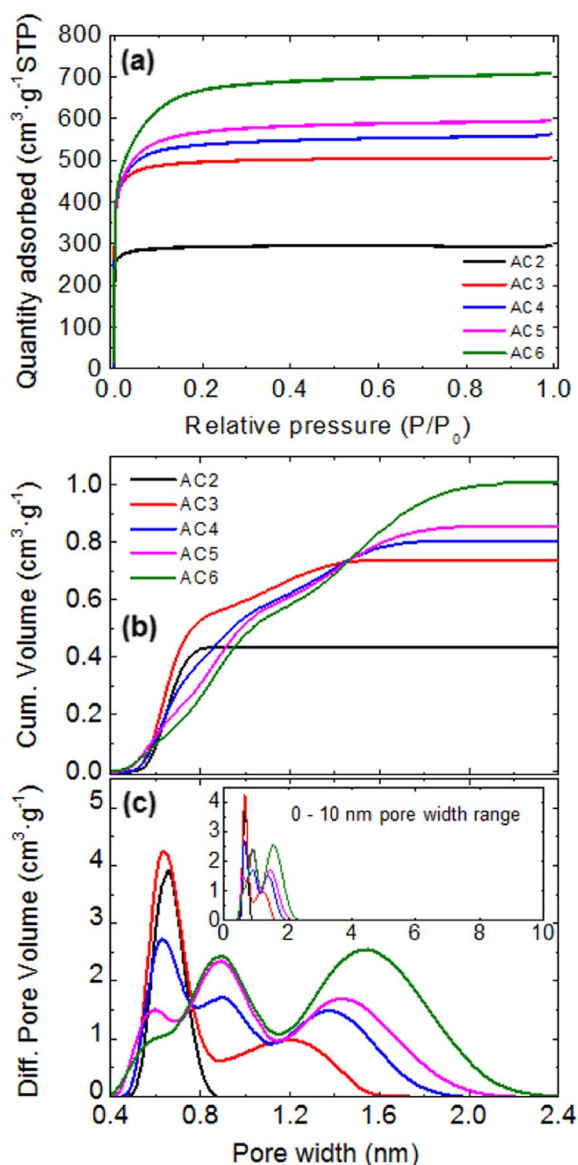


Fig. 1. (a) N₂ adsorption/desorption isotherms (b) cumulative (c) differential pore volume (dV/dlgL) vs pore size calculated by the 2D-NLDFT model.

total pore volume and their use was recently suggested for assessing PSD [17]. All the ACs have pores in the micropore range (< 2 nm) and, as reported elsewhere [18], PSD is widened with the higher KOH/carbon ratio. Thus, AC2 exhibits the smallest L₀ and d₅₀ among the studied ACs. Although AC3–AC6 have similar SSA, an increasing L₀ is observed from AC3 to AC6. Moreover, the difference between d₉₀ and d₅₀ increases correspondingly, meaning higher pore size dispersity with more KOH.

Fig. 2a and b show the CVs of symmetric cells for AC2–AC6 at 5 mV·s⁻¹ in EMI-TFSI. Most of the samples exhibit rectangular CVs typical of supercapacitors. Most importantly, high specific capacitance of 179 F·g⁻¹, 163 F·g⁻¹ and 171 F·g⁻¹ was measured for AC4, AC5 and AC6, respectively. To our knowledge, such high capacitance values have never been reported for purely microporous carbons in neat RTILs. By contrast, AC2 shows very low gravimetric capacitance since d₉₀ is below 0.75 nm, thus poorly accessible to cations and anions, in agreement with the accessible SSA of only 292 m²·g⁻¹ (Table 1). Compared with AC2, AC3 shows decent gravimetric capacitance with huge distortion at high polarisation, meaning that, even with higher SSA, not all the pores are easily accessible to the electrolyte. The increase in d₅₀ beyond 0.70 nm and the associated L_i, such as that

Download English Version:

<https://daneshyari.com/en/article/4766566>

Download Persian Version:

<https://daneshyari.com/article/4766566>

[Daneshyari.com](https://daneshyari.com)