



Contents lists available at ScienceDirect

Journal of Rock Mechanics and Geotechnical Engineering

journal homepage: www.rockgeotech.org

Full length article

Influence of zeolite and cement additions on mechanical behavior of sandy soil



Hossein Mola-Abasi*, Issa Shooshpasha

Geotechnical Department, Babol University of Technology, Babol, Iran

ARTICLE INFO

Article history:

Received 3 September 2015
 Received in revised form
 30 January 2016
 Accepted 31 January 2016
 Available online 28 June 2016

Keywords:

Zeolite
 Cemented sand
 Strength
 Unconfined compressive strength (UCS)
 Void-cement ratio

ABSTRACT

It is well known that the cemented sand is one of economic and environmental topics in soil stabilization. In this instance, a blend of sand, cement and other materials such as fiber, glass, nanoparticle and zeolite can be commercially available and effectively used in soil stabilization in road construction. However, the influence and effectiveness of zeolite on the properties of cemented sand systems have not been completely explored. In this study, based on an experimental program, the effects of zeolite on the characteristics of cemented sands are investigated. Stabilizing agent includes Portland cement of type II and zeolite. Results show the improvements of unconfined compressive strength (UCS) and failure properties of cemented sand when the cement is replaced by zeolite at an optimum proportion of 30% after 28 days. The rate of strength improvement is approximately between 20% and 78%. The efficiency of using zeolite increases with the increases in cement amount and porosity. Finally, a power function of void-cement ratio and zeolite content is demonstrated to be an appropriate method to assess UCS of zeolite-cemented mixtures.

© 2016 Institute of Rock and Soil Mechanics, Chinese Academy of Sciences. Production and hosting by Elsevier B.V. This is an open access article under the CC BY-NC-ND license (<http://creativecommons.org/licenses/by-nc-nd/4.0/>).

1. Introduction

Soil stabilization with cement has been a ground improvement method in geotechnical engineering for many years. Using cemented soil is a versatile and reliable technique among others to increase shear strength parameters. By borrowing materials from elsewhere, the cemented soils have advantages of economy, simple and rapid performances. The cemented technique is particularly suited for stabilization of problematic soils such as loose sand deposit. Cementation of sand can result in increasing brittle behavior of the material. The unconfined compression test is one of the major and rapid laboratory tests to evaluate the effectiveness of the stabilization with cement or other additives. The compressive strength of artificially cemented soils has been studied in the past by several investigators (e.g. Clough et al., 1981; Huang and Airey, 1998; Consoli et al., 2007, 2009a, 2013a; Dalla Rosa et al., 2008; Horpibulsuk et al., 2014; Yilmaz et al., 2015).

A number of studies have been done to assess the mechanical behavior and compressive strength increase of cemented sands

using added fiber, glass, fly ash, silica fume and nanoparticle in the same manner (e.g. Consoli et al., 1998, 2009b, 2013b; Arabani et al., 2012; Choobbasti et al., 2015). However, there has been a little effort to the use of pozzolans such as natural zeolite. The natural zeolite, an extender, has been investigated for use as cement and concrete improver (Poon et al., 1999; Perraki et al., 2003). The natural zeolite contains large quantities of reactive SiO_2 and Al_2O_3 (Poon et al., 1999). Similar to other pozzolanic materials, zeolite substitution can improve the strength of cement by pozzolanic reaction with $\text{Ca}(\text{OH})_2$, prevent undesirable expansion due to alkali–aggregate reaction, reduce the porosity of the blended cement paste, and improve the interfacial microstructure properties between the blended cement paste (Feng et al., 1990; Poon et al., 1999; Canpolat et al., 2004). Poon et al. (1999) observed that the pozzolanic activity of natural zeolite is higher than that of fly ash but lower than that of silica fume. Yilmaz et al. (2007) concluded that the clinoptilolite blend decreases the specific weight of cements.

This study aims to quantify the influence of the amount of zeolite and cement and relative density of artificially cemented sandy soils cured for 28 days on the strength parameters via unconfined compression tests, as well as to evaluate the power function fits to predict unconfined compressive strength (UCS) of the soils.

* Corresponding author. Tel.: +98 9113700669.

E-mail address: hma@stu.nit.ac.ir (H. Mola-Abasi).

Peer review under responsibility of Institute of Rock and Soil Mechanics, Chinese Academy of Sciences.

2. Experimental program

2.1. Materials

The base sandy soil was obtained from Babolsar City located on the southern shorelines of the Caspian Sea. The soil is classified as poor-graded sand (SP) according to the Unified Soil Classification System (ASTM D422, 2003) with angular particle and specific weight (G_s) of 2.74. The soil is pure sand with a mean effective diameter (D_{50}) of 0.24 mm, and the uniformity and curvature coefficients are 1.75 and 0.89, respectively. The minimum and maximum unit weights are 14.9 kN/m² and 17.7 kN/m², respectively.

Portland cement of type II (ASTM C150, 2003) was applied in this research. The specific weight of the cement grains, specific surface and initial setting time are 3.11, >3000 cm²/g, and >75 min, respectively.

The zeolite is of natural clinoptilolite kind and particles smaller than 75 μm (No. 200 sieve) are referred to as fine aggregates located near Aftar City in Semnan Province of Iran. The zeolite is non-plastic and classified as silt (ML) according to the Unified Soil Classification System (ASTM D422, 2003) with $G_s = 2.2$. The grain size distribution curves of the materials including sand, cement and zeolite are presented in Fig. 1.

2.2. Experimental program, sample preparation and test process

The positive effect of zeolite on cemented sand strength requires the curing time to be long enough due to pozzolanic reaction. The pozzolanic activity of zeolites with cement depends on their chemical and mineralogical compositions. In this study, the curing time of 28 days is selected.

Cement content (C), replacement of cement by zeolite (Z) and void ratio (e) are the variable parameters in the testing program to identify the effect of cement and zeolite additives on sand strength. The variables measured in sample preparation are presented in Table 1.

For unconfined compression tests, cylindrical specimens ($\phi 38$ mm \times 76 mm) were used. Given a void ratio e , the target dry unit weight γ_d can be calculated according to the following equation:

$$\gamma_d = \frac{G_s \gamma_w}{1 + e} \quad (1)$$

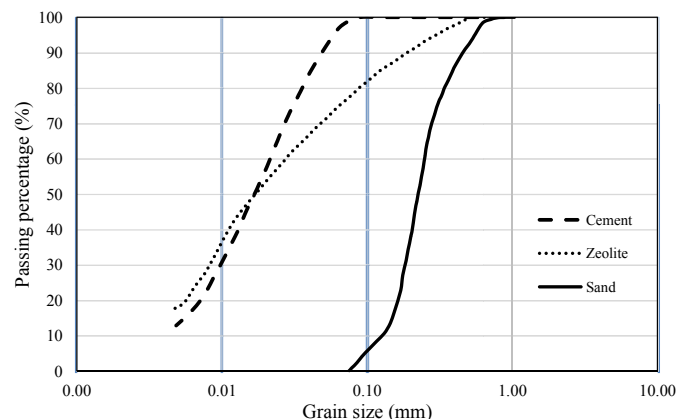


Fig. 1. Grain size distribution curves of sand, cement and zeolite.

Table 1
Description of parameters.

Variable	Description of samples
Soil type	Poorly graded sand from Babolsar City (Shores of Caspian Sea)
Cement agent	Portland cement (type II)
Cement content	2%, 4%, 6% and 8% dry unit weight of base soil
Type of zeolite	Natural clinoptilolite zeolite
Zeolite content (replacement by cement)	0%, 10%, 30%, 50%, 70% and 90% of cement content
Void ratio	0.648, 0.591 and 0.563 corresponding to $D_r = 50\%$, 70% and 85% sands, respectively, where D_r is the relative density
Water content	10% weight of base soil
Sample size	38 mm in diameter and 76 mm in height, compacted in three layers
Curing condition	28 d in humid room with the relative humidity greater than 90%

where G_s is a composite specific weight (due to the specific weight of cement grains (3.11) greater than that of sand and zeolite grains (2.74 and 2.2, respectively)) based on the zeolite, cement and sand percentages in the specimens. This equation is also used for precise calculation of void ratio and porosity. Sand, cement and zeolite (based on the mixture procedure shown in Table 1) were mixed uniformly, then tap water (10% of dry unit weight) was added continuously to the soil-cement mixture. The specimens were tamped into three identical layers to reach the specified dry unit weight considering the compaction method proposed by Ladd (1978). The top of each sample was slightly scarified. The time used to preparation, mixture, and compaction was always less than 1 h, although using zeolite increases the initial setting time of cement. A small portion of mixture was also taken for moisture content determination. Additionally, the specimens were wrapped in plastic bags and cured for 28 days in a humid room at 24 °C with the relative humidity greater than 90%.

The unconfined compression test is one of the major and rapid laboratory tests to evaluate the effects of zeolite quantity, cement content, porosity, and void-cement ratio on the mechanical strength of soil-zeolite-cement mixture. An automatic loading machine with a maximum capacity of 10 kN and proving rings with capacities of 2 kN \pm 0.0014 kN and 10 kN \pm 0.0061 kN, respectively, were used for the unconfined compression tests. Seventy two unconfined compression tests in total were performed (0.76 mm/min) according to ASTM D2166 (2000). Failure types of stabilized specimens are shown in Fig. 2. Because of the typical scatter of data obtained from unconfined compression tests, every three specimens were tested and the average was considered. The satisfactory number of tests per class of specimens is checked by the calculated value of standard deviation/mean of UCS obtained from the three samples, which was 4.

3. Results

The stress–strain curves of specimens stabilized with 4% and 8% cement contents with respect to different zeolite substitutions, under the condition of constant void ratio ($e = 0.591$), are illustrated in Fig. 3. It is shown that the maximum axial stress significantly increases due to cement stabilization, and the strain corresponding to the peak axial stress decreases. By increasing zeolite replacement of cement, the peak strain increases in comparison with cemented samples. In other words, utilizing zeolite in cemented sand increases the displacement at failure, and reduces the brittle behavior. Since the main objective of this paper is to estimate UCS, less attention is paid to the strain and failure types.

Download English Version:

<https://daneshyari.com/en/article/4923716>

Download Persian Version:

<https://daneshyari.com/article/4923716>

[Daneshyari.com](https://daneshyari.com)