Contents lists available at ScienceDirect



International Journal of Heat and Mass Transfer

journal homepage: www.elsevier.com/locate/ijhmt

Design and characterization of an additive manufactured hydraulic oil cooler



HEAT and M

Brandon J. Hathaway, Kunal Garde, Susan C. Mantell, Jane H. Davidson*

Department of Mechanical Engineering, University of Minnesota, 111 Church St SE, Minneapolis, MN 55455, United States

ARTICLE INFO

Article history: Received 9 August 2017 Received in revised form 2 October 2017 Accepted 3 October 2017

Keywords: Additive manufacturing 3D printing Heat exchanger Oil cooler Off-set strip fins Tube bank

ABSTRACT

A hydraulic oil cooler was fabricated from an aluminum alloy by selective laser melting. The plate-fin tube bank has special features, including non-circular, internally finned tubes, and external angled fins to allow flexibility in the printing process. The study demonstrates the capability to additively manufacture commercial-scale heat exchangers with intricate features. Heat transfer and pressure drop performance are characterized in a wind tunnel over a range of oil- and air-side flow rates for inlet temperatures representing high limits for a commercial hydraulic excavator. The data and results of a computational fluid dynamic model provide insight on the impact of features that are dictated by the manufacturing process on thermal and hydraulic performance.

© 2017 Published by Elsevier Ltd.

1. Introduction

At inception, additive manufacturing (AM) was a tool used primarily for fabrication of prototypes. The advancement of additive manufacturing processes now promises the potential for production of functional components where the flexibility of 3D printing makes it a cost-effective alternative for small quantities. Direct metal laser sintering, direct metal laser melting (or selective laser melting), and electron beam melting allow the use of metal alloy powders. At present, there are a number of initiatives to expand the use of metal additive manufacturing to heat exchangers but few studies appear in the archival scientific literature. Saltzman et al. applied a laser based powder bed fusion process to fabricate an aircraft oil cooler similar to a conventional design but with modifications such as orienting the air and liquid side extended features and the header walls at an angle for compatibility with additive manufacturing [1]. Kirsch and Thole studied the heat transfer and pressure losses in additively manufactured wavy micro channels for gas turbine engines. The wavy shapes and the small sizes of these channels are examples of the design freedom that additive manufacturing offers [2]. Arie et al. developed a manifold-microchannel design allowing for more compact gasliquid heat exchangers utilizing metal additive manufacturing techniques [3]. Norfolk and Johnson fabricated a microchannel heat exchanger using the hybrid ultrasonic sheet lamination (USL) process, which combines additive and subtractive manufacture [4]. Assad et al. produced a wire mesh compact heat exchanger using pulsed gas dynamic spraying to deposit metal powder on a wire mesh [5]. Another application of the same process reported by Dupais et al. is tapered pin fins for heat sinks [6].

In the present work, the design and characterization of an aluminum oil cooler printed via powder bed selective laser melting (SLM) are presented. The study provides a demonstration of the use of additive manufacture for a functional and relatively large heat exchanger. As an example of such an application, we consider an oil cooler for a commercial excavator. The stock oil cooler is a microchannel brazed aluminum oil-to-air heat exchanger (Fig. 1) used to cool hydraulic oil in a 27.6 kW excavator. The stock heat exchanger is 430 mm \times 530 mm \times 50 mm including the inlet and outlet manifolds with an air-flow cross sectional area of 373 imes467 mm. Heat transfer surface area is estimated to be 1.23 m² on the oil-side and 2.54 m² on the air-side. There are 38 microchannel tubes, each with internal offset strip fins to enhance heat transfer on the high Prandtl number oil-side ($Pr \sim 100$) [7]. On the airside, the plain fins are 0.1 mm thick with a pitch of 1.8 mm. In the excavator, the oil cooler is sandwiched between the condenser of the air conditioning circuit and the engine radiator with a single fan drawing air across the three exchangers. At the design operating conditions listed in Table 1, the stock oil cooler provides a measured heat duty of 11.5 kW with pressure drops of 75 Pa and 15 kPa on the air- and oil-side respectively (experiments are described in Section 5).

^{*} Corresponding author. E-mail address: jhd@umn.edu (J.H. Davidson).

Nomenclature

Α	area [m ²]	Subscrip	ots
С	nozzle flow coefficient [–]	air	pertaining to the air-side of the heat exchanger
$C_{\rm P}$	heat capacity at constant pressure [J/kg K]	с	collar diameter
COP	coefficient of performance [–]	CF	counter-flow arrangement value
D	diameter [m]	CFD	computational fluid dynamic simulation result
F	log-mean temperature difference correction factor [–]	CX	cross sectional area
Κ	minor loss coefficient [–]	fin	pertaining to the external fins
L	length [m]	h	hydraulic diameter
'n	mass flow rate [kg/s]	i	general index variable
Р	pressure [Pa] or wetted perimeter [m]	in	inlet condition
Q	heat transfer rate [kW]	LM	log-mean temperature difference
Т	temperature [K]	L	loss
t	fin thickness [m] or t-statistic value [–]	m	minor loss
UA	overall heat transfer coefficient and area product.	nozzle	pertaining to the air-flow measurement nozzles
	$\dot{Q}/\Delta T_{LM}$ [W/K]	0	outside dimension
Ň	volumetric flow rate [L/s]	oil	pertaining to the oil-side of the heat exchanger
w	uncertainty in measured or calculated variable	OSF	pertaining to the offset strip fins
Y	dimensionless expansion factor [-]	out	outlet condition
		sim	value obtained from numerical simulation
Greek		std	value at standard conditions (101.3 kPa, 25 °C)
ρ	density [kg/m ³]	total	total pressure drop including minor losses
,		tube	value for the full oil-side tube length
		∞	bulk or far-field fluid value

Additive manufacturing of a replacement heat exchanger considers the option of a plate-fin tube bank heat exchanger. The selective laser melting process allows one-step fabrication of the manifold, tubes, and internal and external heat transfer augmentation features. It provides the option of design with non-circular tubes and intricate fin shapes. At the same time, the design of the tube bank is inherently tied to the printing process. The overall size and the detailed features required to achieve heat transfer performance impose unique requirements for the cooler design. Experimental and numerical analysis of the thermal and hydraulic performance of the fabricated heat exchanger are presented. The results illustrate the impact of key aspects of design dictated by the printing process on thermal performance.

2. Design for additive manufacturing

In SLM, a high-power laser traces a slice of the part onto a powder bed. The fine grain metal powder particles are melted and fused, both in the build plane (x-y plane) and with the previously bonded layer. Upon completion of the layer by layer build, the solid metal powder, which surrounds and fills the part, is removed. The process allows for parts with intricate geometries not producible by traditional methods. The mechanical and thermal properties for SLM fabricated metal parts are as good or better than those for cast or wrought materials [8,9]. Furthermore, SLM offers the benefit of consolidating multiple components into a single manufactured part [8]. For heat exchangers, this feature reduces the

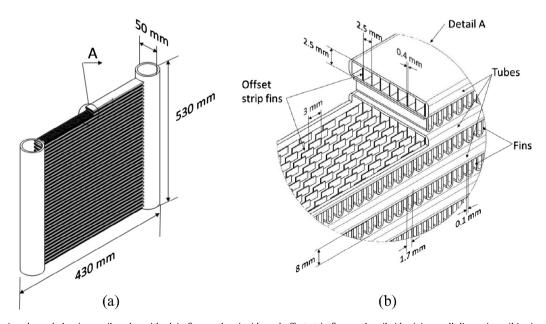


Fig. 1. Stock microchannel aluminum oil cooler with plain fins on the air side and offset strip fins on the oil side: (a) overall dimensions, (b) microchannel detail.

Download English Version:

https://daneshyari.com/en/article/4993390

Download Persian Version:

https://daneshyari.com/article/4993390

Daneshyari.com