

## Short Communication

## Thermally decomposed Ni-Fe-hydrotalcite: A highly active catalyst for the solvent-free N-acylation of different amines by acid chlorides

V.R. Choudhary\*, D.K. Dumbre

Chemical Engineering and Process Development Division, National Chemical Laboratory, Pune, 411008, India

## ARTICLE INFO

## Article history:

Received 15 April 2011

Received in revised form 12 May 2011

Accepted 15 May 2011

Available online 23 May 2011

## Keywords:

Amines

Acid chlorides

Ni-Fe-hydrotalcite derived catalyst

Decomposition of Ni-Fe-hydrotalcite

N-acylation of amines

## ABSTRACT


A composite Ni-Fe catalyst obtained from the thermal decomposition of Ni-Fe-hydrotalcite at 600 °C shows very high activity in the solvent-free N-acylation of amines by different acid chlorides with high product yields under very mild reaction conditions (viz. room temperature, short reaction period and small amount of catalyst). The catalyst also shows excellent reusability in the reaction. The crystalline phases present in the catalyst are mixed oxides and hydroxides of nickel and iron. The high catalytic activity of the decomposed Ni-Fe-hydrotalcite is attributed to the formation of uniformly distributed Ni-Fe metal oxides and hydroxides.

© 2011 Elsevier B.V. All rights reserved.

## 1. Introduction

Acylation of amines is among the most widely used transformations in organic synthesis. N-acylated amines and their derivatives are widely used as starting materials for various organic transformations. The N-acylation of amines also provides an efficient and inexpensive means to protect their –NH groups in a multistep organic synthesis [1,2]. Earlier N-acylation was usually carried out using acylating agents, such as acid anhydrides or acyl chlorides in presence of organic bases [2–7]. This base catalyzed N-acylation is slow and requiring harsh and cumbersome procedures. As an alternative to basic catalysts, recently homogeneous Lewis acid (such as  $\text{ZnCl}_2$ ,  $\text{FeCl}_3$ ,  $\text{MoCl}_5$ ,  $\text{B}(\text{C}_6\text{F}_5)_3$  [8] and anhydrous  $\text{NiCl}_2$  [9]) and iodine [10] have been reported for the N-acylation under solvent-free conditions. However, these homogeneous catalysts are difficult to remove from the reaction mixture and also cannot be reused. Hence they are not environmentally benign. Moreover, most of them need expensive acylating agent such as acid anhydride [8,9]. Heterogeneous catalysts, such as magnesium oxide [11] and yttria-zirconia [12], have also been reported for the N-acylation of amino compounds. However, although these catalysts can be easily separated, they require solvent and/or harsh reaction conditions (higher temperature and/or higher reaction time). Non-catalytic procedure for N-acylation at room temperature has also been reported [13]. But in this case, the acylation period is very long

and, moreover, the reaction involves the use of ethyl acetate (as a solvent) and expensive acid anhydride. Hence there is a genuine

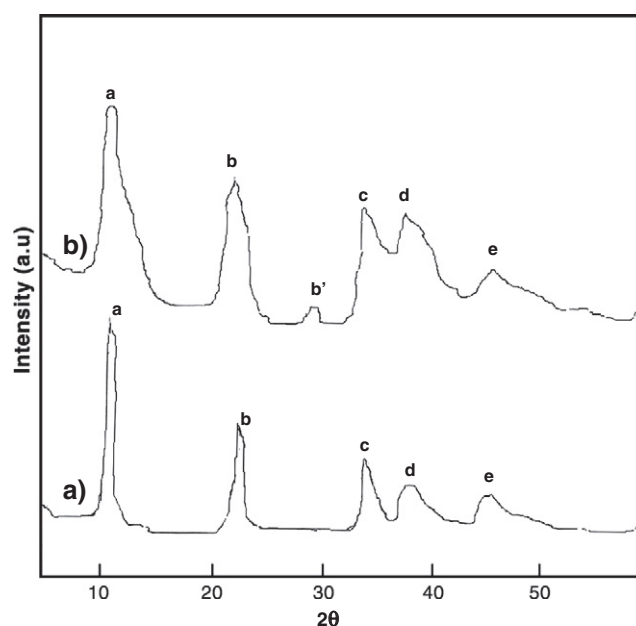

**Fig. 1.** XRD spectra of catalyst obtained from the thermal decomposition of a) Ni-Fe-HT and b) Ni(II)-Fe(III) nitrates, at 600 °C [Crystalline phases: a)  $\text{Fe}(\text{OH})_3$ , b)  $\text{Ni}(\text{OH})_2$ , c) NiOxide-OH-Fe, d) NiO, e) Ni-Fe-Oxide and b')  $\text{Fe}_2\text{O}_3$ ].

\* Corresponding author. Tel.: +91 20 25902318; fax: +91 20 25902612.

E-mail addresses: [vr.choudhary@ncl.res.in](mailto:vr.choudhary@ncl.res.in), [vrc0001@yahoo.co.in](mailto:vrc0001@yahoo.co.in) (V.R. Choudhary).

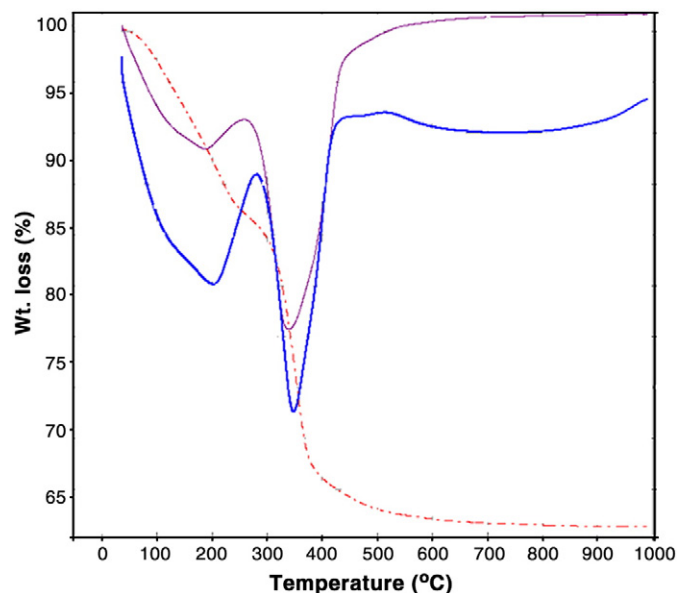


Fig. 2. TG, DTG and DTA of the Ni-Fe-hydrotalcite.

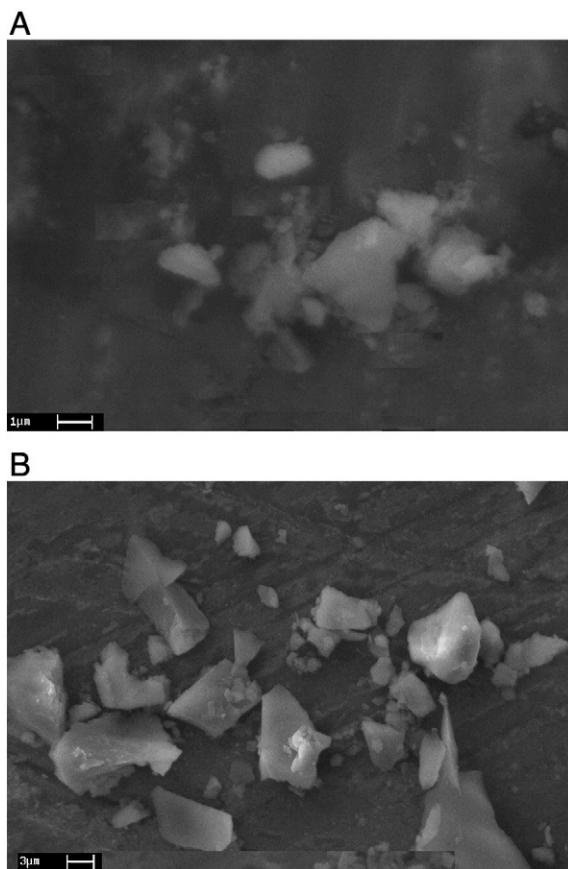


Fig. 3. SEM Photograph of catalyst obtained from the thermal decomposition of a) Ni-Fe-HT and b) physically mixed Ni(II)-Fe(III) nitrates (Ni/Fe = 3) at 600 °C.

need for developing a simple but rapid and environmentally benign method for the N-acylation of amines.

In this paper we report a solvent-free rapid selective N-acylation of aliphatic, cyclic and aromatic amines with inexpensive acid chlorides at room temperature using a highly active solid catalyst derived from Ni-Fe-hydrotalcite. The catalysts can be easily separated and reused several times in the reaction.

## 2. Experimental

The solid catalyst used in this investigation was obtained from the thermal decomposition of Ni-Fe-hydrotalcite (Ni/Fe mole ratio of 3.0) in a muffle furnace at 600 °C for 4 h. The resulting mass was finely powdered. The preparation and characterization of Ni-Fe-hydrotalcite have been given in our earlier publications [14,15].

The catalyst was characterized for crystalline phases by XRD (using a Phillips Diffractometer (1730 series) and  $\text{CuK}\alpha$  radiations), particle/crystal size by SEM (using Stereo Scan 440 made in Cambridge UK). Its formation was studied by the thermal analysis (TG, DTG and DTA) of the Ni-Fe-hydrotalcite from 100 °C to 1000 °C at a linear heating rate of 20 °C/min in air (using Diamond TG/DTA).


The catalytic N-acylation reaction was carried out in a magnetically stirred round bottom flask (capacity: 25  $\text{cm}^3$ ), at the following reaction conditions: reaction mixture = 5 mmol amine + 7 mmol acid chloride + catalyst (10 wt.% w.r.t. amine) at room temperature (300 K) and reaction time = 1–30 min. Reaction was monitored by TLC. After completion of the reaction, the catalyst was separated by filtration and the filtrate was treated with a saturated solution of sodium bicarbonate, followed by extraction with ethyl acetate to give the crude product, which was subsequently purified by column chromatography on silica gel with petroleum ether/ethyl acetate as eluent. The catalyst was further washed with acetone, dried and reused. The reaction product was isolated by column chromatography and was confirmed by NMR spectroscopy.

## 3. Results and discussion

### 3.1. Catalyst formation and characterization

The catalyst was obtained from the thermal decomposition of Ni-Fe-HT (Ni/Fe = 3,  $\text{CO}_3^{2-}$  concentration = 0.66 mmol/g, surface area = 60  $\text{m}^2/\text{g}$ ) [14] at 600 °C. The XRD of the catalyst (Fig. 1a) revealed that the hydrotalcite structure is totally destroyed after decomposition of the Ni-Fe-hydrotalcite. The main crystalline phase present in the catalyst were found to be uniformly distributed  $\text{Fe}(\text{OH})_3$ ,  $\text{Ni}(\text{OH})_2$ , Ni-oxide-OH-Fe, NiO and Ni-Fe-Oxide. The phases are expected to be uniformly distributed in the catalyst.

In order to study the catalyst formation, the Ni-Fe-HT was subjected to thermal analysis from 100 °C to 1000 °C. The TG, DTG and DTA graphs for the same are presented in Fig. 2. The TG, DTG and DTA curves indicate that the decomposition is endothermic and it occurs in two distinct steps- step-I between 100 °C and 300 °C, with the DTG and DTA peaks at 185 °C and 200 °C, respectively, and step-II between 300 °C and 900 °C, with the DTG and DTA peaks at 330 °C and 340 °C, respectively. The weight loss in step-I and step-II was about 16% and 67.5%, respectively. The weight loss up to the temperature of 400 °C was quite fast. The weight loss in step-I is expected due to loss of physically adsorbed water in the hydrotalcite. Whereas,

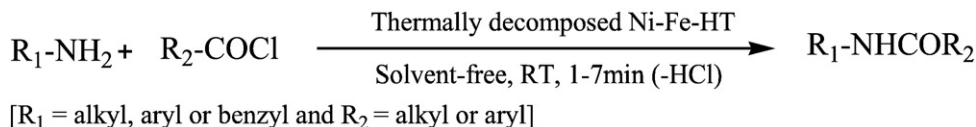

Scheme 1. N-acylation of amines.

Download English Version:

<https://daneshyari.com/en/article/51852>

Download Persian Version:

<https://daneshyari.com/article/51852>

[Daneshyari.com](https://daneshyari.com)