



## Polymer Communication

# Preparation of a super-hydrophobic poly(vinyl chloride) surface via solvent–nonsolvent coating

Xinhong Li, Guangming Chen, Yongmei Ma \*, Lin Feng, Hongzhi Zhao, Lei Jiang, Fosong Wang \*\*

*Laboratory of New Materials, Institute of Chemistry, The Chinese Academy of Sciences, Beijing 100080, People's Republic of China*

Received 12 May 2005; received in revised form 8 August 2005; accepted 9 August 2005

Available online 15 December 2005

## Abstract

A new simple approach was developed to obtain a super-hydrophobic PVC surface via solvent–nonsolvent coating without addition of low-surface-energy compounds. Also, the PVC film is nearly or still maintains its super-hydrophobicity when contacting with acid, alkali or salt solutions. SEM shows that compared with common smooth PVC surface, a lotus-like structure with micro- and nano-papillae was obviously observed on the hydrophobic PVC surfaces. Such a special surface microstructure may result in the super-hydrophobicity. A brief explanation to the formation of the special microstructure was put forward on the basis of diffusion, tension break and micro- and nano-phase separation.

© 2005 Elsevier Ltd. All rights reserved.

*Keywords:* Super-hydrophobic; Poly(vinyl chloride); Solvent–nonsolvent coating

## 1. Introduction

Wettability is important for solid surface. A surface having water contact angle greater than  $150^\circ$  is commonly called super-hydrophobic [1]. Super-hydrophobic surfaces have attracted much attention from both industrial and fundamental research. Recently, many works focused on super-hydrophobic surfaces have been carried out [1–25], such as super-hydrophobic fluorocarbon coating with ribbon surface structures [9], super-hydrophobic silica aerogels [10], chemical vapor deposition of trimethylmethoxysilane [11], super-hydrophobic surface based on a steric acid self-assembled monolayer over polyethyleneimine thin films [13]. We have succeeded in preparing super-hydrophobicity carbon films in a wide range of pH values [18], super-hydrophobic zinc oxide thin films after modification with fluoroalkyl silane [20], and honeycomb-like aligned carbon nanotube films [21]. Most of these super-hydrophobic surfaces were prepared by first functionalized the precursor materials with low-surface-energy groups such as fluorinate, silicon and fluoroalkyl silane [15–18,20,21] or some expensive ones such as carbon nanotubes [9–11,14,19].

Thus, how to prepare a super-hydrophobic surface from a commonly hydrophobic material without addition of low-surface-energy ingredients is commercially important and scientifically challenging. Although some progresses have been reported [22,24,25], the preparation procedures were rather complicated or carried out at fairly high temperatures. Besides surface functionalization, the roughness and surface microstructure are important factors to surface hydrophobicity [26]. For example, natural lotus leaf with micro- and nano-papillae two-length-scaled hierarchical structure shows super-hydrophobic. Utilizing the difference in solubility of polymer materials in solvent, a super-hydrophobic surface of poly(methyl methacrylate) (PMMA) and fluorine-end-capped polyurethane with lotus-like microstructure [23], and a submicrometer-scale heterogeneous surface of polystyrene (PS)–PMMA [27] were obtained. By controlling the crystallization time and nucleation rate, super-hydrophobic surfaces of a semicrystalline polymer, low-density polyethylene (LDPE), were achieved [28]. In addition, a flow-induced stripe pattern with improved surface roughness occurred in phase-separated polymer fluids by introduction of temperature gradient [29]. In this work, we report a simple and novel method using solvent–nonsolvent coating to prepare super-hydrophobic surfaces with micro- and nano-papillae hierarchical microstructure. More specifically, a commonly used amorphous polymer, poly(vinyl chloride) (PVC), was adopted, and no low-surface-energy material was added.

\* Corresponding authors. Tel./fax: +86 10 62659019.

E-mail address: maym@iccas.ac.cn (Y. Ma).

## 2. Experimental

one gram of PVC resin (obtained from Beijing No. 2 Chemical Corporation, SG5 type) was dissolved in 18 g tetrahydrofuran to form a pre-solution. At room temperature, one volume of nonsolvent was dropped onto a clean glass plate. Then, it was coated with 1–1.5 times the volume of the PVC solution rapidly. Three nonsolvents were adopted, i.e. 2:1 (v/v) ethanol/water, 5:1 (v/v) acetone/water, and ethanol. By control of the ratios of the solvent and the nonsolvent, porous PVC films were obtained. After drying for 2 h in vacuum, the wettability of the porous film was measured on a dataphysics OCA20 contact-angle system at ambient temperature with about 7  $\mu\text{l}$  droplets. The surface morphology of the porous film was collected on a scanning electron microscopy (SEM) of JEOL JSM-6700F (Fig. 1).

## 3. Results and discussion

In general, PVC is an amorphous material, and coating the PVC solution on a glass plate normally forms a smooth film. The morphology of the PVC smooth film is shown by SEM in

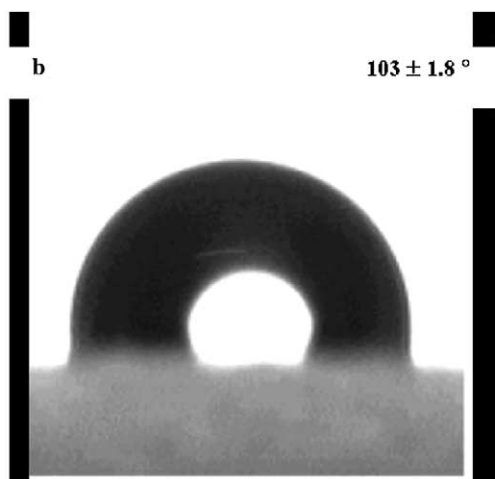
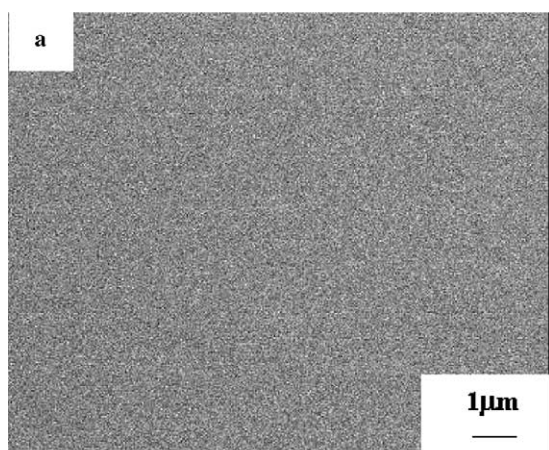


Fig. 1. Surface morphology (a) and water contact angle (b) of smooth PVC film formed by coating directly on a glass plate.

Table 1

The contact angle ( $\theta^\circ$ ) of PVC film contacting with water, acid, alkali, and salt aqueous solutions

Precipitator	Pure water	HCl	$\text{Na}_2\text{CO}_3$	KCl
None	$103 \pm 1.8$	$79.4 \pm 1.6$	$78.9 \pm 1.8$	$79.9 \pm 1.5$
2:1 $\text{CH}_3\text{CH}_2\text{OH}/\text{H}_2\text{O}$	$155.3 \pm 1.9$	$147.6 \pm 2.2$	$148.5 \pm 1.8$	$143.8 \pm 2.0$
5:1 $\text{CH}_3\text{COCH}_3/\text{H}_2\text{O}$	$163.5 \pm 2.1$	$149.5 \pm 2.3$	$150.3 \pm 2.5$	$151.2 \pm 1.9$
$\text{CH}_3\text{CH}_2\text{OH}$	$163.6 \pm 1.8$	$150.9 \pm 1.9$	$154.7 \pm 1.7$	$150.5 \pm 2.1$

Fig. 1. And its water contact angle of the smooth film is about  $103 \pm 1.8^\circ$ , indicating it is hydrophobic.

Table 1 shows the contact angles of the PVC films contacting with water, 2% (w/w) hydrochloric acid, sodium carbonate, and potassium chloride aqueous solutions. For the smooth PVC film, the contact angle with water is  $103 \pm 1.8^\circ$  and becomes lower than  $90^\circ$  when contacting with acid, alkali and salt aqueous solutions. This may suggest that the smooth PVC film could be wetted by acid, alkali or salt aqueous solution. By solvent–nonsolvent coating procedure, hydrophobic PVC surfaces could be successfully obtained with their contact angles with water higher than  $150^\circ$ , using any of the three nonsolvents, 2:1 (v/v) ethanol/ $\text{H}_2\text{O}$ , 5:1 (v/v) acetone/ $\text{H}_2\text{O}$  or ethanol, as shown in both Table 1 and Fig. 2. It is also interesting that these super-hydrophobic surfaces maintained high hydrophobicity after being wetted by acid, alkali and salt solutions. Their contact angles are slightly lower than  $150^\circ$  or still higher than  $150^\circ$ .

As is well known, Wenzel [26] first derived the relationship between contact angle of a liquid on a smooth surface ( $\theta$ ) and on a rough surface ( $\theta_r$ ) made of the same material (Eq. (1)), where  $r$  is the roughness factor. According to the equation, if the roughness is high enough, a super-hydrophobic surface can

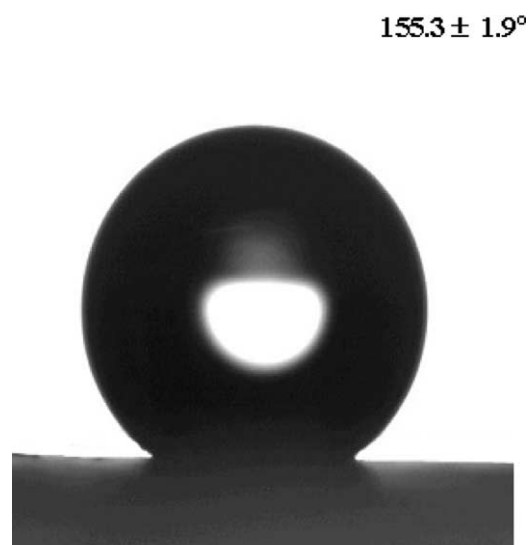


Fig. 2. Water contact angles of super-hydrophobic PVC films prepared by coating on a glass plate with 2:1  $\text{CH}_3\text{CH}_2\text{OH}/\text{H}_2\text{O}$ .

Download English Version:

<https://daneshyari.com/en/article/5189399>

Download Persian Version:

<https://daneshyari.com/article/5189399>

[Daneshyari.com](https://daneshyari.com)