



## Solvent-free selective oxidation of primary and secondary alcohols catalyzed by ruthenium-bis(benzimidazole)pyridinedicarboxylate complex using hydrogen peroxide as an oxidant <sup>☆</sup>

Xian-Tai Zhou <sup>a</sup>, Hong-Bing Ji <sup>a,\*</sup>, Sheng-Gui Liu <sup>b,\*</sup>

<sup>a</sup> School of Chemistry and Chemical Engineering, Key Laboratory of Low-Carbon Chemistry & Energy Conservation of Guangdong Province, Sun Yat-sen University, 510275 Guangzhou, PR China

<sup>b</sup> School of Chemistry Science and Technology, Development Center for New Materials Engineering & Technology in Universities of Guangdong, Zhanjiang Normal University, 524048 Zhanjiang, PR China

### ARTICLE INFO

#### Article history:

Received 17 February 2013

Revised 11 April 2013

Accepted 13 May 2013

Available online 21 May 2013

#### Keywords:

Solvent-free

Oxidation

Alcohols

Hydrogen peroxide

Ruthenium complex

### ABSTRACT

A convenient and selective oxidation of alcohols with aqueous hydrogen peroxide to give the corresponding carbonyl compounds under solvent-free conditions has been developed. By applying ruthenium-bis(benzimidazole)pyridinedicarboxylate complex [Ru(bbp)(pydic)] as catalyst, primary, and secondary alcohols were oxidized to aldehydes and ketones in good yield and excellent selectivity under mild conditions.

© 2013 The Authors. Published by Elsevier Ltd. All rights reserved.

### Introduction

Oxidation of alcohols to corresponding carbonyl compounds is of great importance for both laboratory and synthetic industrial applications.<sup>1</sup> In traditional oxidation processes, large amounts of toxic and volatile organic solvents and metal oxidants were extensively used. The need for environmentally benign and clean oxidation reactions remains an important goal of chemical research.<sup>2</sup> Hence, developing green selective oxidation process of alcohols is still a challenging task in catalysis.<sup>3</sup> By comparing different oxidation methods, it is apparent that the oxidant used in the respective transformation defines the quality and applicability of the method. In addition to molecular oxygen, hydrogen peroxide is an environmentally benign oxidant, which theoretically generates only water as a by-product.<sup>4</sup> Therefore, the discovery of new protocol catalyst using H<sub>2</sub>O<sub>2</sub> is gathering much attention. In this content, variety of transition metal-based catalysts has been intensively investigated toward the oxidation of alcohols so far.<sup>5</sup>


<sup>☆</sup> This is an open-access article distributed under the terms of the Creative Commons Attribution-NonCommercial-No Derivative Works License, which permits non-commercial use, distribution, and reproduction in any medium, provided the original author and source are credited.

\* Corresponding authors. Tel.: +86 20 84113658; fax: +86 20 84113654.

E-mail addresses: [jihb@mail.sysu.edu.cn](mailto:jihb@mail.sysu.edu.cn) (H.-B. Ji), [lsgui@sohu.com](mailto:lsgui@sohu.com) (S.-G. Liu).

Ruthenium complexes with nitrogen-based ligands have been intensively investigated in order to develop catalysts for organic oxidation processes.<sup>6</sup> We ever reported an efficient oxidation process of alcohols catalyzed ruthenium porphyrins in the presence of molecular oxygen.<sup>7</sup> Nishiyama first reported the asymmetric epoxidation by one kind of ruthenium complex based on bis(oxazolinyl)pyridine, that is, ruthenium-(pyridinebisoxazoline) (pyridinedicarboxylate) complex [Ru(pybox)(pydic)].<sup>8</sup> Through modification of Nishiyama's catalyst, Beller research group developed efficient asymmetric epoxidation processes with a greener oxidant such as *tert*-butylhydroperoxide (TBHP) or hydrogen peroxide in recent years.<sup>9</sup>

We looked for ruthenium complexes that should be efficient for the oxidation of alcohols. Inspired by the efficiency of Nishiyama's catalyst in the epoxidation, we adopted the introduction of 2,6-bis(benzimidazole)pyridine as the counterpart to synthesize new catalyst with dual closed meridional stereotopes around an active metal. Hence, based on 2,6-bis(benzimidazole)pyridine and pyridinedicarboxylate, the novel kind ruthenium complex [Ru(bbp)(pydic)] (Scheme 1) was successfully synthesized and was applied as catalyst in the oxidation reactions. Interestingly to find this ruthenium complex is efficient for the selective oxidation of alcohols to corresponding carbonyl compounds with hydrogen peroxide as oxidant. Meanwhile, the noteworthy feature for this catalytic system could be that the selective oxidation of alcohols can be achieved under solvent-free conditions.

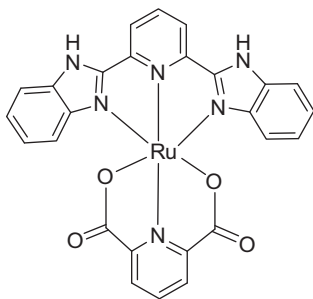

Scheme 1. The structure of Ru(bbp)(pydic).

**Table 1**  
Oxidation of benzyl alcohol catalyzed by Ru(bbp)(pydic) with aqueous H<sub>2</sub>O<sub>2</sub><sup>a</sup>

Entry	Solvent	Conv. <sup>b</sup> (%)	Yield <sup>b</sup> (%)
1	Toluene	5	4
2	Ethyl acetate	12	10
3	CH <sub>3</sub> OH	66	63
4	CH <sub>3</sub> CN	78	74
5	Solvent free	97	96

<sup>a</sup> Reaction condition: benzyl alcohol (2 mmol), catalyst ( $2 \times 10^{-3}$  mmol), 30% H<sub>2</sub>O<sub>2</sub> (10 mmol), 60 °C, 60 min. solvent (2 mL).

<sup>b</sup> Determined by GC.

**Table 2**  
Optimization of reaction conditions under solvent free conditions<sup>a</sup>

Entry	Substrate: H <sub>2</sub> O <sub>2</sub> <sup>b</sup>	T (°C)	Conv. <sup>c</sup> (%)	Yield <sup>c</sup> (%)
1	1:5	40	37	35
2	1:5	80	>99	87
3	1:2	60	43	40
4	1:3	60	64	62
5	1:6	60	98	93
6 <sup>d</sup>	1:5	60	5	3
7 <sup>e</sup>	1:5	60	83	80
8 <sup>f</sup>	1:5	60	>99	92

<sup>a</sup> Reaction condition: benzyl alcohol (2 mmol), catalyst ( $2 \times 10^{-3}$  mmol), 60 min.

<sup>b</sup> Molar ratio.

<sup>c</sup> Determined by GC.

<sup>d</sup> In the absence of catalyst.

<sup>e</sup> Catalyst ( $2 \times 10^{-4}$  mmol).

<sup>f</sup> Catalyst ( $2 \times 10^{-2}$  mmol).

## Results and discussion

To explore the reactivity and selectivity of the Ru(bbp)(pydic) catalyst,<sup>10</sup> benzyl alcohol was used as a model substrate. Various solvents were examined in the presence of Ru(bbp)(pydic) catalyst and H<sub>2</sub>O<sub>2</sub> (Table 1, entries 1–8).<sup>11</sup> After much experimentation on optimizing solvent, it was found that the use of a less-polar solvent like toluene and ethyl acetate afforded benzaldehyde in low yields (entries 1 and 2). Higher yield of benzaldehyde was obtained using polar solvents like methanol and acetonitrile (entries 3 and 4). Gratifyingly, it was found under solvent free conditions, the catalyst gave excellent conversion to benzaldehyde with 96% yield (entry 5).

The effect of reaction parameters was examined by performing the reaction in solvent-free conditions, as listed in Table 2. Only 35% yield of benzaldehyde was obtained when the reaction was conducted at 40 °C, while the selectivity would become poor as further rising the temperature to 80 °C (entries 1 and 2). Therefore, the optimized temperature was proved to be 60 °C. The yield of benzaldehyde increased with increasing the molar ratio of H<sub>2</sub>O<sub>2</sub>/benzyl alcohol (entries 3 and 4). The large excess amount of H<sub>2</sub>O<sub>2</sub> could promote the over-oxidation of benzaldehyde, which resulted in the slight decreasing of selectivity toward benzaldehyde (entry 5). The reaction almost did not occur in the absence of catalyst (entry 6). Similarly, the yield of benzaldehyde increased with the rising amount of catalyst. And the excess amount of catalyst caused decrease of selectivity to benzaldehyde (entry 8).

To examine the scope of the alcohol reaction with H<sub>2</sub>O<sub>2</sub>–Ru(bbp)(pydic) system, we extended our studies to various primary alcohols. The results are summarized in Table 3.

It was found that most primary alcohols were smoothly converted to corresponding carbonyl compounds with high conversion rate and excellent selectivity. Compared with the electron-withdrawing groups at *para*-position for benzylic alcohols, the electron-donating groups seemed more favorable to the formation of carbonyl compounds (entries 1–4, Table 3). For basic substrates like 4-pyridinemethanol (entry 5, Table 3), additional amounts of catalyst are needed to improve reaction rates and to ensure good conversions. The catalytic system is also efficient for the oxidation of saturated primary aliphatic alcohols such as 2-phenylethanol and 1-octanol (entries 6 and 7, Table 3).

As shown in Table 3, the H<sub>2</sub>O<sub>2</sub>–Ru(bbp)(pydic) system was found to be selective, efficient for the oxidation of secondary

**Table 3**  
Oxidation of various alcohols with H<sub>2</sub>O<sub>2</sub> catalyzed by Ru(bbp)(pydic)<sup>a</sup>

Entry	Substrate	Product	Time (h)	Conv. <sup>b</sup> (%)	Yield <sup>b</sup> (%)
1			1	97	96
2			1	98	96
3			1	96	93
4			2	82	81
5 <sup>c</sup>			3	76	74

(continued on next page)

Download English Version:

<https://daneshyari.com/en/article/5264191>

Download Persian Version:

<https://daneshyari.com/article/5264191>

[Daneshyari.com](https://daneshyari.com)